

Refractive index of alkaline earth halides and its wavelength and temperature derivatives

Cite as: Journal of Physical and Chemical Reference Data **9**, 161 (1980); <https://doi.org/10.1063/1.555616>
Published Online: 15 October 2009

H. H. Li



[View Online](#)



[Export Citation](#)

ARTICLES YOU MAY BE INTERESTED IN

[Refractive index of alkali halides and its wavelength and temperature derivatives](#)

Journal of Physical and Chemical Reference Data **5**, 329 (1976); <https://doi.org/10.1063/1.555536>

[Refractive index of silicon and germanium and its wavelength and temperature derivatives](#)

Journal of Physical and Chemical Reference Data **9**, 561 (1980); <https://doi.org/10.1063/1.555624>

[High-accuracy, midinfrared \(\$450\text{cm}^{-1} \leq \omega \leq 4000\text{cm}^{-1}\$ \) refractive index values of silicon](#)

Journal of Applied Physics **97**, 123526 (2005); <https://doi.org/10.1063/1.1923612>

Where in the world is AIP Publishing?
Find out where we are exhibiting next

AIP Publishing

Refractive Index of Alkaline Earth Halides and Its Wavelength and Temperature Derivatives

H. H. Li

Center for Information and Numerical Data Analysis and Synthesis, Purdue University, West Lafayette, Indiana 47906

Available data on the refractive index and its temperature derivative for alkaline earth halides were exhaustively surveyed, compiled, and analyzed. The most probable values of the refractive index at 293 K for the transparent region were generated for the materials for which experimental data were sufficiently abundant and reliable. Provisional values were also generated for the wavelength regions where available data were less abundant. Reasonable estimations of refractive index for the very scantily measured materials were made by incorporating the dielectric constants and wavelengths of absorption peaks into a simplified dispersion equation. It was found that of the twenty alkaline earth halides only seven, namely, MgF_2 , CaF_2 , SrF_2 , BaF_2 , $CaCl_2$, $SrCl_2$, and $BaCl_2$, appear in the open literature with refractive index measurements. Most of the available data are for the first four of the seven materials. Temperature derivatives of refractive index for most of the alkaline earth halides were unavailable. As a result, data analysis on dn/dT was limited to CaF_2 , SrF_2 , and BaF_2 .

Key words: Alkaline earth halides; optical constants; refractive index; temperature coefficient of refractive index.

Contents

	Page
List of Tables	161
List of Figures	162
List of Symbols	163
1. Introduction	163
2. Theoretical Background	167
2.1. Refractive Index	167
2.2. Temperature Derivative of Refractive Index, dn/dT	169
3. Numerical Data.....	175
3.1. Calcium Fluoride, CaF_2	177
3.2. Strontium Fluoride, SrF_2	207
3.3. Barium Fluoride, BaF_2	226
3.4. Magnesium Fluoride, MgF_2	247
3.5. Calcium Chloride, $CaCl_2$	272
3.6. Strontium Chloride, $SrCl_2$	276
3.7. Barium Chloride, $BaCl_2$	280
4. Conclusions and Recommendations.....	284
5. Acknowledgments	288
6. References	288
6. Spectral Position of the Fundamental Optical Phonon of Alkaline Earth Halides	170
7. Temperature Dependence of the Energies of Sharp Reflectance Peaks	174
8. Recommended Values of the Refractive Index and Its Wavelength at Temperature Derivatives for CaF_2 at 293 K	180
9. Measurement Information on the Refractive Index of CaF_2 (Wavelength Dependence)	185
10. Experimental Data on the Refractive Index of CaF_2 (Wavelength Dependence)	190
11. Measurement Information on the Refractive Index of CaF_2 (Temperature Dependence)	195
12. Experimental Data on the Refractive Index of CaF_2 (Temperature Dependence)	196
13. Measurement Information on the Temperature Derivative of Refractive Index of CaF_2 (Wave- length Dependence)	198
14. Experimental Data on the Temperature Derivative of Refractive Index of CaF_2 (Wavelength Depend- ence)	201
15. Measurement Information on the Temperature Derivative of Refractive Index of CaF_2 (Tempera- ture Dependence)	204
16. Experimental Data on the Temperature Derivative of Refractive Index of CaF_2 (Temperature Dependence)	205
17. Comparison of Dispersion Equations Proposed for CaF_2	206
18. Recommended Values of the Refractive Index and Its Wavelength and Temperature Derivatives for SrF_2 at 293 K	210

List of Tables

1. Available Data Sets
2. Crystal Structure of Alkaline Earth Halides.....
3. The Crystal Radii of Ions
4. Optical Dielectric Constant of Alkaline Earth Halides
5. Static Dielectric Constant of Alkaline Earth Halides

164
164
165
168
169

© 1980 by the U.S. Secretary of Commerce on behalf of the United States. This copyright is assigned to the American Institute of Physics and the American Chemical Society.

19. Measurement Information on the Refractive Index of SrF ₂ (Wavelength Dependence)	215
20. Experimental Data on the Refractive Index of SrF ₂ (Wavelength Dependence).....	217
21. Measurement Information on the Refractive Index of SrF ₂ (Temperature Dependence)	220
22. Experimental Data on the Refractive Index of SrF ₂ (Temperature Dependence).....	221
23. Measurement Information on the Temperature Derivative of Refractive Index of SrF ₂ (Wavelength Dependence)	223
24. Experimental Data on the Temperature Derivative of Refractive Index of SrF ₂ (Wavelength Dependence)	224
25. Comparison of Dispersion Equations Proposed for SrF ₂	225
26. Recommended Values of the Refractive Index and Its Wavelength and Temperature Derivatives for BaF ₂ at 293 K	228
27. Measurement Information on the Refractive Index of BaF ₂ (Wavelength Dependence)	233
28. Experimental Data on the Refractive Index of BaF ₂ (Wavelength Dependence)	235
29. Measurement Information on the Refractive Index of BaF ₂ (Temperature Dependence)	238
30. Experimental Data on the Refractive Index of BaF ₂ (Temperature Dependence).....	239
31. Measurement Information on the Temperature Derivative of Refractive Index of BaF ₂ (Wavelength Dependence)	241
32. Experimental Data on the Temperature Derivative of Refractive Index of BaF ₂ (Wavelength Dependence)	242
33. Measurement Information on the Temperature Derivative of Refractive Index of BaF ₂ (Temperature Dependence)	244
34. Experimental Data on the Temperature Derivative of Refractive Index of BaF ₂ (Temperature Dependence)	245
35. Comparison of Dispersion Equations Proposed for BaF ₂	246
36. Recommended Values of the Refractive Index and Its Wavelength Derivative for MgF ₂ at 293 K	248
37. Measurement Information on the Refractive Index of MgF ₂ (Wavelength Dependence)	254
38. Experimental Data on the Refractive Index of MgF ₂ (Wavelength Dependence)	259
39. Measurement Information on the Refractive Index of MgF ₂ (Temperature Dependence)	263
40. Experimental Data on the Refractive Index of MgF ₂ (Temperature Dependence)	264
41. Measurement Information on the Temperature Derivative of Refractive Index of MgF ₂ (Wavelength Dependence)	266
42. Experimental Data on the Temperature Derivative of Refractive Index of MgF ₂ (Wavelength Dependence)	267

Page		Page
43. Measurement Information on the Birefringence of MgF ₂ (Temperature Dependence)	269	
44. Experimental Data on the Birefringence of MgF ₂ (Temperature Dependence)	270	
45. Comparison of Dispersion Equations Proposed for MgF ₂	271	
46. Measurement Information on the Refractive Index of CaCl ₂ (Wavelength Dependence)	274	
47. Experimental Data on the Refractive Index of CaCl ₂ (Wavelength Dependence)	275	
48. Measurement Information on the Refractive Index of SrCl ₂ (Wavelength Dependence)	278	
49. Experimental Data on the Refractive Index of SrCl ₂ (Wavelength Dependence)	279	
50. Measurement Information on the Refractive Index of BaCl ₂ (Wavelength Dependence)	282	
51. Experimental Data on the Refractive Index of BaCl ₂ (Wavelength Dependence)	283	
List of Figures		
1. Absorption Spectrum of an Alkaline Earth Halide Crystal	166	
2. Temperature Dependence of the Static Dielectric Constant of Alkaline Earth Fluorides	171	
3. Temperature Dependence of the Wavelength of Fundamental Transverse Optical Phonon of Alkaline Earth Fluorides.....	172	
4. Near-normal Incidence Reflectance Spectrum of CaF ₂	173	
5. Near-normal Incidence Reflectance Spectrum of SrF ₂	173	
6. Near-normal Incidence Reflectance Spectrum of BaF ₂	174	
7. Refractive Index of CaF ₂ (Wavelength Dependence)	183	
8. Wavelength Derivative of Refractive Index of CaF ₂	184	
9. Refractive Index of CaF ₂ (Temperature Dependence)	194	
10. Temperature Derivative of Refractive Index of CaF ₂ (Wavelength Dependence).....	197	
11. Temperature Derivative of Refractive Index of CaF ₂ (Temperature Dependence)	203	
12. Refractive Index of SrF ₂ (Wavelength Dependence)	213	
13. Wavelength Derivative of Refractive Index of SrF ₂	214	
14. Refractive Index of SrF ₂ (Temperature Dependence)	219	
15. Temperature Derivative of Refractive Index of SrF ₂ (Wavelength Dependence).....	222	
16. Refractive Index of BaF ₂ (Wavelength Dependence)	231	
17. Wavelength Derivative of Refractive Index of BaF ₂	232	
18. Refractive Index of BaF ₂ (Temperature Dependence)	237	
19. Temperature Derivative of Refractive Index of BaF ₂ (Wavelength Dependence)	240	

20. Temperature Derivative of Refractive Index of BaF ₂ (Temperature Dependence).....	243	26. Refractive Index of CaCl ₂ (Wavelength Dependence)	273
21. Refractive Index of MgF ₂ (Wavelength Dependence)	252	27. Refractive Index of SrCl ₂ (Wavelength Dependence)	277
22. Wavelength Derivative of Refractive Index of MgF ₂	253	28. Refractive Index of BaCl ₂ (Wavelength Dependence)	281
23. Refractive Index of MgF ₂ (Temperature Dependence)	262	29. Refractive Index of Alkaline Earth Halides at 293 K	285
24. Temperature Derivative of Refractive Index of MgF ₂ (Wavelength Dependence).....	265	30. Wavelength Derivative of Refractive Index of Alkaline Earth Halides at 293 K	286
25. Birefringence of MgF ₂ (Wavelength Dependence)..	268	31. Temperature Derivative of Refractive Index of Alkaline Earth Halides at 293 K	287

List of Symbols

<i>a</i>	Constant	<i>T</i>	Temperature
A	Code for Abele method	<i>v</i>	Phase velocity of light in medium
<i>A</i> , <i>A</i> ₀ ,	Constant	<i>V</i>	Volume
<i>A</i> ₁ , <i>A</i> ₂	Constant	<i>α</i>	Linear thermal expansion coefficient
<i>b</i>	Constant	<i>γ</i>	Damping factor
B	Code for Brewster angle determination method	<i>ε</i>	Complex dielectric constant
<i>c</i>	Constant; velocity of light	<i>ε</i> ₁	Real part of <i>ε</i>
C	Code for polarization method	<i>ε</i> ₂	Imaginary part of <i>ε</i>
D	Code for deviation method; sodium line of 0.589 μm	<i>ε</i> ₀	Static dielectric constant
F	Code for focal length method	<i>ε</i> _∞	Optical dielectric constant
H	Code for high frequency modulation method	<i>k</i>	Extinction coefficient; oscillator strength
I	Code for interference method	<i>λ</i>	Wavelength of light
L	Code for multilayer method	<i>λ</i> _i	Wavelength of the <i>i</i> th absorption band
M	Code for immersion method	<i>λ</i> _I	Wavelength of infrared absorption band
<i>n</i>	Refractive index, relative to air	<i>λ</i> _u	Effective wavelength of ultraviolet absorption band
<i>n</i> ₀	Refractive index of short (uv) wavelengths		
P	Code for Pulfrich refractometer measurement		
<i>P</i>	Electrical polarizability		
R	Code for reflection method		
S	Code for thickness determination method		
T	Code for transmission method		

1. Introduction

The purpose of this work is to present and review the available data and information on the refractive index of alkaline earth halides, to critically evaluate, analyze, and synthesize the data, and to make recommendations for the most probable values of the refractive index, its wavelength derivative $dn/d\lambda$ and temperature derivative dn/dT . The recommended and provisional values generated cover the widest possible transparent wavelength ranges and are for the purest form of each alkaline earth halide for which measurements have been made. How-

ever, for the materials which have been scantily measured, reasonable estimations are made.

The introductory text describes the general procedures and methods for the evaluation and synthesis of the available data and for the generation of recommended values. It also discusses the present status of the experimental data and other considerations concerning the body of data.

In the theoretical background section, the general theory of the refractive index and its temperature derivative is discussed. Correlations of the dielectric constants, absorption bands, and the refractive index are described.

In the data presentation section we treat each material separately, review the available data and information, and describe the considerations involved in arriving at the final assessment and recommendation and the theoretical guidelines or semi-empirical correlations on which the data analysis and synthesis are based. Figures and tables follow to present the recommended values, the original data, specimen characterization, and measurement information. At present, we have compiled 182 sets of data extracted from some 80 documents in the primary literature. Distribution of the available data sets is shown in table 1.

TABLE 1. Available data sets

Material	Number of data sets		
	<i>n</i>	<i>dn/dT</i>	<i>n₀-n_e</i>
MgF ₂	42	2	7
CaF ₂	44	29	
SrF ₂	13	4	
BaF ₂	15	12	
CaCl ₂	7		
SrCl ₂	7		
BaCl ₂	6		

In the conclusion, figures are presented in which all the recommended curves on the refractive index, $dn/d\lambda$, and dn/dT are grouped for visual comparison. The accomplishments in this work are discussed and the need for further work is suggested.

The last section consists of the source references used in the extraction of data and/or information. Only original sources of data have been used in the analysis. The effective cut-off date for literature research was May 1977, while the earliest referenced source was dated 1874. With such a comprehensive compilation of information and presentation of results, the author believes that scientists and engineers in the optical trade will find this report useful in regard to refractive index and its temperature and wavelength derivatives.

In order to utilize any dispersive medium, spectroscopists must have a knowledge of the index of refraction and $dn/d\lambda$ for all wavelengths transmitted by the medium. Such data are also useful to physicists for evaluating theoretical dispersion equations and for studying the forces between the constituents of the crystal. For a transparent medium, the refractive index, n , is defined as the ratio of the velocity, c , of electromagnetic radiation of a given wavelength in vacuum to the phase velocity, v , in the medium, i.e.,

$$n = c/v. \quad (1)$$

Since the index of refraction of air is about 1.0003, n is conventionally measured with respect to air instead of vacuum and no correction is made. In a non-absorbing medium the refractive index is a real quantity, while in an absorbing medium a complex index of refraction, N , is used. The complex index is defined as

$$N = n + ik, \quad (2)$$

where k is the extinction coefficient or absorption index. Both n and k are frequency dependent. The real and imaginary parts of the square of the complex refractive index are the real and imaginary parts of the complex dielectric constant, ϵ , of the medium:

$$\epsilon = \epsilon_1 + i\epsilon_2 = N^2 = (n^2 - k^2) + i2nk. \quad (3)$$

The dispersion in an optical material is intimately related to the microscopic structure of the material. On the short wavelength side transmission is limited by electronic excitation, and for long wavelengths by molecular vibrations and rotations. The width of the transparent spectral range increases as the energy for electronic excitation is increased and that for molecular vibrations is decreased. Theoretical and experimental studies on ionic crystals indicate that crystals having small ions with strong bonding have a wide spectral range of transparency. This is true for alkali halides and alkaline earth halides.

Unlike the alkali halides, which form only cubic crystals, the alkaline earth halides form crystals with a variety of structures. The four types of structure that are found in the alkaline earth halides are indicated in table 2. A review of tables 1 and 2 will show that, with the exception of MgF₂, only crystals of cubic structure have been investigated.

TABLE 2. Crystal structure of alkaline earth halides

Material	Structure
BeF ₂	Tetragonal, Orthorhombic, Hexagonal
BeCl ₂	Orthorhombic
BeBr ₂	Orthorhombic
BeI ₂	Orthorhombic, Tetragonal
MgF ₂	Tetragonal
MgCl ₂	Hexagonal
MgBr ₂	Hexagonal
MgI ₂	Hexagonal
CaF ₂	Cubic
CaCl ₂	Orthorhombic
CaBr ₂	Orthorhombic
CaI ₂	Hexagonal
SrF ₂	Cubic
SrCl ₂	Cubic
SrBr ₂	Tetragonal
SrI ₂	Hexagonal
BaF ₂	Cubic
BaCl ₂	Cubic, Orthorhombic
BaBr ₂	Orthorhombic
BaI ₂	Orthorhombic

Calcium fluoride in its naturally-occurring form is known as fluorite. It is conventional to describe a crystal as having the fluorite structure if its lattice is similar to that of calcium fluoride. In a fluorite-structure crystal of a compound AB_2 each ion of species A is surrounded by eight equivalent nearest-neighbour ions of species B forming the corners of a cube with A at its center. Each ion of species B is surrounded by a tetrahedron of four equivalent A ions. More fundamentally, the structure has a face-centered-cubic translational group and a space lattice of symmetry O_h^5 . If the structure is interpreted in terms of a primitive cube of side a , it comprises three inter-penetrating face-centered-cubic lattices. The first is a lattice of species A with its origin at the point (0,0,0) and with primitive translational vectors $(0, a/2, a/2); (a/2, 0, a/2); (a/2, a/2, 0)$ in the cube of side a . The B species are located on two further lattices with similar translational vectors but with origins at $(a/4, a/4, a/4)$ and at $(3a/4, 3a/4, 3a/4)$. The site of the A ion has O_h^5 symmetry and the site of the B ion has T symmetry. The interstitial site again has O_h^5 symmetry, being at the center of a cube of eight B ions. The crystal is not piezoelectric.

It is apparent that the fluorite structure provides close contact between the different species of atom or ion. Furthermore if the ions of species A are sufficiently large, close contact between the ions of species B is prevented. If the constituent species are regarded as hard spheres with radii $r(A)$ and $r(B)$, contact occurs between the A and B ions to the exclusion of B-B contact and of A-A contact [1]¹ when the radii satisfy the condition

$$4.45 > r(A)/r(B) > 0.73.$$

The energetic advantages of close contact between dissimilar ions suggest that the fluorite structure will be favoured by those strongly ionic compounds with formula AB_2 which possess large ions of type A. Study of a self-consistent table of ionic radii, such as that of Zachariasen [2] summarized in table 3, shows that one is unlikely to find a hypothetical compound in which contact between A ions could occur. This would require that the A ions be exceptionally large, with

$$r(A) > 4.45r(B).$$

In fact, the A ions are normally relatively small and it is possible to find several series of compounds in which the lower limiting value is passed, and contact between B ions can occur. For example, among the halides of barium one finds that the fluorite lattice structure occurs for the smaller halide B ions while the iodides possess orthorhombic or sheet-like structures.

Among the compounds of alkaline earth halides those which possess the fluorite structure are, according to Wyckoff [1], CaF_2 , SrF_2 , BaF_2 , CaCl_2 , SrCl_2 , BaCl_2 . The absence of bromides and of iodides may be interpreted in terms of a violation of the radius requirement, the anions being relatively too large. It is apparent on inspection of table 3 that close contact between A and B ions cannot occur for the light cations.

There were two major reasons why only crystals of cubic structure have been investigated. The first is that cubic crystals

TABLE 3. The crystal radii of ions

Be^{2+}	0.30 Å	F^-	1.33 Å
Mg^{2+}	0.65 Å	Cl^-	1.81 Å
Ca^{2+}	0.94 Å	Br^-	1.96 Å
Sr^{2+}	1.10 Å	I^-	2.19 Å
Ba^{2+}	1.29 Å		

are optically isotropic. It is true that optical anisotropy is highly desirable in a number of special uses, but for the fabrication of optical components in general, anisotropy of dispersion may become an objective. It is therefore understandable that early investigations were limited to the cubic crystals, but it is surprising that even at the present age of modern technology our knowledge of optical dispersion is still limited to that of cubic crystals. With regard to the dispersion of the non-cubic crystals, little work has been reported.

The second reason for inattention to non-cubic alkaline earth halide crystals is the unavailability of the crystals or their undesirable chemical and physical properties, such as hygroscopy and softness. With advances in the technique of crystal growth, crystals which do not occur naturally are made available in workable sizes. Examples are BeF_2 [3], MgCl_2 [4], and BaBr_2 [5]. However, no measurements on the optical dispersion of these crystals are reported.

The applications of high-power infrared lasers, which are now being developed at a rapid rate, are partly limited by the lack of suitable transparent optical materials. As a result, much of the high-power laser research is directed toward finding adequate high-temperature window and dome materials in the wavelength regions from 2 to 6 micrometers and near 10.6 micrometers. The alkaline earth halides have large transmission ranges spreading from the ultraviolet to the infrared and are available in large sizes and high purity. They are good materials for photochemists and spectroscopists who are interested in ultraviolet transparency, and for laser scientists who are concerned with infrared transmission. They are considered good window materials and are recommended by the National Materials Advisory Board [6]. Through the studies of the Advisory Board, crystals of fluorite-type are among the serious candidates for laser materials. Efforts are being made to improve their mechanical strength and thermal endurance without altering their optical properties, particularly the refractive index.

The available refractive indices of alkaline earth halides and their temperature derivatives have been surveyed and studied from time to time by a number of investigators, including Smakula [7], Ballard [8], Coblenz [9], to name just a few. Refractive index data are compiled in a number of handbooks such as those sponsored by Landolt-Bornstein [10], American Institute of Physics Handbook [11], and Handbook of Chemistry and Physics [12], etc. However, their main concern is to provide a general picture through a few particular sets of data. The purpose of the present work is quite different from that of the above-mentioned works. It has two major aims: (1) to exhaustively search the open literature so that a complete and comprehensive bibliographic reference is compiled, and (2) to generate recommended values based on the existing experimental data on the refractive index and its temperature deriv-

¹ Numbers in brackets indicate literature references at the end of this paper.

ative, so that evaluated and/or synthesized numerical data are made available for scientific and engineering use.

In figure 1, a schematic view of the absorption spectrum of a typical alkaline earth halide crystal is shown. At the right, at about 30 micrometers, are seen the absorption peaks associated with optical phonons, while nearer to the left, at about 0.1 micrometer, are seen the absorption peaks associated with excitons. In the transparent region between the two extremes the crystal absorbs little light and has a dispersion which can be characterized by an optical dielectric constant $\epsilon_\infty \approx n_0^2$, where n_0 is the refractive index at short wavelength. In absorbing regions of the spectrum, the imaginary part of ϵ is non-zero. Both the real and imaginary parts of ϵ can be obtained from the experimental reflectivity (preferably over a wide range of wave-lengths) and the use of the Kramers-Kronig relation or the Lorentz oscillator model. In optical technology, the refractive index is needed only for the transparent region of the material. One does not have to carry out a complicated analysis and calculation to obtain the refractive index. Direct methods are available for high precision measurements. The minimum deviation method is usually used to obtain the refractive index accurate to the fourth decimal place, and the interference method to the third.

Scanning the open literature, one finds that in most cases the measurements of refractive index were carried out at various temperatures and reduced to a reference temperature chosen according to the investigators' preference. It is highly desirable to reduce the existing refractive index data and to present them at a uniform reference temperature. It is therefore important that the temperature derivative of the refractive index be made

available in the form of a function of wavelength based on the existing data and theory, so that the users can easily calculate the required values over a limited range of temperature.

The first task in generating recommended values was to analyze the data on the temperature derivative of refractive index. With the analyzed values of dn/dT , all the refractive index data were then reduced to the reference temperature of 293 K chosen for the present work. The corrected data were then subjected to evaluation and critical selection. Least-squares fitting of the selected data to a given equation was then carried out.

Recommended values for refractive index (relative to air), and wavelength and temperature derivatives, $dn/d\lambda$, and dn/dT , have been calculated from the correlating equations where sufficient experimental values are available. However, for the region where experimental evidence is either insufficient or poor, only provisional values are provided. Data for the transparent region are presented at integral wavelengths with small increment. Intermediate values can be obtained by the following linear interpolations:

$$\begin{aligned} n_{\lambda'} &= n_\lambda + (dn/d\lambda)_\lambda (\lambda' - \lambda), \\ n_{\lambda T'} &= n_{\lambda T} + (dn/dT)_\lambda (T' - T). \end{aligned} \quad (4)$$

The second expression in eq (4) is based on the fact that dn/dT is relatively independent of temperature over a fairly wide range of temperatures. However, the application of this expression should be limited to the temperature range 293 ± 50 K.

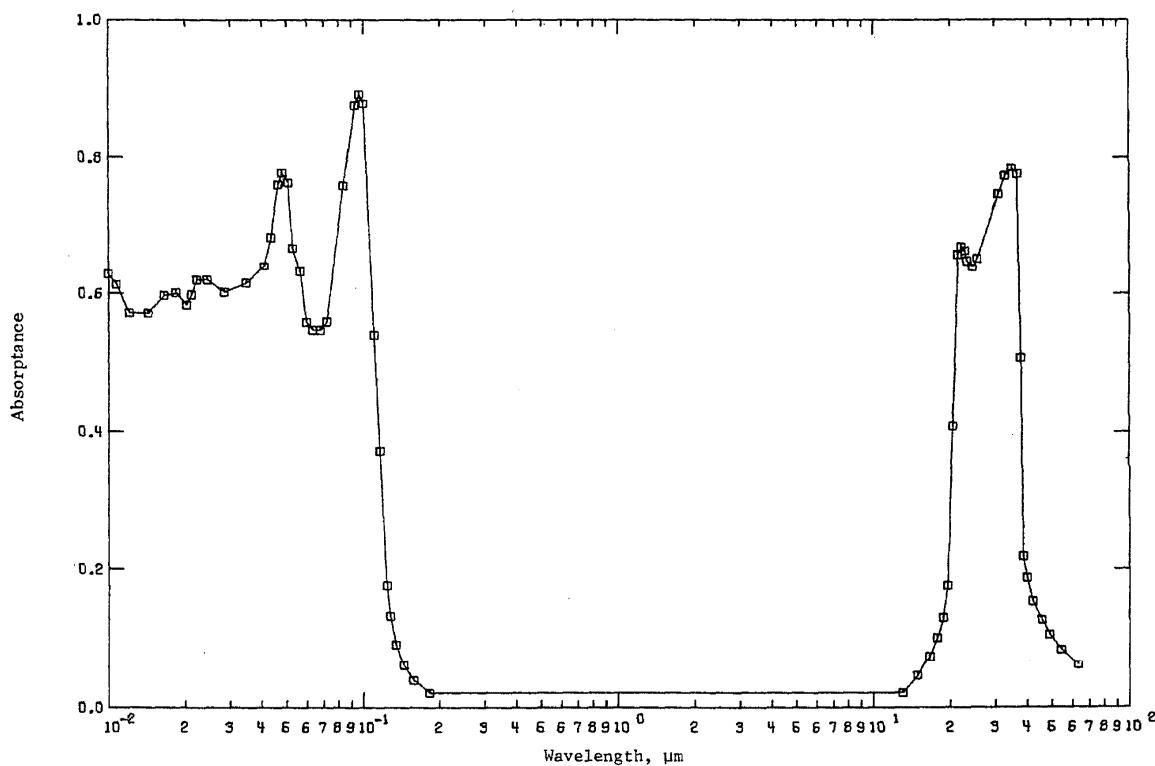


Figure 1. Absorption Spectrum of an Alkaline Earth Halide Crystal

2. Theoretical Background and Empirical Relations

The study of the propagation of light through matter, particularly solids, comprises one of the important and interesting branches of optics. The many and varied optical phenomena exhibited by solids include selective absorption, dispersion, double refraction, polarization effects, and electro-optical and magneto-optical effects. Many of the optical properties of solids can be understood on the basis of classical electromagnetic theory.

The macroscopic electromagnetic state of matter at a given point is described by four quantities:

(1) the volume density of electric charge.

(2) the volume density of electric dipole strength, called the polarization,

(3) the volume density of magnetic dipole strength, called the magnetization,

(4) the electric current per unit area, called the current density.

All of these quantities are macroscopic averages over the microscopic variations due to the atomic makeup of matter. They are related to the macroscopically averaged electric and magnetic fields by the well-known Maxwell equations [13].

Detailed discussion of Maxwell's equations is beyond the scope of the present work. What we should bear in mind is that the general solution of Maxwell's equations is made up of electric and magnetic fields. In the treatment of the interaction of light and matter, the light is considered as an oscillating electric field that engulfs the component molecules of matter. Each of the molecules may be considered to be a charged simple harmonic oscillator. When these component oscillators are driven by the engulfing electric field of the light they emit Huygens-like spherical wavelets that contribute to and modify the electric and magnetic fields. In the early development of the theory of propagation of light in matter, there was no practical alternative to treating the matter as a collection of charged harmonic oscillators subject, perhaps, to damping forces. Fortunately, the modern developments in the theory of matter and its interaction with radiation have shown that this simple model has broad utility, and that it can be employed in the discussion of refractive indices. In this section, only a brief summary of results of the theory of the refractive index and its temperature derivative is given.

2.1 Refractive Index

Maxwell's theory gives the relationship

$$n^2 = \epsilon = 1 + P \quad (5)$$

where n is the refractive index, ϵ the dielectric constant, and P the polarizability. If one treats the material as equivalent to a collection of harmonic oscillators resonant to radiations of various wavelengths λ_i , one can derive [13] the equation

$$n^2 - 1 = \sum_i \frac{c_i \lambda^2}{\lambda^2 - \lambda_i^2} \quad (6)$$

where λ is the wavelength of the incident radiation, and c_i is a constant which depends on the number of oscillators per unit volume or the "oscillator strength" of the oscillators resonant at wavelength λ_i . Equation (6) is generally called the Sellmeier formula. It can be derived by modern quantum theory from more sophisticated models of the solid, with λ_i denoting the wavelengths of the various absorption bands of the material.

For the transparent region, it was traditionally believed that the dispersion formula of the Sellmeier type best fit the ionic crystals. The consequence of this was that most of the early experimental works adopted eq (6) with the λ_i 's and c_i 's as adjustable empirical constants chosen only to fit the data, with no other experimental and theoretical basis. Nevertheless, this equation, if used correctly, gives a good deal of information concerning the position of absorption bands, oscillator strengths, and the dielectric constant for a static field.

For the transparent region, eq (6) can be written as

$$\epsilon = n^2 = 1 + \sum_i \frac{a_i \lambda^2}{\lambda^2 - \lambda_i^2} + \frac{b_j \lambda^2}{\lambda^2 - \lambda_j^2} \quad (7)$$

Terms in the first summation are contributions from the ultraviolet absorption bands and those in the second from the infrared absorption bands. In the infrared region, however, the λ_i 's of uv absorption peaks are much smaller than λ and eq (7) is reduced to

$$\epsilon = \epsilon_\infty + \sum_j \frac{b_j \lambda^2}{\lambda^2 - \lambda_j^2}, \quad (8)$$

where $\epsilon_\infty = 1 + \sum a_i = \epsilon_0 - \sum b_i$ is the optical dielectric constant.

Real crystals are neither perfectly linear dielectrically, nor are they perfectly harmonic. The effect of nonlinearity and anharmonicity is to introduce a damping term [14]. Equation (8) is extended to become

$$\epsilon = \epsilon_1 + i\epsilon_2 = \epsilon_\infty + \sum_j \frac{b_j \lambda^2}{\lambda^2 - \lambda_j^2 - i\gamma_j \lambda} \quad (9)$$

Equation (9) is widely used in investigating the infrared optical properties of ionic crystals. In the transparent wavelength region, the effects contributed by absorption bands are negligibly small. In such cases the damping terms can be omitted and eq (9) is reduced to the Sellmeier formula.

In an ideal application of eq (7), one would need to know the wavelength of all of the absorption peaks. This is very difficult in practice because of the large number of absorption peaks. In fact, only a few absorption peaks are accessible for experimental observation. In order to include the effects due to unobserved absorption bands on the refractive index in the transparent region, an equation similar to eq (7) is used to interpret the experimental data:

$$n^2 = A + \sum_i \frac{a_i \lambda^2}{\lambda^2 - \lambda_i^2} + \sum_j \frac{b_j \lambda^2}{\lambda^2 - \lambda_j^2}, \quad (10)$$

where λ_i 's and λ_j 's are the observed wavelength of absorption bands. A is a constant which equals the quantity $1 + \sum a_k$ where a_k 's are the coefficients of the ultraviolet terms with λ_k 's much smaller than the wavelengths in the transparent region. In the infrared region, the dominant contribution to the refractive index in the transparent region comes from the fundamental phonons, while other absorption bands contribute little effect on the refractive index in the transparent region. As a result, in most cases, only one or two terms due to the predominant contribution are included in eq (10). The relationships between the dielectric constants and the coefficients in the dispersion equation remain with no change:

$$\epsilon_{\infty} = A + \sum a_i, \quad (11)$$

$$\epsilon_0 = A + \sum a_i + \sum b_j. \quad (12)$$

For some materials, experimental data on n are insufficient to justify the least-squares fitting. A means should be developed to obtain reasonable estimates by use of the available data for other properties which are related to n . The following simplified equation (two-oscillator model) of the Sellmeier type is proposed for this purpose:

$$n^2 = A + \frac{(\epsilon_{\infty} - A)\lambda^2}{\lambda^2 - \lambda_u^2} + \frac{(\epsilon_0 - \epsilon_{\infty})\lambda^2}{\lambda^2 - \lambda_l^2}, \quad (13)$$

where A is an adjustable parameter, λ_u the unweighted averaged value of the wavelengths of the ultraviolet absorption peaks, and λ_l the wavelength of the fundamental infrared absorption peak. The adjustable parameter A in eq (13) can be determined even if only one measurement of n is available because the quantities ϵ_0 , ϵ_{∞} , λ_u , and λ_l are in general available.

It is clear that the parameter ϵ_{∞} , ϵ_0 , λ_u and λ_l play important roles in the calculations of the refractive index. On account of this, these parameters were also included in our searches, though not in an exhaustive way. Listed in tables 4, 5, and 6 are the results of our searches for ϵ_{∞} , ϵ_0 and λ_l .

The values of optical dielectric constant listed in table 4 are determined either by curve fit of refractive indices to the dispersion equation or by Kramers-Kronig analysis of reflection spectra. No method is designed for direct measurement of ϵ_{∞} . As a consequence, the accuracy of ϵ_{∞} depends largely on the accuracies of input refractive indices and on the spectral range covered. It is interesting to note that at a given temperature the values of ϵ_{∞} obtained from various sources are in close agreement. Although the values are made available at several temperatures, the paucity of data hampers the estimation of temperature variation of the optical dielectric constant.

The values of static dielectric constants given in table 5 indicate discrepancies between investigators. Such discrepancies can be attributed to the different methods used and the impurity contents of the samples. Without question, the results reported by Andeen et al. [19] are the best, because the method of substitution is by far the most reliable direct means of measuring the static dielectric constant and the samples they used are believed to be the purest available. However, the work of Lowndes [15] is

important, because not only do his values at room temperature agree closely with those of Andeen et al., but also his measurements cover a wide temperature range, as shown in figure 2. In fact, his measurements give the only set of reliable dielectric constants as a function of temperature, a very important basis for determining the temperature variation of static dielectric constants.

The spectral position of the fundamental optical phonon, λ_l , is an important input parameter in the dispersion equation for the materials with scanty infrared data. Among the data listed in table 6, the values reported by Lowndes are most reliable and might be used in our correlation of physical properties to calculate the missing refractive indices. However, as the values from a number of other papers agree closely with Lowndes', the averaged values will actually be used. Lowndes' measurements not only are believed to be the most reliable ones available but also are used to evaluate the temperature variation of λ_l . Such variations are indispensable input parameters for estimating the temperature derivative of the refractive index. Figure 3 presents Lowndes results of $\lambda_l(T)$.

The uv absorption of alkaline earth halides is quite complicated. There are many absorption peaks of about equal strength, spreading into a wide uv region from about $0.124 \mu\text{m}$ down to $0.04 \mu\text{m}$. There is no direct measurement of absorption peaks available in the vacuum uv region because there experimental work is difficult. To estimate the effective wavelength, λ_u , of vacuum uv absorption, we have to rely on the observed far uv

TABLE 4. Optical dielectric constant of alkaline earth halides

Material	Temperature (K)	ϵ_{∞}	Author ^b
MgF_2	300	1.9(o) ^a	Barker [14] Barker [14]
	300	1.9(e)	
CaF_2	4	2.05	L
	80	2.047	B
	200	2.044	B
	300	2.040 \pm 0.001	B
	300	2.045	K
	300	2.04	L
SrF_2	350	2.04	L
	4	2.08	L
	80	2.07	B
	300	2.07	K
	350	2.07	L
BaF_2	4	2.18	L
	80	2.157 \pm 0.001	B
	300	2.150	B
	300	2.16	K
	300	2.17	L
	350	2.17	L

^aThe letters o and e in the parentheses indicate the ordinary-ray and extraordinary-ray, respectively.

^bThe capital letters in this column carry the following abbreviations:

L—Lowndes [15],

B—Bosomworth [16],

K—Kaiser et al [17].

TABLE 5. Static dielectric constant of alkaline earth halides

Material	Temperature (K)	ϵ_0	Author ^b
MgF_2	300	4.87(o) ^a	D
		4.6(o)	Barker [14]
		4.826 \pm 0.01(o)	A
	300	5.45(e)	D
		5.4(e)	Barker [14]
		5.501 \pm 0.01(e)	A
	300	5.26(p)	D
		5.1(p)	Kodak [20]
		5.289(p)	A
CaF_2	4	6.47 \pm 0.03	L
	80	6.38 \pm 0.08	B
	80	6.51 \pm 0.03	L
	200	6.53 \pm 0.08	B
	200	6.66 \pm 0.03	L
	300	6.7 \pm 0.3	K
	300	6.63 \pm 0.08	B
	300	6.81 \pm 0.03	L
	300	6.78 \pm 0.03	R
	300	6.35 \pm 0.06	J
	300	6.8120 \pm 0.0007	A
SrF_2	4	6.15 \pm 0.03	L
	80	6.04 \pm 0.08	B
	80	6.19 \pm 0.03	L
	200	6.30 \pm 0.03	L
	300	6.6 \pm 0.3	K
	300	6.20 \pm 0.07	B
	300	6.50 \pm 0.03	L
	300	6.48 \pm 0.03	R
	300	6.4679 \pm 0.0006	A
BaF_2	4	6.96 \pm 0.03	L
	80	6.56 \pm 0.09	B
	80	7.01 \pm 0.04	L
	200	7.16 \pm 0.04	L
	300	7.2 \pm 0.4	K
	300	6.94 \pm 0.08	B
	300	7.32 \pm 0.04	L
	300	7.28 \pm 0.04	R
	300	7.02 \pm 0.07	J
	300	7.3605 \pm 0.0007	A

^aThe letters o, e, and p in the parentheses indicate the ordinary-ray, extraordinary-ray, and polycrystalline.

^bThe capital letters in this column carry the following abbreviations:

D—Duncanson [18],

A—Andeen et al [19],

L—Lowndes [15],

B—Bosomworth [16],

K—Kaiser et al [17],

R—Rao and Smakula [21],

J—Jones [22].

reflection spectra. It is accepted that corresponding to each of the peaks of a reflection spectrum there is an absorption peak at somewhat shifted wavelength; the sharper the peak, the less the shift. The far ultraviolet spectra of alkaline earth fluorides have been studied by Rubloff [24], Nisar and Robin [25], etc. Rubloff's work is used in the present work because his observations were made at several discrete temperatures. This feature opened the possibility of estimating the temperature variation of λ_u . Figures 4, 5, and 6 show his results for the normal reflection spectra of CaF_2 , SrF_2 and BaF_2 crystals in the far ultraviolet. For clarity, a vertical shift of 0.0175, respectively, separating the 90

K spectra (above) and the 400 K spectra (below) from the spectra taken at 300 K, were made in these figures. According to Rubloff, the spectral regions marked in each of the spectra with I, II, and III correspond, respectively to:

I. excitation of an electron from the upper valence bands to the lower conduction bands,

II. excitation of an electron from the outermost core states of the metal ion,

III. interband and ionizing transitions of core electrons.

Shifts in energy with temperature are observed and are determined for sharp peaks. The energies of such peaks at various temperatures are given in table 7, from which the room temperature effective wavelength, λ_u , can be estimated. The results are: $\lambda_u=0.09315$ micrometer for CaF_2 , $\lambda_u=0.09566$ micrometer for SrF_2 and $\lambda_u=0.10208$ micrometer for BaF_2 . These values will be used as guidelines in the data analysis.

2.2. Temperature Derivative of Refractive Index, dn/dT

For users of the refractive index, information on the temperature derivative, dn/dT , is indispensable. The temperature dependence of the refractive index of crystals is of considerable interest in connection with a wide variety of optics applications. In the area of high-power lasers, dn/dT plays an important role in thermal lensing problems. A great deal of research effort is spent in finding the magnitude of dn/dT and its frequency dependence on the laser wavelength regions.

With regard to the thermo-optical behavior of the alkaline earth halides, the existing data are not useful. Much of the data is for two materials, CaF_2 and BaF_2 , and is concentrated in limited spectral regions, the visible and near ultraviolet. Outside these regions, especially in the infrared, limited data are available, a very discouraging fact to workers in laser research. It is, therefore, highly desirable to obtain a theoretical prescription which allows prediction of dn/dT over a wide range of wavelengths, based on at most a small number of experimental measurements.

Ramachandran [26] presented a semiempirical theory of thermo-optical effects in crystals, in which the dispersion was fitted to experimental data, employing a series of oscillator frequencies and strengths as adjustable parameters. A close correlation was found between temperature shifts of various parameters and those of the fundamental oscillator frequencies. Unfortunately, the parameters chosen were rather numerous and often physically obscure or not unique; no general prescription was presented for determining their temperature variations, which are necessary for calculating dn/dT . Teay, Bendow, and Mitra [27] introduced a two-oscillator model which accounts for the variation with temperature of the energy gap (electronic contribution to dn/dT) and the fundamental phonon frequency (lattice contribution to dn/dT). This model seems to fit the infrared data, but it does not agree well with the existing data in the uv region. A somewhat modified approach is to formulate a semi-empirical equation which serves the dual purpose of giving a good fit to existing data and a reasonable prediction of missing information.

Unlike the case of alkali halides, dn/dT data for the alkaline earth halides are not abundant enough to establish an

TABLE 6. Special position of the fundamental optical phonon of alkaline earth halides

Material	Temperature (K)	λ_{TO} (Micrometer)	λ_{LO} (Micrometer)	Author ^b
MgF_2	300	22.2, 24.2, 40.6(o) ^a		Baker [14]
	300	18.0, 25.0(e)		Baker [14]
CaF_2	5	37.04 ± 0.19	20.66 ± 0.10	L
	80	37.45 ± 0.28		B
	100	37.00 ± 0.19		L
	200	37.45 ± 0.19		L
	300	38.9	21.6	K
	300	38.02 ± 0.19	20.75 ± 0.10	L
	400	38.76 ± 0.19		L
	500	39.53 ± 0.20		L
SrF_2	5	43.76 ± 0.22	25.19 ± 0.13	L
	80	44.44 ± 0.40		B
	100	43.86 ± 0.22		L
	100	44.64		D
	200	44.25 ± 0.22		L
	300	45.05 ± 0.23	25.32 ± 0.13	L
	300	46.1	26.74	K
	300	45.66		D
	400	46.30 ± 0.23		L
	500	47.39 ± 0.24		L
BaF_2	5	52.68 ± 0.26	28.90 ± 0.14	L
	80	52.91 ± 0.56		B
	100	52.63 ± 0.26		L
	200	52.91 ± 0.26		L
	300	53.33 ± 0.27	29.07 ± 0.15	L
	300	54.3	30.67	K
	400	54.20 ± 0.27		L
	500	55.56 ± 0.28		L

^aThe letters o and e in the parentheses indicate the ordinary-ray and extraordinary-ray, respectively.^bThe capital letters in this column carry the following abbreviations:

- L—Lowndes [15],
 B—Bosomworth [16],
 K—Kaiser et al [17],
 D—Denham et al [23].

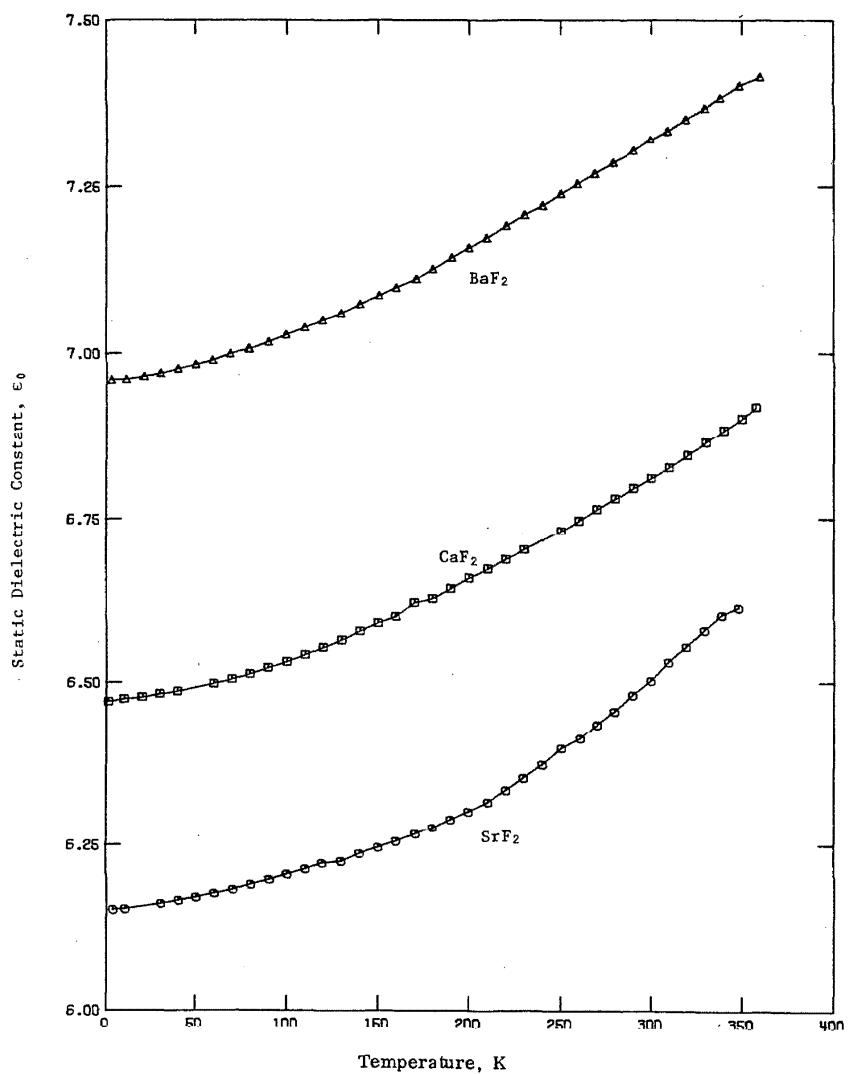


Figure 2. Temperature dependence of the Static Dielectric Constant of Alkaline Earth Fluorides [16]

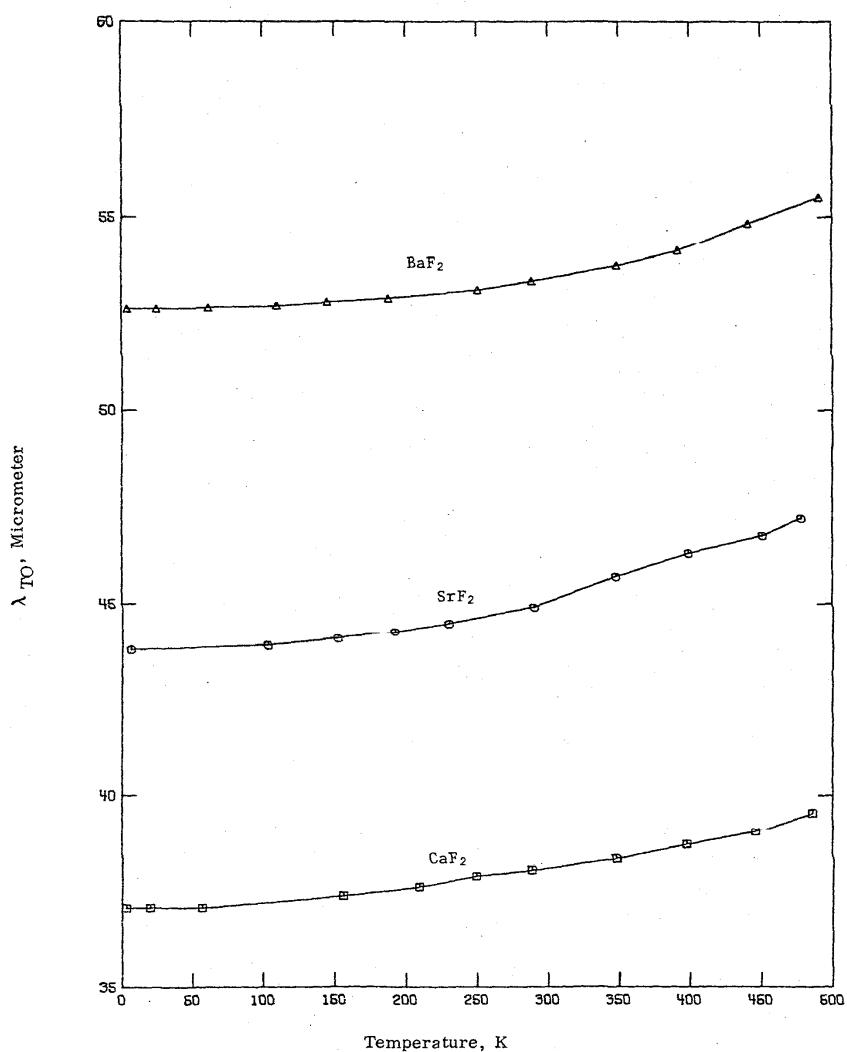


Figure 3. Temperature dependence of the Wavelength of Fundamental Transverse Optical Phonon of Alkaline Earth Fluorides [15]

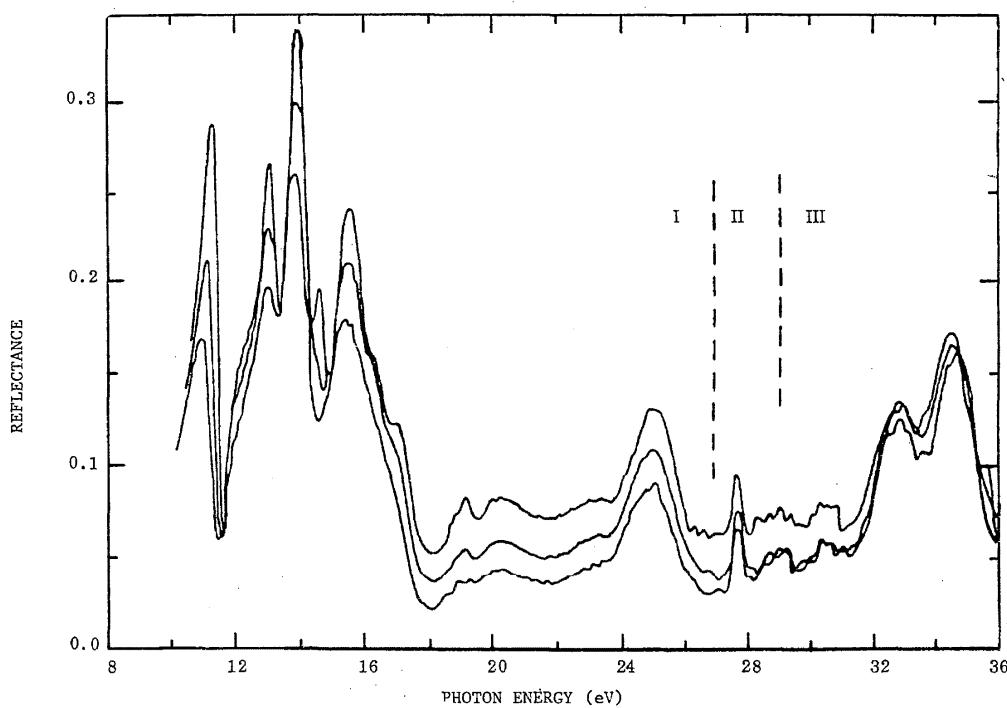


Figure 4. Near-Normal Incidence ($\approx 6^\circ$) Reflectance Spectrum of CaF_2 Crystal in the Far Ultraviolet [24].

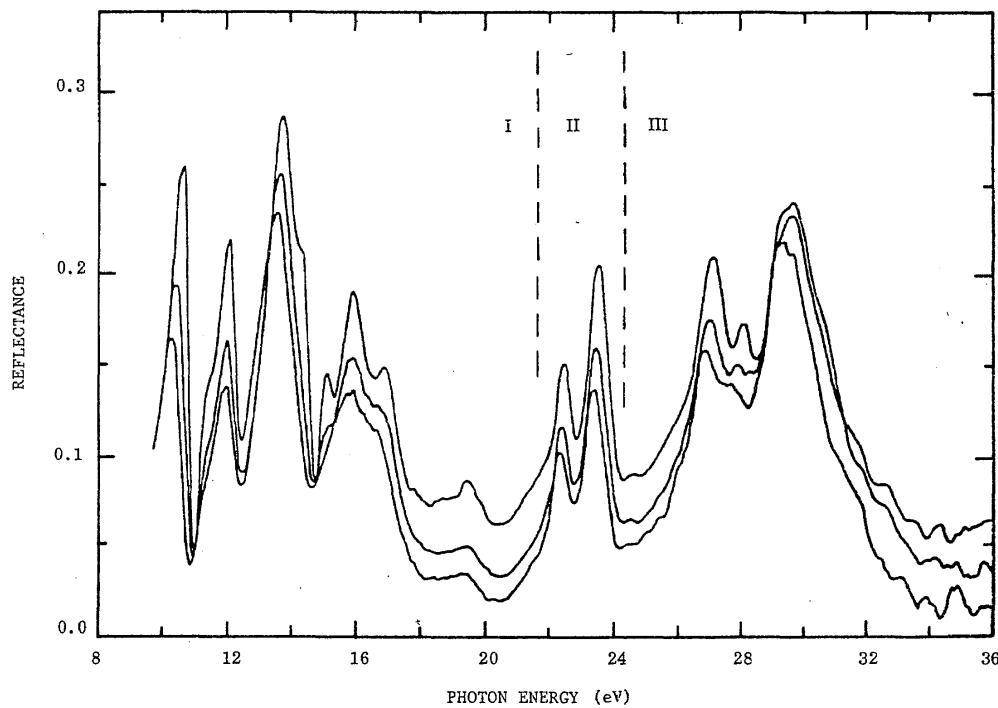


Figure 5. Near-Normal Incidence ($\approx 6^\circ$) Reflectance Spectrum of SrF_2 Crystal in the Far Ultraviolet [24].

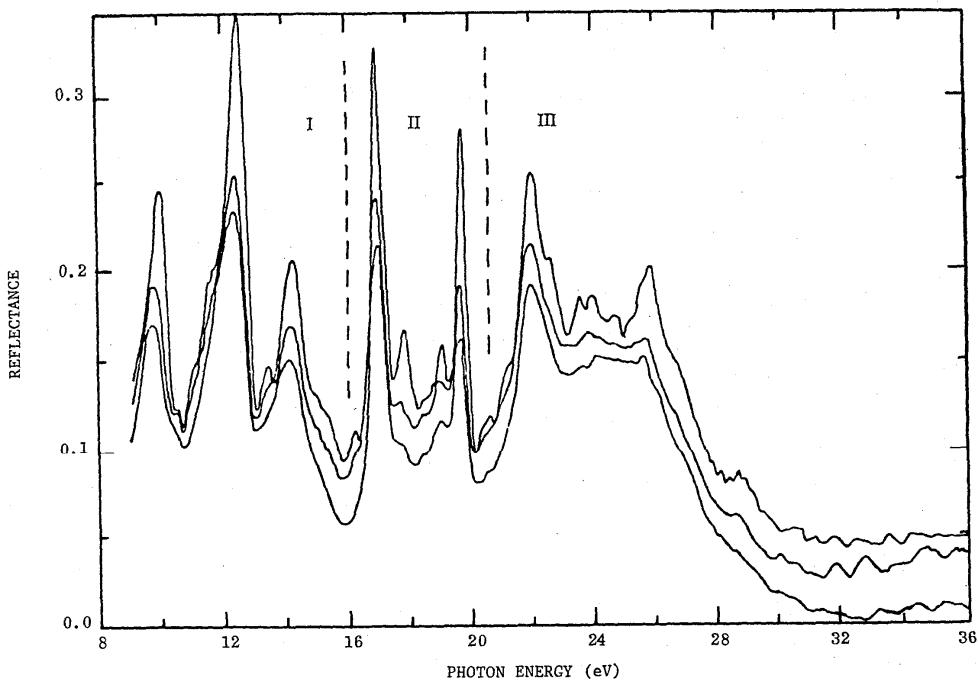
Figure 6. Near-Normal Incidence ($\approx 6^\circ$) Reflectance Spectrum of BaF_2 Crystal in the Far Ultraviolet [24].

TABLE 7. Temperature dependence of the energies of sharp reflectance peaks (after Rubloff)

Material	Peak energy (eV)		
	90 K	300 K	400 K
CaF_2	11.18	11.02	10.85
	13.04	12.97	12.92
	13.93	13.86	13.79
	15.53	15.40	15.37
	25.10	25.05	25.00
	27.70	27.75	27.75
	32.85	32.85	32.85
	34.50	34.50	34.50
SrF_2	10.60	10.41	10.27
	12.02	11.98	11.91
	13.71	13.61	13.55
	15.86	15.85	15.80
	22.47	22.42	22.37
	23.56	23.50	23.46
	27.14	27.10	26.95
	29.70	29.70	29.40
BaF_2	10.00	9.80	9.76
	12.66	12.44	12.46
	14.34	14.20	14.24
	17.10	17.08	17.09
	19.19	19.12	19.14
	19.89	19.81	19.80
	22.13	22.05	22.10

observable trend of data among materials. This leaves us no choice but to resort to the existing theories. Furthermore, in practical applications, the true dn/dT of the material rather than the relative dn/dT (relative to air) is generally used. Therefore, the true dn/dT is discussed in the present work. The following terms appear in various theories of dn/dT :

- (1) A constant, A_0 , representing the total effect of contributions other than those considered explicitly in other terms.
- (2) A term arising from thermal expansion of the crystal. Various theories yield the same expression, $-3\alpha(n^2-1)$, for this term, where α is the linear thermal expansion and n the refractive index corresponding to the wavelength under consideration.
- (3) A term due to thermal shift of the uv resonant wavelength. Starting from the two oscillator model, it is found that this contribution is

$$(\epsilon_\infty - A) \frac{\lambda^4}{\lambda_u} \frac{d\lambda_u}{dT} / (\lambda^2 - \lambda_u^2)^2$$

where λ_u is the effective wavelength of uv absorption bands. In some theories λ_u is replaced by ω_g , the frequency corresponding to the gap energy of the crystal. To evaluate this term requires knowledge which is in general not accurate or is missing. In cases where there are sufficient dn/dT data for the uv region, one can determine this quantity through curve fitting. We shall consider the quantity

$$(\epsilon_\infty - A) \frac{1}{\lambda_u} \frac{d\lambda_u}{dT}$$

as an adjustable parameter A_1 in the data-fitting calculation.
(4) A term due to the thermal shift of the optical phonons. This contribution can be evaluated using the expression

$$(\epsilon_0 - \epsilon_\infty) \frac{\lambda^4}{\lambda_1} \frac{d\lambda_1}{dT} / (\lambda^2 - \lambda_1^2)^2,$$

where λ_1 corresponds to the wavelength of the TO optical phonon. The quantities ϵ_∞ , ϵ_0 , and λ_1 are in general available in the literature and $d\lambda_1/dT$ can be estimated from Lowndes' work (see figure 3). Therefore there is no unknown parameters in this term.

(5) A term due to the thermal variation of the transverse effective charge, e^* . This term is proportional to the expression

$$(\epsilon_0 - \epsilon_\infty) \frac{1}{e^*} \frac{de^*}{dT} / (\lambda^2 - \lambda_1^2).$$

Theoretical treatments and direct measurements of de^*/dT do not appear to exist. There is therefore no alternative but to estimate the effect of this contribution by fitting the dn/dT data to the dn/dT formula with

$$(\epsilon_0 - \epsilon_\infty) \frac{1}{e^*} \frac{de^*}{dT}$$

as an adjustable parameter A_2 .

The following equation summarizes the five contributions mentioned above:

$$\begin{aligned} 2n(dn/dT) = & -3u(n^2 - 1) + A_0 + \frac{A_1 \lambda^4}{(\lambda^2 - \lambda_u^2)^2} \\ & + \frac{A_2 \lambda^2}{\lambda^2 - \lambda_1^2} + \frac{2(\epsilon_0 - \epsilon_\infty) \lambda^4}{(\lambda^2 - \lambda_1^2)^2} \left(\frac{1}{\lambda_1} \frac{d\lambda_1}{dT} \right) \end{aligned} \quad (14)$$

In the cases of CaF_2 , SrF_2 , and BaF_2 , the quantities ϵ_0 , λ_1 , and $d\lambda_1/dT$ are made available by Lowndes [15], and ϵ_∞ is available from the literature. Although λ_u and $d\lambda_u/dT$ can be estimated from Rubloff's [24] observations on the reflection spectra at various temperatures, it is preferred to determine A_1 through the data fitting for CaF_2 and BaF_2 . For SrF_2 , uv dn/dT data are not available, and Rubloff's results must be used. However, in the case of MgF_2 , CaCl_2 , SrCl_2 , and BaCl_2 , such information is not readily available, and no attempt is made to apply the dn/dT formula. It should be emphasized that equation (14) gives the true dn/dT of the material, not that relative-to-air. True dn/dT can be determined either by an interferometric method or by reduction of relative dn/dT values which are usually determined by the prism method. The following relation is used to calculate true dn/dT from the corresponding relative-to-air values:

$$\frac{dn}{dT} = \left(\frac{dn}{dT} \right)_{\text{relative}} + n \frac{dn_{\text{air}}}{dT}$$

dn_{air}/dT is approximately proportional to the volumetric expansion coefficient of the air [11]. It can be shown that the value of dn_{air}/dT is about -1.1×10^{-6} . Therefore, a correction of $-1.1 \times 10^{-6}n$ should be added to relative dn/dT to obtain the true dn/dT .

3. Numerical Data

Reference data are generated through critical evaluation, analysis, and synthesis of the available experimental data. The procedure involves critical evaluation of the validity and accuracy of available data and information, resolution and reconciliation of disagreements in conflicting data, correlation of data in terms of various controlling parameters, curve fitting with theoretical or empirical equations, comparison of resulting values with theoretical predictions or with results derived from semi-theoretical relationships. Physical optical principles and semi-empirical techniques are employed to fill gaps and to extrapolate existing data so that the resulting recommended values are internally consistent and cover as wide a range of each of the controlling parameters as possible. No attempt was made to analyze the thin film data and the regions of strong absorption, because of the scantiness of reliable information. However, experimental data for such regions are also presented along with those for the transparent region in the experimental data tables.

A number of figures and tables summarize the information and give data as a function of wavelength and temperature. The conventions used in this presentation, and specific comments on the interpretation and use of data are given below. Each subsection in this section gives all the information and data for a given material. The subsections are arranged in the following order:

- 3.1. Calcium Fluoride, CaF_2
- 3.2. Strontium Fluoride, SrF_2
- 3.3. Barium Fluoride, BaF_2
- 3.4. Magnesium Fluoride, MgF_2
- 3.5. Calcium Chloride, CaCl_2
- 3.6. Strontium Chloride, SrCl_2
- 3.7. Barium Chloride, BaCl_2

Presented in each subsection are information and data in the following order:

- a text describing the material and discussing the data, analysis, and recommendations,
- a table of recommended (including provisional) values on n , $dn/d\lambda$, and dn/dT ,
- a figure of n ,
- a figure of $dn/d\lambda$,
- a figure of dn/dT ,
- a table of measurement information on n ,
- a table of experimental data on n ,
- a table of measurement information on dn/dT (if any),
- a table of experimental data on dn/dT (if any),
- a table for comparison of proposed dispersion equations (if any).

In all figures containing experimental data, a curve number corresponds to a data set number assigned in the accompanying tables on the measurement information and experimental data. When several sets of data are too close to be resolved, some of

the data sets, though listed in the table, are omitted from the figure for the sake of clarity.

In the figures of index n and dn/dT , the wavelength is plotted on a logarithmic scale in order to cover a wide wavelength range in a single plot. In the figures for $dn/d\lambda$, both $dn/d\lambda$ and λ are logarithmically plotted. The tables on the measurement information give for each set of data the following information: the reference number, author's name (or names), year of publication, experimental method used for the measurement, wavelength range covered by the data, temperature range, the description and characterization of the specimen, and information on measurement conditions contained in the original paper. In these tables the code designations used for the experimental methods for refractive index determinations are as following:

- A Abeles method
- D Deviation method (prism method)
- P Pulfrich or Abbe refractometer
- I Interference method
- T Transmission method
- R Reflection method
- M Immersion method
- H High frequency modulation method
- B Brewster angle method
- C Polarization method
- S Thickness determination method
- L Multilayer method
- F Focal length method

The methods listed above are arranged in the order of the inherent accuracy or their popularity. The deviation method is the most popular and accurate means of determining the refractive indices to the fifth decimal place or better. The Pulfrich refractometer and interference technique can be used up to the fourth decimal place. Transmission, reflection, and immersion methods yield results good to the third place, while the multilayer and focal length results are no better than two or three places. For a comprehensive yet concise review of all these methods, the reader is referred to the text in [8] and [9].

For some materials, dispersion equations have been proposed in a number of earlier works. In such cases, a table listing a few typical proposed equations is given. All equations are converted to the form of eq (7) whenever possible so as to facilitate a visual comparison. This table is by no means an exhaustive collection; however, it gives the reader a general picture on the evolution of the dispersion formulas used in the calculation of the refractive index.

In the tables of recommended (including provisional) values, the values are presented with step-wise increasing increments in wavelength. The magnitudes of the increments vary with the slope and curvature of the curve to facilitate linear

interpolations. The following scheme (in units of micrometer) is uniformly adopted for this presentation.

Wavelength range	Increment
< 0.30	0.002
0.30— 0.40	0.005
0.40— 0.60	0.01
0.60— 1.00	0.02
1.00— 5.00	0.05
5.00— 10.00	0.10
10.00— 15.00	0.20
> 15.00	0.50

In the tables, values for each property are given to the same number of decimal places in order to show the variations of the property and for tabular smoothness; this should not be interpreted as indicative of the accuracy of the values. The uncertainties of the tabulated values for the refractive index, $dn/d\lambda$ and dn/dT for each material in different wavelength ranges is given in the discussion pertaining to the material. In connection with this, the tabulated values are classified as "recommended values" or "provisional values". The criteria of the classification depend upon the level of confidence in the values as given below:

Uncertainty range	Classification
For refractive index:	
≤ 0.005	recommended
> 0.005	provisional
For dn/dT (in units of 10^{-6} K^{-1}):	
≤ 3.0	recommended
> 3.0	provisional

It should be noted that recommendations are made only for the bulk materials at 293 K in the transparent wavelength region.

In general, refractive indices obtained by the deviation method are reported to the fifth or sixth decimal place. However, detailed compositions and characterizations of the specimens are usually not clearly given. Since impurities in the sample and conditions of the surfaces are decisive factors affecting the observed results, such highly precise data can not be applied to a sample chosen at random. For this reason we do not attempt to recommend any particular set of data with the reported high accuracy, but to generate the most probable values for the pure crystals. As a result, the estimated uncertainties for the recommended values on the refractive index are higher than those for the reported data obtained by high-precision measurements. In this work, the highest estimated accuracy of the refractive index is to the fourth decimal place.

3.1. Calcium Fluoride, CaF_2

Calcium fluoride, one of the fluorite-type crystals, is of considerable interest from the experimental and theoretical point of view. The compound is ionic but, in contrast to binary NaCl -type crystals, it has a number of structural features associated primarily with the presence of two equivalent F^- ions in a unit fluorite cell.

Rather pure single crystal calcium fluoride is found in nature and is called "Fluorite" or "Fluorspar". Calcium fluoride of similar purity, but of larger dimensions, has been produced by controlled freezing of purified molten calcium fluoride after an initial scavenging with lead fluoride. Fluorspar is widely used in iron foundry operations, the manufacture of primary aluminum and magnesium, as source of fluorine chemicals, for the production of glass and enamels, and innumerable other uses.

Calcium fluoride has been an important optical material used in the design of optical components and systems for many years because it occurs naturally in large sizes and many measurements on the refractive index are available. The crystal is transparent in the region from about 0.15 to 15 micrometers. The transparent region may be divided into three subregions, in each of which CaF_2 has useful applications. From 0.15 up to 0.3 micrometer and from 6.0 up to 15 micrometers the dispersion is high and the crystal is used for high dispersion devices, in spite of low transmittance at the limits. In the region from 0.3 up to 6.0 micrometers dispersion is low but transmission is high, and it is therefore used as windows and lenses in optical systems.

Among the alkaline earth halides, calcium fluoride is the most used material. One of the reasons is that it is readily available in large sizes. In the present work we have compiled more than thirty data sets. The earliest measurement on the refractive index of CaF_2 was made by Stefan [28] in 1871. Since then, numerous observations were carried out. Among the early active investigators are Ruben [32], Paschen [37] and Martens [41]. As can be anticipated, the early work was performed in the transparent region by the prism method. As a result, refractive indices of CaF_2 in the wavelength region from 0.18 to 9.43 micrometers were already available by the turn of the century. Coblenz [9], in 1920, reduced the measured and computed values of Langley [39], Paschen [39] and Rubens [35] to a common temperature of 293 K and after careful analysis adopted a table of refractive index from a smooth curve drawn through these data. This table of refractive index was thought to represent the most accurate and comprehensive values available in the literature. Another table of refractive index was compiled by Kohlrausch [95] in 1940, including data in the ultraviolet region.

It can also be anticipated that refractive indices in the visible region are accurate, while those in the invisible regions need further verification because of inadequate infrared detecting devices and inaccurate spectral line identification. Most of these data have been referenced and compared and quoted in the literature through the years, but no further measurement in this region was made until 1963, when Malitson [48] performed a systematic measurement of the refractive index for both natural and synthetic CaF_2 crystals in the spectral region from 0.22 to 9.73 micrometers, using the prism method. He found that the difference in refractive index of the synthetic and natural fluorite is of the order of 3×10^{-5} . This excellent agreement

between samples demonstrates that the artificial crystal, when properly synthesized, should be comparable in refractive properties to good natural fluorite. Compared with values of Coblenz and Kohlrausch, good agreement is observed in the visible region and discrepancies occur in the ultraviolet and infrared as expected. Dodge [93] measured refractive indices for a sample of hot-forged CaF_2 , polycrystalline, in the wavelength range from 0.25 to 8.0 μm by means of minimum deviation method at two temperatures, 294 K and 307 K. Each of the data sets was fitted to a three-term Sellmeier equation within a few parts in the fifth decimal place. Compared with the single crystal data, it was found that in most parts of the wavelength region considered where the refractive index of the hot-forged CaF_2 is always less than that of single crystal. The discrepancies reach to a minimum between 0.7 and 0.9 μm and a maximum discrepancy of 0.00066 occurs at 0.28 μm and 4.8 μm . Beyond these two wavelengths in the ultraviolet and infrared, refractive index of hot-forged CaF_2 becomes sharply higher than that of a single crystal.

Experimental measurements on the refractive index of CaF_2 in the transparent region were made for the purpose of optical applications such as optical components and system design, particularly for the ultraviolet and infrared regions. Experimental studies outside the transparent region were performed with different purposes in mind. In the ultraviolet region the main interest is to determine the band structure of the crystal. Because of high absorption in the vacuum ultraviolet, the optical properties in the short wavelength region can only be derived through the analysis of reflection spectra. Fabre et al. [49] found, through Kramers-Kronig analysis, a strong absorption peak located at 0.112 micrometer which sets the lower wavelength limit of the transparency of CaF_2 . Field et al. [52] found, by the oscillator fit method, that the absorption peak nearest to the transparent region is at 0.119 micrometer. The complexity of absorption in the UV region is revealed by further exploration into the UV region with higher photon energy. Ganin et al. [53] studied the optical properties in the energy range 5–20 eV by Kramers-Kronig analysis of the reflection spectrum. In addition to the first absorption peak at 0.112 micrometer, he observed more absorption peaks with intensities comparable to that of the first peak. Further details of the reflection spectrum in the UV region were investigated by Rubloff [24], with photon energy up to 36 eV, at three temperatures as shown in figure 4 and table 7.

In the far infrared region, the purpose of the majority of studies has been to determine precisely the frequencies of the optically active lattice vibrations, and the refractive index at long wavelength. In the absence of absorption, refractive index at long wavelength is approximately the square root of the static dielectric constant. Berman et al. [50] investigated the region from 294 to 580 micrometers using the reflection and transmission method. The resulted refractive indices in the region from 290 to 580 shown no dispersion within the limits of experimental error and the averaged value of refractive index, 2.58, is in agreement with that calculated from the static dielectric constant. However, dispersion of n occurs in the region from 110 to 280 micrometers. Kaiser et al. [17] studied the reflection spectrum in the restrahlen region from 10 to 80 micrometers. Two

absorption peaks were deduced from the reflection spectrum by the Lorentz oscillator theory. The stronger one, at 38.9 micrometers, was identified as the optical active TO resonance and the other one, about one order of magnitude weaker, is at 30.5. The origin of this weaker absorption was unknown and Kaiser proposed the possibility of a two-phonon combination band involving the TO mode. However, this weak absorption does not appear in Lowndes' work [15] in which the reflection spectrum was studied by Kramers-Kronig analysis. Since Lowndes may have used a purer sample than that used by Kaiser, it is likely that the weaker absorption at 30.5 micrometers is due to impurity contents of the sample.

On the basis of our review of available data, data sets measured by Maltison [48], Martens [41], and Paschen [40] were selected as the basis for reference data generation because of the consistency of their results. Malitson used the Sellmeier formula to mathematically fit his experimental data. The resulting Sellmeier formula is listed in table 17, where dispersion quotations proposed by various investigators are listed together to facilitate a visual comparison. The optical dielectric constant calculated from his equation is 2.04, which is in agreement with those obtained from other dispersion equations. However, the static dielectric constant based on his equation is 5.887, substantially lower than the experimental value, 6.81. This large discrepancy is mainly due to a low value of the infrared absorption wavelength used in his equation. The dispersion equation obtained by Martens included three terms due to infrared absorption and yielded a value of 6.92 for the static dielectric constant. He used as wavelengths of the three absorption bands 24.0, 31.6, and 40.53 micrometers. The second corresponds to that reported by Kaiser et al. and the third and first correspond to the TO and LO mode phonons, respectively. Although these wavelengths are somewhat longer than the corresponding but more reliable values now available, it is indeed surprising that Martens could make a prediction based on the then available refractive index data in a limited wavelength range.

To account for the ultraviolet absorption effects, Malitson used two terms, the one with the longer resonant wavelength representing the total effect of the first few strong absorption peaks and the other representing the effect of the remaining absorption. Martens used a single term and a constant to account for the effect of ultraviolet absorptions. The first term represented the total effect of excitations of electrons from the upper valence bands to the lower conduction bands, while the constant represented the total effect of excitations of the outermost core electrons, the interband and ionizing transitions.

In the present work, we followed Marten's treatment for uv contributions and used the available wavelengths of optical phonons for the infrared terms in the dispersion equation. More precisely, the equation consists of a constant, one term from uv contributions and two terms from infrared contributions. The following two values were chosen as the wavelengths of optical phonons:

$$\lambda_{LO} = 21.18 \text{ micrometers (average of two entries in table 6)},$$

$$\lambda_{TO} = 38.46 \text{ micrometers (average of three entries in table 6)},$$

The calculation yielded the following dispersion equation for

CaF_2 at 293 K in the transparent region, 0.15–12.0 micrometers:

$$n^2 = 1.33973 + \frac{0.69913 \lambda^2}{\lambda^2 - (0.09374)^2} + \frac{0.11994 \lambda^2}{\lambda^2 - (21.18)^2} \\ + \frac{4.35181 \lambda^2}{\lambda^2 - (38.46)^2}, \quad (1)$$

where λ is in units of micrometers.

This dispersion equation closely fits Malitson's values, with root mean square residual of 2.4×10^{-5} in the spectral region from 0.22 to about 10.0 micrometers. However, in extending the use of the equation beyond this region care must be exercised because of the uncertain accuracy with which it represents effects of the nearby absorption bands. In the infrared region beyond 10.0 micrometers, this equation would be expected to be valid up to 12 micrometers, because absorption bands in the infrared regions have little effect on the refractive index in the transparent region. In the ultraviolet region the situation is different. The effective wavelength, λ_u , can be used in representing the total effect of a number of absorption bands on the refractive index in the transparent region far enough from the first exciton peak at 0.112 micrometer, but in the spectral range from 0.15 to 0.22 micrometer errors may arise from errors in the values of λ_u , which was determined by fitting the available data at wavelengths longer than 0.22 micrometers. An estimate of an upper limit on the uncertainties can be evaluated by the following equation, obtained by differentiating eq (15) with respect to λ :

$$\Delta n = \frac{0.69913 \lambda^2}{(\lambda^2 - \lambda_u^2)^2} \left(\frac{\lambda_u \Delta \lambda_u}{n} \right), \quad (16)$$

$$\text{where } \Delta \lambda_u = 0.112 - \lambda_u.$$

The optical dielectric constant obtained from eq (15) is 2.03866, in good agreement with that from other work. The static dielectric constant implied by this equation is 6.511, about 0.3 less than Andeen's value (see table 5). This discrepancy is no larger than that is to be expected, since there are still many resonant far infrared absorptions, not accounted for by eq (15), which make small contributions to the static dielectric constant. The Sellmeier formula is at best an approximation describing the observed data in the transparent region by neglecting the damping factors in the dispersion equation. Ignoring the damping factors effectively reduces the magnitude of the coefficients of the corresponding terms, and leads to a smaller value of the static dielectric constant.

In addition to the room temperature refractive index, dn/dT data is needed for evaluation of n at other temperatures. Among the alkaline earth halides, calcium fluoride is the only material for which dn/dT has been frequently investigated. The resulting data are given in figure 10 and table 13. It is clear from figure 10 that discrepancies between investigators are quite appreciable at wavelengths longer than that of visible light. However, the magnitude of the discrepancies is in the order of $1 \text{ to } 2 \times 10^{-6} \text{ K}^{-1}$, which is in same order of magnitude of dn_{air}/dT as discussed in section 2.2. The other source may be due to uncertainties in the determination of refractive indices, because the tem-

perature intervals used in these experiments are in general less than 100 degrees; thus discrepancies of a few units in the fifth decimal place or of one unit in the fourth place of the refractive indices will give large discrepancies in dn/dT . It can be seen from figure 10 that the discrepancies become noticeable in the region beyond about one micrometer in the infrared. Experimental errors in measuring refractive indices are likely to be large in this region because no photographic method can be used. However, among the available data, those reported by Lipson et al. [59], by Harris et al. [60], and by Tsay et al. [92] were obtained by using an interference method in which dn/dT was determined directly by observing the changes in the number of fringes in a given temperature interval. This method is believed to be the most accurate method for the determination of dn/dT , but data obtained by this method are available only at five spectral lines, wavelengths 0.325, 0.4416, 0.6328, 1.15, and 3.39 micrometers.

With the existing data we have no alternative but to use the data of Micheli [56], Liebreich [57, 58], and Malitson [48] at wavelengths shorter than 0.8 micrometer in the determination of the coefficients of the constant and ultraviolet terms, neglecting the infrared terms. This approximation is valid because a simple calculation will show that the effect of the infrared terms on dn/dT in the wavelength range mentioned is less than 0.1, while the magnitude of dn/dT is about 10. Then, by using the data of Lipson et al. [59] and of Tsay et al. [92] in the calculation of the coefficients of the infrared terms, we found the equation given below, which closely fits the selected data:

$$2n \frac{dn}{dT} = -16.6 - 57.3(n^2 - 1) + \frac{44.9\lambda^4}{[\lambda^2 - (0.09374)^2]^2} + \frac{151.54\lambda^2}{[\lambda^2 - (38.46)^2]} + \frac{1654.6\lambda^4}{[\lambda^2 - (38.46)^2]^2} \quad (17)$$

Data on the temperature dependence of dn/dT have been obtained for five spectral lines by Houston et al. [47], Selezneva [68], Lipson et al. [59], and Tsay et al. [92]. The measurement information and results of their work are given in tables 15 and 16 and are plotted in figure 11. A general trend revealed by the available data is that in the vicinity of room temperature and magnitude of dn/dT increases slightly with temperature. Although available data on dn/dT versus temperature are limited

to a few particular wavelengths, the same trend is likely to hold at other wavelengths. A similar effect was noted by Malitson [48]. The possible origin of this increase was discussed by Lipson et al. and Tsay et al., with the conclusion that the dn/dT of CaF_2 exhibits a variation with temperature comparable to that of the thermal expansion coefficient. However, the relation between the variation of dn/dT with temperature and the change of the thermal expansion coefficient has not yet been established for general applications because it varies very much with wavelengths. For the time being the application of eq (4) to evaluate dn/dT at temperatures not far from 293 K is recommended.

Equations (15) and (17) were used to generate the reference data given in the table of recommended values. Values of $dn/d\lambda$ were simply evaluated by the first derivative of eq (15). Although the values of n are given to the fourth decimal place and those of dn/dT to the first, this does not reflect the accuracy and reliability of the results; they are so given simply for smoothness of tabulation. However, an overstrike is placed to indicate the insignificant part of the value. For the proper use of the tabulated values the reader should follow the criteria given below.

For refractive index:

Wavelength range micrometer	Estimated uncertainty, \pm
0.15–0.20	0.005
0.20–0.30	0.0005
0.30–0.40	0.0002
0.40–9.00	0.0001
9.00–10.0	0.0005
10.0–12.0	0.005

For dn/dT :

0.15–0.20	3.0
0.20–0.30	2.0
0.30–1.00	1.0
1.0–6.00	1.5
6.0–10.0	2.0
10.0–12.0	3.0

TABLE 8. RECOMMENDED VALUES ON THE REFRACTIVE INDEX AND ITS WAVELENGTH AND
TEMPERATURE DERIVATIVES FOR CALCIUM FLUORIDE AT 293K *

λ μm	n	$-\frac{dn}{d\lambda}$ μm^{-1}	$\frac{dn}{dT}$ 10^{-6}K^{-1}	λ μm	n	$-\frac{dn}{d\lambda}$ μm^{-1}	$\frac{dn}{dT}$ 10^{-6}K^{-1}	λ μm	n	$-\frac{dn}{d\lambda}$ μm^{-1}	$\frac{dn}{dT}$ 10^{-6}K^{-1}
0.150	1.5769	3.1079	6.1	0.220	1.4811	0.5819	-6.1	0.290	1.4560	0.2163	-8.5
0.152	1.5709	2.9003	5.2	0.222	1.4800	0.5623	-6.2	0.292	1.4556	0.2113	-8.6
0.154	1.5653	2.7121	4.3	0.224	1.4788	0.5436	-6.3	0.294	1.4552	0.2065	-8.6
0.156	1.5600	2.5412	3.6	0.226	1.4778	0.5258	-6.4	0.296	1.4548	0.2018	-8.6
0.158	1.5551	2.3854	2.9	0.228	1.4767	0.5088	-6.5	0.298	1.4544	0.1972	-8.7
0.160	1.5505	2.2429	2.3	0.230	1.4757	0.4925	-6.6	0.300	1.4540	0.1928	-8.7
0.162	1.5461	2.1125	1.7	0.232	1.4748	0.4769	-6.7	0.305	1.4531	0.1823	-8.8
0.164	1.5420	1.9926	1.1	0.234	1.4738	0.4620	-6.8	0.310	1.4522	0.1727	-8.9
0.166	1.5382	1.8823	0.6	0.236	1.4729	0.4478	-6.9	0.315	1.4513	0.1637	-8.9
0.168	1.5345	1.7806	0.1	0.238	1.4720	0.4341	-7.0	0.320	1.4505	0.1553	-9.0
0.170	1.5310	1.6865	-0.3	0.240	1.4712	0.4211	-7.1	0.325	1.4498	0.1475	-9.1
0.172	1.5278	1.5994	-0.7	0.242	1.4704	0.4086	-7.2	0.330	1.4490	0.1403	-9.1
0.174	1.5246	1.5186	-1.1	0.244	1.4696	0.3965	-7.2	0.335	1.4484	0.1335	-9.2
0.176	1.5217	1.4435	-1.5	0.246	1.4688	0.3850	-7.3	0.340	1.4477	0.1272	-9.3
0.178	1.5189	1.3736	-1.8	0.248	1.4680	0.3739	-7.4	0.345	1.4471	0.1212	-9.3
0.180	1.5162	1.3084	-2.1	0.250	1.4673	0.3633	-7.5	0.350	1.4465	0.1157	-9.4
0.182	1.5136	1.2475	-2.4	0.252	1.4666	0.3531	-7.5	0.355	1.4459	0.1105	-9.4
0.184	1.5112	1.1906	-2.7	0.254	1.4659	0.3433	-7.6	0.360	1.4454	0.1056	-9.5
0.186	1.5089	1.1373	-3.0	0.256	1.4652	0.3338	-7.7	0.365	1.4449	0.1010	-9.5
0.188	1.5066	1.0873	-3.3	0.258	1.4645	0.3247	-7.7	0.370	1.4444	0.0967	-9.6
0.190	1.5045	1.0403	-3.5	0.260	1.4639	0.3160	-7.8	0.375	1.4439	0.0926	-9.6
0.192	1.5025	0.9962	-3.7	0.262	1.4633	0.3075	-7.8	0.380	1.4435	0.0887	-9.6
0.194	1.5005	0.9547	-4.0	0.264	1.4627	0.2994	-7.9	0.385	1.4430	0.0851	-9.7
0.196	1.4986	0.9156	-4.2	0.266	1.4621	0.2916	-8.0	0.390	1.4426	0.0817	-9.7
0.198	1.4969	0.8787	-4.4	0.268	1.4615	0.2840	-8.0	0.395	1.4422	0.0784	-9.7
0.200	1.4951	0.8439	-4.6	0.270	1.4609	0.2768	-8.1	0.400	1.4418	0.0754	-9.8
0.202	1.4935	0.8110	-4.8	0.272	1.4604	0.2697	-8.1	0.410	1.4411	0.0697	-9.8
0.204	1.4919	0.7798	-4.9	0.274	1.4599	0.2630	-8.2	0.420	1.4404	0.0646	-9.9
0.206	1.4904	0.7503	-5.1	0.276	1.4593	0.2564	-8.2	0.430	1.4398	0.0601	-9.9
0.208	1.4889	0.7224	-5.2	0.278	1.4588	0.2501	-8.3	0.440	1.4392	0.0559	-10.0
0.210	1.4875	0.6959	-5.4	0.280	1.4583	0.2440	-8.3	0.450	1.4387	0.0522	-10.0
0.212	1.4861	0.6708	-5.5	0.282	1.4578	0.2381	-8.4	0.460	1.4382	0.0488	-10.1
0.214	1.4848	0.6469	-5.7	0.284	1.4574	0.2324	-8.4	0.470	1.4377	0.0456	-10.1
0.216	1.4835	0.6241	-5.8	0.286	1.4569	0.2268	-8.4	0.480	1.4373	0.0428	-10.1
0.218	1.4823	0.6025	-5.9	0.288	1.4565	0.2215	-8.5	0.490	1.4368	0.0402	-10.2

TABLE 8. RECOMMENDED VALUES ON THE REFRACTIVE INDEX AND ITS WAVELENGTH AND
TEMPERATURE DERIVATIVES FOR CALCIUM FLUORIDE AT 293K (CONTINUED)*

λ μm	n	$-\frac{dn}{d\lambda}$ μm^{-1}	$\frac{dn}{dT}$ 10^{-6} K^{-1}	λ μm	n	$-\frac{dn}{d\lambda}$ μm^{-1}	$\frac{dn}{dT}$ 10^{-6} K^{-1}	λ μm	n	$-\frac{dn}{d\lambda}$ μm^{-1}	$\frac{dn}{dT}$ 10^{-6} K^{-1}
0.500	1.4365	0.0378	-10.2	1.250	1.4275	0.0050	-10.8	3.000	1.4179	0.0070	-10.7
0.510	1.4361	0.0356	-10.2	1.300	1.4272	0.0049	-10.8	3.050	1.4175	0.0071	-10.7
0.520	1.4357	0.0336	-10.3	1.350	1.4270	0.0048	-10.8	3.100	1.4171	0.0072	-10.7
0.530	1.4354	0.0318	-10.3	1.400	1.4267	0.0047	-10.8	3.150	1.4168	0.0073	-10.7
0.540	1.4351	0.0301	-10.3	1.450	1.4265	0.0047	-10.8	3.200	1.4164	0.0075	-10.7
0.550	1.4348	0.0285	-10.3	1.500	1.4263	0.0046	-10.8	3.250	1.4160	0.0076	-10.7
0.560	1.4345	0.0270	-10.4	1.550	1.4260	0.0046	-10.8	3.300	1.4156	0.0077	-10.7
0.570	1.4343	0.0257	-10.4	1.600	1.4258	0.0046	-10.8	3.350	1.4153	0.0078	-10.7
0.580	1.4340	0.0244	-10.4	1.650	1.4256	0.0047	-10.8	3.400	1.4149	0.0079	-10.6
0.590	1.4338	0.0232	-10.4	1.700	1.4253	0.0047	-10.8	3.450	1.4145	0.0080	-10.6
0.600	1.4336	0.0221	-10.4	1.750	1.4251	0.0047	-10.8	3.500	1.4140	0.0082	-10.6
0.620	1.4331	0.0202	-10.5	1.800	1.4249	0.0048	-10.8	3.550	1.4136	0.0083	-10.6
0.640	1.4327	0.0185	-10.5	1.850	1.4246	0.0048	-10.8	3.600	1.4132	0.0084	-10.6
0.660	1.4324	0.0170	-10.5	1.900	1.4244	0.0049	-10.8	3.650	1.4128	0.0085	-10.6
0.680	1.4321	0.0157	-10.5	1.950	1.4241	0.0050	-10.8	3.700	1.4124	0.0086	-10.6
0.700	1.4318	0.0145	-10.6	2.000	1.4239	0.0050	-10.8	3.750	1.4119	0.0088	-10.6
0.720	1.4315	0.0135	-10.6	2.050	1.4236	0.0051	-10.8	3.800	1.4115	0.0089	-10.6
0.740	1.4312	0.0126	-10.6	2.100	1.4233	0.0052	-10.8	3.850	1.4110	0.0090	-10.6
0.760	1.4310	0.0117	-10.6	2.150	1.4231	0.0053	-10.8	3.900	1.4106	0.0091	-10.6
0.780	1.4307	0.0110	-10.6	2.200	1.4228	0.0054	-10.8	3.950	1.4101	0.0092	-10.5
0.800	1.4305	0.0104	-10.7	2.250	1.4225	0.0055	-10.8	4.000	1.4096	0.0094	-10.5
0.820	1.4303	0.0098	-10.7	2.300	1.4223	0.0055	-10.8	4.050	1.4092	0.0095	-10.5
0.840	1.4301	0.0093	-10.7	2.350	1.4220	0.0056	-10.8	4.100	1.4087	0.0096	-10.5
0.860	1.4300	0.0088	-10.7	2.400	1.4217	0.0057	-10.8	4.150	1.4082	0.0097	-10.5
0.880	1.4298	0.0084	-10.7	2.450	1.4214	0.0058	-10.8	4.200	1.4077	0.0099	-10.5
0.900	1.4296	0.0080	-10.7	2.500	1.4211	0.0059	-10.8	4.250	1.4072	0.0100	-10.5
0.920	1.4295	0.0077	-10.7	2.550	1.4208	0.0060	-10.8	4.300	1.4067	0.0101	-10.5
0.940	1.4293	0.0073	-10.7	2.600	1.4205	0.0061	-10.8	4.350	1.4062	0.0102	-10.4
0.960	1.4292	0.0071	-10.7	2.650	1.4202	0.0062	-10.8	4.400	1.4057	0.0104	-10.4
0.980	1.4290	0.0068	-10.7	2.700	1.4199	0.0064	-10.7	4.450	1.4052	0.0105	-10.4
1.000	1.4289	0.0066	-10.7	2.750	1.4196	0.0065	-10.7	4.500	1.4046	0.0106	-10.4
1.050	1.4286	0.0061	-10.8	2.800	1.4192	0.0066	-10.7	4.550	1.4041	0.0108	-10.4
1.100	1.4283	0.0057	-10.8	2.850	1.4189	0.0067	-10.7	4.600	1.4035	0.0109	-10.4
1.150	1.4280	0.0054	-10.8	2.900	1.4186	0.0068	-10.7	4.650	1.4030	0.0110	-10.4
1.200	1.4277	0.0052	-10.8	2.950	1.4182	0.0069	-10.7	4.700	1.4024	0.0111	-10.3

TABLE 8. RECOMMENDED VALUES ON THE REFRACTIVE INDEX AND ITS WAVELENGTH AND
TEMPERATURE DERIVATIVES FOR CALCIUM FLUORIDE AT 293K (CONTINUED)*

λ μm	n	$-\frac{dn}{d\lambda}$ μm^{-1}	$\frac{dn}{dT}$ 10^{-6}K^{-1}	λ μm	n	$-\frac{dn}{d\lambda}$ μm^{-1}	$\frac{dn}{dT}$ 10^{-6}K^{-1}	λ μm	n	$-\frac{dn}{d\lambda}$ μm^{-1}	$\frac{dn}{dT}$ 10^{-6}K^{-1}
4.750	1.4019	0.0113	-10.3	6.700	1.3745	0.0168	-9.4	8.900	1.3292	0.0246	-7.1
4.800	1.4013	0.0114	-10.3	6.800	1.3728	0.0171	-9.3	9.000	1.3268	0.0250	-7.0
4.850	1.4007	0.0115	-10.3	6.900	1.3711	0.0175	-9.2	9.100	1.3242	0.0254	-6.9
4.900	1.4001	0.0117	-10.3	7.000	1.3693	0.0178	-9.1	9.200	1.3217	0.0258	-6.8
4.950	1.3996	0.0118	-10.3	7.100	1.3675	0.0181	-9.1	9.300	1.3191	0.0263	-6.7
5.000	1.3990	0.0119	-10.1	7.200	1.3657	0.0184	-9.0	9.400	1.3164	0.0267	-6.6
5.100	1.3977	0.0122	-10.1	7.300	1.3638	0.0188	-8.9	9.500	1.3137	0.0271	-6.5
5.200	1.3965	0.0125	-10.1	7.400	1.3619	0.0191	-8.8	9.600	1.3110	0.0276	-6.4
5.300	1.3952	0.0128	-10.1	7.500	1.3600	0.0194	-8.7	9.700	1.3082	0.0280	-5.9
5.400	1.3939	0.0130	-10.1	7.600	1.3580	0.0198	-8.7	9.800	1.3054	0.0285	-5.8
5.500	1.3926	0.0133	-10.0	7.700	1.3560	0.0201	-8.6	9.900	1.3025	0.0289	-5.7
5.600	1.3913	0.0136	-10.0	7.800	1.3540	0.0205	-8.5	10.000	1.2996	0.0294	-5.6
5.700	1.3899	0.0139	-9.9	7.900	1.3519	0.0208	-8.4	10.200	1.2936	0.0304	-4.9
5.800	1.3885	0.0142	-9.9	8.000	1.3498	0.0212	-8.3	10.400	1.2874	0.0314	-4.8
5.900	1.3871	0.0144	-9.8	8.100	1.3477	0.0215	-8.1	10.600	1.2810	0.0324	-3.8
6.000	1.3856	0.0147	-9.8	8.200	1.3455	0.0219	-8.0	10.800	1.2744	0.0335	-3.7
6.100	1.3841	0.0150	-9.7	8.300	1.3433	0.0223	-7.9	11.000	1.2676	0.0346	-2.9
6.200	1.3826	0.0153	-9.7	8.400	1.3411	0.0226	-7.8	11.200	1.2606	0.0357	-2.8
6.300	1.3810	0.0156	-9.6	8.500	1.3388	0.0230	-7.7	11.400	1.2533	0.0369	-1.9
6.400	1.3795	0.0159	-9.6	8.600	1.3364	0.0234	-7.5	11.600	1.2458	0.0382	-0.9
6.500	1.3778	0.0162	-9.5	8.700	1.3341	0.0238	-7.4	11.800	1.2380	0.0395	-0.9
6.600	1.3762	0.0165	-9.4	8.800	1.3317	0.0242	-7.3	12.000	1.2299	0.0408	0.7

* IN THIS TABLE MORE DECIMAL PLACES ARE REPORTED THAN WARRANTED MERELY FOR THE PURPOSE OF TABULAR SMOOTHNESS AND INTERNAL COMPARISON. FOR UNCERTAINTIES OF TABULATED VALUES IN VARIOUS WAVELENGTH RANGES, SEE THE TEXT OF SUBSECTION 3.1. THE NUMBER OF DIGITS WITH AN OVERSTRIKE IS NOT RELATED TO THE ACCURACY OF THE VALUES.

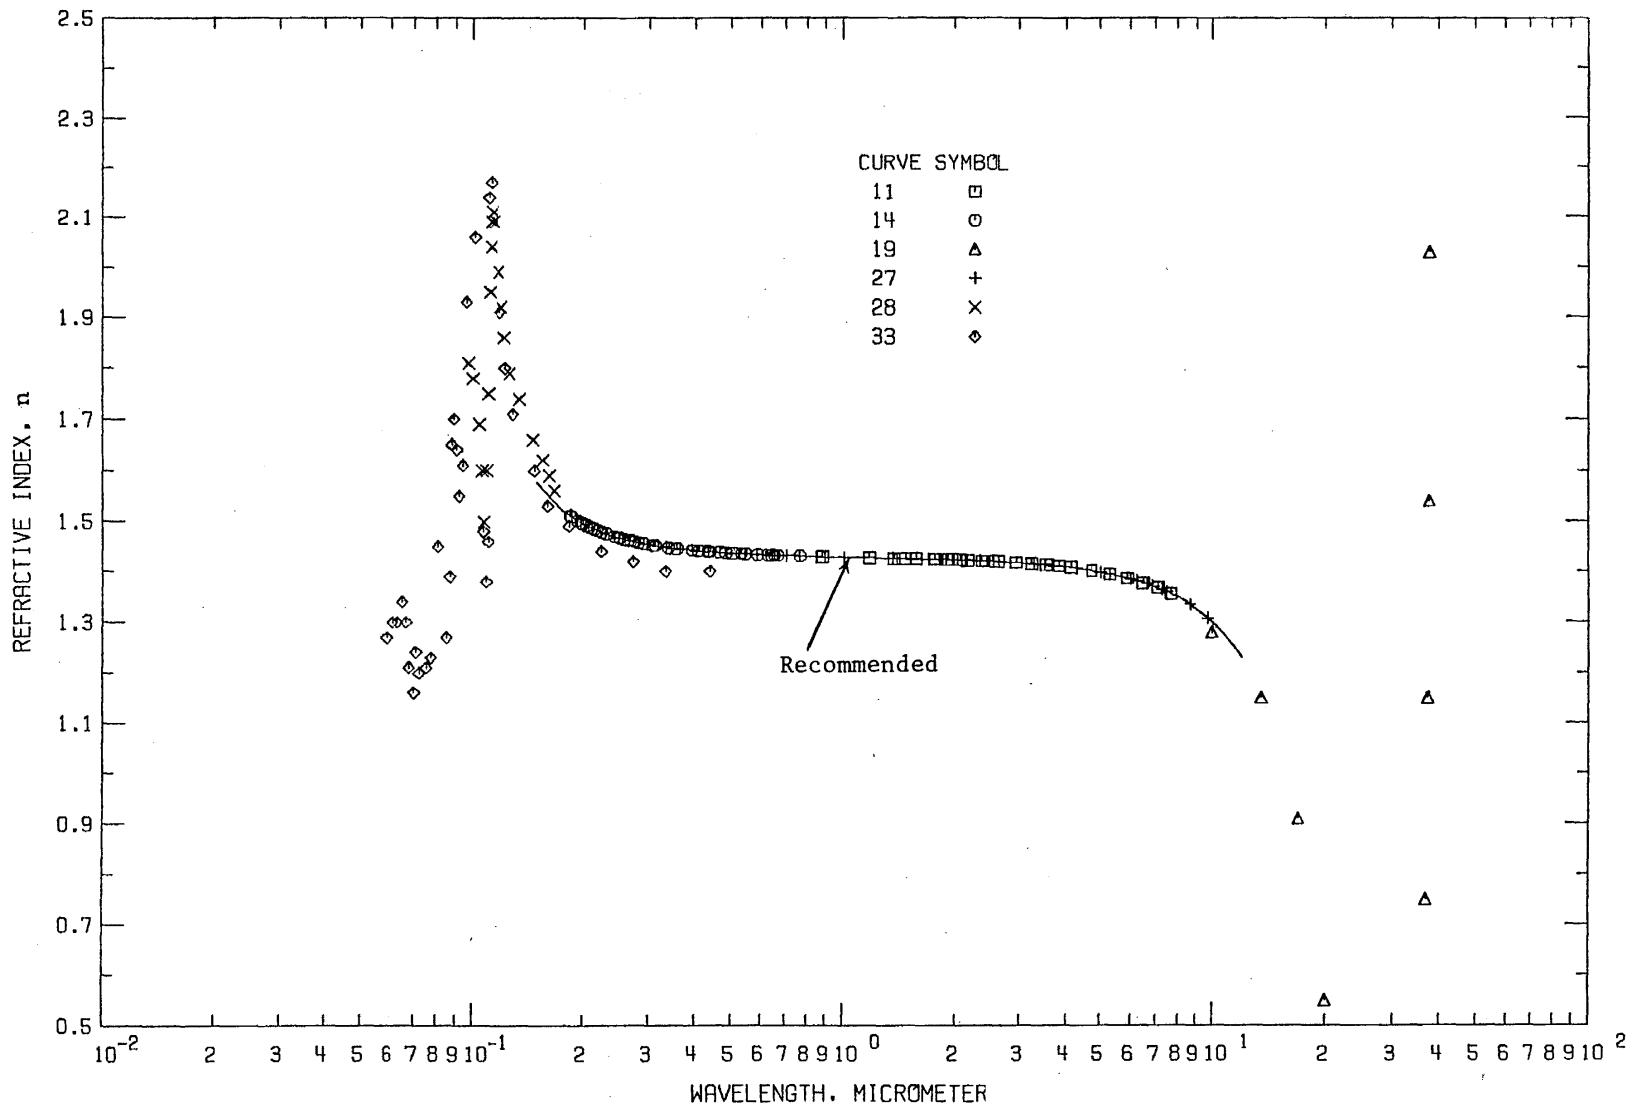


FIGURE 7. REFRACTIVE INDEX OF CALCIUM FLUORIDE (WAVELENGTH DEPENDENCE).

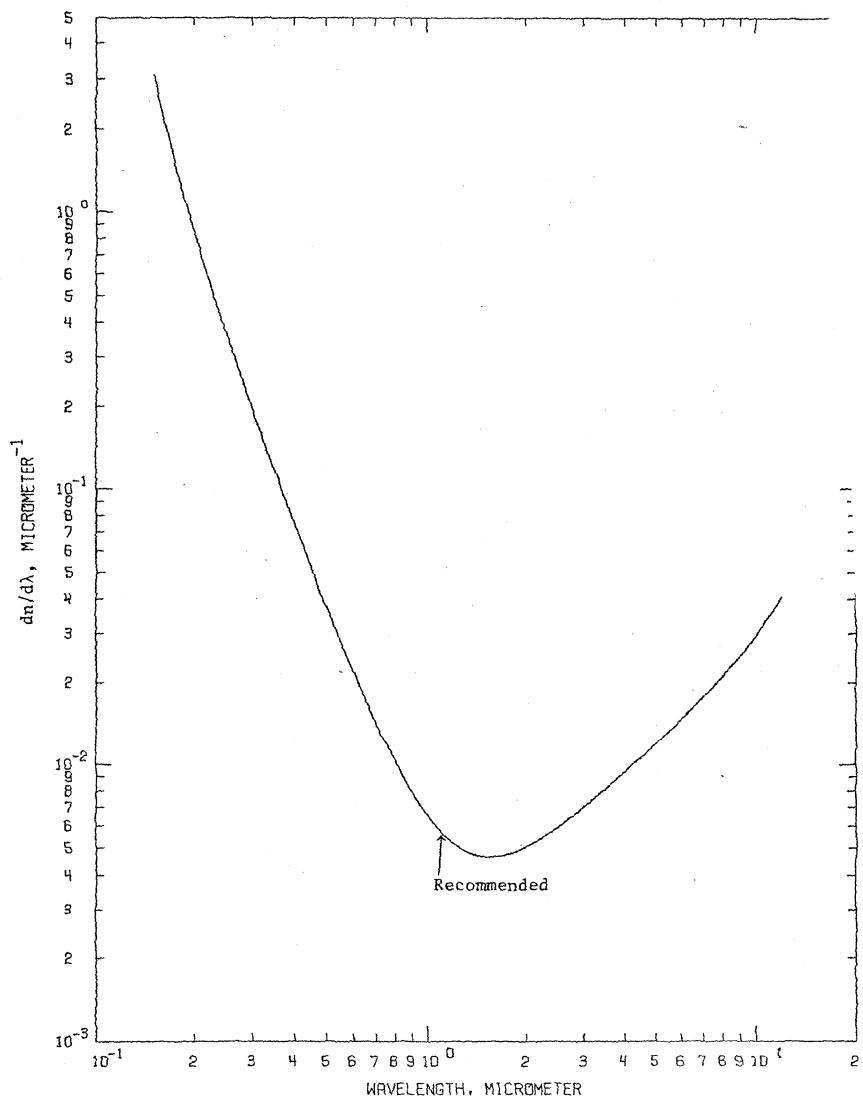


FIGURE 8. WAVELENGTH DERIVATIVE OF REFRACTIVE INDEX OF CALCIUM FLUORIDE.

TABLE 9. MEASUREMENT INFORMATION ON THE REFRACTIVE INDEX OF CALCIUM FLUORIDE (WAVELENGTH DEPENDENCE)

DATA SET NO.	REF. NO.	AUTHOR(S)	YEAR	METHOD USED	WAVELENGTH RANGE, μm	TEMP. K	SPECIFICATIONS AND REMARKS
1	28	STEFAN, J.M.	1871	D	0.39-0.69	294	NATURAL CRYSTAL; PRISMATIC SPECIMEN; NEAR 44 DEGREE APEX ANGLE; REFRACTIVE INDEX DETERMINED BY DEVIATION METHOD FOR 5 SPECTRAL LINES; DATA EXTRACTED FROM A TABLE.
2	29	SARASIN, M.E.	1883	D	0.18-0.76	293	NATURAL CRYSTAL; PRISMATIC SPECIMEN; NEAR 60 DEGREE APEX ANGLE; REFRACTIVE INDEX DETERMINED BY DEVIATION METHOD FOR 24 SPECTRAL LINES; DATA EXTRACTED FROM A TABLE; TEMPERATURE NOT GIVEN, 293K ASSUMED.
3	30	PULFRICH, C.	1892	P	0.589	290	NATURAL CRYSTAL; PRISMATIC SPECIMEN; NEAR 25.5 DEGREE APEX ANGLE; REFRACTIVE INDEX DETERMINED BY AN ABBE AUTO COLLIMATION METHOD FOR THE MEAN OF SODIUM D LINES; DATA EXTRACTED FROM A TABLE.
4	31	RUBENS, H. SNOW, B.W.	1892	D	0.43-8.07	291	NATURAL CRYSTAL; PRISMATIC SPECIMEN; NEAR 60 DEGREE APEX ANGLE; REFRACTIVE INDEX DETERMINED BY MINIMUM DEVIATION METHOD FOR 25 SPECTRAL LINES; DATA EXTRACTED FROM A TABLE.
5	32	RUBENS, H.	1892	D	0.43-3.33	291	NATURAL CRYSTAL; PRISMATIC SPECIMEN; NEAR 60 DEGREE APEX ANGLE, 5.5 CM EDGE; REFRACTIVE INDEX DETERMINED BY MINIMUM DEVIATION METHOD FOR 19 SPECTRAL LINES; DATA EXTRACTED FROM A TABLE.
6	33	CARVALLO, M.E.	1893	D	0.63-1.85	293	NATURAL CRYSTAL; PRISMATIC SPECIMEN; NEAR 69 DEGREE APEX ANGLE; REFRACTIVE INDEX DETERMINED BY MINIMUM DEVIATION METHOD FOR 8 SPECTRAL LINES; DATA EXTRACTED FROM A TABLE; TEMPERATURE NOT GIVEN, 293K ASSUMED; A BRIOT FORMULA BEST FIT THE RESULTS ALSO GIVEN.
7	34	SIMON, H.T.	1894	D	0.20-0.77	293	NATURAL CRYSTAL; PRISMATIC SPECIMEN; DIMENSIONS NOT GIVEN; REFRACTIVE INDEX DETERMINED BY DEVIATION METHOD FOR 37 SPECTRAL LINES; DATA EXTRACTED FROM A TABLE; TEMPERATURE NOT GIVEN, 293K ASSUMED.
8	35	RUBENS, H.	1894	D	1.98-6.48	291	NATURAL CRYSTAL; PRISMATIC SPECIMEN; 60 DEGREE APEX ANGLE; REFRACTIVE INDEX DETERMINED BY MINIMUM DEVIATION METHOD FOR 18 SPECTRAL LINES; DATA EXTRACTED FROM A TABLE.
9	36	RUBENS, H.	1894	D	6.90-8.95	291	NATURAL CRYSTAL; PRISMATIC SPECIMEN; 60 DEGREE APEX ANGLE; REFRACTIVE INDEX DETERMINED BY MINIMUM DEVIATION METHOD FOR 10 SPECTRAL LINES; DATA EXTRACTED FROM A TABLE.

TABLE 9. MEASUREMENT INFORMATION ON THE REFRACTIVE INDEX OF CALCIUM FLUORIDE (WAVELENGTH DEPENDENCE) (CONTINUED)

DATA SET NO.	REF. NO.	AUTHOR(S)	YEAR	METHOD USED	WAVELENGTH RANGE, μm	TEMP. K	SPECIFICATIONS AND REMARKS
10	37	PASCHEN,F.	1894	D	0.88-9.43	291	NATURAL CRYSTAL; PRISMATIC SPECIMEN; NEAR 60 DEGREE APEX ANGLE; REFRACTIVE INDEX DETERMINED BY MINIMUM DEVIATION METHOD FOR 34 SPECTRAL LINES; DATA EXTRACTED FROM A TABLE; TEMPERATURE UNCONTROLLED BUT WITHIN THE RANGE 290-293K; A ERIOT FORMULA BEST FIT THE RESULTS ALSO GIVEN.
11	38	PASCHEN,F.	1895	D	0.88-7.66	290	NATURAL CRYSTAL; PRISMATIC SPECIMEN; NEAR 60 DEGREE APEX ANGLE; REFRACTIVE INDEX DETERMINED BY MINIMUM DEVIATION METHOD FOR 24 SPECTRAL LINES; DATA EXTRACTED FROM A TABLE; TEMPERATURE UNCONTROLLED BUT WITHIN THE RANGE 288-291K; A KETTELER FORMULA ALSO GIVEN; THE AUTHOR POINTED OUT THAT THE APEX ANGLE OF THE PRISM IN HIS 1894 WORK MISDETERMINED.
12	39	LANGLEY,S.P.	1900	D	0.76-3.41	293	SINGLE CRYSTAL; PRISMATIC SPECIMEN; NEAR 60 DEGREE APEX ANGLE, 30MMX38MM VIEW SURFACE; REFRACTIVE INDEX DETERMINED BY DEVIATION METHOD; DATA EXTRACTED FROM A TABLE; UNCERTAINTY OF INDEX LESS THAN ONE UNIT OF THE FIFTH DECIMAL PLACE.
13	40	PASCHEN,F.	1901	D	0.88-7.07	284	NATURAL CRYSTAL; PRISMATIC SPECIMEN; NEAR 60 DEGREE APEX ANGLE; REFRACTIVE INDEX DETERMINED BY MINIMUM DEVIATION METHOD FOR 18 SPECTRAL LINES; DATA EXTRACTED FROM A TABLE; KETTELER FORMULA ALSO GIVEN.
14	41	MARTENS,F.F.	1901	D	0.18-0.77	291	NATURAL CRYSTAL; PRISMATIC SPECIMEN; NEAR 60 DEGREE APEX ANGLE, 54MM HEIGHT, 54X50MM VIEW SURFACE; REFRACTIVE INDEX DETERMINED BY DEVIATION METHOD FOR 40 SPECTRAL LINES; DATA EXTRACTED FROM A TABLE; A SELLMEIRE TYPE DISPERSION EQUATION BEST FIT THE DATA ALSO GIVEN.
15	42	MARTENS,F.F.	1902	D	0.50-0.65	291	NATURAL CRYSTAL; PRISMATIC SPECIMEN; NEAR 60 DEGREE APEX ANGLE; REFRACTIVE INDEX DETERMINED BY DEVIATION METHOD FOR 3 SPECTRAL LINES; DATA EXTRACTED FROM A TABLE.
16	43	PFUND,A.H.	1941	B	0.56	293	CRYSTAL OF UNSPECIFIED TYPE; FRESHLY POLISHED SURFACE; REFRACTIVE INDEX DETERMINED BY MEANS OF BREWSTERIAN ANGLE; DATA EXTRACTED FROM A TABLE; TEMPERATURE NOT GIVEN, 293K ASSUMED.
17	44	RAMADIER-DELBES	1950	I	8.0-15.0	293	SINGLE CRYSTAL; THIN FILM SPECIMEN OF 25-50 MICROMETER ON METALLIC SUBSTRATE; REFRACTIVE INDEX DETERMINED BY INTERFERENCE METHOD FOR 15 SPECTRAL LINES; DATA EXTRACTED FROM A TABLE; TEMPERATURE NOT GIVEN, 293K ASSUMED.

TABLE 3. MEASUREMENT INFORMATION ON THE REFRACTIVE INDEX OF CALCIUM FLUORIDE (WAVELENGTH DEPENDENCE) (CONTINUED)

DATA SET NO.	REF. NO.	AUTHOR(S)	YEAR	METHOD USED	WAVELENGTH RANGE, μm	TEMP. K	SPECIFICATIONS AND REMARKS
18	45	HEISEN, A.	1961	I	0.43-0.54	293	THIN FILM SPECIMEN OF WEDGE SHAPED; VACUUM DEPOSITED; REFRACTIVE INDEX DETERMINED BY INTERFERENCE METHOD FOR 2 SPECTRAL LINES; DIGITIZED VALUES REPORTED; REPORTED UNCERTAINTY 0.5%; TEMPERATURE NOT GIVEN, 293K ASSUMED; IT WAS FOUND THAT THE THIN FILM VALUES AGREED WITH THOSE OF THE BULK MATERIAL.
19	17	KAISER, W. SPITZER, W.G. KAISER, R.H. HOWARTH, L.E.	1962	R	10.0-80.0	300	SINGLE CRYSTAL; PLATE SPECIMEN; 0.1-5.0MM THICK; HIGHLY POLISHED SURFACES; NEAR NORMAL INCIDENT REFLECTION SPECTRUM OBTAINED; REFRACTIVE INDEX DEDUCED FROM REFLECTION SPECTRUM WITH LORENTZ THEORY; DATA EXTRACTED FROM A SMOOTH CURVE; LORENTZ DAMPED-OSCILLATOR DISPERSION EQUATION ALSO GIVEN.
20	46	HEILMANN, G.	1963	R	15.0-48.0	293	SYNTHETIC CRYSTAL; PLATE SPECIMEN; 70 DEGREE INCIDENT REFLECTION SPECTRUM OBTAINED; REFRACTIVE INDEX DEDUCED FROM REFLECTION SPECTRUM WITH FRESNEL FORMULAE; DATA EXTRACTED FROM A SMOOTH CURVE.
21	47	HOUSTON, T.W. JOHNSON, L.F. KISLIUK, P. WALSH, D.J.	1963	D	0.54-1.85	93	SINGLE CRYSTAL; HIGH PURITY; PRISMATIC SPECIMEN; POLISHED SURFACES FLAT TO 1/2 WAVELENGTH OF 0.535 MICROMETER LINE; REFRACTIVE INDEX DETERMINED BY MINIMUM DEVIATION METHOD FOR 6 SPECTRAL LINES; DATA EXTRACTED FROM A TABLE.
22	47	HOUSTON, T.W. ET AL.	1963	D	0.54-1.85	298	SIMILAR TO ABOVE BUT FOR 7 LINES AND AT A HIGHER TEMPERATURE.
23	48	MALITSON, I.H.	1963	D	0.40-0.77	288	SYNTHETIC CRYSTAL; GROWN BY THE STOCKBARGER TECHNIQUE; PRISMATIC SPECIMEN; REFRACTIVE INDEX DETERMINED BY DEVIATION METHOD FOR 9 SPECTRAL LINES; DATA EXTRACTED FROM A TABLE; ESTIMATED UNCERTAINTY ABOUT 2×10^{-5} ; THIS DATA SET WAS OBTAINED AT NBS IN 1944.
24	48	MALITSON, I.H.	1963	D	0.40-0.77	308	SIMILAR TO ABOVE BUT AT A HIGHER TEMPERATURE OF 308K.
25	48	MALITSON, I.H.	1963	D	0.40-0.77	328	SIMILAR TO ABOVE BUT AT A HIGHER TEMPERATURE OF 328K.
26	48	MALITSON, I.H.	1963	D	0.22-9.73	297	SYNTHETIC CRYSTAL; GROWN AT MIT BY D. C. STOCKBARGER; PRISMATIC SPECIMEN; NEAR 70 DEGREE APEX ANGLE, 55MMX73MM VIEW SURFACE; REFRACTIVE INDEX DETERMINED BY MINIMUM DEVIATION METHOD FOR 46 SPECTRAL LINES; DATA EXTRACTED FROM A TABLE; ESTIMATED UNCERTAINTY ABOUT 2.5×10^{-5} ; A SELLMEIRE TYPE DISPERSION EQUATION BEST FIT THE DATA ALSO GIVEN.

TABLE 9. MEASUREMENT INFORMATION ON THE REFRACTIVE INDEX OF CALCIUM FLUORIDE (WAVELENGTH DEPENDENCE) (CONTINUED)

DATA SET NO.	REF. NO.	AUTHOR(S)	YEAR	METHOD USED	WAVELENGTH RANGE, μm	TEMP. K	SPECIFICATIONS AND REMARKS
27	48	MALITSON, I.H.	1963	D	0.22-9.73	297	NATURAL CRYSTAL; PRODUCED IN EUROPE; PRISMATIC SPECIMEN; NEAR 60 DEGREE APEX ANGLE, 50MMX50MM VIEW SURFACE; REFRACTIVE INDEX DETERMINED BY MINIMUM DEVIATION METHOD FOR 46 SPECTRAL LINES; DATA EXTRACTED FROM A TABLE; ESTIMATED UNCERTAINTY ABOUT 2.83×10^{-5} .
28	49	FABRE, D. ROMAND, J. VODAR, B.	1964	R	0.10-0.17	293	THIN FILM SPECIMEN OF VARYING THICKNESS; VACUUM DEPOSITED; REFRACTIVE INDEX DETERMINED BY REFLECTANCE OF VARYING THICKNESS; DATA EXTRACTED FROM A FIGURE; TEMPERATURE NOT GIVEN, 293K ASSUMED.
29	50	BERMAN, L.U. ZHUKOV, A.G.	1964	I	294-512	300	CRYSTAL OF UNSPECIFIED TYPE; PLATE SPECIMEN; REFRACTIVE INDEX DETERMINED CORRESPONDING TO MAXIMA IN THE INTERFERENCE CURVE OF NORMAL TRANSMITTANCE; DATA EXTRACTED FROM A TABLE.
30	50	BERMAN, L.U. ET AL.	1964	I	314-580	300	CRYSTAL OF UNSPECIFIED TYPE; PLATE SPECIMEN; REFRACTIVE INDEX DETERMINED CORRESPONDING TO MINIMA IN THE INTERFERENCE CURVE OF NORMAL TRANSMITTANCE; DATA EXTRACTED FROM A TABLE.
31	16	BOSOMWORTH, D.R.	1967	I	55-422	80	SINGLE CRYSTAL; IMPURITIES $10-100 \times 10^{-6}$ FE; OBTAINED FROM THE HARSHAW CHEMICAL CO.; PLATE SPECIMEN; 0.3-10MM THICK; REFRACTIVE INDEX DETERMINED BY INTERFERENCE METHOD; DATA EXTRACTED FROM A FIGURE; DISPERSION EQUATION FOR INFRARED ALSO GIVEN.
32	16	BOSOMWORTH, D.R.	1967	I	150-443	300	SIMILAR TO ABOVE BUT AT A HIGHER TEMPERATURE OF 300K.
33	51	HEITMANN, W. KOPPELMANN, C.	1967	L	0.6328	293	SINGLE CRYSTAL; HIGH PURITY; PRODUCTION OF SCHUCHARDT CO.; VACUUM DEPOSITED; THIN FILM SPECIMEN OF QUARTER WAVELENGTH ALTERNATE WITH ZNS AND ZNSE FILMS; REFRACTIVE INDEX DETERMINED BY MULTILAYER METHOD FOR 1 SPECTRAL LINES; DATA EXTRACTED FROM A TABLE; TEMPERATURE NOT GIVEN, 293K ASSUMED.
34	20	EASTMAN KODAK CO.	1971	D	1.00-11.0	293	POLYCRYSTALLINE; KODAK INFRARED OPTICAL MATERIAL IRTRAN 3; DESCRIPTION OF SPECIMEN AND EXPERIMENT NOT GIVEN; TEMPERATURE NOT GIVEN, 293K ASSUMED; DATA EXTRACTED FROM A TABLE COMPUTED BY A GIVEN HERZBERGER DISPERSION EQUATION.
35	52	FIELD, G.R. WILKINSON, G.R.	1973		0.21-5.19	293	THIS EXPERIMENTAL DATA SET WAS OBTAINED BY THE AUTHORS THROUGH A PRIVATE COMMUNICATION; NO INFORMATION OTHER THAN VALUES WAS GIVEN; DATA EXTRACTED FROM A TABLE; TEMPERATURE NOT GIVEN, 293K ASSUMED; THE AUTHORS, HOWEVER, GAVE THE LORENTZ DAMPED-OSCILLATOR DISPERSION EQUATION.

H.H.LI

TABLE 9. MEASUREMENT INFORMATION ON THE REFRACTIVE INDEX OF CALCIUM FLUORIDE (WAVELENGTH DEPENDENCE) (CONTINUED)

DATA SET NO.	REF. NO.	AUTHOR(S)	YEAR	METHOD USED	WAVELENGTH RANGE, μm	TEMP. K	SPECIFICATIONS AND REMARKS
36	53	GANIN,U., SIDORIN,U. KARIN,M., SIDORIN,K. STAROSTIN,N., STARTSEV,G.	1975	R	0.06-0.25	300	SINGLE CRYSTAL; FRESHLY CLEAVED SPECIMEN; NEAR NORMAL REFLECTION SPECTRUM OBTAINED; REFRACTIVE INDEX DEDUCED FROM REFLECTION SPECTRUM WITH KRAMERS-KRONIG RELATION; DATA EXTRACTED FROM A FIGURE.
37	93	DODGE,M.J.	1976	D	0.25-8.0	294	POLYCRYSTALLINE; HOT-FORGED; OBTAINED FROM HARSHAW CHEMICAL CORP.; PRISMATIC SPECIMEN WITH REFRACTING ANGLE NEAR 60 DEGREES AND 4CMX5CM FACES; REFRACTIVE INDICES OF 69 SPECTRAL LINES MEASURED AND FITTED TO A SELLMEIER TYPE DISPERSION EQUATION.
38	93	DODGE,M.J.	1976	n	0.25-8.0	307	SIMILAR TO ABOVE BUT REFRACTIVE INDICES OF 47 SPECTRAL LINES MEASURED AT A HIGHER TEMPERATURE.

TABLE 10. EXPERIMENTAL REFRACTIVE INDEX OF CALCIUM FLUORIDE (WAVELENGTH DEPENDENCE)

[WAVELENGTH, λ , μm ; TEMPERATURE, T , K; REFRACTIVE INDEX, n]

λ	n	λ	n	λ	n	λ	n	λ	n	λ	n
DATA SET 1 $T = 294.0$		DATA SET 4 $T = 291.0$		DATA SET 5 (CONT.)		DATA SET 7 (CONT.)		DATA SET 8 (CONT.)		DATA SET 10 (CONT.)	
0.397	1.44204	0.434	1.4398	1.110	1.4284	0.2763	1.45927	5.52	1.3931	3.2413	1.41608
0.431	1.43982	0.485	1.4372	1.212	1.4279	0.2801	1.45846	5.70	1.3918	3.5359	1.41378
0.486	1.43703	0.589	1.4340	1.332	1.4273	0.2818	1.45791	6.02	1.3860	3.8306	1.41122
0.589	1.43390	0.656	1.4325	1.480	1.4267	0.2880	1.45653	6.48	1.3798	4.1252	1.40850
0.687	1.43200	0.807	1.4307	1.666	1.4260	0.2980	1.45447			4.4199	1.40559
		0.850	1.4303	1.902	1.4248	0.3072	1.45282	DATA SET 9 $T = 291.0$		4.7146	1.40244
				2.221	1.4234	0.3081	1.45265		5.0092	1.39902	
DATA SET 2 $T = 293.0$		0.896	1.4299	2.663	1.4214	0.3133	1.45173	6.90	1.3734	5.3039	1.39532
		0.950	1.4294	3.332	1.4170	0.3252	1.44988	7.14	1.3693	5.5985	1.39145
		1.009	1.4290			0.3345	1.44868	7.36	1.3654	5.8932	1.38721
0.1856	1.50940	1.076	1.4286	DATA SET 6 $T = 293.0$		0.3403	1.44785	7.54	1.3608	6.4825	1.37837
0.1931	1.50205	1.152	1.4281			0.3456	1.44708	7.66	1.3570	7.0718	1.36806
0.19881	1.49629	1.240	1.4277			0.3630	1.44547	7.86	1.3570	7.5612	1.35672
0.20243	1.49326	1.345	1.4272	0.637	1.43292	0.4340	1.43968	8.13	1.3510	8.2505	1.34444
0.20610	1.49041	1.466	1.4267	0.670	1.43192	0.4678	1.43782	8.34	1.3472	8.8398	1.33079
0.20988	1.48766	1.613	1.4260	0.777	1.43096	0.4800	1.43724	8.56	1.3432	9.4291	1.31612
0.21441	1.48462	1.792	1.4250	0.878	1.42996	0.4851	1.43698	8.73	1.3391		H
0.21935	1.48150	2.019	1.4240	1.009	1.42904	0.5086	1.43614	8.95	1.3348	DATA SET 11 $T = 290.0$	H
0.22645	1.47762	2.303	1.4224	1.187	1.42804	0.5349	1.43536				
0.23125	1.47517	2.689	1.4205	1.444	1.42676	0.5892	1.43379	DATA SET 10 $T = 291.0$		0.8840	1.42982
0.25713	1.46475	3.225	1.4174	1.849	1.42460	0.6563	1.43244			1.1786	1.42787
0.27467	1.45953	4.035	1.4117			0.763	1.43089	1.3756		1.42690	
0.32525	1.44987	4.62	1.408	DATA SET 7 $T = 293.0$				0.8840	1.42996	1.4733	1.42641
0.34015	1.44775	5.38	1.403					1.1786	1.42799	1.42699	1.42596
0.34655	1.44697	6.46	1.396					1.3751	1.42699	1.5715	1.42596
0.36090	1.44533	8.07	1.378	0.2024	1.49332			1.4733	1.42653	1.7680	1.42507
0.39681	1.44214			0.2061	1.49031	1.981	1.4241	1.5715	1.42607	1.9153	1.42437
0.41012	1.44122	DATA SET 5 $T = 291.0$		0.2098	1.48735	2.48	1.4212	1.6206	1.42592	1.9644	1.42413
0.48607	1.43705			0.2144	1.48444	2.66	1.4200	1.7680	1.42517	2.0626	1.42359
0.58920	1.43394			0.2239	1.47879	2.93	1.4182	1.8153	1.42438	2.1608	1.42308
0.65618	1.43257	0.434	1.4398	0.2329	1.47432	3.22	1.4166	1.9644	1.42412	2.3573	1.42159
0.58671	1.43200	0.485	1.4372	0.2439	1.46961	3.56	1.4135	2.0626	1.42363	2.5537	1.42088
0.71836	1.43153	0.590	1.4340	0.2474	1.46805	3.70	1.4126	2.1608	1.42317	2.6519	1.42016
0.76040	1.43101	0.656	1.4325	0.2491	1.46748	3.92	1.4107	2.2100	1.42297	2.9466	1.41826
		0.740	1.4312	0.2542	1.46572	4.10	1.4093	2.3573	1.42208	3.2413	1.41612
DATA SET 3 $T = 290.0$		0.784	1.4308	0.2580	1.46450	4.28	1.4069	2.5537	1.42092	3.5359	1.41379
		0.834	1.4304	0.2608	1.46373	4.52	1.4045	2.6519	1.42015	3.8306	1.41120
		0.889	1.4300	0.2639	1.46274	4.71	1.4027	2.7502	1.41969	4.1252	1.40855
0.5893	1.4399	0.952	1.4295	0.2677	1.46157	4.94	1.4000	2.9466	1.41823	4.7146	1.40238
		1.024	1.4289	0.2684	1.46150	5.18	1.3970	3.1430	1.41704	5.3036	1.39529

REFRACTIVE INDEX OF ALKALINE EARTH HALIDES

191

TABLE 10. EXPERIMENTAL REFRACTIVE INDEX OF CALCIUM FLUORIDE (WAVELENGTH DEPENDENCE) (CONTINUED)

[WAVELENGTH, λ , μm ; TEMPERATURE, T , K; REFRACTIVE INDEX, n]

λ	n	λ	n	λ	n	λ	n	λ	n	λ	n
DATA SET 11(CONT.)		DATA SET 12(CONT.)		DATA SET 14 $T = 291.0$		DATA SET 14(CONT.)		DATA SET 19 $T = 300.0$		DATA SET 19(CONT.)	
5.8932	1.38719	2.2016	1.422851	0.185	1.51024	0.768	1.43093	10.0	1.28	40.3	8.11
6.4825	1.37819	2.2900	1.422328	0.186	1.50930	DATA SET 15 $T = 291.0$		13.5	1.15	40.7	7.36
7.0718	1.36805	2.3508	1.422009	0.193	1.50150			16.9	0.91	41.0	6.69
7.6612	1.35680	2.3846	1.421819	0.197	1.49755			20.0	0.55	41.6	5.99
		2.4160	1.421637							42.2	5.45
DATA SET 12 $T = 293.0$		2.4496	1.421427	0.198	1.49643	0.508	1.43620	21.2	0.36	43.0	4.98
		2.9575	1.418182	0.200	1.49547	0.533	1.43537	22.1	0.20	44.2	4.58
		3.0430	1.417569	0.204	1.49190	0.643	1.43274	23.7	0.16	45.5	4.26
0.7604	1.431020	3.0900	1.417205	0.208	1.48907			25.8	0.23	47.0	4.01
0.7627	1.430996	3.1340	1.416829	0.211	1.48705	DATA SET 16 $T = 293.0$		28.0	0.32	48.7	3.81
0.8162	1.430425	3.2100	1.416356	0.214	1.48480			30.2	0.35	50.9	3.62
0.8227	1.430357	3.2610	1.415935	0.219	1.48167			32.8	0.35	53.9	3.39
0.8538	1.430072	3.3000	1.415621	0.224	1.47911	0.56	1.433	34.8	0.35	56.6	3.25
0.8658	1.429953	3.4090	1.414827	0.231	1.47533			36.4	0.47	59.3	3.14
0.8992	1.429674			0.242	1.47025	DATA SET 17 $T = 293.0$		37.1	0.75	62.6	3.06
0.9090	1.429601	DATA SET 13 $T = 284.0$		0.250	1.46732			37.4	1.15	66.2	3.00
0.9135	1.429555			0.257	1.46490			37.7	1.54	70.0	2.96
0.9232	1.429500			0.263	1.46302	8.0	1.349	37.9	2.03	73.8	2.90
0.9357	1.429398	0.8840	1.42989	0.267	1.46175	8.5	1.339	38.1	2.68	76.8	2.85
0.9443	1.429328	1.1786	1.42798	0.274	1.45976	9.0	1.325	38.2	3.38	80.0	2.85
0.9759	1.429119	1.4733	1.42652	0.281	1.45806	9.5	1.311	38.2	4.00	DATA SET 20 $T = 293.0$	
1.0041	1.428922	1.5715	1.42608	0.291	1.45586	10.0	1.292	38.2	4.64		
1.0728	1.428516	1.7680	1.42515	0.308	1.45257	10.5	1.271	38.4	5.39		
1.1240	1.428175	2.0626	1.42368	0.312	1.45187	11.0	1.253	38.4	6.07		
1.1399	1.428138	2.1608	1.42317	0.340	1.44774	11.5	1.235	38.4	6.76	15.0	1.02
1.1481	1.428063	2.3573	1.42208	0.358	1.44560	12.0	1.215	38.5	7.34	16.0	1.00
1.1833	1.427870	2.6519	1.42032	0.394	1.44231	12.5	1.195	38.6	8.09	17.1	0.93
1.2016	1.427768	2.9466	1.41835	0.410	1.44112	13.0	1.175	38.6	8.91	18.6	0.79
1.2658	1.427428	3.2413	1.41623	0.434	1.43960	13.5	1.150	38.6	9.64	20.0	0.61
1.3306	1.427107	3.5359	1.41388	0.441	1.43920	14.0	1.124	38.6	10.02	21.2	0.38
1.4333	1.426616	4.1252	1.40858	0.467	1.43787	14.5	1.090	38.8	10.65	22.1	0.26
1.4692	1.426459	4.7146	1.40242	0.486	1.43706	15.0	1.055	38.8	11.19	23.1	0.20
1.5734	1.425953	5.3039	1.39531	0.508	1.43619			38.9	11.79	25.0	0.20
1.6017	1.425812	5.8932	1.38721	0.533	1.43535	DATA SET 18 $T = 293.0$		39.2	12.35	26.7	0.22
1.6362	1.425637	6.4825	1.37834	0.546	1.43497			39.3	11.86	28.2	0.26
2.0000	1.423869	7.0718	1.36810	0.589	1.43385			39.5	11.16	30.0	0.33
2.0536	1.423595			0.627	1.43302	0.4358	1.440	39.6	10.62	31.7	0.26
2.0556	1.423601			0.643	1.43271	0.5460	1.434	39.7	10.09	33.6	0.20
2.1172	1.423287			0.656	1.43251			39.9	9.50	35.0	0.27
2.1658	1.423035			0.670	1.43226			40.1	8.88	36.0	0.43

TABLE 10. EXPERIMENTAL REFRACTIVE INDEX OF CALCIUM FLUORIDE (WAVELENGTH DEPENDENCE) (CONTINUED)

[WAVELENGTH, λ , μm ; TEMPERATURE, T , K; REFRACTIVE INDEX, n]

λ	n	λ	n	λ	n	λ	n	λ	n	λ	n
DATA SET 20(CONT.)		DATA SET 22(CONT.)		DATA SET 25(CONT.)		DATA SET 26(CONT.)		DATA SET 27(CONT.)		DATA SET 28(CONT.)	
36.5	0.65	1.2434	1.4279	0.706518	1.431331	3.7067	1.41231	1.52952	1.42816	0.1218	1.86
37.0	0.96	1.5166	1.4266	0.767858	1.430546	4.258	1.40717	1.7012	1.42535	0.1262	1.79
37.5	1.57	1.8459	1.4247			5.01882	1.39874	1.81307	1.42487	0.1342	1.74
37.7	1.98			DATA SET 26		5.3034	1.39523	1.97009	1.42404	0.1465	1.66
37.9	2.51			$T = 297.0$		6.0140	1.38544	2.1526	1.42307	0.1553	1.62
38.2	3.03			$T \approx 288.0$		6.238	1.38194	2.32542	1.42216	0.1624	1.59
38.4	3.59					0.228803	1.47633	2.4374	1.42149	0.1672	1.56
38.6	3.97	0.404656	1.441573	0.24827	1.46796	6.8559	1.37178	3.3026	1.41564		
38.8	4.59	0.435834	1.439555	0.2537	1.46611	7.268	1.36445	3.422	1.41469	DATA SET 29	
39.0	5.07	0.486132	1.437106	0.26520	1.46232	7.4644	1.36075	3.5070	1.41400	$T = 300.0$	
39.1	5.23	0.546074	1.435023	0.28035	1.45827	8.662	1.33496	3.7067	1.41231		
39.5	5.34	0.589262	1.433893	0.296728	1.45465	9.724	1.30757	4.258	1.40717	294.0	2.57
39.7	5.22	0.656279	1.432545	0.334148	1.44851			5.01882	1.39878	340.0	2.55
40.1	5.01	0.667814	1.432356	0.34662	1.44691			5.3034	1.39523	395.0	2.47
40.8	4.76	0.706518	1.431763	0.365015	1.44486			6.0140	1.38544	512.0	2.86
41.7	4.54	0.767858	1.430984	0.404656	1.44148			6.238	1.38200		
42.6	4.37			0.435834	1.43946	0.228803	1.47636	6.63306	1.37566	DATA SET 30	
43.6	4.19	DATA SET 24		0.486132	1.43699	0.24827	1.46798	6.8559	1.37188	$T = 300.0$	
44.9	4.02			0.546074	1.43491	0.2537	1.46614	7.268	1.36450		
46.1	3.86			0.589262	1.43379	0.26520	1.46233	7.4644	1.36076	314.0	2.55
47.0	3.75	0.404656	1.441378	0.643847	1.43266	0.28035	1.45829	8.662	1.33503	362.0	2.49
47.9	3.64	0.435834	1.439354	0.656279	1.43244	0.296728	1.45467	9.724	1.30761	453.0	2.55
		0.486132	1.436894	0.667814	1.43225	0.334148	1.44854			580.0	2.54
DATA SET 21		0.546074	1.434813	0.706518	1.43165	0.34662	1.44694	DATA SET 28			
$T = 93.0$		0.589262	1.433683	0.767858	1.43086	0.365015	1.44490	$T = 293.0$		DATA SET 31	
		0.656279	1.432335	0.85212	1.43001	0.404656	1.44152			$T = 80.0$	
0.5461	1.4378	0.667814	1.432142	0.8944	1.42966	0.435834	1.43949	0.0976	1.81		
0.5890	1.4358	0.706518	1.431553	1.01398	1.42877	0.486132	1.43703	0.1001	1.78	55.18	3.16
0.8195	1.4324	0.767858	1.430768	1.3622	1.42692	0.546074	1.43495	0.1040	1.69	56.02	3.09
1.0140	1.4313			1.39506	1.42676	0.589262	1.43383	0.1059	1.60	57.04	3.08
1.5166	1.4281	DATA SET 25		1.52952	1.42616	0.643847	1.43272	0.1072	1.50	58.30	3.06
1.8459	1.4265	$T = 328.0$		1.7012	1.42533	0.656279	1.43247	0.1086	1.60	59.45	3.01
				1.81307	1.42478	0.667814	1.43227	0.1098	1.75	61.12	2.99
DATA SET 22		0.404656	1.441168	1.97009	1.42404	0.706518	1.43169	0.1113	1.95	62.38	2.96
$T = 298.0$		0.435834	1.439143	2.1526	1.42305	0.767858	1.43090	0.1121	2.04	63.89	2.92
		0.486132	1.436680	2.32542	1.42215	0.85212	1.43006	0.1123	2.09	65.83	2.89
0.5461	1.4352	0.546074	1.434593	2.4374	1.42147	0.8944	1.42957	0.1130	2.11	67.75	2.88
0.5890	1.4340	0.589262	1.433465	3.3026	1.41561	1.01398	1.42879	0.1146	2.09	69.78	2.85
0.8195	1.4301	0.656279	1.432114	3.422	1.41469	1.3622	1.42699	0.1169	1.99	71.94	2.82
1.0140	1.4291	0.667814	1.431922	3.5070	1.41397	1.39506	1.42681	0.1195	1.92	74.12	2.78

REFRACTIVE INDEX OF ALKALINE EARTH HALIDES

TABLE 10. EXPERIMENTAL REFRACTIVE INDEX OF CALCIUM FLUORIDE (WAVELENGTH DEPENDENCE) (CONTINUED)
 [WAVELENGTH, λ , nm ; TEMPERATURE, T , K; REFRACTIVE INDEX, n]

λ	n	λ	n	λ	n	λ	n	λ	n	λ	n
DATA SET 31(CONT.)		DATA SET 34(CONT.)		DATA SET 35(CONT.)		DATA SET 36 T = 300.0		DATA SET 37 T = 294.0		DATA SET 38 T = 307.0	
87.87	2.70	1.7500	1.4251	0.2378	1.47215	0.0588	1.27	0.25	1.467296	0.25	1.467287
91.99	2.68	2.0000	1.4239	0.2399	1.47124	0.0608	1.30	0.26	1.463886	0.26	1.463871
97.08	2.67	2.2500	1.4226	0.2698	1.46100	0.0630	1.30	0.28	1.458320	0.28	1.458292
102.56	2.65	2.5000	1.4211	0.2752	1.45954	0.0652	1.34	0.30	1.453986	0.30	1.453949
109.05	2.63	2.7500	1.4196	0.2893	1.45621	0.0668	1.30	0.35	1.446520	0.35	1.446470
116.41	2.62	3.0000	1.4179	0.2967	1.45466	0.0680	1.21	0.40	1.441853	0.40	1.441798
125.00	2.60	3.2500	1.4161	0.3341	1.44852	0.0700	1.16	0.45	1.438716	0.45	1.438659
135.31	2.59	3.5000	1.4141	0.3345	1.44847	0.0707	1.24	0.50	1.436491	0.50	1.436433
147.49	2.58	3.7500	1.4120	0.4046	1.44148	0.0721	1.20	0.55	1.434845	0.55	1.434788
162.60	2.57	4.0000	1.4097	0.4358	1.43949	0.0754	1.21	0.60	1.433585	0.60	1.433527
179.85	2.56	4.2500	1.4072	0.4678	1.43785	0.0775	1.23	0.65	1.432590	0.65	1.432533
204.08	2.54	4.5000	1.4047	0.4799	1.43732	0.0810	1.45	0.70	1.431784	0.70	1.431728
233.10	2.54	4.7500	1.4019	0.5085	1.43620	0.0855	1.27	0.75	1.431117	0.75	1.431060
277.00	2.54	5.0000	1.3990	0.5460	1.43496	0.0909	1.34	0.80	1.430551	0.80	1.430495
346.02	2.57	5.2500	1.3959	0.5875	1.43389	0.0871	1.39	0.85	1.430063	0.85	1.430008
421.94	2.56	5.5000	1.3926	0.6438	1.43272	0.0881	1.55	0.90	1.429634	0.90	1.429579
DATA SET 32		6.0000	1.3856	0.7065	1.43171	0.0909	1.54	0.95	1.429251	0.95	1.429196
T = 300.0		6.2500	1.3818	0.7800	1.43080	0.0922	1.55	1.00	1.428903	1.00	1.428848
		6.5000	1.3778	0.8520	1.43007	0.0943	1.51	1.10	1.428285	1.10	1.428230
150.15	2.63	6.7500	1.3737	0.8943	1.42971	0.0962	1.33	1.20	1.427735	1.20	1.427682
166.11	2.62	7.0000	1.3693	1.0139	1.42884	0.1013	2.06	1.40	1.426744	1.40	1.426691
184.16	2.61	7.2500	1.3648	1.1287	1.42815	0.1068	1.48	1.60	1.425803	1.60	1.425752
209.64	2.60	7.5000	1.3600	1.5295	1.42617	0.1088	1.38	1.80	1.424853	1.80	1.424802
241.54	2.60	7.7500	1.3550	1.8132	1.42484	0.1101	1.46	2.00	1.423861	2.00	1.423812
283.28	2.59	8.0000	1.3498	1.9700	1.42407	0.1101	2.14	2.20	1.422810	2.20	1.422762
348.43	2.58	8.2500	1.3445	2.0580	1.42359	0.1118	2.17	2.50	1.421098	2.50	1.421052
442.47	2.60	8.5000	1.3388	2.3250	1.42216	0.1180	1.31	3.00	1.417836	3.00	1.417794
		8.7500	1.3330	2.7300	1.41970	0.1228	1.30	3.50	1.414017	3.50	1.413978
DATA SET 33		9.0000	1.3269	3.0030	1.41786	0.1290	1.71	4.00	1.409506	4.00	1.409571
T = 293.0		9.2500	1.3206	3.2765	1.41584	0.1476	1.50	4.50	1.404579	4.50	1.404547
		9.5000	1.3141	3.5498	1.41366	0.1606	1.53	5.00	1.398912	5.00	1.398883
0.6328	1.23	9.7500	1.3073	3.8226	1.41130	0.1834	1.49	5.50	1.392582	5.50	1.392554
		10.0000	1.3002	4.0950	1.40876	0.2246	1.44	6.00	1.385561	6.00	1.385533
DATA SET 34		11.0000	1.2694	4.3687	1.40604	0.2731	1.42	6.50	1.377821	6.50	1.377791
T = 293.0		DATA SET 35		4.6425	1.40313	0.3342	1.40	7.00	1.369330	7.00	1.369295
		T = 293.0		4.9140	1.40002	0.4412	1.40	7.50	1.360051	7.50	1.360009
1.0000	1.4289		5.1867	1.39670			8.00	1.349845	8.00	1.349892	
1.2500	1.4275	0.2138	1.48496								
1.5000	1.4263										

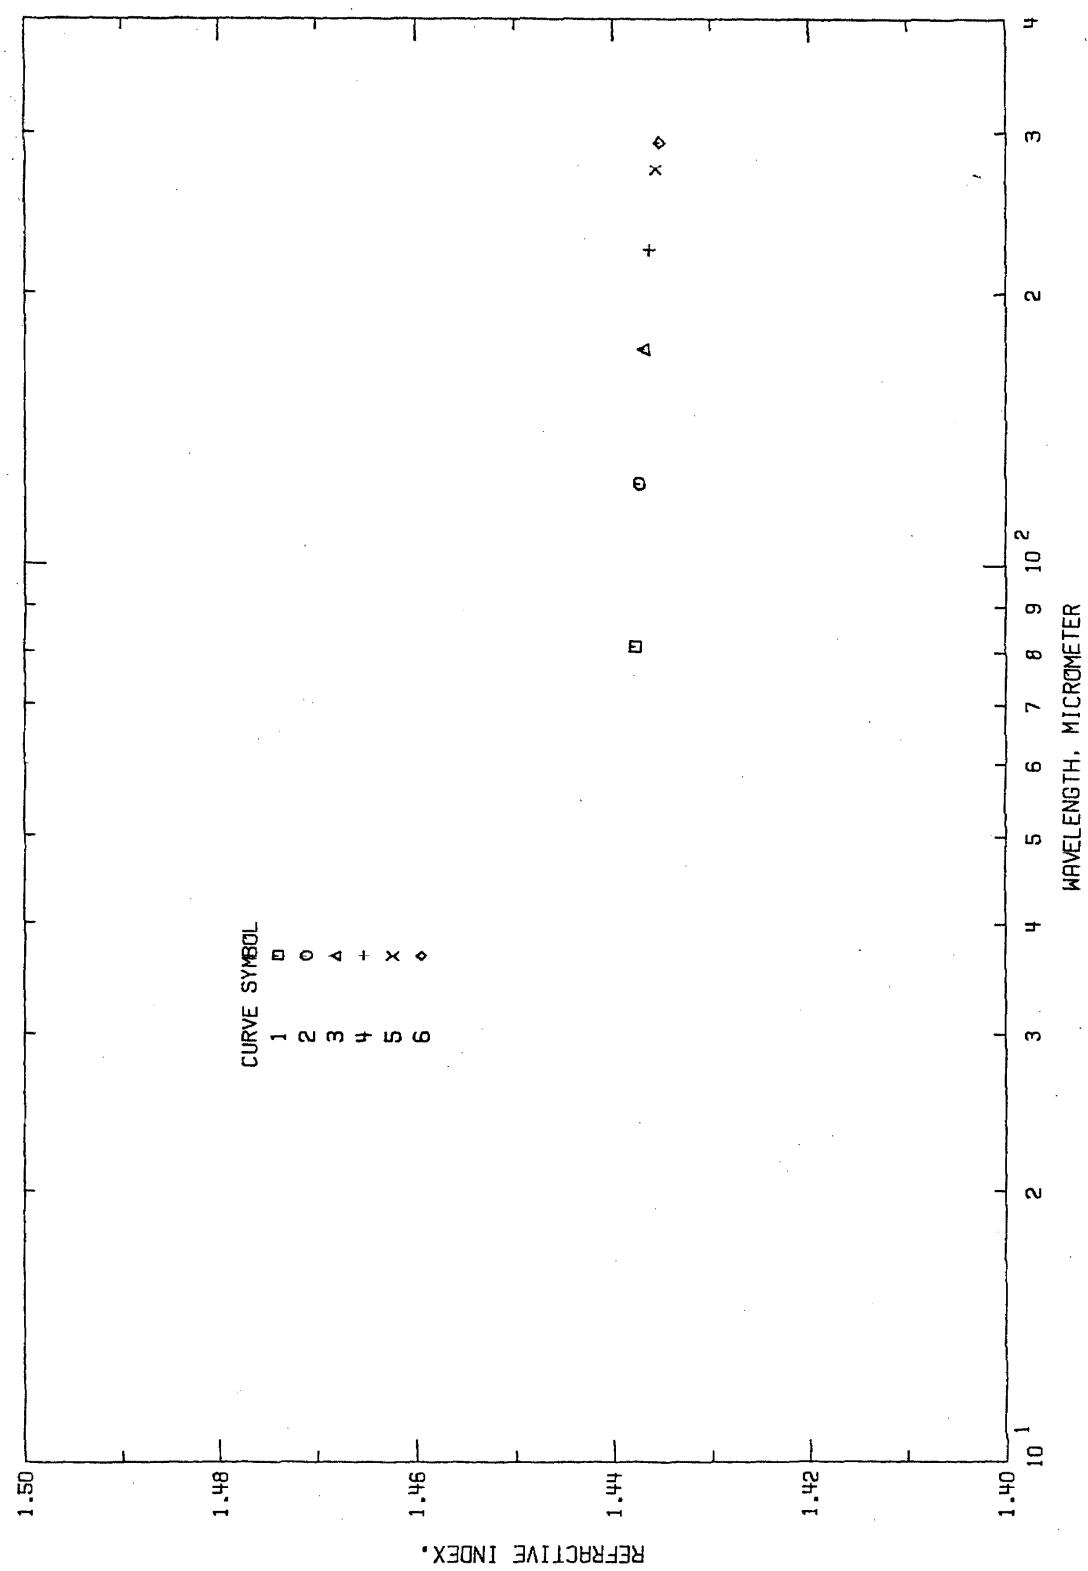


TABLE 11. MEASUREMENT INFORMATION ON THE REFRACTIVE INDEX OF CALCIUM FLUORIDE (TEMPERATURE DEPENDENCE)

DATA SET NO.	REF. NO.	AUTHOR(S)	YEAR	METHOD USED	WAVELENGTH RANGE, μm	TEMP. K	SPECIFICATIONS AND REMARKS
1	54	BARBARON, M.	1951	D	0.546	81	SINGLE CRYSTAL: PRISMATIC SPECIMEN; 60 DEGREE APEX ANGLE. 1.2CM HEIGHT: REFRACTIVE INDEX DETERMINED BY MINIMUM DEVIATION METHOD FOR THE SPECTRAL LINE 0.546 MICROMETERS; DATA EXTRACTED FROM A TABLE.
2	54	BARBARON, M.	1951	D	0.546	123	SIMILAR TO ABOVE BUT AT A HIGHER TEMPERATURE OF 123K.
3	54	BARBARON, M.	1951	D	0.546	173	SIMILAR TO ABOVE BUT AT A HIGHER TEMPERATURE OF 173K.
4	54	BARBARON, M.	1951	D	0.546	223	SIMILAR TO ABOVE BUT AT A HIGHER TEMPERATURE OF 223K.
5	54	BARBARON, M.	1951	D	0.546	273	SIMILAR TO ABOVE BUT AT A HIGHER TEMPERATURE OF 273K.
6	54	BARBARON, M.	1951	D	0.546	293	SIMILAR TO ABOVE BUT AT A HIGHER TEMPERATURE OF 293K.

TABLE 12. EXPERIMENTAL REFRACTIVE INDEX OF CALCIUM FLUORIDE (TEMPERATURE DEPENDENCE)

[WAVELENGTH, λ , μm ; TEMPERATURE, T , K; REFRACTIVE INDEX, n]

T	n
DATA SET 1	
$\lambda = 0.546$	
81.0	1.4377
DATA SET 2	
$\lambda = 0.546$	
123.0	1.4374
DATA SET 3	
$\lambda = 0.546$	
173.0	1.4369
DATA SET 4	
$\lambda = 0.546$	
223.0	1.43631
DATA SET 5	
$\lambda = 0.546$	
273.0	1.43565
DATA SET 6	
$\lambda = 0.546$	
293.0	1.43538

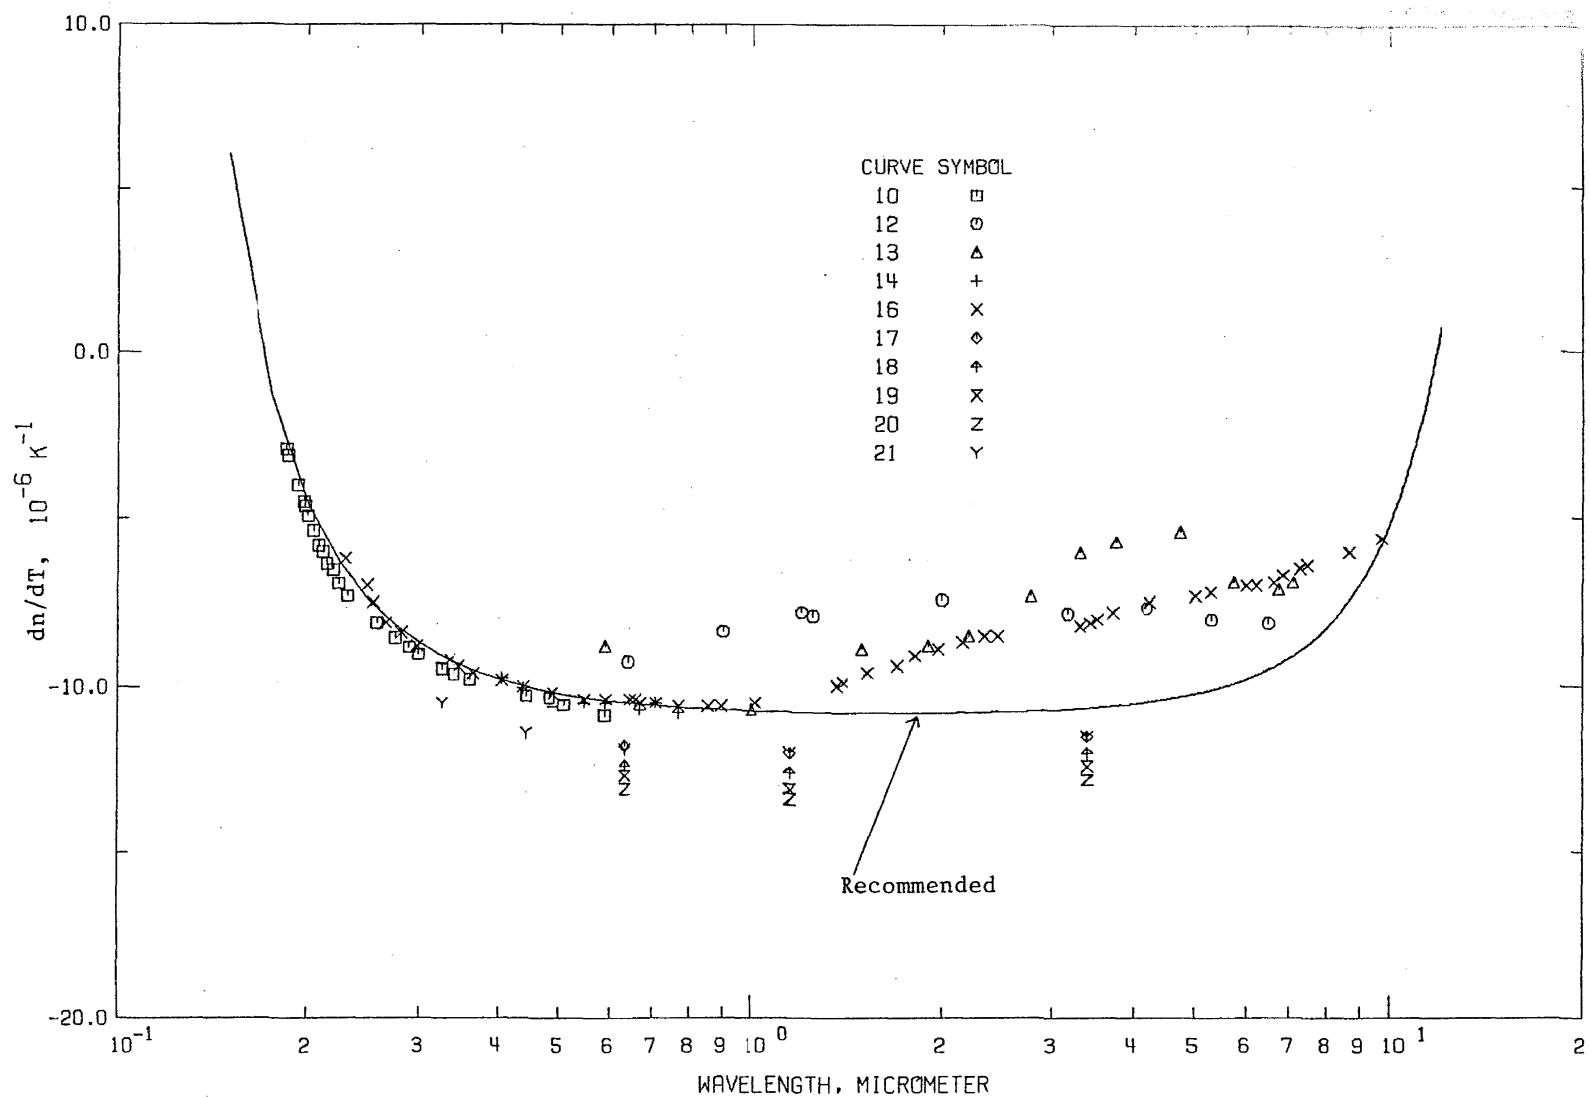


FIGURE 10. TEMPERATURE DERIVATIVE OF REFRACTIVE INDEX OF CALCIUM FLUORIDE (WAVELENGTH DEPENDENCE).

TABLE 13. MEASUREMENT INFORMATION ON THE TEMPERATURE DERIVATIVE OF REFRACTIVE INDEX OF CALCIUM FLUORIDE (WAVELENGTH DEPENDENCE)

DATA SET NO.	REF. NO.	AUTHOR(S)	YEAR	METHOD USED	WAVELENGTH RANGE, μm	TEMP. K	SPECIFICATIONS AND REMARKS
1	28	STEFAN, J.M.	1871	D	0.39-0.59	330	NATURAL CRYSTAL; PRISMATIC SPECIMEN; NEAR 44 DEGREE APEX ANGLE; DN/DT DETERMINED FOR 3 SPECTRAL LINES USING THE INDICES MEASURED AT 294 AND 366K; DATA EXTRACTED FROM A TABLE.
2	30	PULFRICH, C.	1892	P	0.43-0.66	333	NATURAL CRYSTAL; PRISMATIC SPECIMEN; NEAR 25.5 DEGREE APEX ANGLE; DN/DT DETERMINED FOR 4 SPECTRAL LINES USING THE INDICES MEASURED AT 294 AND 372K; DATA EXTRACTED FROM A TABLE.
3	55	REED, J.O.	1898	P	0.43-0.66	332	NATURAL CRYSTAL; PRISMATIC SPECIMEN; NEAR 29.33 DEGREE APEX ANGLE; DN/DT DETERMINED BY AN ABBE AUTO COLLIMATION METHOD FOR 4 SPECTRAL LINES; ONLY DN/DT REPORTED IN THIS PAPER; DATA EXTRACTED FROM A TABLE.
4	55	REED, J.O.	1898	P	0.43-0.66	340	SIMILAR TO ABOVE BUT AT A HIGHER TEMPERATURE OF 340.1K.
5	55	REED, J.O.	1898	P	0.43-0.66	426	SIMILAR TO ABOVE BUT AT A HIGHER TEMPERATURE OF 426.1K.
6	55	REED, J.O.	1898	P	0.43-0.66	506	SIMILAR TO ABOVE BUT AT A HIGHER TEMPERATURE OF 506.2K.
7	55	REED, J.O.	1898	P	0.43-0.66	551	SIMILAR TO ABOVE BUT AT A HIGHER TEMPERATURE OF 550.7K.
8	55	REED, J.O.	1898	P	0.43-0.66	600	SIMILAR TO ABOVE BUT AT A HIGHER TEMPERATURE OF 599.7K.
9	55	REED, J.O.	1898	P	0.43-0.66	658	SIMILAR TO ABOVE BUT AT A HIGHER TEMPERATURE OF 658.2K.
10	56	MICHELI, E.J.	1902	D	0.18-0.59	334	NATURAL CRYSTAL; PRISMATIC SPECIMEN; NEAR 60 DEGREE APEX ANGLE, 38MMX23MM VIEW SURFACE; REFRACTIVE INDEX DETERMINED BY DEVIATION METHOD; DN/DT DETERMINED FOR 24 SPECTRAL LINES USING THE INDICES MEASURED AT 295 AND 373K; DATA EXTRACTED FROM A TABLE; ONLY DN/DT REPORTED IN THIS PAPER.
11	57	LIEBREICH, E.	1911	D	0.58-6.50	333	NATURAL CRYSTAL; PRISMATIC SPECIMEN; NEAR 29 DEGREE APEX ANGLE, 1.8 CM HEIGHT, 2.0 CM EDGE; REFRACTIVE INDEX DETERMINED BY DEVIATION METHOD; DN/DT DETERMINED FOR 11 SPECTRAL LINES USING THE INDICES MEASURED AT 287 TO 347K; DATA EXTRACTED FROM A TABLE; ONLY DN/DT REPORTED IN THIS PAPER; ESTIMATED UNCERTAINTY ABOUT 14%.
12	57	LIEBREICH, E.	1911	D	0.64-6.50	317	SIMILAR TO ABOVE BUT FOR 9 SPECTRAL LINES AND A DIFFERENT TEMPERATURE INTERVAL.

TABLE 13. MEASUREMENT INFORMATION ON THE TEMPERATURE DERIVATIVE OF REFRACTIVE INDEX OF CALCIUM FLUORIDE (WAVELENGTH DEPENDENCE) (CONTINUED)

DATA SET NO.	REF. NO.	AUTHOR(S)	YEAR	METHOD USED	WAVELENGTH RANGE, μm	TEMP. K	SPECIFICATIONS AND REMARKS
13	58	LIEBREICH, E.	1911	D	0.58-7.10	267	NATURAL CRYSTAL; PRISMATIC SPECIMEN; REFRACTIVE INDEX DETERMINED BY DEVIATION METHOD; DN/DT DETERMINED FOR 12 SPECTRAL LINES USING THE INDICES MEASURED AT 241 TO 293K; DATA EXTRACTED FROM A TABLE; ONLY DN/DT REPORTED IN THIS PAPER.
14	48	MALITSON, I.H.	1963	D	0.40-0.77	298	SYNTHETIC CRYSTAL; GROWN BY THE STOCKBARGER TECHNIQUE; PRISMATIC SPECIMEN; REFRACTIVE INDEX DETERMINED BY DEVIATION METHOD; DN/DT DETERMINED FOR 9 SPECTRAL LINES USING THE INDICES MEASURED AT 288 AND 308K; DATA EXTRACTED FROM A TABLE.
15	48	MALITSON, I.H.	1963	D	0.40-0.77	318	SIMILAR TO ABOVE DN/DT DETERMINED FOR 9 SPECTRAL LINES USING THE INDICES MEASURED AT 308 AND 328K.
16	48	MALITSON, I.H.	1963	D	0.22-3.73	292	SYNTHETIC CRYSTAL; GROWN AT MIT BY D. C. STOCKBARGER; PRISMATIC SPECIMEN; NEAR 70 DEGREE APEX ANGLE, 55MMX73MM VIEW SURFACE; REFRACTIVE INDEX DETERMINED BY MINIMUM DEVIATION METHOD; DN/DT DETERMINED FOR 46 SPECTRAL LINES USING THE INDICES MEASURED AT 287 AND 297K; DATA EXTRACTED FROM A TABLE.
17	93	DODGE, M.J.	1976	D	0.25-8.0	300	POLYCRYSTALLINE; HOT-FORGED; OBTAINED FROM HARSHAW CHEMICAL CORP.; PRISMATIC SPECIMEN WITH REFRACTING ANGLE NEAR 60 DEGREES AND 4CMX5CM FACES; REFRACTIVE INDICES MEASURED AT TEMPERATURES 294 K AND 307 K; DATA EXTRACTED FROM A FIGURE.
18	59	LIPSON, H.G. TSAY, Y.F. BENDOW, B. LIGOR, P.A.	1976	I	0.63-3.39	310	SINGLE CRYSTAL; DISC SPECIMEN; 1.90CM DIAMETER, 1CM TO 2.5CM THICK; DN/DT DETERMINED FOR 3 SPECTRAL LINES BY OBSERVING THE INTERFERENCE FRINGE CHANGES AND THE CORRESPONDING TEMPERATURE CHANGES; DATA EXTRACTED FROM A TABLE; UNCERTAINTY OF DN/DT ABOUT $0.6 \times 10^{-6} \text{ K}^{-1}$.
19	59	LIPSON, H.G. ET AL.	1976	I	0.63-3.39	330	SIMILAR TO ABOVE BUT AT A HIGHER TEMPERATURE OF 330K; UNCERTAINTY OF DN/DT $0.5 \times 10^{-6} \text{ K}^{-1}$.
20	59	LIPSON, H.G. ET AL.	1976	I	0.63-3.39	350	SIMILAR TO ABOVE BUT AT A HIGHER TEMPERATURE OF 350K; UNCERTAINTY OF DN/DT $0.5 \times 10^{-6} \text{ K}^{-1}$.
21	60	HARRIS, R.J. JOHNSTON, G.T. KEPPEL, G.A. KROK, P.C., MUKAI, H.	1977	I	0.63-3.39	318	POLYCRYSTALLINE; OBTAINED FROM THE HARSHAW CHEMICAL CO.; PLATE SPECIMEN; DN/DT DETERMINED DIRECTLY FOR 3 SPECTRAL LINES BY OBSERVING THE FIZEAU INTERFERENCE FRINGE CHANGES AND THE CORRESPONDING TEMPERATURE CHANGES; MEASUREMENTS MADE FROM 298 TO 338K, THE AVERAGED VALUES OF DN/DT WERE GIVEN; DATA EXTRACTED FROM A TABLE.

TABLE 13. MEASUREMENT INFORMATION ON THE TEMPERATURE DERIVATIVE OF REFRACTIVE INDEX OF CALCIUM FLUORIDE (WAVELENGTH DEPENDENCE) (CONTINUED)

DATA SET NO.	REF. NO.	AUTHOR(S)	YEAR	METHOD USED	WAVELENGTH RANGE, μm	TEMP. K	SPECIFICATIONS AND REMARKS
22	92	TSAY, Y.F. LIPSON, H.G. LIGOR, P.A.	1977	I	0.32-3.39	310	SINGLE CRYSTAL; DISC SPECIMEN; 1.90CM DIAMETER, 1.27CM THICK; DN/DT DETERMINED BY OBSERVING THE INTERFERENCE FRINGE CHANGES AND THE CORRESPONDING TEMPERATURE CHANGES DATA EXTRACTED FROM A FIGURE; UNCERTAINTY OF DN/DT ABOUT $1.0 \times 10^{-6} \text{ K}^{-1}$.

TABLE 14. EXPERIMENTAL TEMPERATURE DERIVATIVE OF REFRACTIVE INDEX OF CALCIUM FLUORIDE (WAVELENGTH DEPENDENCE)
 [WAVELENGTH, λ , μm ; TEMPERATURE, T , K; TEMPERATURE DERIVATIVE OF REFRACTIVE INDEX, dn/dT , 10^{-6}K^{-1}]

λ	dn/dT	λ	dn/dT	λ	dn/dT	λ	dn/dT	λ	dn/dT	λ	dn/dT
DATA SET 1 $T = 330.0$		DATA SET 6 $T = 506.2$		DATA SET 10(CONT.)		DATA SET 12(CONT.)		DATA SET 15(CONT.)		DATA SET 16(CONT.)	
0.397 -12.4	0.436 -12.67	0.208 -5.82	2.0 -7.44	0.486132 -10.70	2.32542 -8.5						
0.486 -12.3	0.486 -12.81	0.211 -6.01	3.16 -7.82	0.546074 -11.00	2.4374 -8.5						
0.589 -12.4	0.589 -13.18	0.214 -6.37	4.2 -7.67	0.589262 -10.90	3.3026 -8.2						
	0.656 -13.32	0.219 -6.55	5.3 -8.02	0.656279 -11.05	3.422 -8.1						
		0.224 -6.96	6.5 -8.13	0.667814 -10.85	3.5070 -8.0						
		0.231 -7.32		0.706518 -11.10	3.7067 -7.8						
DATA SET 2 $T = 333.0$		DATA SET 7 $T = 550.7$	0.257 -8.11	DATA SET 13 $T = 267.0$	0.767858 -11.10						
0.434 -10.39	0.436 -13.78	0.298 -9.04	0.589 -8.8	DATA SET 16 $T = 292.0$	5.3034 -7.0						
0.486 -10.67	0.486 -13.87	0.325 -9.48	1.0 -10.7		6.0140 -7.0						
0.589 -11.04	0.589 -14.32	0.340 -9.64	1.5 -8.9	0.228803 -6.2	6.238 -7.0						
0.656 -11.18	0.656 -14.43	0.361 -9.79	1.9 -8.8	0.24827 -7.0	6.63306 -6.9						
		0.441 -10.28	2.2 -8.5	0.2537 -7.5	6.8559 -6.7						
DATA SET 3 $T = 332.0$		DATA SET 8 $T = 599.7$	0.480 -10.35	2.75 -7.3	7.268 -6.5						
0.436 -10.57	0.436 -14.43	0.508 -10.56	3.3 -6.0	0.26520 -8.1	7.4644 -6.4						
0.486 -10.67	0.486 -14.56	0.589 -10.89	3.75 -5.7	0.28035 -8.4	8.662 -6.0						
0.589 -10.92	0.589 -14.93		4.75 -5.4	0.296728 -8.8	9.724 -5.6						
0.656 -11.11	0.656 -15.08			0.334148 -9.2							
		0.589 -11.11		0.346662 -9.4	DATA SET 17						
DATA SET 4 $T = 340.1$		DATA SET 9 $T = 658.2$	0.64 -11.13	DATA SET 14 $T = 298.0$	$T = 300.0$						
0.436 -10.74	0.436 -15.21	0.9 -10.31		0.546074 -10.4	0.28 -2.0						
0.486 -10.83	0.486 -15.35	1.2 -10.40		0.589262 -10.4	0.29 -1.8						
0.589 -11.03	0.589 -15.84	1.25 -10.29	0.404656 -9.75	0.643847 -10.4	0.29 -2.9						
0.656 -11.14	0.656 -16.04	1.3 -10.18	0.435834 -10.05	0.656279 -10.4	0.30 -2.6						
		2.0 -9.32	0.486132 -10.60	0.667814 -10.5	0.31 -3.2						
		3.16 -8.81	0.546074 -10.50	0.706518 -10.5	0.33 -2.8						
DATA SET 5 $T = 426.1$		DATA SET 10 $T = 334.0$	4.2 -8.31	0.589262 -10.50	0.34 -1.5						
0.436 -12.15	0.185 -2.96	5.3 -8.21	0.656279 -10.50	0.767858 -10.6	0.37 -4.4						
0.486 -12.24	0.186 -3.13	6.5 -7.87	0.667814 -10.70	0.85212 -10.6	0.38 -3.6						
0.589 -12.63	0.193 -4.02			0.8944 -10.6	0.42 -4.3						
0.656 -12.71	0.197 -4.51	0.64 -9.27	0.706518 -10.50	1.01398 -10.5	0.44 -4.2						
	0.198 -4.64	0.9 -8.36	0.767858 -10.80	1.3622 -10.0	0.57 -4.4						
	0.200 -4.93	1.2 -7.79		1.39506 -9.9	0.58 -4.3						
	0.204 -5.38	1.25 -7.92	0.404656 -10.12	1.52952 -9.6	1.03 -5.1						
			0.435834 -10.55	1.7012 -9.4	1.14 -2.8						
				1.81307 -9.1	1.40 -3.7						
				1.97009 -8.9	1.57 -3.4						
				2.1526 -8.7	1.74 -4.4						

TABLE 14. EXPERIMENTAL TEMPERATURE DERIVATIVE OF REFRACTIVE INDEX OF CALCIUM FLUORIDE (WAVELENGTH DEPENDENCE) (CONTINUED)
 [WAVELENGTH, λ , μm ; TEMPERATURE, T , K; TEMPERATURE DERIVATIVE OF REFRACTIVE INDEX, dn/dT , 10^{-6}K^{-1}]

λ	dn/dT	λ	dn/dT
DATA SET 17 (CONT.)			
DATA SET 20 $T = 350.0$			
2.13	-3.9		
2.66	-3.1	0.6328	-12.7
3.37	-4.8	1.15	-13.1
3.43	-4.1	3.39	-12.4
3.55	-4.6		
3.67	-5.4	DATA SET 21	
3.79	-4.0	$T = 318.0$	
4.34	-3.4		
5.31	-0.3	0.6328	-13.1
5.41	-2.1	1.15	-13.4
5.50	-1.3	3.39	-12.8
5.59	-0.3		
5.89	-2.4	DATA SET 22	
5.98	-2.2	$T = 310.0$	
6.09	-3.0		
6.41	-3.0	0.325	-10.5
6.41	-3.8	0.4416	-11.4
6.63	-3.1	0.6328	-11.9
6.74	-2.7	1.15	-12.0
6.85	-1.5	3.39	-11.5
6.97	-2.4		
7.33	-2.5		
7.72	-2.4		
8.13	-4.7		
8.28	-7.2		
DATA SET 18			
$T = 310.0$			
0.6328	-11.8		
1.15	-12.0		
3.39	-11.5		
DATA SET 19			
$T = 330.0$			
0.6328	-12.4		
1.15	-12.6		
3.39	-12.0		

H. H. LI

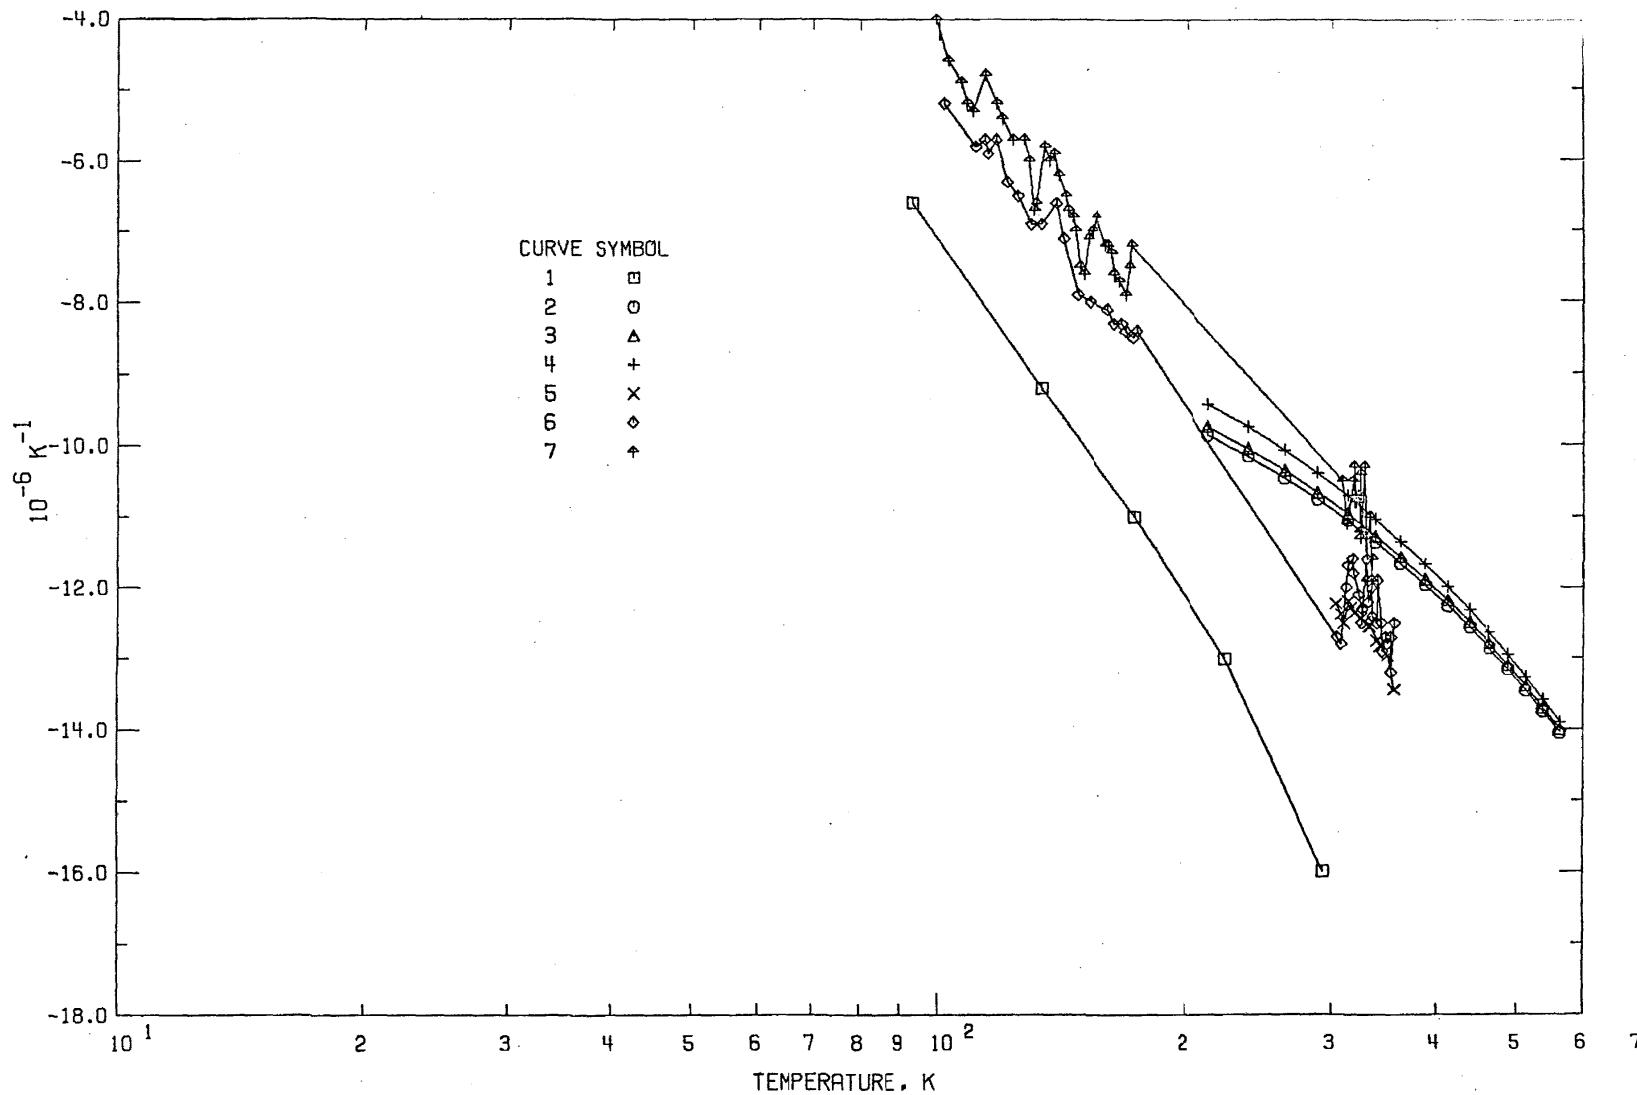


FIGURE 11. TEMPERATURE DERIVATIVE OF REFRACTIVE INDEX OF CALCIUM FLUORIDE (TEMPERATURE DEPENDENCE).

TABLE 15. MEASUREMENT INFORMATION ON THE TEMPERATURE DERIVATIVE OF REFRACTIVE INDEX OF CALCIUM FLUORIDE (TEMPERATURE DEPENDENCE)

DATA SET NO.	REF. NO.	AUTHOR(S)	YEAR	METHOD USED	WAVELENGTH RANGE, μm	TEMP. K	SPECIFICATIONS AND REMARKS
1	47	HOUSTON,T.W. JOHNSON,L.F. KISLIUK,P. WALSH,D.J.	1963	D	0.5461	93-293	SINGLE CRYSTAL; HIGH PURITY; PRISMATIC SPECIMEN; POLISHED SURFACES FLAT TO 1/2 WAVELENGTH OF 0.535 MICROMETER LINE; REFRACTIVE INDEX DETERMINED BY MINIMUM DEVIATION METHOD; DN/DT DETERMINED USING INDICES MEASURED AT 93 TO 293K, FOR 0.5461 MICROMETER; DATA EXTRACTED FROM A TABLE.
2	68	SELEZNEVA,A.M.	1969	I	0.656	213-573	SYNTHETIC CRYSTAL; PRODUCED IN THE SOVIET UNION; WELL ANNEALED; DN/DT DETERMINED BY INTERFERENCE METHOD; EMPIRICAL FORMULA PROPOSED FOR CALCULATION OF DN/DT; DATA EXTRACTED BY EVALUATING A GIVEN EQUATION.
3	68	SELEZNEVA,A.M.	1969	I	0.589	213-573	SIMILAR TO ABOVE BUT FOR WAVELENGTH 0.589 MICROMETERS.
4	68	SELEZNEVA,A.M.	1969	I	0.486	213-573	SIMILAR TO ABOVE BUT FOR WAVELENGTH 0.486 MICROMETERS.
5	59	LIPSON,H.G. TSAY,Y.F. BENDOW,B LIGOR,P.A.	1976	I	1.15	300-360	SINGLE CRYSTAL; DISC SPECIMEN; 1.90CM DIAMETER, 1CM TO 2.5CM THICK; DN/DT DETERMINED BY OBSERVING THE INTERFERENCE FRINGE CHANGES AND THE CORRESPONDING TEMPERATURE CHANGES; DATA EXTRACTED FROM A FIGURE; UNCERTAINTY OF DN/DT ABOUT $0.5 \times 10^{-6} \text{K}^{-1}$.
6	92	TSAY,Y.F. LIPSON,H.G. LIGOR,P.A.	1977	I	0.6328	100-360	SINGLE CRYSTAL; DISC SPECIMEN; 1.90CM DIAMETER, 1.27CM THICK; DN/DT DETERMINED BY OBSERVING THE INTERFERENCE FRINGE CHANGES AND THE CORRESPONDING TEMPERATURE CHANGES DATA EXTRACTED FROM A FIGURE; UNCERTAINTY OF DN/DT ABOUT $1.0 \times 10^{-6} \text{K}^{-1}$.
7	92	TSAY,Y.F. ET AL.	1977	I	0.325	100-340	SIMILAR TO ABOVE BUT FOR WAVELENGTH 0.325 MICROMETERS; UNCERTAINTY OF DN/DT $1.0 \times 10^{-6} \text{K}^{-1}$.

H. H. L

TABLE 16. EXPERIMENTAL TEMPERATURE DERIVATIVE OF REFRACTIVE INDEX OF CALCIUM FLUORIDE (TEMPERATURE DEPENDENCE)
[WAVELENGTH, λ , μm ; TEMPERATURE, T, K; TEMPERATURE DERIVATIVE OF REFRACTIVE INDEX, dn/dT , 10^{-6} K^{-1}]

T	dn/dT	T	dn/dT	T	dn/dT	T	dn/dT	T	dn/dT		
DATA SET 1											
$\lambda = 0.546$											
93.0	-6.6	488.0	-13.10	357.009	-13.445	345.1	-12.9	166.0	-7.7		
133.0	-9.2	513.0	-13.40			347.9	-12.7	168.8	-7.9		
173.0	-11.0	538.0	-13.71	DATA SET 6		349.7	-12.8	170.7	-7.5		
223.0	-13.0	563.0	-14.01	$\lambda = 0.632$		353.4	-12.7	171.6	-7.2		
293.0	-16.0	DATA SET 4		101.5	-5.2	353.7	-13.2	309.0	-10.5		
		$\lambda = 0.486$		110.7	-5.8	357.1	-12.5	312.6	-11.1		
DATA SET 2											
$\lambda = 0.656$											
213.0	-9.86	213.0	-9.43	113.5	-5.7	DATA SET 7		318.2	-10.5		
238.0	-10.16	238.0	-9.75	117.2	-5.7	$\lambda = 0.325$		319.1	-10.8		
263.0	-10.46	313.0	-10.71	129.2	-6.9			319.2	-10.3		
288.0	-10.76	338.0	-11.03	132.9	-6.9	99.0	-4.0	321.0	-10.8		
313.0	-11.06	363.0	-11.35	138.4	-6.6	102.6	-4.6	322.8	-10.7		
338.0	-11.36	388.0	-11.67	141.2	-7.1	106.3	-4.9	324.6	-11.2		
363.0	-11.66	413.0	-11.99	146.8	-7.9	108.1	-5.2	324.7	-10.4		
388.0	-11.96	438.0	-12.31	152.3	-8.0	113.7	-4.8	324.6	-11.3		
413.0	-12.26	463.0	-12.63	160.6	-8.1	117.3	-5.2	330.1	-11.9		
438.0	-12.56	488.0	-12.95	163.4	-8.3	119.1	-5.4	330.2	-11.3		
463.0	-12.86	513.0	-13.27	167.1	-8.3	122.8	-5.7	333.0	-11.0		
488.0	-13.16	538.0	-13.59	168.9	-8.4	126.5	-5.7	334.7	-11.9		
513.0	-13.46	563.0	-13.91	172.6	-8.5	128.3	-6.0	335.7	-11.6		
538.0	-13.76	DATA SET 5		174.4	-8.4	130.1	-6.7				
563.0	-14.06	$\lambda = 1.15$		303.7	-12.7	133.9	-5.8				
DATA SET 3											
$\lambda = 0.589$											
213.0	-9.74	303.174	-12.230	311.9	-12.0	135.7	-6.0				
238.0	-10.05	307.054	-12.376	313.7	-11.7	137.6	-5.9				
263.0	-10.35	313.753	-12.195	317.4	-11.6	139.4	-6.2				
288.0	-10.66	315.796	-12.283	318.4	-11.8	142.1	-6.5				
313.0	-10.96	318.855	-12.355	323.0	-12.1	143.0	-6.7				
338.0	-11.27	324.966	-12.426	325.7	-12.3	144.9	-6.8				
363.0	-11.57	327.820	-12.484	330.3	-11.6	147.6	-7.5				
388.0	-11.88	331.692	-12.541	331.3	-12.2	151.3	-7.1				
413.0	-12.18	333.523	-12.540	334.9	-12.0	153.2	-7.0				
438.0	-12.49	339.647	-12.744	335.0	-12.4	155.0	-6.8				
463.0	-12.79	342.706	-12.817	339.6	-12.5	159.6	-7.2				
		350.656	-12.960	340.5	-11.9	160.6	-7.2				
				344.2	-12.5	162.4	-7.3				
						163.3	-7.6				

TABLE 17. COMPARISON OF DISPERSION EQUATIONS PROPOSED FOR CaF₂

Source	Wavelength and Temperature Ranges	Dispersion Equation λ in μm ; ν in cm^{-1}
Carvallo, M. E. 1893	0.63-1.85 μm 293 K	$\frac{1}{n^2} = 0.490335 - 0.000713835 \lambda^{-2} + 0.001584 \lambda^2 - 0.000001042 \lambda^{-4}$ where $\lambda = \frac{\lambda}{n}$
Paschen, F. 1894	0.88-9.43 μm 291.0 K	$\frac{1}{n^2} = 0.490133 - 0.00067877 \lambda^{-2} + 0.0016894 \lambda^2 - 0.000001578 \lambda^{-4}$ where $\lambda = \frac{\lambda}{n}$
Paschen, F. 1895	0.88-7.66 μm 290 K	$n^2 = 2.03882 + \frac{0.00621828}{\lambda^2 - 0.007706} - 0.00319987 \lambda^2 - 0.0000029160 \lambda^4$
Paschen, F. 1901	0.88-7.07 μm 284 K	$n^2 = 2.03913 - \frac{0.006125}{\lambda^2 - 0.008884} - 0.0032055 \lambda^2 - 0.000002894 \lambda^4$
Martens, F. F. 1901	0.18-0.77 μm 291 K	$n^2 = 1.361140 + \frac{0.677860 \lambda^2}{\lambda^2 - (0.0950790)^2} + \frac{0.160020 \lambda^2}{\lambda^2 - (24.0)^2} + \frac{0.193620 \lambda^2}{\lambda^2 - (31.6)^2} + \frac{4.527470 \lambda^2}{\lambda^2 - (40.52605)^2}$
Kaiscr, W., Spitzer, W.G., Kaiser, R.H., and Howarth, L.E. 1962	10-00 μm	$n^2 - k^2 = \epsilon_{\infty} + \sum_i 4\pi \rho_i \nu_i^2 \frac{\nu_i^2 - \nu^2}{(\nu_i^2 - \nu^2)^2 + \gamma_i^2 \nu^2 \nu_i^2}$ $2nk = \sum_i 4\pi \rho_i \nu_i^2 \frac{\gamma_i \nu \nu_i}{(\nu_i^2 - \nu^2)^2 + \gamma_i^2 \nu^2 \nu_i^2} \text{ a}$
Malitson, I. H. 1963	0.23-9.7 μm 297 K	$n^2 = 1 + \frac{0.5675888 \lambda^2}{\lambda^2 - (0.050263605)^2} + \frac{0.4710914 \lambda^2}{\lambda^2 - (0.1003909)^2} + \frac{3.8484723 \lambda^2}{\lambda^2 - (34.649040)^2}$
Eastman Kodak Co. 1971	1.0-11.0 μm 293 K	$n = 1.4278071 + \frac{2.2806966 \times 10^{-3}}{\lambda^2 - 0.028} - \frac{9.1939015 \times 10^{-5}}{(\lambda^2 - 0.028)^2} - 1.1165792 \times 10^{-3} \lambda^2 - 1.5949659 \times 10^{-6} \lambda^4$
Field, G. R. and Wilkinson, G. R. 1973	0.2138-5.187 μm 293 K	$n^2 - k^2 = \epsilon_{\infty} + \sum_i \frac{4\pi \rho_i (\nu_i^2 - \nu^2) \nu_i^2}{(\nu_i^2 - \nu^2)^2 + \gamma_i^2 \nu_i^2 \nu^2}$ $2nk = \sum_i \frac{4\pi \rho_i (\gamma_i \nu_i^3 \nu)}{(\nu_i^2 - \nu^2)^2 + \gamma_i^2 \nu_i^2 \nu^2} \text{ b}$
Dodge, M. J. 1976 for hot-forged sample	0.25 - 8.0 μm	$n^2 = 1 + \sum_i \frac{A_i \lambda^2}{\lambda^2 - \lambda_i^2} \text{ c}$
Present work 1977	0.15-12.0 μm 293 K	$n^2 = 1.33973 + \frac{0.69913 \lambda^2}{\lambda^2 - (0.09374)^2} + \frac{0.11994 \lambda^2}{\lambda^2 - (21.18)^2} + \frac{4.35181 \lambda^2}{\lambda^2 - (98.46)^2}$

^a i = 1, 2; $4\pi \rho_1 = 4.20$, $4\pi \rho_2 = 0.40$; $\nu_1 = 257 \text{ cm}^{-1}$, $\nu_2 = 328 \text{ cm}^{-1}$; $\gamma_1 = 0.018$, $\gamma_2 = 0.35$; $\epsilon_{\infty} = 2.045$.^b i = 1, 2, 3; $4\pi \rho_1 = 0.370$, $4\pi \rho_2 = 0.032$, $4\pi \rho_3 = 0.036$; $\nu_1 = 266.0$, $\nu_2 = 328.0$, $\nu_3 = 83500.0$; $\gamma_1 = 0.052$, $\gamma_2 = 0.350$, $\gamma_3 = 0.120$; $\epsilon_{\infty} = 2.516$.^c At 294 K, $A_1 = 0.98584551$, $A_2 = 0.05290246$, $A_3 = 4.2816899$, $\lambda_1 = 0.07218116$, $\lambda_2 = 0.14114719$, $\lambda_3 = 36.465937$;At 307 K, $A_1 = 0.97066991$, $A_2 = 0.06792205$, $A_3 = 4.1634415$, $\lambda_1 = 0.07115659$, $\lambda_2 = 0.13670627$, $\lambda_3 = 35.984292$.

3.2 Strontium Fluoride, SrF_2

Strontium fluoride, one of the fluoride-type crystals, is of considerable interest from the experimental and theoretical point of view. The compound is ionic but, in contrast to NaCl -type crystals, it has a number of structural features associated primarily with the presence of two equivalent F^- ions in a unit cell.

Strontium fluoride crystal has a large electronic forbidden gap and therefore the fundamental absorption is found to be in the vacuum ultraviolet beyond 10 eV. As a consequence, transparency of the crystal extends into ultraviolet region to as low as 0.12 micrometer. This makes strontium fluoride a material useful in fabrication of optical components for vacuum ultraviolet investigations.

The strontium fluoride crystal belongs to the space group O_h^5 and is expected to have one infrared active transverse optical mode (TO) of vibration. The corresponding strong resonant absorption occurs at about 46 micrometers. However, the long wavelength limit of transparency for optical usages is about 20 micrometers.

Although the crystal is transparent from 0.12 up to 20 micrometers, only in the region 0.3–7 micrometers is the dispersion low and the transmission high. Less transmission and higher dispersion are found near the low and high limits. From the point of view of optical applications, the crystal is a good window material for wavelengths from 0.3 to 7.0 micrometers, and is a preferred material of dispersion devices, such as prisms, for regions near the ultraviolet and infrared limits of the crystal.

Having low dispersion and high transmission in the spectral region of 2–6 micrometers, being not hygroscopic, having a high optical figure of merit and having better mechanical properties than the alkali halides, the strontium fluoride crystal is among the serious candidates for laser window materials. The widespread use of SrF_2 as a host crystal in laser applications encouraged attempts to grow single crystals with low impurity content. However, difficulties were experienced in the growth of pure crystals because of the low electronic mobility of conduction electrons in the crystal. Synthetic material of high purity is now commercially available or may be made by reacting the purified oxide or chloride with gaseous HF. Single crystals of SrF_2 can be grown by using the Stockbarger-Bridgman technique if adequate precautions are taken to eliminate oxygen and water from the atmosphere of the growing process. The crystal cleaves readily along [1,1,1] planes which meet to form <1,1,0> cleavage edges. The cleavage is of value in the alignment of specimens.

It would be misleading to think that the optical properties of SrF_2 have been extensively studied and that experimental data are readily at our disposal. A quick scan of the data will show that there are wide gaps and large discrepancies: see figure 12 and tables 19 and 20.

Strontium fluoride is receiving considerable attention since it has a nearly ideal host lattice for paramagnetic ions. The ionic radius of Sr^{++} (1.10 \AA) is close to those of the ions of the rare-earth group and certain elements of the actinide group. Strontium fluoride doped with up to one percent of some foreign ions demonstrates observable fluorescence. Because of this, some investigations have been directed toward finding evidence of

interactions between electronic transitions and lattice vibrations of this host crystal. Data from this work are concentrated near the restrahlen region. Only one set of data is available for the refractive index in the infrared region from 15 to 80 micrometers: Kaiser et al. [17]. The accuracy of this set of data is open to question because it was deduced from the reflection spectrum by classic dispersion theory. However, the spectral positions obtained for the fundamental absorption peaks were in agreement with those obtained from other sources. In addition, the static dielectric constant derived from the dispersion equation agrees with their own experimental values, which in turn agree with measurements of Andeen et al. [19] and of Lowndes [15]. This additional evidence positively support the correctness of their positions for the infrared absorption peaks.

At the other extreme, research activities were directed toward finding the electronic structure of the crystal. Since strontium fluoride has a large forbidden gap, much of the work was carried out in the vacuum ultraviolet. Lukirskii et al. [63] measured the refractive index for the wavelength region from 0.002 to 0.112 micrometer, Niser et al. [25] for 0.03 to 0.1234 micrometer and Ganin et al. [53] for 0.06 to 0.25 micrometer. Since all of them obtained their results by reducing the observed reflection spectra, discrepancies among their results are to be expected. However, all these studies yield similar structures for the spectrum of the refractive index in the vacuum ultraviolet, as shown in figure 12.

With regard to the refractive index in the transparent region, 0.3 to 7.0 micrometers, it is unfortunate that data are available only through four experimental investigations. Refractive indices for the wavelength region between 0.4046 and 0.7678 μm were determined by Malitson at three different temperatures, 288 K, 305 K, and 328 K, and were published by Smakula [94]. Refractive indices for the mean of the sodium D lines and for 4.5 micrometers were reported by Wulff et al. [62] and by Gisin [64], respectively. Gisin's values, which were obtained for thin films of various thickness, are expected to be lower than that of the bulk crystal. The only data set which covers a wide transparent region from 0.37 to 10 micrometers is a set of preliminary data by the OPTOVAC company, compiled by Dickison [65]. As the data set was presented in a coarse diagram, values read from this diagram carry large uncertainty, particularly in the near ultraviolet region where the plotted diagram curves most. As a result, the values read from the diagram are not adequate for data analysis. In addition, Dickison quoted two values for refractive indices at wavelengths 4.0 and 10.0 micrometers. The value at 4.0 micrometers is 1.44 (for a Harshaw grown crystal) which differs considerably from that read from the OPTOVAC diagram, about 1.41. The value at 10.0 micrometers is 1.36, which is consistent with the value from the diagram. Therefore, we are left only one set of reliable refractive index values in the visible region by Malitson. The value 1.36 at 10.0 micrometers, though not accurate, will be used to evaluate the coefficients for infrared terms.

From this brief review of available data, it may appear that we lack data to make recommendations. However, we are not prevented from making reasonable predictions because we do have information on infrared absorption peaks, the static dielectric constant, the optical dielectric constant and the available refractive indices in the visible region by Malitson and at 10 microm-

eters from OPTOVAC diagram. A correlation of these quantities through the dispersion equation is possible. Since reliability of the predicted value depends largely on the reliability of these parameters, a careful selection of the available data for these parameters plays a decisive role in making recommendations.

The available data on the optical and static dielectric constants and the wavelength of the fundamental optical phonon for SrF₂ are given in tables 4, 5, and 6, where values reported by different authors were grouped to facilitate an easy comparison. From these table, the parameters at room temperature are chosen:

$$\begin{aligned}\epsilon_0 &= 6.4679 \pm 0.0006 \text{ (Andeen et al.)}, \\ \lambda_{LO} &= 26.03 \mu\text{m, average of two entries in table 6,} \\ \lambda_{TO} &= 45.6 \pm 0.6 \mu\text{m, average of three entries in table 6.}\end{aligned}$$

Furthermore, two facts were observed in the study of CaF₂ and BaF₂: the value of the constant term in each of the dispersion equations is the same, 1.33973, and the effective wavelength of the ultraviolet absorption band in each case agrees closely with that estimated from Rubloff's work. Assuming that this is also the case for SrF₂, the coefficient of the ultraviolet term can easily be determined. As the contributions of the infrared terms to the refractive index in the visible region are negligibly small, the uv coefficient can be obtained by including the first two terms in the dispersion equation. Using Malitson's values, a fitting calculation yields a value 0.7097 for the coefficient, which agrees with the value, 0.73, based on the difference of the available optical dielectric constant and the constant term in the dispersion equation. The resulted value of λ_u is 0.09597 μm which is in close agreement with the value, 0.09566, estimated from Rubloff's work.

In the determination of the coefficients of infrared terms, two observations are taken as guides. In the first place, the sum of the coefficients in the dispersion equation should agree with the static dielectric constant. However, in the cases of CaF₂ and BaF₂ this sum is less than the corresponding static dielectric constants, about 0.3 less for CaF₂ and 0.5 less for BaF₂, because the approximation of neglecting the effects of damping factors and absorption bands other than the predominant ones. A similar difference is likely to hold for SrF₂, and a value about 0.4 is allowed to the discrepancy, corresponding to the average of those for CaF₂ and BaF₂. The second fact is that the contribution to the refractive index from the TO phonon predominates over that of the LO phonon. With these considerations, and by using the value 1.36 for the refractive index at 10 micrometers, the coefficients of the infrared terms can be calculated. The results are 3.8796 for the TO term and 0.1788 for the LO term.

The dispersion equation thus obtained is

$$\begin{aligned}n^2 = 1.33973 + \frac{0.7097 \lambda^2}{\lambda^2 - 0.09597^2} + \frac{0.1788 \lambda^2}{\lambda^2 - 26.03^2} \\ - \frac{3.8796 \lambda^2}{\lambda^2 - 45.60^2},\end{aligned}\quad (18)$$

Where λ is in unit of micrometers. When this equation is used to evaluate the refractive index at 4.0 micrometers, the result is 1.424, about 0.014 higher than that obtained from the OPTOVAC diagram and about 0.016 lower than that of the Harshaw crystal. The following consideration would lend support to this prediction. On close examination of the OPTOVAC diagram one will find that a wide section of the curve between 1.0 to 10 micrometers is actually a straight line, probably constructed by connecting the data points at visible wavelengths and at 10 micrometers. This is in contradiction to the general behavior of the refractive index as a function of wavelength. As a rule of thumb, the refractive index varies slowly in the wide middle section of the transparent region, but large variations occur near the ends. According to this rule, the refractive index at 4.0 micrometer should be higher than the diagram indicates. The quoted refractive index value for the Harshaw crystal is apparently too high for pure strontium fluoride. A simple calculation shows that this value is the square root of the optical dielectric constant. The contribution to the refractive index in the transparent region for the infrared terms is always negative. At 4.0 micrometers, the refractive index must be lower than the square root of optical dielectric constant. The high refractive index for the Harshaw crystal is probably due to impurities.

Equation (18) is used to represent the refractive index of SrF₂ at 293 K from 0.15 to 14.0 micrometers. As this equation is obtained mainly by correlation of physical parameters which are either available through literature or estimated empirically, large uncertainties are expected, especially near the limits of the transparent region. The estimated uncertainties in the refractive index for the visible region are about 0.0005 while in other low dispersion regions uncertainties are about 0.005. In the ultraviolet region from 0.15 to 0.3 micrometer, additional uncertainty is estimated using the formula:

$$\Delta n = \frac{0.720 \lambda^2}{(\lambda^2 - \lambda_u^2)^2} \left(\frac{\lambda_u \Delta \lambda_u}{n} \right), \quad (19)$$

where $\Delta \lambda_u = 0.119 - \lambda_u$. In the infrared region from 7.0 to 14.0 micrometers the additional uncertainty mainly comes from the uncertainty (estimated at 0.4) in the static dielectric constant. The predominant contribution to the uncertainty is:

$$\Delta n = \left(\frac{1}{2n} \right) \left(\frac{0.4}{\lambda^2 - 45.6^2} \right).$$

Although SrF₂ has been recognized as a good optical material, especially for laser applications where the temperature derivative of the refractive index is a parameter of prime importance, the experimental data on the refractive index is scarce. With regard to dn/dT data nothing was available until recently, Lipson et al. [59] reported dn/dT measurement for three spectral lines, 0.6328, 1.15, and 3.39 micrometers, and Tsay et al. [92] reported measurements for five lines, 0.325, 0.4416, 0.6328, 1.15, and 3.39 micrometers. The available dn/dT data are found to fit the equation

$$\begin{aligned} \frac{dn}{dT} &= -28.0 - 55.2(n^2 - 1) + \frac{50.0 \lambda^4}{(\lambda^2 - 0.09566^2)^2} \\ &+ \frac{198.1 \lambda^2}{\lambda^2 - 45.6^2} + \frac{1980.8 \lambda^4}{(\lambda^2 - 45.6^2)^2} \quad (20) \end{aligned}$$

For refractive index:

Wavelength range micrometers	Estimated uncertainty, \pm
0.15-0.20	0.05
0.20-0.30	0.02
0.30-0.40	0.005
0.40-0.70	0.0005
0.70-7.00	0.005
7.00-10.0	0.01
10.0-14.0	0.02

Equations (18) and (20) were used to generate the reference data given in the table of recommended values. Values of $dn/d\lambda$ were simply evaluated by the first derivative of eq (18). Although values of n are given to the fourth decimal place and dn/dT to the first, this does not reflect the reliability of the numbers; they are so given simply for smoothness of tabulation. However, an overstrike is placed to indicate the insignificant part of the value. For the proper use of the tabulated values the reader should follow the criteria given below:

For dn/dT :

0.15-0.20	>3.0
0.20-0.30	3.0
0.30-1.00	1.5
1.00-6.00	1.0
6.00-9.00	1.5
9.00-10.0	2.0
10.0-14.0	3.0

TABLE 18. RECOMMENDED VALUES ON THE REFRACTIVE INDEX AND ITS WAVELENGTH AND
TEMPERATURE DERIVATIVES FOR STRONTIUM FLUORIDE AT 293K*

λ μm	n	$-\frac{dn}{d\lambda}$ μm^{-1}	$\frac{dn}{dT}$ 10^{-6}K^{-1}	λ μm	n	$-\frac{dn}{d\lambda}$ μm^{-1}	$\frac{dn}{dT}$ 10^{-6}K^{-1}	λ μm	n	$-\frac{dn}{d\lambda}$ μm^{-1}	$\frac{dn}{dT}$ 10^{-6}K^{-1}
0.150	1.5941	3.4826	9.1	0.220	1.4886	0.6292	-6.4	0.290	1.4616	0.2316	-9.5
0.152	1.5874	3.2425	7.9	0.222	1.4874	0.6078	-6.6	0.292	1.4612	0.2262	-9.6
0.154	1.5811	3.0258	6.6	0.224	1.4862	0.5873	-6.7	0.294	1.4607	0.2210	-9.6
0.156	1.5752	2.8235	5.5	0.226	1.4850	0.5678	-6.8	0.296	1.4603	0.2159	-9.7
0.158	1.5698	2.6510	5.0	0.228	1.4839	0.5492	-7.0	0.298	1.4599	0.2110	-9.7
0.160	1.5646	2.4834	4.2	0.230	1.4828	0.5314	-7.1	0.300	1.4595	0.2062	-9.7
0.162	1.5598	2.3339	3.4	0.232	1.4818	0.5144	-7.2	0.305	1.4585	0.1950	-9.8
0.164	1.5553	2.2038	2.7	0.234	1.4808	0.4982	-7.4	0.310	1.4575	0.1845	-9.9
0.166	1.5510	2.0738	2.1	0.236	1.4798	0.4827	-7.5	0.315	1.4566	0.1749	-10.0
0.168	1.5469	1.9637	1.5	0.238	1.4788	0.4678	-7.6	0.320	1.4558	0.1659	-10.1
0.170	1.5431	1.8576	0.9	0.240	1.4779	0.4536	-7.7	0.325	1.4549	0.1575	-10.2
0.172	1.5395	1.7595	0.4	0.242	1.4770	0.4400	-7.8	0.330	1.4542	0.1497	-10.3
0.174	1.5361	1.6637	-0.1	0.244	1.4762	0.4269	-7.9	0.335	1.4534	0.1424	-10.4
0.176	1.5328	1.5844	-0.6	0.246	1.4753	0.4144	-8.0	0.340	1.4528	0.1356	-10.4
0.178	1.5297	1.5051	-1.0	0.248	1.4745	0.4023	-8.1	0.345	1.4521	0.1292	-10.5
0.180	1.5268	1.4332	-1.4	0.250	1.4737	0.3908	-8.2	0.350	1.4515	0.1233	-10.5
0.182	1.5240	1.3652	-1.8	0.252	1.4729	0.3797	-8.3	0.355	1.4509	0.1177	-10.6
0.184	1.5213	1.3017	-2.2	0.254	1.4722	0.3690	-8.3	0.360	1.4503	0.1124	-10.7
0.186	1.5188	1.2424	-2.6	0.256	1.4715	0.3588	-8.4	0.365	1.4497	0.1075	-10.8
0.188	1.5164	1.1858	-2.9	0.258	1.4708	0.3489	-8.5	0.370	1.4492	0.1028	-10.8
0.190	1.5140	1.1346	-3.1	0.260	1.4701	0.3394	-8.6	0.375	1.4487	0.0985	-10.9
0.192	1.5118	1.0857	-3.4	0.262	1.4694	0.3303	-8.7	0.380	1.4482	0.0944	-10.9
0.194	1.5097	1.0397	-3.7	0.264	1.4687	0.3215	-8.7	0.385	1.4478	0.0905	-11.0
0.196	1.5077	0.9954	-4.0	0.266	1.4681	0.3130	-8.8	0.390	1.4473	0.0868	-11.0
0.198	1.5057	0.9557	-4.3	0.268	1.4675	0.3048	-8.9	0.395	1.4469	0.0833	-11.0
0.200	1.5038	0.9172	-4.5	0.270	1.4669	0.2969	-8.9	0.400	1.4465	0.0800	-11.1
0.202	1.5020	0.8809	-4.7	0.272	1.4663	0.2893	-9.0	0.410	1.4457	0.0740	-11.1
0.204	1.5003	0.8496	-5.0	0.274	1.4657	0.2820	-9.1	0.420	1.4450	0.0685	-11.1
0.206	1.4986	0.8141	-5.2	0.276	1.4652	0.2749	-9.1	0.430	1.4443	0.0636	-11.3
0.208	1.4970	0.7834	-5.4	0.278	1.4646	0.2681	-9.2	0.440	1.4437	0.0592	-11.4
0.210	1.4955	0.7542	-5.6	0.280	1.4641	0.2615	-9.2	0.450	1.4432	0.0552	-11.4
0.212	1.4940	0.7256	-5.9	0.282	1.4636	0.2551	-9.3	0.460	1.4426	0.0515	-11.5
0.214	1.4926	0.7004	-6.1	0.284	1.4631	0.2489	-9.3	0.470	1.4421	0.0482	-11.5
0.216	1.4912	0.6755	-6.1	0.286	1.4626	0.2430	-9.4	0.480	1.4417	0.0451	-11.6
0.218	1.4899	0.6518	-6.3	0.288	1.4621	0.2372	-9.5	0.490	1.4412	0.0424	-11.6

TABLE 18. RECOMMENDED VALUES ON THE REFRACTIVE INDEX AND ITS WAVELENGTH AND TEMPERATURE DERIVATIVES FOR STRONTIUM FLUORIDE AT 293K (CONTINUED)*

λ μm	n	$-\frac{dn}{d\lambda}$ μm^{-1}	$\frac{dn}{dT}$ 10^{-6} K^{-1}	λ μm	n	$-\frac{dn}{d\lambda}$ μm^{-1}	$\frac{dn}{dT}$ 10^{-6} K^{-1}	λ μm	n	$-\frac{dn}{d\lambda}$ μm^{-1}	$\frac{dn}{dT}$ 10^{-6} K^{-1}
0.500	1.4408	0.0398	-11.6	1.250	1.4318	0.0042	-12.4	3.000	1.4250	0.0047	-12.5
0.510	1.4404	0.0375	-11.7	1.300	1.4316	0.0040	-12.4	3.050	1.4248	0.0047	-12.5
0.520	1.4401	0.0353	-11.7	1.350	1.4314	0.0038	-12.4	3.100	1.4246	0.0048	-12.5
0.530	1.4397	0.0333	-11.7	1.400	1.4312	0.0037	-12.4	3.150	1.4243	0.0049	-12.5
0.540	1.4394	0.0315	-11.8	1.450	1.4311	0.0036	-12.4	3.200	1.4241	0.0049	-12.5
0.550	1.4391	0.0298	-11.8	1.500	1.4309	0.0036	-12.4	3.250	1.4238	0.0050	-12.5
0.560	1.4388	0.0282	-11.8	1.550	1.4307	0.0035	-12.4	3.300	1.4236	0.0051	-12.5
0.570	1.4385	0.0268	-11.9	1.600	1.4305	0.0035	-12.5	3.350	1.4233	0.0052	-12.5
0.580	1.4382	0.0254	-11.9	1.650	1.4304	0.0034	-12.5	3.400	1.4231	0.0052	-12.5
0.590	1.4380	0.0242	-11.9	1.700	1.4302	0.0034	-12.5	3.450	1.4228	0.0053	-12.5
0.600	1.4378	0.0230	-11.9	1.750	1.4300	0.0034	-12.5	3.500	1.4225	0.0054	-12.5
0.620	1.4373	0.0209	-12.0	1.800	1.4298	0.0034	-12.5	3.550	1.4222	0.0055	-12.5
0.640	1.4369	0.0191	-12.0	1.850	1.4297	0.0034	-12.5	3.600	1.4220	0.0055	-12.5
0.660	1.4366	0.0175	-12.0	1.900	1.4295	0.0035	-12.5	3.650	1.4217	0.0056	-12.5
0.680	1.4362	0.0160	-12.1	1.950	1.4293	0.0035	-12.5	3.700	1.4214	0.0057	-12.5
0.700	1.4359	0.0148	-12.1	2.000	1.4291	0.0035	-12.5	3.750	1.4211	0.0058	-12.5
0.720	1.4356	0.0137	-12.1	2.050	1.4289	0.0036	-12.5	3.800	1.4208	0.0058	-12.5
0.740	1.4354	0.0127	-12.1	2.100	1.4288	0.0036	-12.5	3.850	1.4205	0.0059	-12.5
0.760	1.4351	0.0118	-12.1	2.150	1.4286	0.0036	-12.5	3.900	1.4202	0.0060	-12.5
0.780	1.4349	0.0110	-12.2	2.200	1.4284	0.0037	-12.5	3.950	1.4199	0.0061	-12.5
0.800	1.4347	0.0103	-12.2	2.250	1.4282	0.0037	-12.5	4.000	1.4196	0.0061	-12.5
0.820	1.4345	0.0097	-12.2	2.300	1.4280	0.0038	-12.5	4.050	1.4193	0.0062	-12.5
0.840	1.4343	0.0091	-12.2	2.350	1.4278	0.0038	-12.5	4.100	1.4190	0.0063	-12.5
0.860	1.4341	0.0086	-12.2	2.400	1.4276	0.0039	-12.5	4.150	1.4187	0.0064	-12.5
0.880	1.4339	0.0081	-12.2	2.450	1.4274	0.0039	-12.5	4.200	1.4183	0.0065	-12.5
0.900	1.4338	0.0077	-12.3	2.500	1.4272	0.0040	-12.5	4.250	1.4180	0.0065	-12.5
0.920	1.4336	0.0073	-12.3	2.550	1.4270	0.0041	-12.5	4.300	1.4177	0.0066	-12.5
0.940	1.4335	0.0070	-12.3	2.600	1.4268	0.0041	-12.5	4.350	1.4174	0.0067	-12.5
0.960	1.4334	0.0066	-12.3	2.650	1.4266	0.0042	-12.5	4.400	1.4170	0.0068	-12.4
0.980	1.4332	0.0064	-12.3	2.700	1.4264	0.0043	-12.5	4.450	1.4167	0.0069	-12.4
1.000	1.4331	0.0061	-12.3	2.750	1.4262	0.0043	-12.5	4.500	1.4163	0.0069	-12.4
1.050	1.4328	0.0055	-12.4	2.800	1.4260	0.0044	-12.5	4.550	1.4160	0.0070	-12.4
1.100	1.4325	0.0051	-12.4	2.850	1.4257	0.0045	-12.5	4.600	1.4156	0.0071	-12.4
1.150	1.4323	0.0047	-12.4	2.900	1.4255	0.0045	-12.5	4.650	1.4153	0.0072	-12.4
1.200	1.4321	0.0044	-12.4	2.950	1.4253	0.0046	-12.5	4.700	1.4149	0.0073	-12.4

TABLE 18. RECOMMENDED VALUES ON THE REFRACTIVE INDEX AND ITS WAVELENGTH AND TEMPERATURE DERIVATIVES FOR STRONTIUM FLUORIDE AT 293K (CONTINUED)*

λ μm	n	$-\frac{dn}{d\lambda}$ μm^{-1}	$\frac{dn}{dT}$ 10^{-6}K^{-1}	λ μm	n	$-\frac{dn}{d\lambda}$ μm^{-1}	$\frac{dn}{dT}$ 10^{-6}K^{-1}	λ μm	n	$-\frac{dn}{d\lambda}$ μm^{-1}	$\frac{dn}{dT}$ 10^{-6}K^{-1}
4.750	1.4145	0.0073	-12.4	7.100	1.3924	0.0115	-12.0	9.700	1.3552	0.0172	-10.7
4.800	1.4142	0.0074	-12.4	7.200	1.3912	0.0117	-12.0	9.800	1.3535	0.0174	-10.7
4.850	1.4138	0.0075	-12.4	7.300	1.3900	0.0119	-12.0	9.900	1.3518	0.0177	-10.6
4.900	1.4134	0.0076	-12.4	7.400	1.3888	0.0121	-11.9	10.000	1.3500	0.0179	-10.5
4.950	1.4130	0.0077	-12.4	7.500	1.3876	0.0123	-11.9	10.200	1.3463	0.0184	-10.3
5.000	1.4126	0.0078	-12.4	7.600	1.3863	0.0125	-11.9	10.400	1.3426	0.0189	-10.1
5.100	1.4118	0.0079	-12.4	7.700	1.3851	0.0127	-11.8	10.600	1.3387	0.0195	-9.9
5.200	1.4110	0.0081	-12.4	7.800	1.3838	0.0129	-11.8	10.800	1.3348	0.0200	-9.7
5.300	1.4102	0.0083	-12.4	7.900	1.3825	0.0131	-11.8	11.000	1.3307	0.0206	-9.5
5.400	1.4094	0.0084	-12.4	8.000	1.3811	0.0133	-11.7	11.200	1.3265	0.0212	-9.2
5.500	1.4085	0.0086	-12.3	8.100	1.3798	0.0135	-11.7	11.400	1.3222	0.0217	-9.0
5.600	1.4076	0.0088	-12.3	8.200	1.3784	0.0138	-11.6	11.600	1.3178	0.0223	-8.7
5.700	1.4067	0.0090	-12.3	8.300	1.3770	0.0140	-11.6	11.800	1.3133	0.0230	-8.4
5.800	1.4058	0.0091	-12.3	8.400	1.3756	0.0142	-11.5	12.000	1.3086	0.0236	-8.1
5.900	1.4049	0.0093	-12.3	8.500	1.3742	0.0144	-11.5	12.200	1.3038	0.0243	-7.7
6.000	1.4040	0.0095	-12.3	8.600	1.3727	0.0146	-11.4	12.400	1.2989	0.0249	-7.4
6.100	1.4030	0.0097	-12.3	8.700	1.3713	0.0148	-11.4	12.600	1.2938	0.0256	-7.0
6.200	1.4020	0.0099	-12.3	8.800	1.3698	0.0151	-11.3	12.800	1.2886	0.0264	-6.6
6.300	1.4010	0.0100	-12.3	8.900	1.3682	0.0153	-11.3	13.000	1.2832	0.0271	-6.1
6.400	1.4000	0.0102	-12.2	9.000	1.3667	0.0155	-11.2	13.200	1.2777	0.0279	-5.7
6.500	1.3990	0.0104	-12.2	9.100	1.3651	0.0157	-11.2	13.400	1.2721	0.0286	-5.2
6.600	1.3979	0.0106	-12.2	9.200	1.3635	0.0160	-11.1	13.600	1.2663	0.0295	-4.6
6.700	1.3968	0.0108	-12.1	9.300	1.3619	0.0162	-11.0	13.800	1.2603	0.0303	-4.1
6.800	1.3957	0.0110	-12.1	9.400	1.3603	0.0164	-11.0	14.000	1.2541	0.0312	-3.5
6.900	1.3946	0.0111	-12.1	9.500	1.3586	0.0167	-10.9				

* IN THIS TABLE MORE DECIMAL PLACES ARE REPORTED THAN WARRANTED MERELY FOR THE PURPOSE OF TABULAR SMOOTHNESS AND INTERNAL COMPARISON. FOR UNCERTAINTIES OF TABULATED VALUES IN VARIOUS WAVELENGTH RANGES, SEE THE TEXT OF SUBSECTION 3.2. THE NUMBER OF DIGITS WITH AN OVERSTRIKE IS NOT RELAVENT TO THE ACCURACY OF THE VALUES.

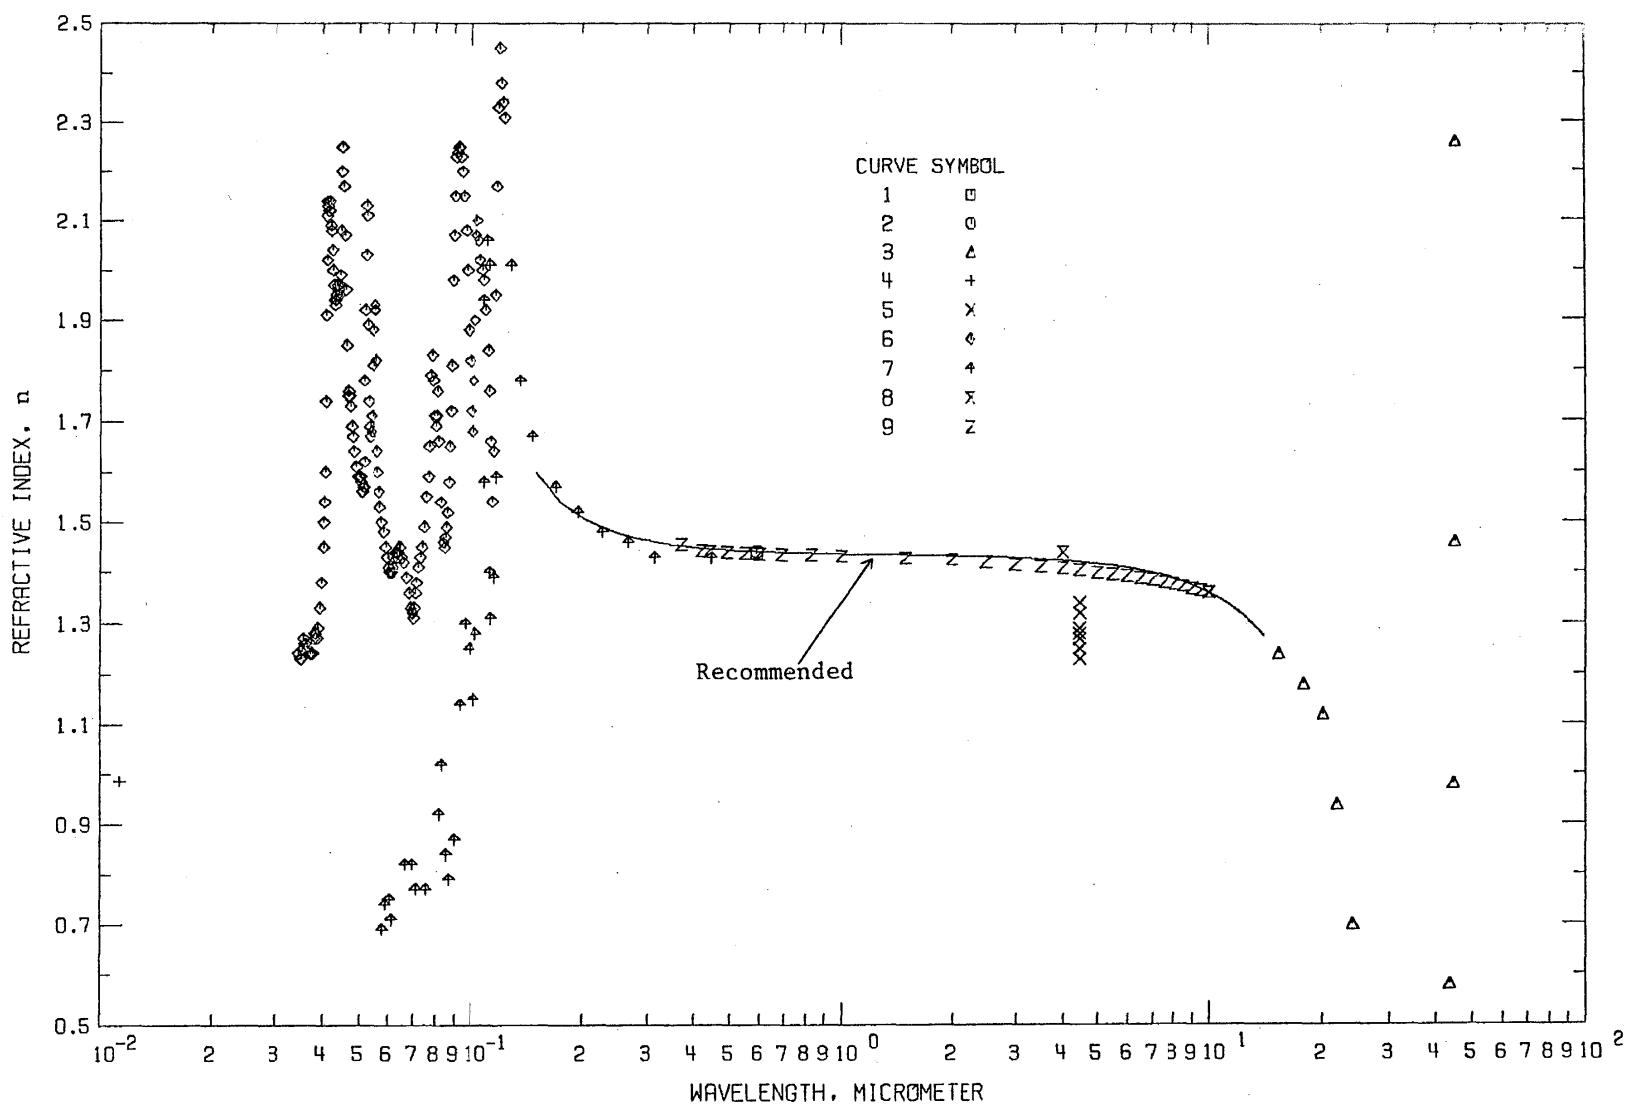


FIGURE 12. REFRACTIVE INDEX OF STRONTIUM FLUORIDE (WAVELENGTH DEPENDENCE).

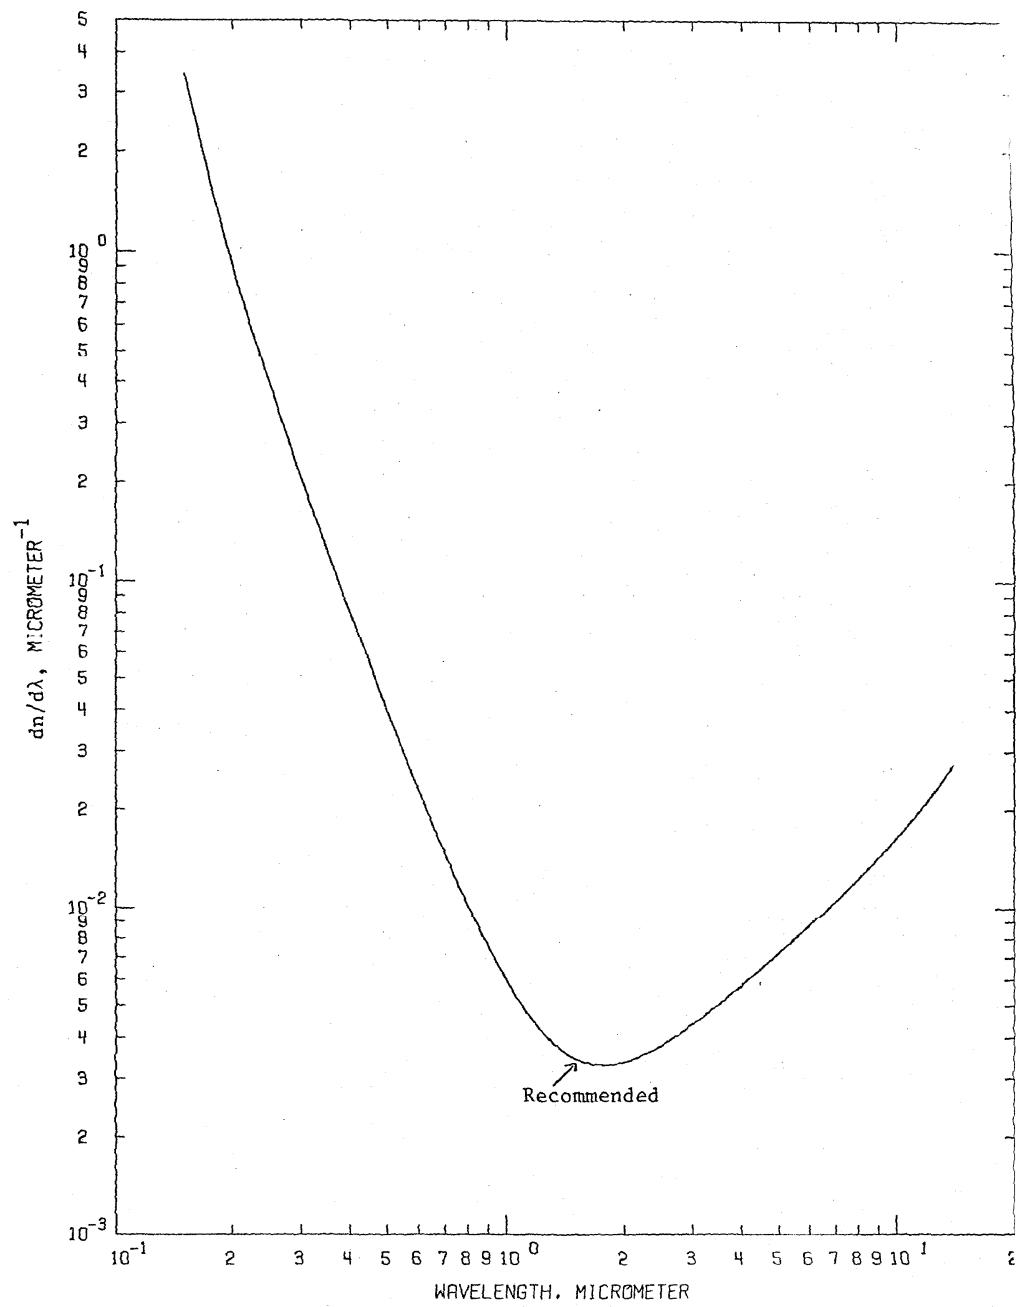


FIGURE 13. WAVELENGTH DERIVATIVE OF REFRACTIVE INDEX OF STRONTIUM FLUORIDE

TABLE 19. MEASUREMENT INFORMATION ON THE REFRACTIVE INDEX OF STRONTIUM FLUORIDE (WAVELENGTH DEPENDENCE)

DATA SET NO.	REF. NO.	AUTHOR(S)	YEAR	METHOD USED	WAVELENGTH RANGE, μm	TEMP. K	SPECIFICATIONS AND REMARKS
1	61	THILO, F.	1927	M	0.589	293	SINGLE CRYSTAL; REFRACTIVE INDEX DETERMINED BY IMMERSION METHOD FOR THE MEAN OF SODIUM D LINES; DATA EXTRACTED FROM A TABLE; TEMPERATURE NOT GIVEN, 293K ASSUMED.
2	62	HULFF, P. HEIGL, A.	1931	M	0.589	298	CRYSTAL OF UNSPECIFIED TYPE; CRYSTAL SIZE NOT LARGE ENOUGH FOR INTERFEROMETRIC MEASUREMENT; REFRACTIVE INDEX DETERMINED BY IMMERSION METHOD FOR THE MEAN OF SODIUM D LINES; DATA EXTRACTED FROM A TABLE; UNCERTAINTY OF INDEX 0.001.
3	94	SMAKULA, A.	1962	D	0.40-0.77	288	REFRACTIVE INDEX VALUES DETERMINED AT NBS BY MALITSON REPORTED IN OSRD REPORT NO. 4690, 1944; THIS DATA SET WAS PUBLISHED BY SMAKULA IN 1962.
4	94	SMAKULA, A.	1962	D	0.40-0.77	308	SIMILAR TO ABOV.
5	94	SMAKULA, A.	1962	D	0.40-0.77	328	SIMILAR TO ABOV.
6	17	KAISER, W. SPITZER, W.G. KAISER, R.H. HOWARTH, L.E.	1962	R	10.0-80.0	300	SINGLE CRYSTAL; PLATE SPECIMEN; 0.1-5.0MM THICK; HIGHLY POLISHED SURFACES; NEAR NORMAL INCIDENT REFLECTION SPECTRUM OBTAINED; REFRACTIVE INDEX DEDUCED FROM REFLECTION SPECTRUM WITH LORENTZ THEORY; DATA EXTRACTED FROM A SMOOTH CURVE; LORENTZ DAMPED-OSCILLATOR DISPERSION EQUATION ALSO GIVEN.
7	63	LUKIRSKII, A.P. SAVINOV, E.P. ERSHOV, O.A. SHEPELEV, YU.F.	1964	R	0.002-0.12	298	THIN FILM SPECIMEN OF STRONTIUM FLUORIDE ON GOLD OR ALUMINIUM SUBSTRATE; REFRACTIVE INDEX DEDUCED FROM REFLECTION SPECTRUM WITH FRESNEL FORMULAE; DATA EXTRACTED FROM A TABLE.
8	64	GISIN, M.A.	1969	I	4.5	298	THIN FILM SPECIMEN OF THICKNESS FROM 0.8 TO 7.4 MICROMETER ON SILICON OR GERMANIUM SUBSTRATE; REFRACTIVE INDEX DETERMINED BY INTERFERENCE METHOD FOR THE SPECTRAL LINE 4.5 MICROMETERS; DATA EXTRACTED FROM A TABLE.
9	25	NISAR, M. ROBIN, S.	1974	R	0.03-0.124	293	SINGLE CRYSTAL; OBTAINED FROM THE HARSHAW CHEMICAL CO.; SPECIMEN CLEAVED IN VACUUM; 20 DEGREE INCIDENT REFLECTION SPECTRUM OBTAINED; REFRACTIVE INDEX DEDUCED FROM REFLECTION SPECTRUM WITH KRAMERS-KRONIG RELATION; DATA EXTRACTED FROM A FIGURE; TEMPERATURE NOT GIVEN, 293K ASSUMED.
10	53	GANIN, U. SIDORIN, U. KARIN, M. SIDORIN, K. STAROSTIN, N., STARTSEV, G.	1975	R	0.06-0.25	300	SINGLE CRYSTAL; FRESHLY CLEAVED SPECIMEN; NEAR NORMAL REFLECTION SPECTRUM OBTAINED; REFRACTIVE INDEX DEDUCED FROM REFLECTION SPECTRUM WITH KRAMERS-KRONIG RELATION; DATA EXTRACTED FROM A FIGURE.

REFRACTIVE INDEX OF STRONTIUM FLUORIDE (WAVELENGTH DEPENDENCE) (CONTINUED)

WAVELENGTH RANGE, μm	TEMP. K	SPECIFICATIONS AND REMARKS
4.0,10.0	293	THE DATA ARE FOR HARSHAW GROWN CRYSTAL COMPILED BY THE AUTHOR; NO DETAILS ABOUT HOW THE DATA WERE OBTAINED WAS GIVEN; TEMPERATURE NOT GIVEN, 293K ASSUMED; DATA EXTRACTED FROM A TABLE.
0.37-10.0	293	THIS DATA SET IS THE PRELIMINARY DATA BY OPTOVAC, INC. COMPILED BY THE AUTHOR; NO DETAILS OF THE MEASUREMENT INFORMATION WAS GIVEN; TEMPERATURE NOT GIVEN, 293K ASSUMED; DATA EXTRACTED FROM A SMOOTH CURVE.

TABLE 20. EXPERIMENTAL REFRACTIVE INDEX OF STRONTIUM FLUORIDE (WAVELENGTH DEPENDENCE)
[WAVELENGTH, λ , μm ; TEMPERATURE, T , K; REFRACTIVE INDEX, n]

λ	n	λ	n	λ	n	λ	n	λ	n	λ	n						
DATA SET 1																	
	$T = 293.0$																
0.589	1.438	0.5460	1.438771	46.9	10.82	4.5	1.23	0.0421	2.08	0.0512	1.62						
		0.5862	1.437606	47.1	10.10			0.0423	2.04	0.0514	1.78						
		0.6562	1.436226	47.3	9.41	DATA SET 9											
DATA SET 2																	
	$T = 298.0$	0.6678	1.436031	47.4	8.65	$T = 293.0$		0.0424	2.00	0.0516	1.92						
		0.7065	1.435431	47.6	7.89			0.0426	1.97	0.0518	2.03						
		0.7678	1.434652	48.0	7.11	0.0345	1.24	0.0429	1.94	0.0521	2.13						
0.589	1.442			48.6	6.46	0.0348	1.23	0.0430	1.93	0.0523	2.11						
DATA SET 3																	
	$T = 300.0$			49.3	5.84	0.0351	1.23	0.0432	1.94	0.0525	1.89						
DATA SET 4																	
	$T = 288.0$			50.0	5.42	0.0354	1.25	0.0433	1.95	0.0527	1.74						
				50.9	4.97	0.0356	1.27	0.0435	1.97	0.0529	1.69						
		15.3	1.24	52.3	4.57	0.0358	1.26	0.0438	1.96	0.0532	1.67						
0.4046	1.446085	17.9	1.18	53.7	4.24	0.0361	1.26	0.0439	1.95	0.0536	1.68						
0.4358	1.443964	20.1	1.12	55.5	3.93	0.0364	1.25	0.0442	1.97	0.0539	1.71						
0.4861	1.441402	22.0	0.94	57.4	3.67	0.0369	1.24	0.0444	1.99	0.0541	1.81						
0.5460	1.439245	24.1	0.70	59.9	3.47	0.0372	1.24	0.0446	2.08	0.0543	1.88						
0.5862	1.438082	26.1	0.37	62.9	3.31	0.0374	1.24	0.0449	2.20	0.0546	1.92						
0.6562	1.436703	27.6	0.16	65.3	3.15	0.0376	1.24	0.0450	2.25	0.0551	1.92						
0.6678	1.436508	30.0	0.16	70.0	3.05	0.0379	1.27	0.0452	2.25	0.0553	1.82						
0.7065	1.435316	33.8	0.16	73.8	2.95	0.0381	1.28	0.0454	2.17	0.0556	1.64						
0.7678	1.435136	37.6	0.16	76.7	2.89	0.0383	1.28	0.0457	2.07	0.0558	1.60						
				40.0	0.21	80.0	2.86	0.0385	1.27	0.0459	1.96						
DATA SET 5																	
	$T = 308.0$	41.8	0.33			0.0386	1.27	0.0462	1.85	0.0568	1.53						
		43.6	0.58	DATA SET 7													
		44.6	0.98		$T = 298.0$	0.0388	1.29	0.0464	1.75	0.0574	1.50						
0.4046	1.445857	45.0	1.46			0.0392	1.33	0.0466	1.75	0.0582	1.48						
0.4358	1.443742	45.3	2.26	0.00236	0.9991	0.0400	1.45	0.0469	1.75	0.0590	1.45						
0.4861	1.441172	45.4	2.99	0.00314	0.9989	0.0401	1.50	0.0471	1.73	0.0601	1.41						
0.5460	1.439008	45.4	3.70	0.0044	0.9987	0.0403	1.54	0.0475	1.69	0.0604	1.40						
0.5862	1.437848	45.6	4.48	0.0067	0.99666	0.0405	1.60	0.0478	1.67	0.0607	1.40						
0.6562	1.436470	45.6	5.20	0.0113	0.9869	0.0406	1.74	0.0482	1.64	0.0613	1.40						
0.6678	1.436268	45.8	6.01			0.0407	1.91	0.0488	1.61	0.0616	1.41						
0.7065	1.435672	45.8	6.67	DATA SET 8													
0.7678	1.434898	45.9	7.57		$T = 298.0$	0.0409	2.02	0.0494	1.59	0.0620	1.43						
			8.51			0.0410	2.11	0.0496	1.59	0.0626	1.44						
DATA SET 5																	
	$T = 328.0$	46.0	9.30	4.5	1.34	0.0413	2.13	0.0500	1.59	0.0632	1.43						
		46.0	10.07	4.5	1.32	0.0414	2.12	0.0502	1.58	0.0635	1.44						
		46.0	10.85	4.5	1.29	0.0416	2.12	0.0504	1.56	0.0642	1.45						
0.4046	1.445632	46.2	11.59	4.5	1.28	0.0417	2.14	0.0506	1.56	0.0645	1.45						
0.4358	1.443505	46.5	12.30	4.5	1.27	0.0418	2.14	0.0508	1.57	0.0652	1.43						
0.4861	1.440932	46.7	11.59	4.5	1.25	0.0420	2.09	0.0510	1.57	0.0659	1.42						

TABLE 20. EXPERIMENTAL REFRACTIVE INDEX OF STRONTIUM FLUORIDE (WAVELENGTH DEPENDENCE) (CONTINUED)
 [WAVELENGTH, λ , μm ; TEMPERATURE, T, K; REFRACTIVE INDEX, n]

λ	n	λ	n	λ	n	λ	n
DATA SET 9(CONT.)		DATA SET 9(CONT.)		DATA SET 10(CONT.)		DATA SET 12 T = 293.0	
0.0670	1.39	0.0939	2.23	0.0710	0.77	0.37	1.455
0.0681	1.36	0.0946	2.20	0.0754	0.77	0.42	1.444
0.0688	1.33	0.0953	2.15	0.0816	0.92	0.44	1.442
0.0696	1.32	0.0968	2.08	0.0831	1.02	0.49	1.440
0.0700	1.31	0.0976	2.00	0.0857	0.84	0.55	1.438
0.0704	1.33	0.0984	1.88	0.0870	0.79	0.60	1.437
0.0708	1.36	0.0992	1.82	0.0899	0.87	0.69	1.435
0.0712	1.38	0.1000	1.72	0.0933	1.14	0.83	1.434
0.0720	1.41	0.1008	1.68	0.0961	1.30	1.00	1.432
0.0729	1.43	0.1016	1.78	0.0988	1.25	1.50	1.429
0.0738	1.45	0.1024	1.90	0.1014	1.15	2.00	1.425
0.0746	1.49	0.1033	2.07	0.1030	1.28	2.50	1.421
0.0756	1.55	0.1042	2.10	0.1088	1.58	3.00	1.416
0.0765	1.59	0.1050	2.06	0.1088	1.94	3.50	1.412
0.0770	1.65	0.1059	2.02	0.1110	2.06	4.00	1.409
0.0779	1.79	0.1078	2.00	0.1128	2.01	4.50	1.406
0.0784	1.83	0.1087	1.98	0.1128	1.40	5.00	1.400
0.0789	1.78	0.1097	1.92	0.1135	1.31	5.50	1.397
0.0794	1.71	0.1117	1.84	0.1157	1.39	6.00	1.393
0.0800	1.69	0.1127	1.76	0.1172	1.59	6.50	1.389
0.0805	1.71	0.1137	1.66	0.1172	2.66	7.00	1.386
0.0810	1.76	0.1148	1.54	0.1184	2.70	7.50	1.381
0.0815	1.66	0.1158	1.64	0.1209	2.66	8.00	1.377
0.0826	1.54	0.1169	1.95	0.1288	2.01	8.50	1.373
0.0837	1.46	0.1180	2.17	0.1364	1.78	9.00	1.369
0.0843	1.45	0.1192	2.33	0.1470	1.67	9.50	1.365
0.0849	1.47	0.1203	2.45	0.1691	1.57	10.00	1.362
0.0855	1.49	0.1215	2.38	0.1943	1.52		
0.0861	1.52	0.1227	2.34	0.2254	1.48		
0.0867	1.58	0.1240	2.31	0.2655	1.46		
0.0873	1.65			0.3139	1.43		
0.0879	1.72	DATA SET 10 T = 300.0		0.4460	1.43		
0.0885	1.81						
0.0892	1.98			DATA SET 11 T = 293.0			
0.0898	2.07	0.0580	0.69				
0.0905	2.15	0.0591	0.74				
0.0911	2.23	0.0607	0.75	4.0	1.44		
0.0918	2.24	0.0614	0.71	10.0	1.36		
0.0925	2.25	0.0668	0.82				
0.0932	2.25	0.0695	0.82				

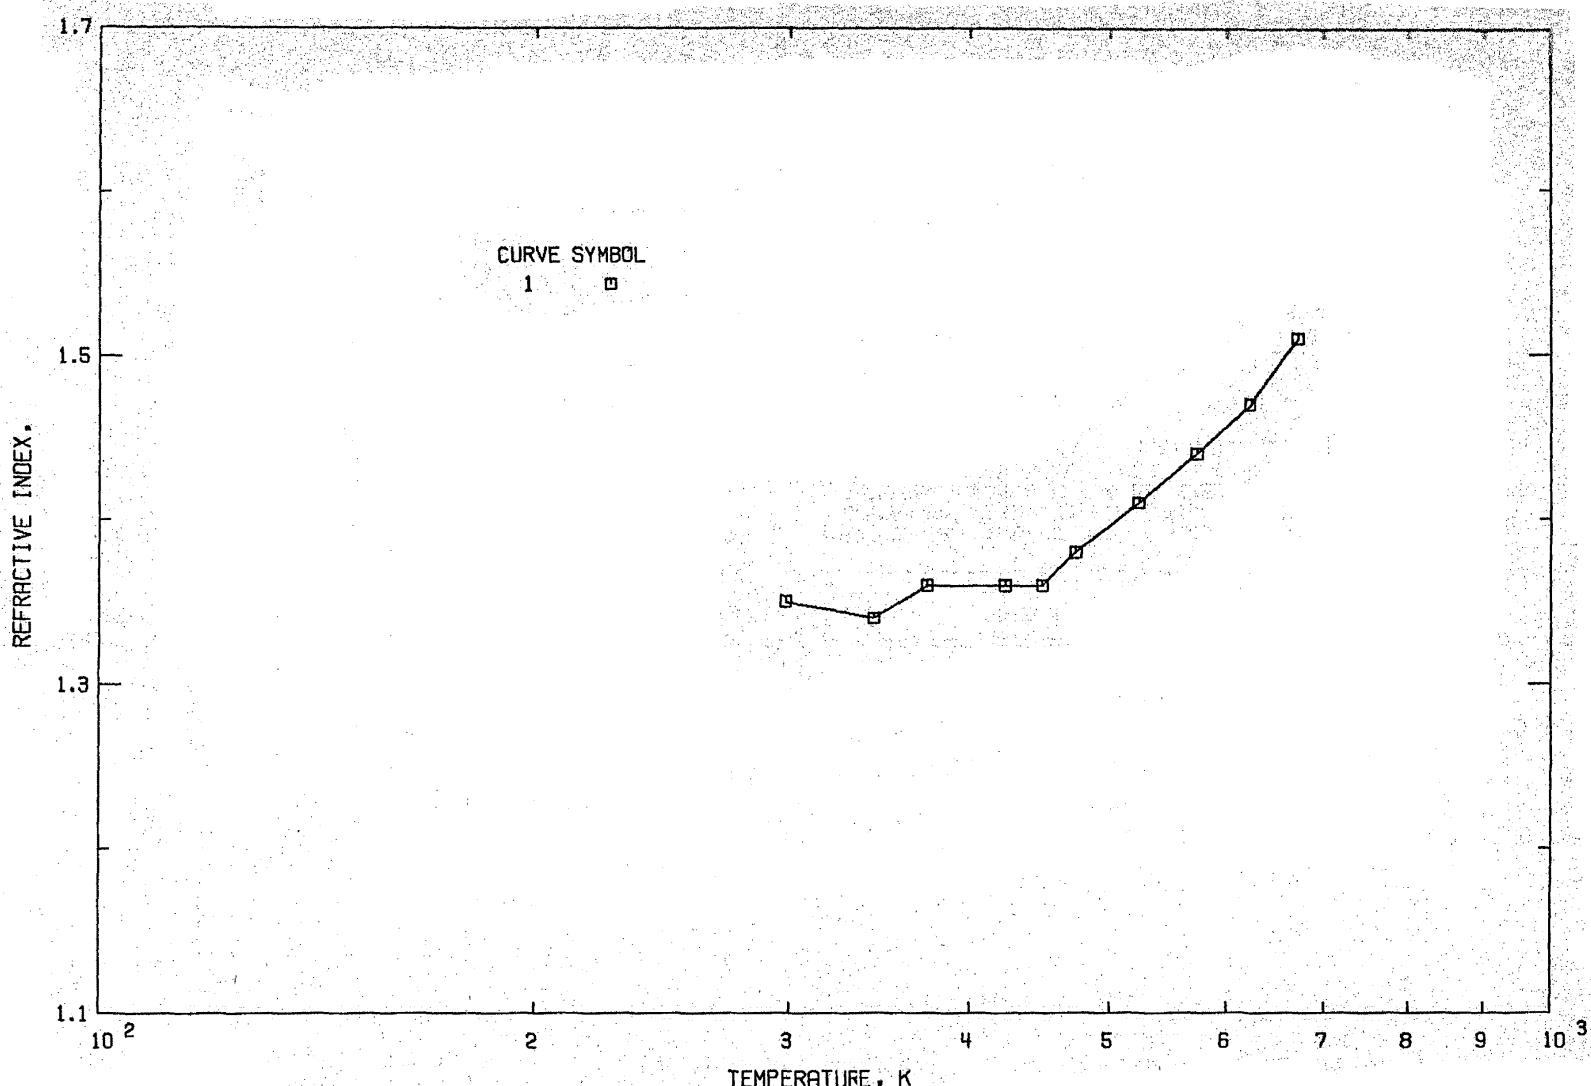


FIGURE 14. REFRACTIVE INDEX OF STRONTIUM FLUORIDE (TEMPERATURE DEPENDENCE).

TABLE 21. MEASUREMENT INFORMATION ON THE REFRACTIVE INDEX OF STRONTIUM FLUORIDE (TEMPERATURE DEPENDENCE)

DATA SET NO.	REF. NO.	AUTHOR(S)	YEAR	METHOD USED	WAVELENGTH RANGE, μm	TEMP. K	SPECIFICATIONS AND REMARKS
1	64	GISIN, M.A.	1969	I	4.5	298-673	THIN FILM SPECIMEN OF 0.7 TO 0.86 MICROMETER ON SILICON OR GERMANIUM SUBSTRATE; REFRACTIVE INDEX DETERMINED BY INTERFERENCE METHOD FOR THE SPECTRAL LINE 4.5 MICROMETERS; DATA EXTRACTED FROM A TABLE.

H. H. LI

TABLE 22. EXPERIMENTAL REFRACTIVE INDEX OF STRONTIUM FLUORIDE (TEMPERATURE DEPENDENCE)
[WAVELENGTH, λ , μm ; TEMPERATURE, T, K; REFRACTIVE INDEX, n]

T	n
DATA SET 1	
$\lambda = 4.5$	
298.0	1.35
343.0	1.34
373.0	1.36
423.0	1.36
448.0	1.36
473.0	1.38
523.0	1.41
573.0	1.44
623.0	1.47
673.0	1.51

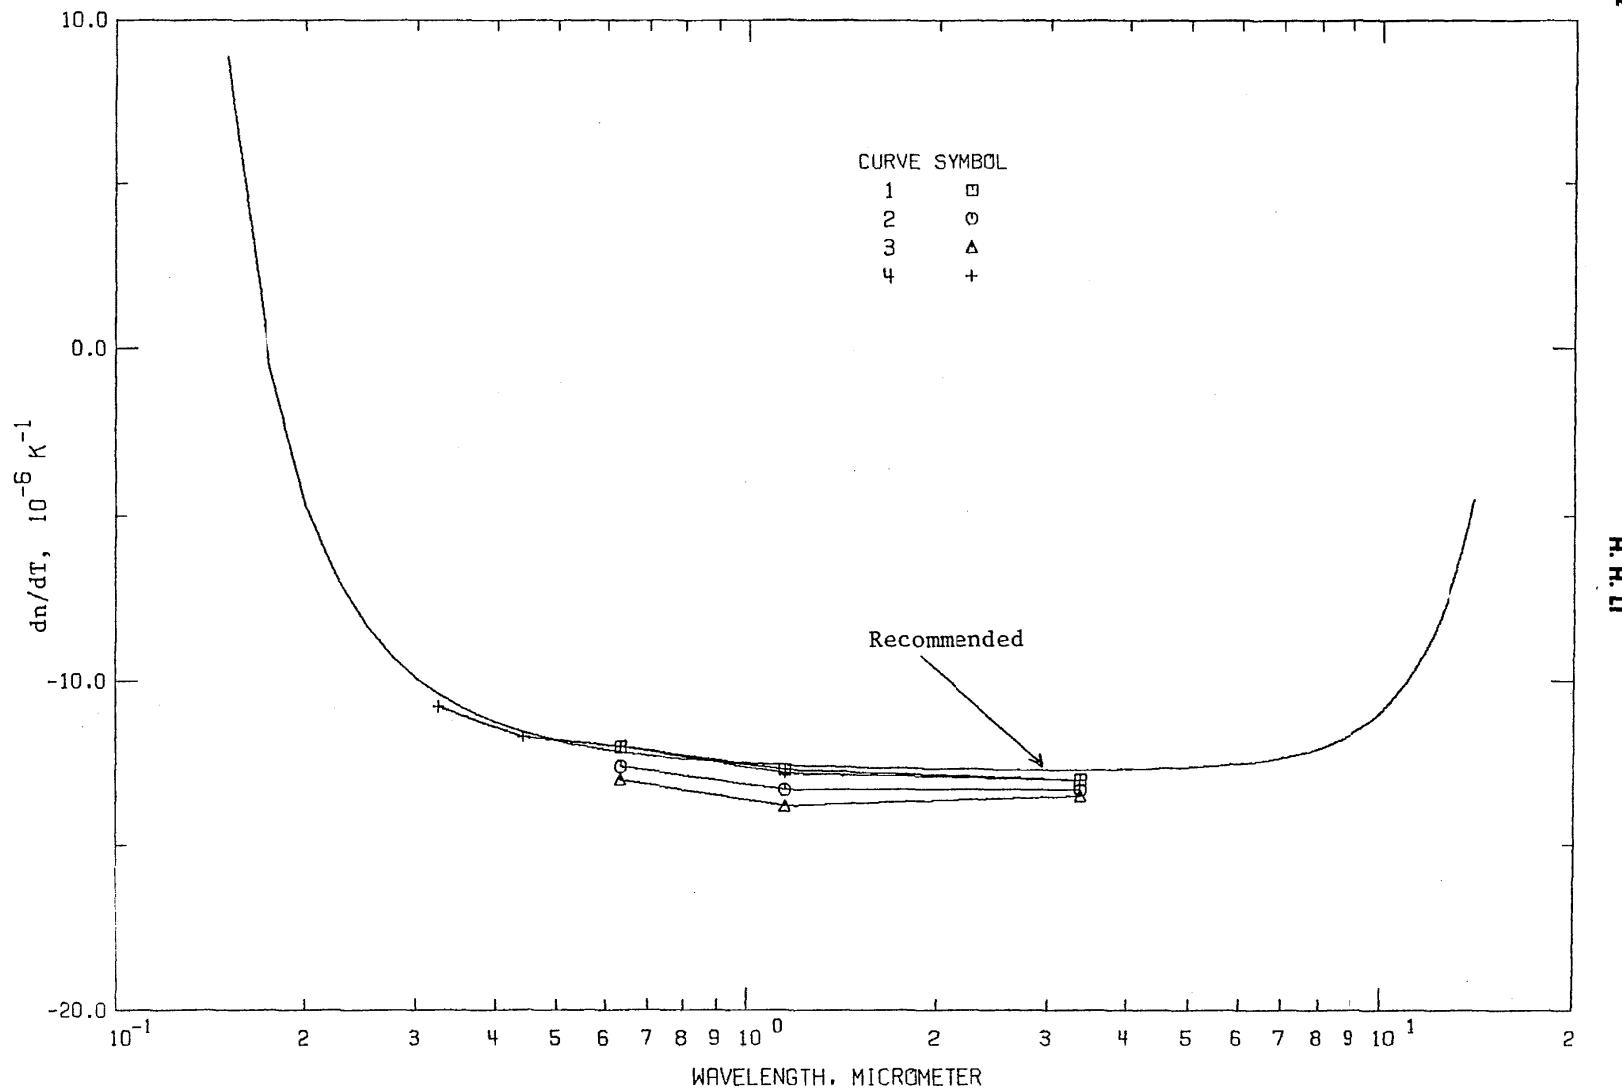


FIGURE 15. TEMPERATURE DERIVATIVE OF REFRACTIVE INDEX OF STRONTIUM FLUORIDE (WAVELENGTH DEPENDENCE)

TABLE 23. MEASUREMENT INFORMATION ON THE TEMPERATURE DERIVATIVE OF REFRACTIVE INDEX OF STRONTIUM FLUORIDE (WAVELENGTH DEPENDENCE)

DATA SET NO.	REF. NO.	AUTHOR(S)	YEAR	METHOD USED	WAVELENGTH RANGE, μm	TEMP. K	SPECIFICATIONS AND REMARKS
1	59	LIPSON, H.G. TSAY, Y.F. BENDOW, B LIGOR, P.A.	1976	I	0.63-3.39	310	SINGLE CRYSTAL; DISC SPECIMEN; 1.90CM DIAMETER, 1CM TO 2.50M THICK; DN/DT DETERMINED FOR 3 SPECTRAL LINES BY OBSERVING THE INTERFERENCE FRINGE CHANGES AND THE CORRESPONDING TEMPERATURE CHANGES; DATA EXTRACTED FROM A TABLE; UNCERTAINTY OF DN/DT ABOUT $0.6 \times 10^{-6} \text{K}^{-1}$.
2	59	LIPSON, H.G. ET AL.	1976	I	0.63-3.39	330	SIMILAR TO ABOVE BUT AT A HIGHER TEMPERATURE OF 330K; UNCERTAINTY OF DN/DT $0.6 \times 10^{-6} \text{K}^{-1}$.
3	59	LIPSON, H.G. ET AL.	1976	I	0.63-3.39	350	SIMILAR TO ABOVE BUT AT A HIGHER TEMPERATURE OF 350K; UNCERTAINTY OF DN/DT $0.5 \times 10^{-6} \text{K}^{-1}$.
4	92	TSAY, Y.F. LIPSON, H.G. LIGOR, P.A.	1977	I	0.32-3.39	310	SINGLE CRYSTAL; DISC SPECIMEN; 1.90CM DIAMETER, 1.27CM THICK; DN/DT DETERMINED BY OBSERVING THE INTERFERENCE FRINGE CHANGES AND THE CORRESPONDING TEMPERATURE CHANGES DATA EXTRACTED FROM A FIGURE; UNCERTAINTY OF DN/DT ABOUT $1.0 \times 10^{-6} \text{K}^{-1}$.

TABLE 24. EXPERIMENTAL TEMPERATURE DERIVATIVE OF REFRACTIVE INDEX OF STRONTIUM FLUORIDE (WAVELENGTH DEPENDENCE)
[WAVELENGTH, λ , μm ; TEMPERATURE, T , K; TEMPERATURE DERIVATIVE OF REFRACTIVE INDEX, dn/dT , 10^{-6}K^{-1}]

λ dn/dT

DATA SET 1
 $T = 310.0$

0.6328 -12.0
1.15 -12.7
3.39 -13.0

DATA SET 2
 $T = 330.0$

0.6328 -12.6
1.15 -13.3
3.39 -13.3

DATA SET 3
 $T = 350.0$

0.6328 -13.0
1.15 -13.8
3.39 -13.5

DATA SET 4
 $T = 310.0$

0.325 -10.8
0.4416 -11.7
0.6328 -12.0
1.15 -12.8
3.39 -13.0

H. H. LI

TABLE 25. COMPARISON OF DISPERSION EQUATIONS PROPOSED FOR SrF_2

Source	Wavelength and Temperature Ranges	Dispersion Equation λ in μm ; ν in cm^{-1}
Aliser, W., Pitzer, W.G., Aliser, R.H., and Owarz, L.E. 062	10-80 μm 293 K	$n^2 - k^2 = \epsilon_{\infty} + \sum_i 4\pi \rho_i \nu_i^2 \frac{\nu_i^2 - \nu^2}{(\nu_i^2 - \nu^2)^2 + \gamma_i^2 \nu_i^2}$ $2nk = \sum_i 4\pi \rho_i \nu_i^2 \frac{\gamma_i \nu \nu_i}{(\nu_i^2 - \nu^2)^2 + \gamma_i^2 \nu_i^2}$ *
Present work 1977	0.15-14.0 μm 293 K	$n^2 = 1.33973 + \frac{0.720 \lambda^2}{\lambda^2 - (0.09566)^2} + \frac{0.066 \lambda^2}{\lambda^2 - (26.03)^2} + \frac{3.94 \lambda^2}{\lambda^2 - (45.60)^2}$

* $i = 1, 2$; $4\pi \rho_1 = 4.00$, $4\pi \rho_2 = 0.07$; $\nu_1 = 217 \text{ cm}^{-1}$, $\nu_2 = 318 \text{ cm}^{-1}$; $\gamma_1 = 0.017$, $\gamma_2 = 0.25$.

3.3. Barium Fluoride, BaF₂

Barium fluoride is transparent in a wide spectral range from 0.14 up to 15 micrometers. The transmittance of a BaF₂ plate 2.3 mm thick increases rapidly from a sharp cutoff at 0.1345 micrometer to 85 percent at 0.4 micrometer and continues at that level to about 10 micrometers, after which it falls off rapidly. The observed transmittance at longer wavelengths varies with the thickness of the sample. For a plate 10 mm thick, the transmittance is 50 percent at 11.7 micrometers and 10 percent at 13.5 micrometers while 60 percent transmittance at 15 micrometers can be obtained for a 3.5 mm plate. Because of its uniform transparency in the spectral region 0.4 to 10 micrometers, barium fluoride is used for window and lens fabrication. As the laser technology advances, the need for optical material with high optical figure of merit and adequate mechanical properties is increasing. Barium fluoride, having the required advantages, is among the serious candidates for window materials for the spectral region between 2 to 6 micrometers.

Unlike calcium fluoride, which occurs naturally in large sizes and of optical quality, barium fluoride crystal for optical applications is synthesized. As a result, early investigations of optical properties did not include barium fluoride. The earliest measurements of the refractive index were probably made by Wulff [66] in 1928 and by Wulff and Heigl [62] in 1931, using the immersion method for the mean of the sodium D lines. The sample they used was in small fragments produced by chemical reaction.

Synthetic barium fluoride crystals of optical quality were successfully grown by Stockbarger during World War II. In the 1950's synthetic BaF₂ crystals became available commercially and found acceptance because of their favorable physical characteristics and broad transparent range. BaF₂ transmits further into the infrared than does either CaF₂ or LiF. However, until 1963, the refractive index data of BaF₂ were reported only by Houston et al. [47] for the spectral range 0.54 to 1.85 micrometers. Data on the refractive index over a wide spectral range were reported by Malitson [67] in 1964, for the region from 0.26 up to 10.4 micrometers, and have served as the reference data since then. As a matter of fact, Malitson's data are the only available set that cover most of the transparent region and is reliable enough to be the basis of data analysis.

Kaiser et al. [17] investigated the reflection spectrum of BaF₂ in the reststrahlen region from 10 to 80 micrometers. Refractive and absorption indices were deduced from the analysis of the reflection spectrum by Lorentz oscillator theory. The strong resonance at 54.3 micrometers was identified as the optically active TO resonance. A second resonance about one order of magnitude weaker than the main resonance is at 36 micrometers. The origin of the weaker absorption was unknown, and Kaiser proposed the possibility of a two-phonon combination band involving the TO mode. However, this weak absorption does not appear in Lowndes' work [15], in which the reflection spectrum was reduced by Kramers-Kronig analysis. Instead of the weak resonance at 36 micrometers, Lowndes obtained a weak absorption at 29.07 micrometers, which was identified as the longitudinal optical resonance, LO mode. Since Lowndes may have used a purer sample than that used by Kaiser, it is likely that the weak absorption at 36 micrometers is due to impurities in Kaiser's sample.

In the vacuum ultraviolet region, Fabre et al. [49] investigated the spectral region from 0.1 to 0.162 micrometers. Kramers-Kronig analysis of the reflection spectrum, and four strong absorption peak at 0.122 micrometer, the lower limit of the transparency of BaF₂. Nisar et al. [25] studied the reflection spectrum in the energy range 8–35 eV and disclosed the continuation of absorption beyond the lower transparent limit. Similar observations were carried out by Ganin et al. [53] and Ruland [24].

From the brief review of available data, it is clear that Malitson's data are the only choice for the basis of data analysis. The problem is to find appropriate input parameters for the dispersion equation. Malitson determined refractive indices for spectral lines, and the values were mathematically fitted to the Sellmeier dispersion equation as given in table 35, while dispersion equations proposed by others are also listed for comparisons.

The high frequency dielectric constant indicated by Malitson's dispersion equation is 2.15, in good agreement with that from other sources. However, the static dielectric constant calculated from his dispersion equation is 5.976, which is substantially lower than the experimental value, 7.36. This large difference can be ascribed to the low value of the infrared resonant wavelength used in his equation. The resonant wavelength resulting from his best fit is 46.39 micrometers, while the accepted value derived from the infrared reflection spectrum of Lowndes [15] is 53.33 micrometers. In the transparent region the contribution to the refractive index from the infrared term is negative. For a given set of refractive index data, the coefficient which in turn is connected to the static dielectric constant depends on the resonant wavelength in the term: the longer the wavelength, the higher the coefficient. It is therefore possible to obtain a proper combination of these two parameters to yield a good fit to the experimental data, but with each parameter in the term having appropriate physical meaning. To this end, proper selection of input parameters is essential.

As in the case of CaF₂, the Sellmeier formula for BaF₂ consists of a constant, a term giving the UV contribution and two terms giving the infrared contribution. The values of the constant, the coefficient of the UV term and the corresponding effective wavelength of the UV absorption band can be determined by data fitting. However, the coefficient and absorption band wavelength for each of the infrared terms cannot be determined in such a way; one must know one or the other of the parameters because the dispersion of available data values at long wavelengths is not high enough for a unique determination of both parameters. It is fortunate that the wavelengths of the absorption bands are available and well determined. From table 6, the average room-temperature wavelengths of TO and LO optical phonons are, respectively, 53.82 and 29.87 micrometers. The result of a least squares calculation is the dispersion equation for BaF₂ at 293 K in the transparent region, 0.15–10 micrometers,

$$n^2 = 1.33973 + \frac{0.81070 \lambda^2}{\lambda^2 - 0.10065^2} + \frac{0.19652 \lambda^2}{\lambda^2 - 29.87^2} + \frac{4.52469 \lambda^2}{\lambda^2 - 53.82^2}, \quad (21)$$

where λ is in micrometers.

This dispersion equation closely fits Malitson's data with a root mean square residual of 2.0×10^{-5} in the spectral region from 0.26 to 10.35 micrometers. Although the use of this equation can be confidently extended into the infrared up to 15 micrometers, its use in the UV region beyond 0.26 micrometers is not recommended, because the value of λ_u is determined by fitting of the available data at wavelengths longer than 0.26 micrometer; in the range from 0.15 to 0.26 micrometers, larger uncertainties must be expected. The upper limit of the uncertainties can be estimated by differentiating eq (21) with respect to λ_u :

$$\Delta n = \frac{0.81070 \lambda^2}{(\lambda^2 - \lambda_u^2)^2} \left(\frac{\lambda_u \Delta \lambda_u}{n} \right), \quad (22)$$

where $\Delta \lambda_u = 0.122 - \lambda_u$.

The optical dielectric constant indicated by eq (21) is 2.15042, which agrees with that from other work. The static dielectric constant implied by this equation is 6.872, about 0.5 less than Andeen's value (see table 5). There are many causes for the discrepancy. Two of the essential ones are that (i) we have ignored small contributions from many absorption bands in the infrared region beyond the predominant phonon; (ii) we have neglected the damping factors in the dispersion equation. Neglecting the damping factors tends to reduce the value of the static dielectric constant.

With regard to the temperature derivative of the refractive index of barium fluoride, little work has been done. Although Malitson [67] also measured refractive indices for 46 wavelengths from 0.26 to 10.35 micrometers at room temperatures in the neighborhood of 288 K and 303 K, the results could not be used to evaluate dn/dT because of excessive fluctuations; only tentative averaged values of dn/dT were given. He found that dn/dT is negative over the entire measured wavelength range. There is evidence that the value of dn/dT (in units of 10^{-6} K^{-1}) ranges from an average of about -11 in the near ultraviolet to -15 in the visible and to a low of about -17 in the near infrared; then it increases to an average of -9 at the long wavelength limit. However, more accurate values were given for visible regions from 0.4 to 0.77 micrometer, based on the observations carried out in 1944 and reported in Malitson's 1963 work. Other dn/dT measurements were recently made by Lipson et al. [59], Harris et al. [60] and Tsay et al. [92]. They used the interference method to obtain dn/dT directly by observing the shift of interference fringes with temperature. This method is believed to yield accurate dn/dT values, but measurements were made only at five wavelengths, 0.325, 0.4416, 0.6328, 1.15, and 3.39 micrometers. Data on dn/dT remains scarce. With the limited data, the generation of probable values for the entire transparent region depends heavily on the selection of input parameters and appropriate determination of the coefficients. As in the case of CaF_2 , we use Malitson's dn/dT values in the 0.4 to 0.77 micrometer region to determine the coefficients of the constant and ultraviolet terms, assuming that the contribution from infrared terms is negligible. This assumption is a good approximation because the contribution of the infrared term to the visible region is at most less than 0.1 (in units of 10^{-6} K^{-1}) while the value of dn/dT is about -15. Then by holding the constant and ultraviolet terms fixed, one can

evaluate the coefficients of the infrared terms using dn/dT values of Lipson, Harris, and Tsay. The following equation was found to represent dn/dT of BaF_2 for the transparent region, at 293 K:

$$2n \frac{dn}{dT} = -8.18 - 59.4(n^2 - 1) + \frac{31.0 \lambda^4}{(\lambda^2 - 0.1036^2)^2} + \frac{225.0 \lambda^2}{\lambda^2 - 53.82^2} + \frac{1600.8 \lambda^4}{(\lambda^2 - 53.82^2)^2} \quad (23)$$

where dn/dT and λ are in units of 10^{-6} K^{-1} and micrometers, respectively.

The variation of dn/dT with temperature has been observed by Houston et al. [47], Selezneva [68], Lipson et al. [59] and Tsay et al. [92]. The measurement information and results of their work are given in tables 33 and 34, and are plotted in figure 18, where we see that such observations are limited at five visible wavelengths. The magnitude of dn/dT is found to increase slightly with temperature. The possible origin of this increase was discussed by Lipson, and Tsay, who concluded that the temperature dependence of dn/dT arises mainly from that of the thermal expansion coefficient, α . However, the relation between the dn/dT variation with temperature and the thermal expansion coefficient has not yet been established for general applications because it varies very much with wavelength. For the time being the application of eq (4) to evaluate dn/dT only at temperatures not far from 293 K is recommended.

Equations (21) and (23) were used to generate the reference data given in the table of recommended values. Values of $dn/d\lambda$ were simply evaluated by the first derivative of eq (21). Although the values of n are given to the fourth decimal place and dn/dT to the first, this does not reflect their accuracy and reliability. They are so given simply for smoothness of tabulation. However, an overstrike is placed to indicate the insignificant part of the value. For the proper use of the tabulated values the reader should follow the criteria given below.

For refractive index:

Vavelength range micrometers	Estimated uncertainty, \pm
0.15-0.20	0.001
0.20-0.30	0.0005
0.30-0.40	0.0003
0.40-10.0	0.0001
10.0-12.0	0.0003
12.0-15.0	0.001

For dn/dT :

0.15-0.20	3.0
0.20-0.30	2.0
0.30-1.00	1.0
1.00-6.00	0.5
6.00-10.0	1.0
10.0-15.0	1.5

TABLE 26. RECOMMENDED VALUES ON THE REFRACTIVE INDEX AND ITS WAVELENGTH AND TEMPERATURE DERIVATIVES FOR BARIUM FLUORIDE AT 293K*

λ μm	n	$-dn/d\lambda$ μm ⁻¹	dn/dT 10 ⁻⁶ K ⁻¹	λ μm	n	$-dn/d\lambda$ μm ⁻¹	dn/dT 10 ⁻⁶ K ⁻¹	λ μm	n	$-dn/d\lambda$ μm ⁻¹	dn/dT 10 ⁻⁶ K ⁻¹
0.150	1.6776	4.795	-0.8	0.220	1.5378	0.8024	-12.4	0.290	1.5037	0.2898	-14.1
0.152	1.6683	4.4456	-1.8	0.222	1.5362	0.7744	-12.5	0.292	1.5031	0.2829	-14.1
0.154	1.6597	4.1287	-2.7	0.224	1.5347	0.7477	-12.6	0.294	1.5026	0.2763	-14.1
0.156	1.6518	3.8437	-3.5	0.226	1.5332	0.7223	-12.6	0.296	1.5020	0.2699	-14.0
0.158	1.6444	3.5864	-4.3	0.228	1.5318	0.6980	-12.7	0.298	1.5015	0.2636	-14.0
0.160	1.6374	3.3535	-4.9	0.230	1.5304	0.6749	-12.8	0.300	1.5010	0.2576	-14.2
0.162	1.6309	3.1419	-5.5	0.232	1.5291	0.6529	-12.9	0.305	1.4997	0.2434	-14.3
0.164	1.6248	2.9491	-6.1	0.234	1.5278	0.6318	-12.9	0.310	1.4986	0.2302	-14.3
0.166	1.6191	2.7730	-6.6	0.236	1.5266	0.6117	-13.0	0.315	1.4974	0.2180	-14.4
0.168	1.6137	2.6117	-7.1	0.238	1.5254	0.5925	-13.1	0.320	1.4964	0.2066	-14.4
0.170	1.6087	2.4636	-7.5	0.240	1.5242	0.5741	-13.1	0.325	1.4954	0.1961	-14.4
0.172	1.6039	2.3274	-7.9	0.242	1.5231	0.5565	-13.2	0.330	1.4944	0.1862	-14.5
0.174	1.5993	2.2017	-8.4	0.244	1.5220	0.5396	-13.2	0.335	1.4935	0.1771	-14.5
0.176	1.5951	2.0855	-8.6	0.246	1.5209	0.5235	-13.3	0.340	1.4926	0.1685	-14.6
0.178	1.5910	1.9780	-8.9	0.248	1.5199	0.5080	-13.3	0.345	1.4918	0.1605	-14.6
0.180	1.5871	1.8782	-9.1	0.250	1.5189	0.4931	-13.4	0.350	1.4910	0.1530	-14.6
0.182	1.5835	1.7855	-9.4	0.252	1.5179	0.4789	-13.4	0.355	1.4903	0.1460	-14.7
0.184	1.5800	1.6992	-9.7	0.254	1.5170	0.4652	-13.5	0.360	1.4896	0.1394	-14.7
0.186	1.5767	1.6187	-9.9	0.256	1.5160	0.4520	-13.5	0.365	1.4889	0.1333	-14.7
0.188	1.5735	1.5436	-10.1	0.258	1.5152	0.4394	-13.6	0.370	1.4882	0.1274	-14.7
0.190	1.5705	1.4734	-10.4	0.260	1.5143	0.4272	-13.6	0.375	1.4876	0.1220	-14.8
0.192	1.5676	1.4076	-10.5	0.262	1.5134	0.4155	-13.6	0.380	1.4870	0.1168	-14.8
0.194	1.5649	1.3459	-10.7	0.264	1.5126	0.4042	-13.7	0.385	1.4864	0.1120	-14.8
0.196	1.5622	1.2880	-10.9	0.266	1.5118	0.3934	-13.7	0.390	1.4859	0.1074	-14.8
0.198	1.5597	1.2336	-11.1	0.268	1.5111	0.3830	-13.8	0.395	1.4854	0.1030	-14.8
0.200	1.5573	1.1823	-11.2	0.270	1.5103	0.3729	-13.8	0.400	1.4849	0.0989	-14.9
0.202	1.5550	1.1341	-11.4	0.272	1.5096	0.3632	-13.8	0.410	1.4839	0.0914	-14.9
0.204	1.5528	1.0886	-11.5	0.274	1.5088	0.3539	-13.9	0.420	1.4830	0.0846	-14.9
0.206	1.5506	1.0456	-11.6	0.276	1.5081	0.3448	-13.9	0.430	1.4822	0.0785	-15.0
0.208	1.5486	1.0050	-11.8	0.278	1.5075	0.3361	-13.9	0.440	1.4815	0.0729	-15.0
0.210	1.5466	0.9665	-11.9	0.280	1.5068	0.3277	-14.0	0.450	1.4808	0.0679	-15.0
0.212	1.5447	0.9302	-12.0	0.282	1.5062	0.3196	-14.0	0.460	1.4801	0.0634	-15.0
0.214	1.5429	0.8957	-12.1	0.284	1.5055	0.3118	-14.0	0.470	1.4795	0.0592	-15.1
0.216	1.5411	0.8630	-12.2	0.286	1.5049	0.3042	-14.0	0.480	1.4789	0.0555	-15.1
0.218	1.5394	0.8319	-12.3	0.288	1.5043	0.2969	-14.1	0.490	1.4784	0.0520	-15.1

TABLE 26. RECOMMENDED VALUES ON THE REFRACTIVE INDEX AND ITS WAVELENGTH AND TEMPERATURE DERIVATIVES FOR BARIUM FLUORIDE AT 293K (CONTINUED)*

λ μm	n	-dn/d λ μm^{-1}	dn/dT 10^{-6}K^{-1}	λ μm	n	-dn/d λ μm^{-1}	dn/dT 10^{-6}K^{-1}	λ μm	n	-dn/d λ μm^{-1}	dn/dT 10^{-6}K^{-1}
0.500	1.4779	0.0488	-15.1	1.250	1.4672	0.0044	-15.5	3.000	1.4612	0.0039	-15.5
0.510	1.4774	0.0459	-15.1	1.300	1.4670	0.0041	-15.5	3.050	1.4610	0.0039	-15.5
0.520	1.4769	0.0433	-15.2	1.350	1.4668	0.0039	-15.5	3.100	1.4608	0.0040	-15.5
0.530	1.4765	0.0408	-15.2	1.400	1.4666	0.0037	-15.5	3.150	1.4606	0.0040	-15.5
0.540	1.4761	0.0385	-15.2	1.450	1.4664	0.0036	-15.5	3.200	1.4604	0.0041	-15.5
0.550	1.4758	0.0364	-15.2	1.500	1.4663	0.0035	-15.5	3.250	1.4602	0.0041	-15.5
0.560	1.4754	0.0345	-15.2	1.550	1.4661	0.0034	-15.5	3.300	1.4600	0.0042	-15.5
0.570	1.4751	0.0327	-15.2	1.600	1.4659	0.0033	-15.5	3.350	1.4598	0.0042	-15.5
0.580	1.4747	0.0310	-15.2	1.650	1.4658	0.0032	-15.5	3.400	1.4596	0.0043	-15.5
0.590	1.4744	0.0294	-15.2	1.700	1.4656	0.0032	-15.5	3.450	1.4593	0.0044	-15.5
0.600	1.4742	0.0280	-15.3	1.750	1.4654	0.0031	-15.5	3.500	1.4591	0.0044	-15.5
0.520	1.4736	0.0254	-15.3	1.800	1.4653	0.0031	-15.5	3.550	1.4589	0.0045	-15.5
0.540	1.4731	0.0231	-15.3	1.850	1.4651	0.0031	-15.5	3.600	1.4587	0.0045	-15.5
0.560	1.4727	0.0211	-15.3	1.900	1.4650	0.0031	-15.5	3.650	1.4584	0.0046	-15.5
0.580	1.4723	0.0193	-15.3	1.950	1.4648	0.0031	-15.5	3.700	1.4582	0.0046	-15.5
0.700	1.4719	0.0178	-15.3	2.000	1.4647	0.0031	-15.5	3.750	1.4580	0.0047	-15.5
0.720	1.4716	0.0164	-15.3	2.050	1.4645	0.0031	-15.5	3.800	1.4577	0.0048	-15.5
0.740	1.4713	0.0152	-15.3	2.100	1.4643	0.0031	-15.5	3.850	1.4575	0.0048	-15.4
0.760	1.4710	0.0141	-15.4	2.150	1.4642	0.0031	-15.5	3.900	1.4572	0.0049	-15.4
0.780	1.4707	0.0131	-15.4	2.200	1.4640	0.0032	-15.5	3.950	1.4570	0.0049	-15.4
0.300	1.4704	0.0122	-15.4	2.250	1.4639	0.0032	-15.5	4.000	1.4567	0.0050	-15.4
0.320	1.4702	0.0114	-15.4	2.300	1.4637	0.0032	-15.5	4.050	1.4565	0.0051	-15.4
0.340	1.4700	0.0107	-15.4	2.350	1.4635	0.0033	-15.5	4.100	1.4562	0.0051	-15.4
0.360	1.4698	0.0100	-15.4	2.400	1.4634	0.0033	-15.5	4.150	1.4560	0.0052	-15.4
0.380	1.4696	0.0094	-15.4	2.450	1.4632	0.0033	-15.5	4.200	1.4557	0.0053	-15.4
0.300	1.4694	0.0089	-15.4	2.500	1.4630	0.0034	-15.5	4.250	1.4554	0.0053	-15.4
0.320	1.4692	0.0084	-15.4	2.550	1.4629	0.0034	-15.5	4.300	1.4552	0.0054	-15.4
0.340	1.4691	0.0080	-15.4	2.600	1.4627	0.0035	-15.5	4.350	1.4549	0.0054	-15.4
0.360	1.4689	0.0076	-15.4	2.650	1.4625	0.0035	-15.5	4.400	1.4546	0.0055	-15.4
0.380	1.4688	0.0072	-15.4	2.700	1.4623	0.0036	-15.5	4.450	1.4543	0.0056	-15.4
1.000	1.4686	0.0069	-15.4	2.750	1.4621	0.0036	-15.5	4.500	1.4541	0.0056	-15.4
1.050	1.4683	0.0062	-15.4	2.800	1.4620	0.0036	-15.5	4.550	1.4538	0.0057	-15.4
1.100	1.4680	0.0056	-15.4	2.850	1.4618	0.0037	-15.5	4.600	1.4535	0.0058	-15.4
1.150	1.4677	0.0051	-15.4	2.900	1.4616	0.0037	-15.5	4.650	1.4532	0.0058	-15.4
1.200	1.4675	0.0047	-15.5	2.950	1.4614	0.0038	-15.5	4.700	1.4529	0.0059	-15.4

TABLE 26. RECOMMENDED VALUES ON THE REFRACTIVE INDEX AND ITS WAVELENGTH AND TEMPERATURE DERIVATIVES FOR BARIUM FLUORIDE AT 293K (CONTINUED)*

λ μm	n	$-dn/d\lambda$ μm ⁻¹	dn/dT $10^{-6} K^{-1}$	λ μm	n	$-dn/d\lambda$ μm ⁻¹	dn/dT $10^{-6} K^{-1}$	λ μm	n	$-dn/d\lambda$ μm ⁻¹	dn/dT $10^{-6} K^{-1}$
4.750	1.4526	0.0060	-15.4	7.200	1.4338	0.0093	-15.1	9.300	1.4027	0.0137	-14.4
4.800	1.4523	0.0060	-15.4	7.300	1.4329	0.0095	-15.1	10.000	1.4014	0.0139	-14.4
4.850	1.4520	0.0061	-15.4	7.400	1.4319	0.0096	-15.1	10.200	1.3985	0.0143	-14.3
4.900	1.4517	0.0061	-15.4	7.500	1.4309	0.0098	-15.1	10.400	1.3956	0.0146	-14.2
4.950	1.4514	0.0062	-15.4	7.600	1.4300	0.0099	-15.1	10.600	1.3926	0.0150	-14.1
5.000	1.4511	0.0063	-15.4	7.700	1.4290	0.0101	-15.1	10.800	1.3896	0.0154	-14.0
5.100	1.4504	0.0064	-15.4	7.800	1.4279	0.0103	-15.0	11.000	1.3865	0.0158	-13.9
5.200	1.4498	0.0065	-15.4	7.900	1.4269	0.0104	-15.0	11.200	1.3833	0.0162	-13.8
5.300	1.4491	0.0067	-15.4	8.000	1.4258	0.0106	-15.0	11.400	1.3800	0.0166	-13.7
5.400	1.4484	0.0068	-15.4	8.100	1.4248	0.0107	-15.0	11.600	1.3766	0.0170	-13.6
5.500	1.4477	0.0069	-15.4	8.200	1.4237	0.0109	-15.0	11.800	1.3731	0.0174	-13.4
5.600	1.4470	0.0071	-15.3	8.300	1.4226	0.0110	-14.9	12.000	1.3695	0.0179	-13.3
5.700	1.4463	0.0072	-15.3	8.400	1.4215	0.0112	-14.9	12.200	1.3660	0.0183	-13.2
5.800	1.4456	0.0074	-15.3	8.500	1.4203	0.0114	-14.9	12.400	1.3623	0.0187	-13.0
5.900	1.4448	0.0075	-15.3	8.600	1.4192	0.0115	-14.9	12.600	1.3585	0.0192	-12.8
6.000	1.4441	0.0076	-15.3	8.700	1.4180	0.0117	-14.8	12.800	1.3545	0.0197	-12.7
6.100	1.4433	0.0078	-15.3	8.800	1.4168	0.0118	-14.8	13.000	1.3505	0.0201	-12.5
6.200	1.4425	0.0079	-15.3	8.900	1.4156	0.0120	-14.8	13.200	1.3465	0.0206	-12.3
6.300	1.4417	0.0080	-15.3	9.000	1.4144	0.0122	-14.7	13.400	1.3423	0.0211	-12.1
6.400	1.4409	0.0082	-15.3	9.100	1.4132	0.0123	-14.7	13.600	1.3380	0.0216	-11.9
6.500	1.4401	0.0083	-15.2	9.200	1.4120	0.0125	-14.7	13.800	1.3335	0.0222	-11.6
6.600	1.4392	0.0085	-15.2	9.300	1.4107	0.0127	-14.7	14.000	1.3292	0.0227	-11.4
6.700	1.4383	0.0085	-15.2	9.400	1.4094	0.0129	-14.6	14.200	1.3245	0.0232	-11.1
6.800	1.4375	0.0088	-15.2	9.500	1.4081	0.0130	-14.6	14.400	1.3198	0.0238	-10.9
6.900	1.4366	0.0089	-15.2	9.600	1.4068	0.0132	-14.5	14.600	1.3150	0.0244	-10.6
7.000	1.4357	0.0091	-15.2	9.700	1.4055	0.0134	-14.5	14.800	1.3101	0.0250	-10.3
7.100	1.4348	0.0092	-15.2	9.800	1.4041	0.0136	-14.5	15.000	1.3050	0.0256	-10.0

* IN THIS TABLE MORE DECIMAL PLACES ARE REPORTED THAN WARRANTED MERELY FOR THE PURPOSE OF TABULAR SMOOTHNESS AND INTERNAL COMPARISON. FOR UNCERTAINTIES OF TABULATED VALUES IN VARIOUS WAVELENGTH RANGES, SEE THE TEXT OF SUBSECTION 3.3. THE NUMBER OF DIGITS WITH AN OVERSTRIKE IS NOT RELATED TO THE ACCURACY OF THE VALUES.

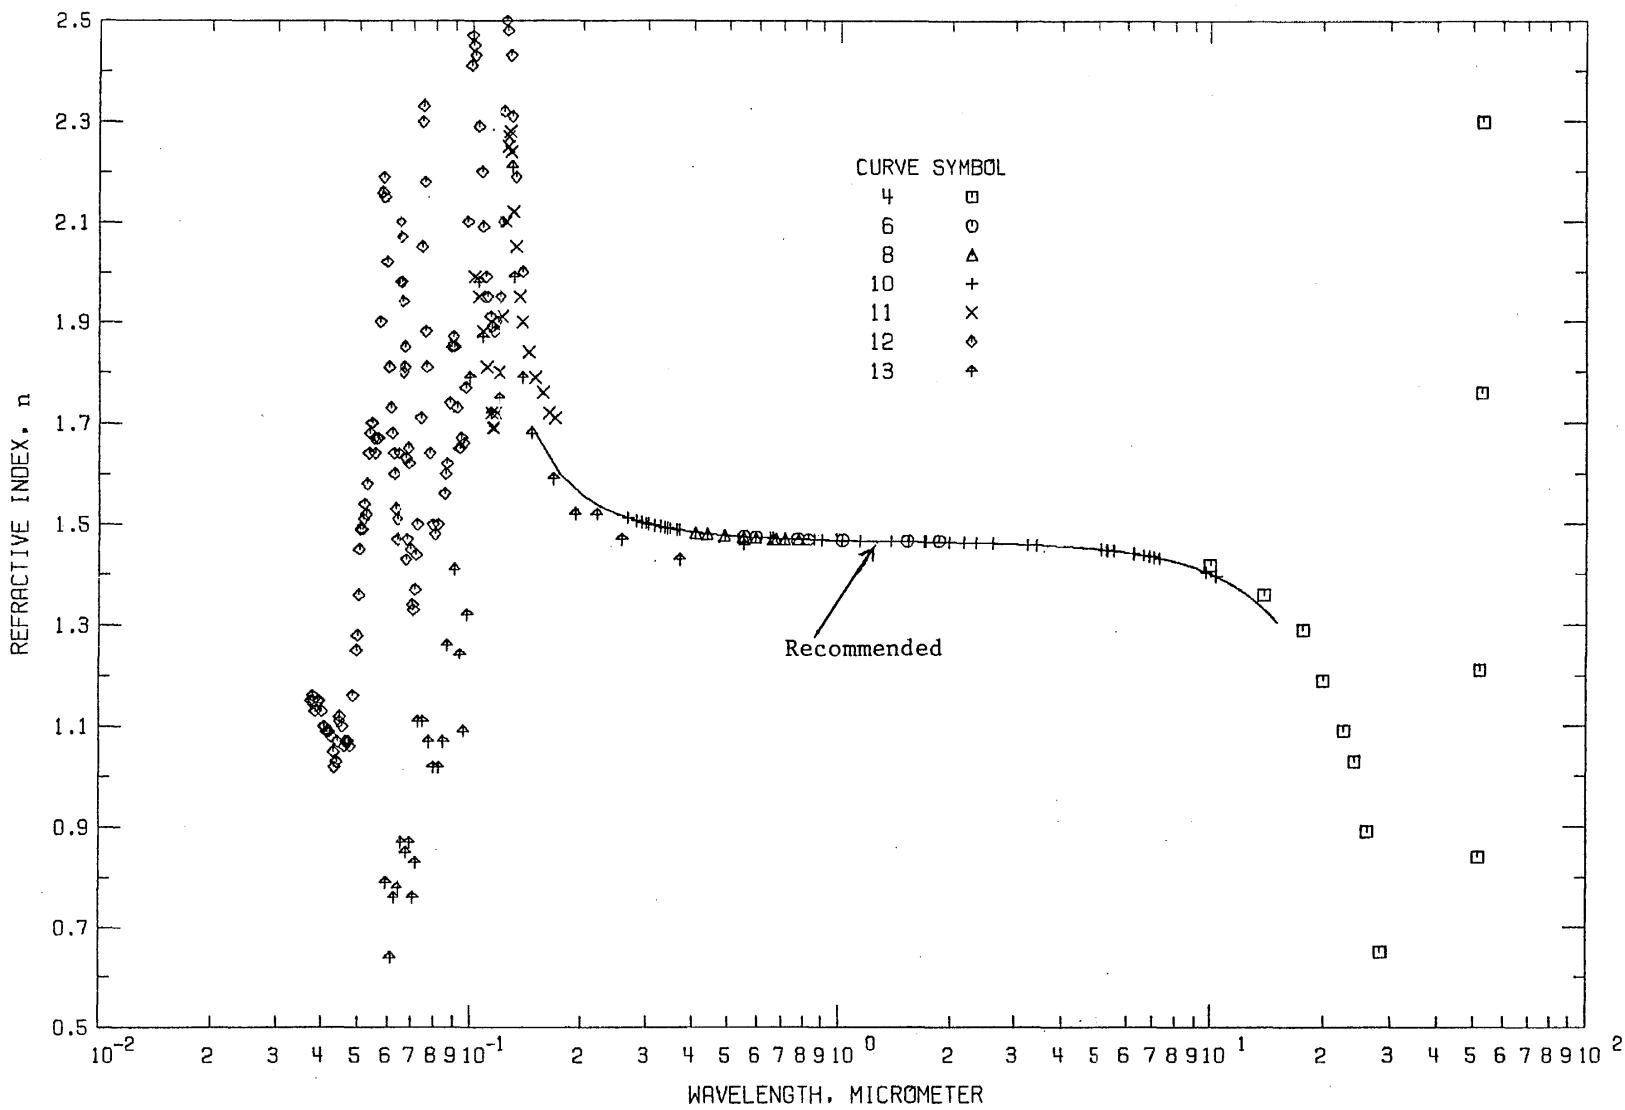


FIGURE 16. REFRACTIVE INDEX OF BARIUM FLUORIDE (WAVELENGTH DEPENDENCE).

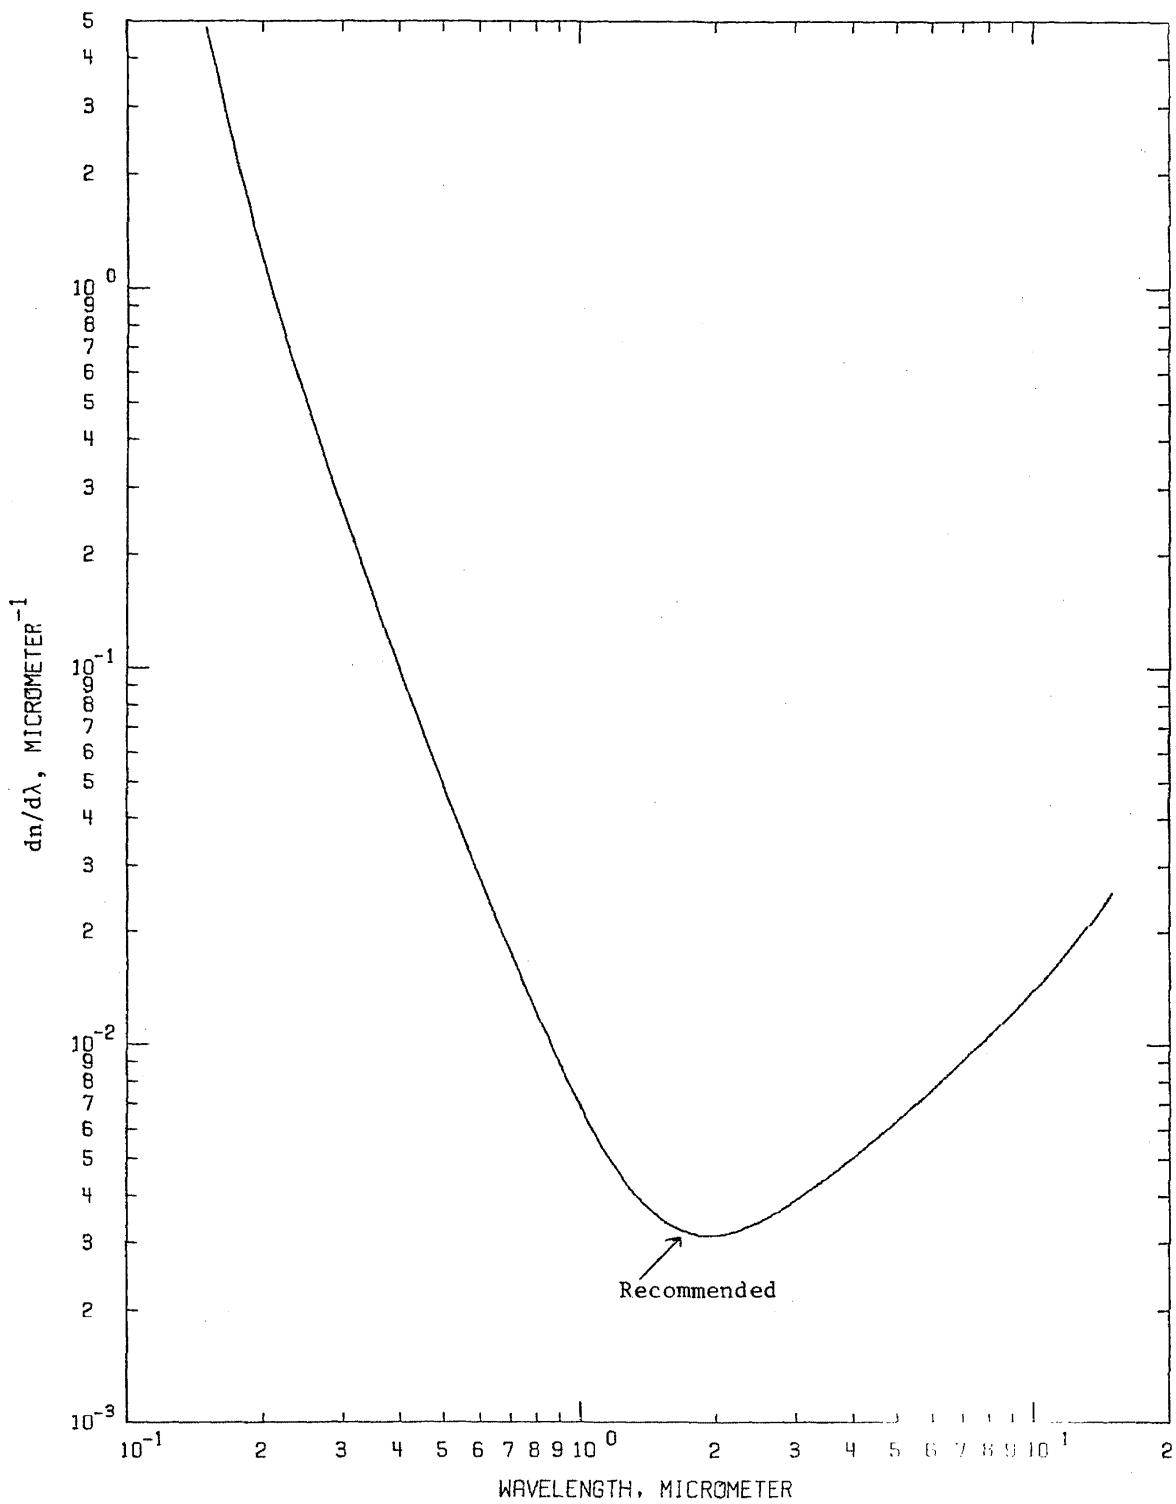


FIGURE 17. WAVELENGTH DERIVATIVE OF REFRACTIVE INDEX OF BARIUM FLUORIDE.

TABLE 27. MEASUREMENT INFORMATION ON THE REFRACTIVE INDEX OF BARIUM FLUORIDE (WAVELENGTH DEPENDENCE)

DATA SET NO.	REF. NO.	AUTHOR(S)	YEAR	METHOD USED	WAVELENGTH RANGE, μm	TEMP. K	SPECIFICATIONS AND REMARKS
1	61	THILO,F.	1927	M	0.589	293	SINGLE CRYSTAL; REFRACTIVE INDEX DETERMINED BY IMMERSION METHOD FOR THE MEAN OF SODIUM D LINES; DATA EXTRACTED FROM A TABLE; TEMPERATURE NOT GIVEN, 293K ASSUMED.
2	66	WULFF,P.	1928	M	0.589	298	CRYSTAL OF UNSPECIFIED TYPE; REFRACTIVE INDEX DETERMINED BY IMMERSION METHOD FOR THE MEAN OF SODIUM D LINES; DATA EXTRACTED FROM A TABLE; UNCERTAINTY OF INDEX 0.00010.
3	62	WULFF,P. HEIGL,A.	1931	M	0.589	298	SINGLE CRYSTAL; 1-2 MM FRAGMENTS; OBTAINED FROM COOLING THE MELT; REFRACTIVE INDEX DETERMINED BY IMMERSION METHOD FOR THE MEAN OF SODIUM D LINES; DATA EXTRACTED FROM A TABLE; UNCERTAINTY OF INDEX 0.0002.
4	17	KAISER,W. SPITZER,W.G. KAISER,R.H. HOWARTH,L.E.	1962	R	10.0-80.0	300	SINGLE CRYSTAL; PLATE SPECIMEN; 0.1-5.0MM THICK; HIGHLY POLISHED SURFACES; NEAR NORMAL INCIDENT REFLECTION SPECTRUM OBTAINED; REFRACTIVE INDEX DEDUCED FROM REFLECTION SPECTRUM WITH LORENTZ THEORY; DATA EXTRACTED FROM A SMOOTH CURVE; LORENTZ DAMPED-OSCILLATOR DISPERSION EQUATION ALSO GIVEN.
5	47	HOUSTON,T.W. JOHNSON,L.F. KISLIUK,P. WALSH,D.J.	1963	D	0.54-1.85	93	SINGLE CRYSTAL; HIGH PURITY; PRISMATIC SPECIMEN; POLISHED SURFACES FLAT TO 1/2 WAVELENGTH OF 0.535 MICROMETER LINE; REFRACTIVE INDEX DETERMINED BY MINIMUM DEVIATION METHOD FOR 7 SPECTRAL LINES; DATA EXTRACTED FROM A TABLE.
6	47	HOUSTON,T.W. ET AL.	1963	D	0.54-1.85	298	SIMILAR TO ABOVE BUT AT A HIGHER TEMPERATURE OF 298K.
7	67	MALITSON,I.H.	1964	D	0.40-0.77	288	SYNTHETIC CRYSTAL; GROWN AT MIT BY D. C. STOCKBARGER; PRISMATIC SPECIMEN; REFRACTIVE INDEX DETERMINED BY DEVIATION METHOD FOR 9 SPECTRAL LINES; DATA EXTRACTED FROM A TABLE; ESTIMATED UNCERTAINTY ABOUT 0.000003; THIS DATA SET WAS MEASURED AT NBS IN 1944.
8	67	MALITSON,I.H.	1964	D	0.40-0.77	308	SIMILAR TO ABOVE BUT AT A HIGHER TEMPERATURE OF 308K.
9	67	MALITSON,I.H.	1964	D	0.40-0.77	328	SIMILAR TO ABOVE BUT AT A HIGHER TEMPERATURE OF 328K.
10	67	MALITSON,I.H.	1964	D	0.26-10.4	298	SYNTHETIC CRYSTAL; OBTAINED FROM THE HARSHAW CHEMICAL CO.; PRISMATIC SPECIMEN; NEAR 51 DEGREE APEX ANGLE, 18MMX18MM VIEW SURFACE; REFRACTIVE INDEX DETERMINED BY MINIMUM DEVIATION METHOD FOR 46 SPECTRAL LINES; DATA EXTRACTED FROM A TABLE; A SELLMEIRE TYPE DISPERSION EQUATION BEST FIT THE DATA ALSO GIVEN.

TABLE 27. MEASUREMENT INFORMATION ON THE REFRACTIVE INDEX OF BARIUM FLUORIDE (WAVELENGTH DEPENDENCE) (CONTINUED)

DATA SET NO.	REF. NO.	AUTHOR(S)	YEAR	METHOD USED	WAVELENGTH RANGE, μm	TEMP. K	SPECIFICATIONS AND REMARKS
11	49	FABRE,D. ROMAND,J. VODAR,B.	1964	R	0.10-0.17	293	THIN FILM SPECIMEN OF VARYING THICKNESS; VACUUM DEPOSITED; REFRACTIVE INDEX DETERMINED BY REFLECTANCE OF VARYING THICKNESS; DATA EXTRACTED FROM A FIGURE; TEMPERATURE NOT GIVEN, 293K ASSUMED.
12	25	NISAR,M. ROBIN,S.	1974	R	0.03-0.138	293	SINGLE CRYSTAL; OBTAINED FROM THE HARSHAW CHEMICAL CO.; SPECIMEN CLEAVED IN VACUUM; 20 DEGREE INCIDENT REFLECTION SPECTRUM OBTAINED; REFRACTIVE INDEX DEDUCED FROM REFLECTION SPECTRUM WITH KRAMERS-KRONIG RELATION; DATA EXTRACTED FROM A FIGURE; TEMPERATURE NOT GIVEN, 293K ASSUMED.
13	53	GANIN,U.,SIDORIN,U. KARIN,M.,SIDORIN,K. STAROSTIN,N., STARTSEV,G.	1975	R	0.06-0.25	300	SINGLE CRYSTAL; FRESHLY CLEAVED SPECIMEN; NEAR NORMAL REFLECTION SPECTRUM OBTAINED; REFRACTIVE INDEX DEDUCED FROM REFLECTION SPECTRUM WITH KRAMERS-KRONIG RELATION; DATA EXTRACTED FROM A FIGURE.

H. H. LI

TABLE 28. EXPERIMENTAL REFRACTIVE INDEX OF BARIUM FLUORIDE (WAVELENGTH DEPENDENCE)
[WAVELENGTH, λ , μm ; TEMPERATURE, T, K; REFRACTIVE INDEX, n]

λ	n	λ	n	λ	n	λ	n	λ	n	λ	n		
DATA SET 1													
<i>T = 293.0</i>													
0.589	1.475	53.6	5.33	0.5461	1.4760	0.486132	1.477628	2.1526	1.46410	0.1430	1.84		
		53.8	6.01	0.5890	1.4745	0.546074	1.474951	2.32542	1.46356	0.1489	1.79		
DATA SET 2													
<i>T = 298.0</i>													
0.589	1.47410	54.0	8.25	0.7665	1.4709	0.656279	1.471830	2.5766	1.46262	0.1562	1.76		
		54.2	9.78	0.8195	1.4701	0.667814	1.471586	2.6738	1.46234	0.1625	1.72		
0.589	1.47410	54.4	10.52	1.0140	1.4696	0.706518	1.470863	3.422	1.45940	0.1684	1.71		
		54.5	11.29	1.5166	1.4684	0.767858	1.469920	5.138	1.45012	DATA SET 12			
		54.7	12.23	1.8459	1.4684			5.3034	1.44904	<i>T = 293.0</i>			
DATA SET 3													
<i>T = 298.0</i>													
0.589	1.47410	55.0	11.63			DATA SET 10		5.343	1.44878	0.0376	1.15		
		55.2	10.91			<i>T = 298.0</i>		5.549	1.44732	0.0379	1.16		
		55.5	10.20			DATA SET 7		6.238	1.44216	0.0380	1.16		
0.589	1.47410	55.7	9.52			0.2652	1.51217	6.6331	1.43899	0.0382	1.15		
		55.9	8.78	0.404656	1.484054	0.28035	1.50668	6.8559	1.43694	0.0385	1.13		
DATA SET 4													
<i>T = 300.0</i>													
10.0	1.42	56.3	8.03	0.435834	1.481416	0.28936	1.50390	7.0442	1.43529	0.0389	1.14		
13.9	1.36	56.6	7.31	0.486132	1.478234	0.296728	1.50186	7.268	1.43314	0.0392	1.15		
17.6	1.29	57.3	6.68	0.546074	1.475559	0.30215	1.50044	8.724	1.40514	0.0386	1.13		
20.0	1.19	58.2	5.94	0.589262	1.474124	0.3130	1.43782	10.346	1.39636	0.0396	1.15		
22.7	1.09	59.1	5.53	0.656279	1.472439	0.32546	1.49521			0.0401	1.13		
24.2	1.03	60.0	5.09	0.667814	1.472196	0.334148	1.49363	DATA SET 11		0.0406	1.10		
26.2	0.89	61.7	4.73	0.706518	1.471474	0.340365	1.49257	<i>T = 293.0</i>		0.0407	1.10		
28.3	0.65	62.4	4.41	0.767858	1.470538	0.348662	1.49158			0.0413	1.09		
30.0	0.41	63.1	4.09			0.361051	1.48939	0.1015	1.99	0.0416	1.09		
31.3	0.16	65.3	3.93			0.366328	1.48869	0.1042	1.95	0.0420	1.09		
33.8	0.16	67.2	3.69			0.404656	1.48438	0.1068	1.88	0.0424	1.08		
37.6	0.16	69.9	3.55			0.435835	1.48173	0.1095	1.81	0.0430	1.05		
40.0	0.11	73.8	3.41	0.404656	1.483753	0.486133	1.47855	0.1123	1.72	0.0433	1.02		
43.8	0.09	77.3	3.41	0.435834	1.481116	0.546074	1.47586	0.1136	1.69	0.0438	1.03		
46.0	0.09	80.0	3.32	0.486132	1.477930	0.589262	1.47443	0.1144	1.69	0.0441	1.07		
48.0	0.24			0.546074	1.475255	0.643847	1.47302	0.1162	1.72	0.0446	1.11		
50.0	0.45			0.589262	1.473820	0.656279	1.47274	0.1189	1.80	0.0454	1.12		
51.4	0.84			0.656279	1.472135	0.706519	1.47177	0.1211	1.91	0.0459	1.06		
52.2	1.21			0.667814	1.471892	0.85211	1.46984	0.1240	2.10	0.0460	1.06		
52.8	1.76			0.706518	1.471167	0.89435	1.46942	0.1258	2.25	0.0464	1.07		
53.1	2.30			0.7665	1.4738	1.01398	1.46847	0.1263	2.27	0.0471	1.07		
53.3	3.07			0.767858	1.470230	1.12866	1.46779	0.1270	2.28	0.0476	1.06		
53.4	3.78					1.36728	1.46673	0.1281	2.24	0.0484	1.16		
53.5	4.51					1.52952	1.46613	0.1302	2.12	0.0494	1.25		
				0.404656	1.483452	1.681	1.46561	0.1321	2.05	0.0496	1.28		
				0.435834	1.480816	1.7012	1.46554	0.1353	1.95				
						1.97009	1.46472	0.1378	1.90				

TABLE 28. EXPERIMENTAL REFRACTIVE INDEX OF BARIUM FLUORIDE (WAVELENGTH DEPENDENCE) (CONTINUED)
 [WAVELENGTH, λ , μm ; TEMPERATURE, T, K; REFRACTIVE INDEX, n]

λ	n	λ	n	λ	n	λ	n
DATA SET 12(CONT.)		DATA SET 12(CONT.)		DATA SET 12(CONT.)		DATA SET 13(CONT.)	
0.0500	1.36	0.0677	1.47	0.1068	2.09	0.0987	1.79
0.0502	1.45	0.0681	1.65	0.1087	1.99	0.1038	1.98
0.0504	1.49	0.0685	1.62	0.1097	1.95	0.1066	1.87
0.0510	1.49	0.0692	1.45	0.1117	1.91	0.1122	1.72
0.0514	1.51	0.0700	1.34	0.1127	1.89	0.1185	1.75
0.0516	1.54	0.0704	1.33	0.1148	1.88	0.1218	2.81
0.0521	1.52	0.0712	1.37	0.1169	1.90	0.1235	2.89
0.0525	1.58	0.0716	1.44	0.1192	1.95	0.1246	2.70
0.0529	1.64	0.0720	1.50	0.1215	2.10	0.1287	2.21
0.0534	1.68	0.0733	1.71	0.1227	2.32	0.1305	1.99
0.0539	1.70	0.0738	2.05	0.1240	2.50	0.1376	1.79
0.0541	1.70	0.0742	2.30	0.1252	2.48	0.1460	1.68
0.0548	1.67	0.0746	2.33	0.1278	2.43	0.1677	1.59
0.0551	1.64	0.0751	2.18	0.1291	2.31	0.1913	1.52
0.0556	1.67	0.0756	1.88	0.1319	2.19	0.2190	1.52
0.0561	1.67	0.0760	1.81	0.1377	2.00	0.2561	1.47
0.0568	1.90	0.0775	1.64			0.3679	1.43
0.0576	2.16	0.0789	1.50	DATA SET 13		0.5486	1.46
0.0579	2.19	0.0800	1.48	T = 300.0			
0.0582	2.15	0.0815	1.50				
0.0590	2.02	0.0849	1.56	0.0592	0.79		
0.0599	1.81	0.0855	1.60	0.0610	0.64		
0.0604	1.73	0.0861	1.62	0.0625	0.76		
0.0610	1.68	0.0873	1.74	0.0641	0.78		
0.0616	1.64	0.0885	1.85	0.0656	0.87		
0.0620	1.60	0.0892	1.87	0.0676	0.85		
0.0626	1.53	0.0898	1.85	0.0691	0.87		
0.0629	1.47	0.0911	1.73	0.0708	0.76		
0.0632	1.51	0.0925	1.65	0.0717	0.83		
0.0639	1.64	0.0932	1.65	0.0726	1.11		
0.0642	1.98	0.0939	1.67	0.0747	1.11		
0.0645	2.10	0.0953	1.66	0.0775	1.07		
0.0649	2.07	0.0961	1.77	0.0795	1.02		
0.0652	1.98	0.0976	2.10	0.0822	1.02		
0.0656	1.94	0.0992	2.41	0.0848	1.07		
0.0659	1.80	0.1000	2.47	0.0864	1.26		
0.0663	1.81	0.1008	2.45	0.0903	1.41		
0.0666	1.85	0.1016	2.43	0.0935	1.24		
0.0670	1.63	0.1042	2.29	0.0956	1.09		
0.0673	1.43	0.1059	2.20	0.0976	1.32		

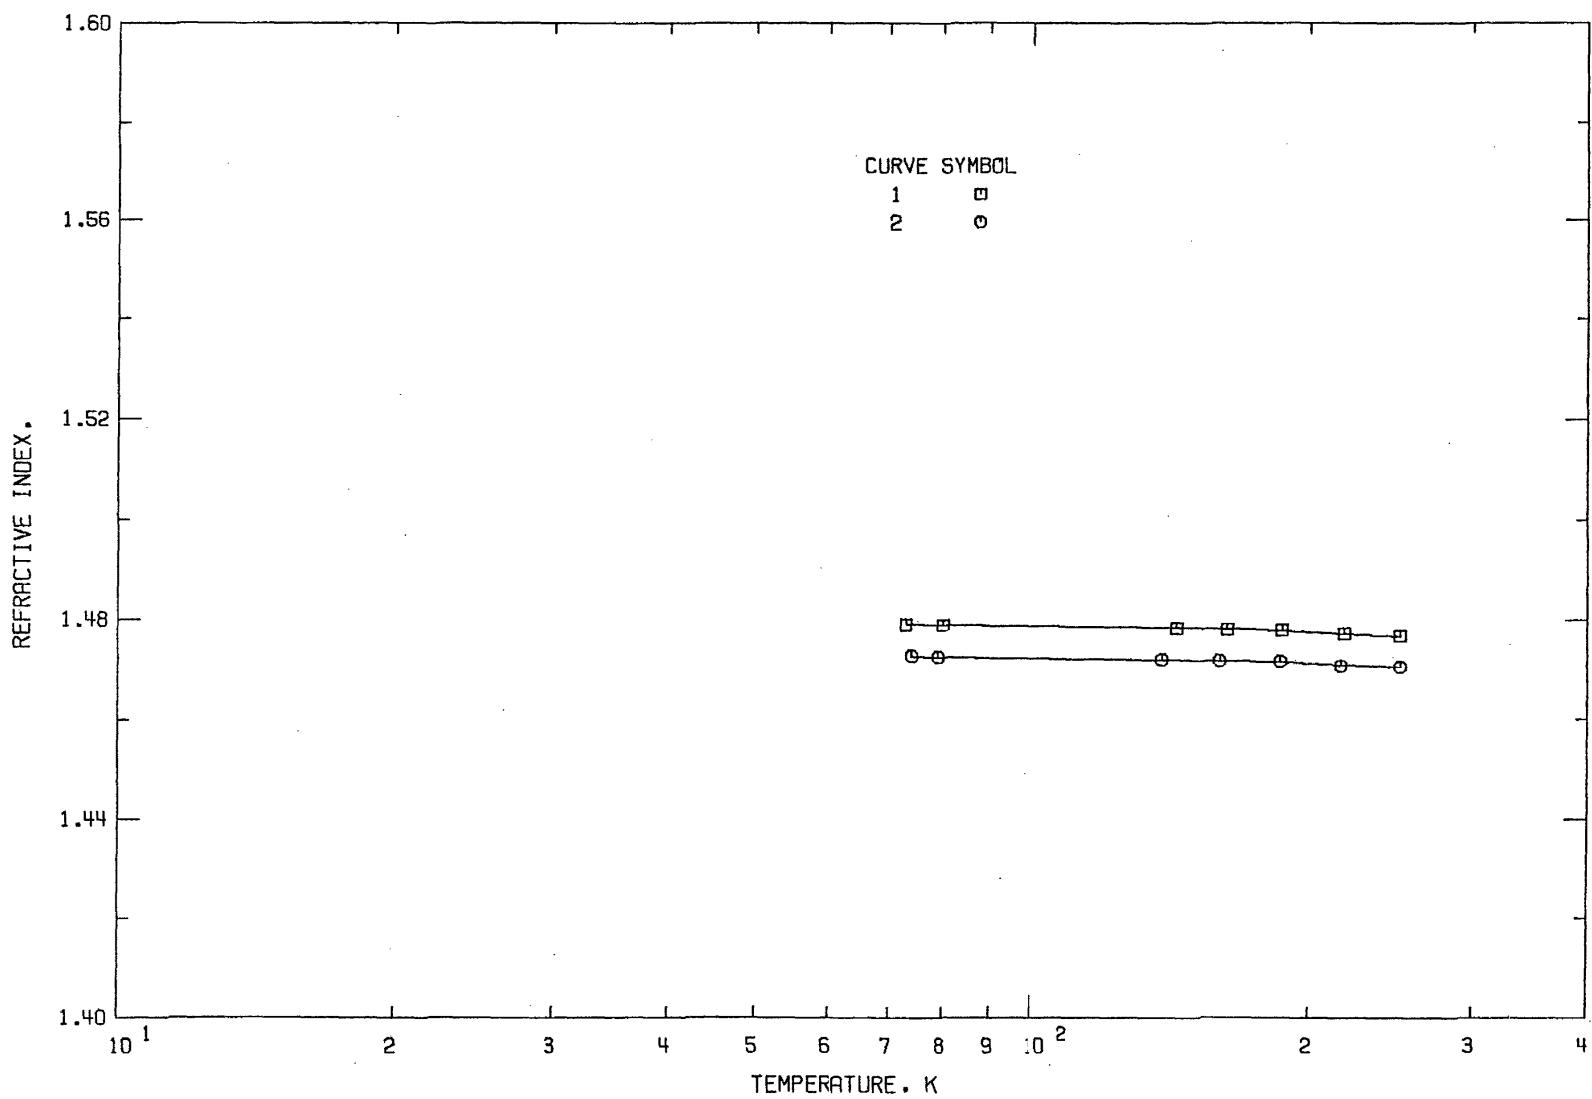


FIGURE 18. REFRACTIVE INDEX OF BARIUM FLUORIDE (TEMPERATURE DEPENDENCE).

TABLE 29. MEASUREMENT INFORMATION ON THE REFRACTIVE INDEX OF BARIUM FLUORIDE (TEMPERATURE DEPENDENCE)

DATA SET NO.	REF. NO.	AUTHOR(S)	YEAR	METHOD USED	WAVELENGTH RANGE, μm	TEMP. K	SPECIFICATIONS AND REMARKS
1	47	HOUSTON, T.W. JOHNSON, L.F. KISLIUK, P. WALSH, D.J.	1963	D	0.5461	73-250	SINGLE CRYSTAL; HIGH PURITY; PRISMATIC SPECIMEN; POLISHED SURFACES FLAT TO 1/2 WAVELENGTH OF 0.535 MICROMETER LINE; REFRACTIVE INDEX DETERMINED BY MINIMUM DEVIATION METHOD FOR THE SPECTRAL LINE 0.5461 MICROMETERS; DATA EXTRACTED FROM A TABLE.
2	47	HOUSTON, T.W. ET AL.	1963	D	1.0140	74-250	SIMILAR TO ABOVE BUT FOR A LONGER WAVELENGTH.

H. H. LI

TABLE 30. EXPERIMENTAL REFRACTIVE INDEX OF BARIUM FLUORIDE (TEMPERATURE DEPENDENCE)
[WAVELENGTH, λ , μm ; TEMPERATURE, T, K; REFRACTIVE INDEX, n]

T n

DATA SET 1
 $\lambda = 0.546$

73.0	1.47909
80.0	1.47898
144.0	1.47842
163.0	1.47820
187.0	1.47798
218.0	1.47731
250.0	1.47675

DATA SET 2
 $\lambda = 1.014$

74.0	1.47278
79.0	1.47253
139.0	1.47208
160.0	1.47186
186.0	1.47175
216.0	1.47086
250.0	1.47063

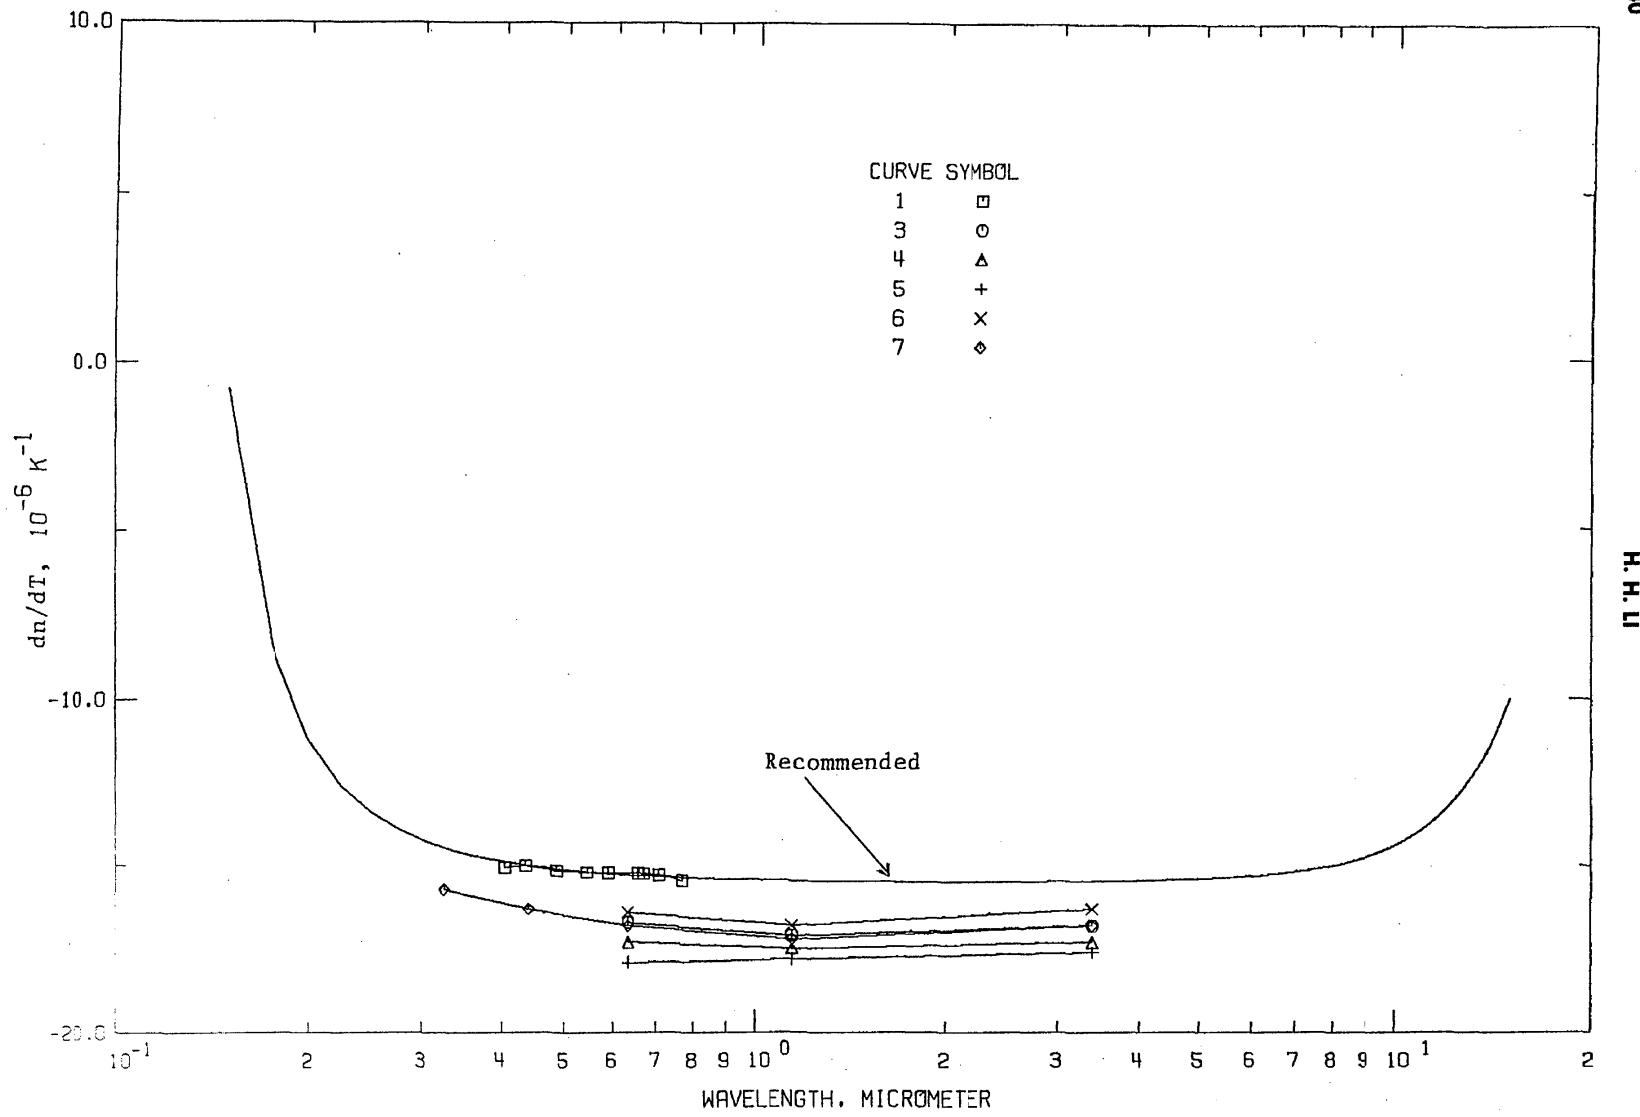


FIGURE 19. TEMPERATURE DERIVATIVE OF REFRACTIVE INDEX OF BARIUM FLUORIDE (WAVELENGTH DEPENDENCE).

TABLE 31. MEASUREMENT INFORMATION ON THE TEMPERATURE DERIVATIVE OF REFRACTIVE INDEX OF BARIUM FLUORIDE (WAVELENGTH DEPENDENCE)

DATA SET NO.	REF. NO.	AUTHOR(S)	YEAR	METHOD USED	WAVELENGTH RANGE, μm	TEMP., K	SPECIFICATIONS AND REMARKS
1	67	MALITSON,I.H.	1964	D	0.40-0.77	308	SYNTHETIC CRYSTAL; GROWN AT MIT BY D. C. STOCKBARGER; PRISMATIC SPECIMEN; REFRACTIVE INDEX DETERMINED BY DEVIATION METHOD; DN/DT DETERMINED FOR 9 SPECTRAL LINES USING THE INDICES MEASURED AT 288, 308 AND 328K; DATA EXTRACTED FROM A TABLE.
2	67	MALITSON,I.H.	1964	D	0.26-10.4	296	SYNTHETIC CRYSTAL; OBTAINED FROM THE HARSHAW CHEMICAL CO.; PRISMATIC SPECIMEN; NEAR 61 DEGREE APEX ANGLE, 18MMX18MM VIEW SURFACE; REFRACTIVE INDEX DETERMINED BY MINIMUM DEVIATION METHOD FOR 46 SPECTRAL LINES; DN/DT DETERMINED USING INDICES MEASURED AT ABOUT 288 AND 303K, NO DEFINITE RESULTS REPORTED BUT AVERAGED VALUES -11X10 ⁻⁵ K IN NEAR ULTRAVIOLET, -15 IN VISIBLE, -17 IN IN NEAR INFRARED AND -9 AT LONG WAVELENGTH LIMIT; DATA EXTRACTED FROM A TABLE.
3	59	LIPSON,H.G. TSAY,Y.F. BENDOW,B LIGOR,P.A.	1976	I	0.63-3.39	310	SINGLE CRYSTAL; DISC SPECIMEN; 1.90CM DIAMETER, 1CM TO 2.5CM THICK; DN/DT DETERMINED FOR 3 SPECTRAL LINES BY OBSERVING THE INTERFERENCE FRINGE CHANGES AND THE CORRESPONDING TEMPERATURE CHANGES; DATA EXTRACTED FROM A TABLE; UNCERTAINTY OF DN/DT ABOUT 0.4X10 ⁻⁵ K\$\$.
4	59	LIPSON,H.G. ET AL.	1976	I	0.63-3.39	330	SIMILAR TO ABOVE BUT AT A HIGHER TEMPERATURE OF 330K; UNCERTAINTY OF DN/DT 0.4X10 ⁻⁵ K\$\$.
5	59	LIPSON,H.G. ET AL.	1976	I	0.63-3.39	350	SIMILAR TO ABOVE BUT AT A HIGHER TEMPERATURE OF 350K; UNCERTAINTY OF DN/DT 0.4X10 ⁻⁵ K\$\$.
6	60	HARRIS,R.J. JOHNSTON,G.T. KEPPEL,G.A. KROK,P.C.,MUKAI,H.	1977	I	0.63-3.39	318	POLYCRYSTALLINE; OBTAINED FROM THE HARSHAW CHEMICAL CO.; PLATE SPECIMEN; DN/DT DETERMINED DIRECTLY FOR 3 SPECTRAL LINES BY OBSERVING THE FIZEAU INTERFERENCE FRINGE CHANGES AND THE CORRESPONDING TEMPERATURE CHANGES; MEASUREMENTS MADE FROM 298 TO 338K. THE AVERAGED VALUES OF DN/DT WERE GIVEN; DATA EXTRACTED FROM A TABLE.
7	92	TSAY,Y.F. LIPSON,H.G. LIGOR,P.A.	1977	I	0.32-3.39	310	SINGLE CRYSTAL; DISC SPECIMEN; 1.90CM DIAMETER, 1.27CM THICK; DN/DT DETERMINED BY OBSERVING THE INTERFERENCE FRINGE CHANGES AND THE CORRESPONDING TEMPERATURE CHANGES DATA EXTRACTED FROM A FIGURE; UNCERTAINTY OF DN/DT ABOUT 1.0X10 ⁻⁵ K\$\$.

TABLE 32. EXPERIMENTAL TEMPERATURE DERIVATIVE OF REFRACTIVE INDEX OF BARIUM FLUORIDE (WAVELENGTH DEPENDENCE)
 [WAVELENGTH, λ , μm ; TEMPERATURE, T , K; TEMPERATURE DERIVATIVE OF REFRACTIVE INDEX, dn/dT , 10^{-6}K^{-1}]

λ	dn/dT	λ	dn/dT
DATA SET 1			DATA SET 6
$T = 308.0$			$T = 318.0$
0.404656	-15.05	0.6328	-16.4
0.435834	-15.00	1.15	-16.8
0.486132	-15.15	3.39	-16.3
0.546074	-15.20		
0.589262	-15.22		
0.656279	-15.23		
0.667814	-15.25		
0.706518	-15.28	0.325	-15.7
0.767858	-15.45	0.4416	-16.3
		0.6328	-16.8
DATA SET 2			1.15 -17.2
$T = 296.0$			3.39 -16.8
0.26-0.4	-11.0		
0.40-0.7	-15.0		
0.70-9.7	-17.0		
10.35	-9.0		
DATA SET 3			
$T = 310.0$			
0.6328	-16.7		
1.15	-17.1		
3.39	-16.8		
DATA SET 4			
$T = 330.0$			
0.6328	-17.3		
1.15	-17.5		
3.39	-17.3		
DATA SET 5			
$T = 350.0$			
0.6328	-17.9		
1.15	-17.8		
3.39	-17.6		

H. H. LI

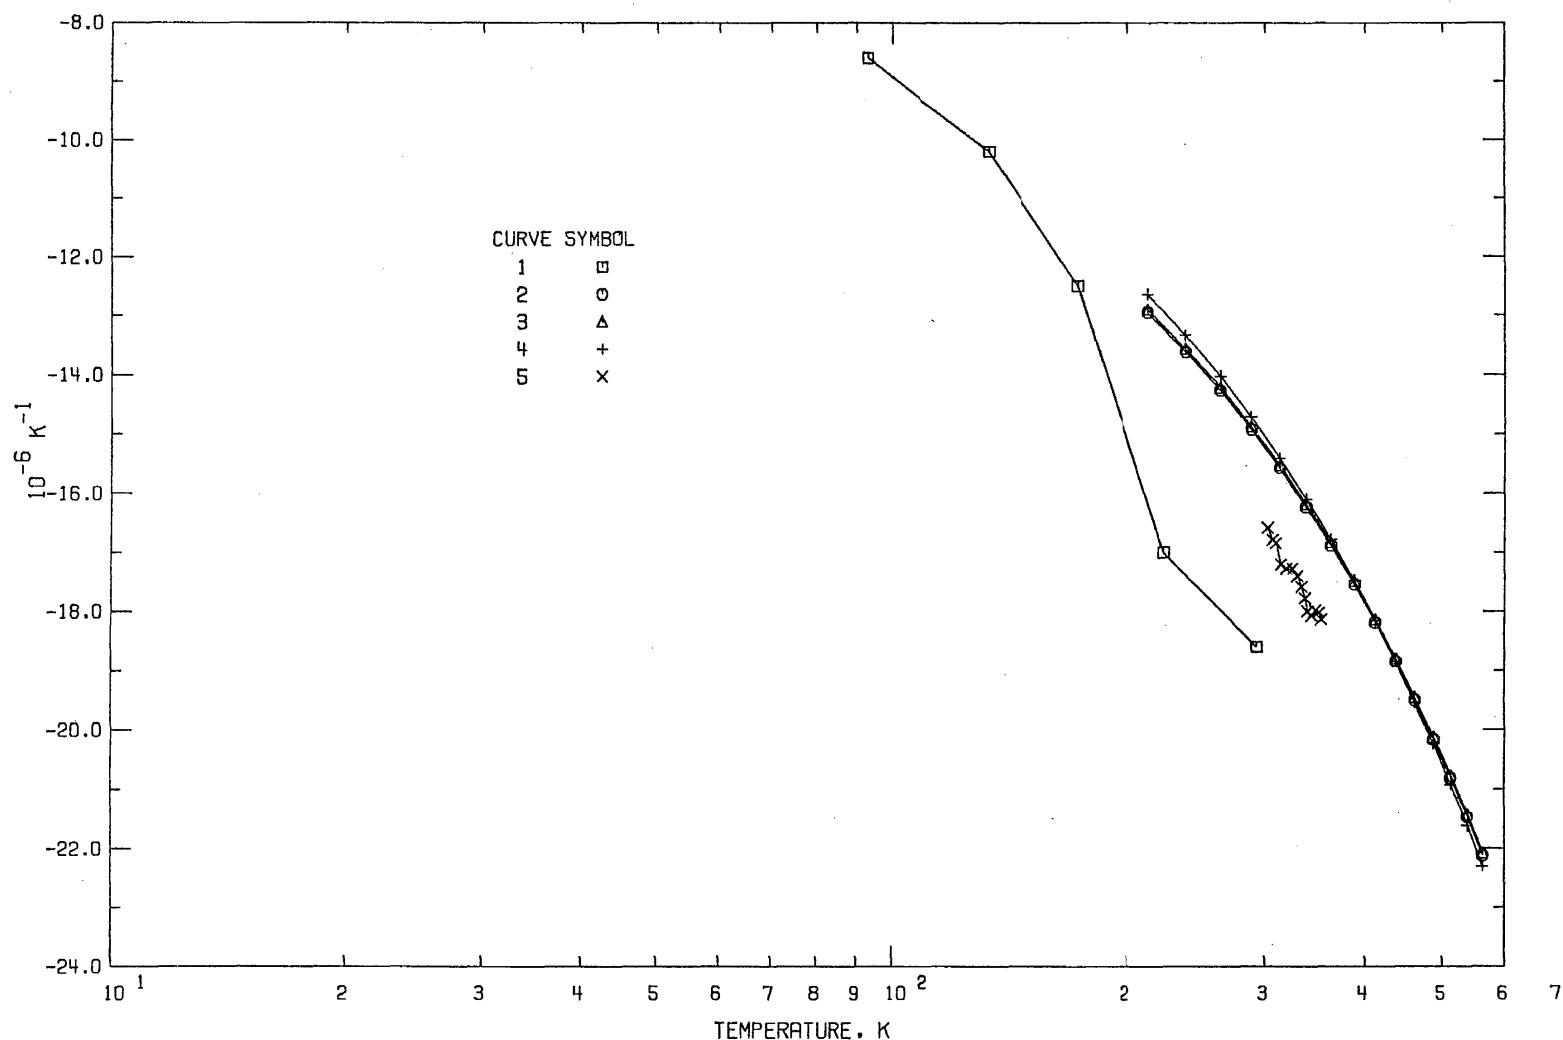


FIGURE 20. TEMPERATURE DERIVATIVE OF REFRACTIVE INDEX OF BARIUM FLUORIDE (TEMPERATURE DEPENDENCE).

TABLE 33. MEASUREMENT INFORMATION ON THE TEMPERATURE DERIVATIVE OF REFRACTIVE INDEX OF BARIUM FLUORIDE (TEMPERATURE DEPENDENCE)

DATA SET NO.	REF. NO.	AUTHOR(S)	YEAR	METHOD USED	WAVELENGTH RANGE, μm	TEMP. K	SPECIFICATIONS AND REMARKS
1	47	HOUSTON, T.W. JOHNSON, L.F. KISLIUK, P. WALSH, D.J.	1963	D	0.5461	93-293	SINGLE CRYSTAL; HIGH PURITY; PRISMATIC SPECIMEN; POLISHED SURFACES FLAT TO 1/2 WAVELENGTH OF 0.535 MICROMETER LINE; REFRACTIVE INDEX DETERMINED BY MINIMUM DEVIATION METHOD; DN/DT DETERMINED USING INDICES MEASURED AT 93 TO 293K, FOR 0.5461 MICROMETER LINE; DN/DT VALUES FOR 1.014 MICROMETER ARE THE SAME AS THIS SET; DATA EXTRACTED FROM A TABLE.
2	68	SELEZNEVA, A.M.	1969	I	0.656	213-573	SYNTHETIC CRYSTAL; PRODUCED IN THE SOVIET UNION; WELL ANNEALED; TEMPERATURE COEFFICIENT OF REFRACTIVE INDEX DETERMINED BY INTERFERENCE METHOD; EMPIRICAL FORMULA PROPOSED FOR CALCULATION OF DN/DT; DATA EXTRACTED BY EVALUATING A GIVEN EQUATION.
3	68	SELEZNEVA, A.M.	1969	I	0.589	213-573	SIMILAR TO ABOVE BUT FOR WAVELENGTH 0.589 MICROMETERS.
4	68	SELEZNEVA, A.M.	1969	I	0.486	213-573	SIMILAR TO ABOVE BUT FOR WAVELENGTH 0.486 MICROMETERS.
5	59	LIPSON, H.G. TSAY, Y.F. BENDOW, B LIGOR, P.A.	1976	I	0.6328	300-353	SINGLE CRYSTAL; DISC SPECIMEN; 1.90CM DIAMETER, 1CM TO 2.5CM THICK; DN/DT DETERMINED BY OBSERVING THE INTERFERENCE FRINGE CHANGES AND THE CORRESPONDING TEMPERATURE CHANGES; DATA EXTRACTED FROM A FIGURE; UNCERTAINTY OF DN/DT ABOUT $0.5 \times 10^{-5} \text{ K}^{-1}$.

H. H. LI

TABLE 34. EXPERIMENTAL TEMPERATURE DERIVATIVE OF REFRACTIVE INDEX OF BARIUM FLUORIDE (TEMPERATURE DEPENDENCE)
 [WAVELENGTH, λ , μm ; TEMPERATURE, T, K; TEMPERATURE DERIVATIVE OF REFRACTIVE INDEX, dn/dT , 10^{-6}K^{-1}]

T	dn/dT	T	dn/dT	T	dn/dT				
DATA SET 1									
$\lambda = 0.546$									
93.0	-8.6	488.0	-20.11	352.821	-18.140				
133.0	-10.2	513.0	-20.76						
173.0	-12.5	538.0	-21.42						
223.0	-17.0	563.0	-22.07						
293.0	-18.6	DATA SET 3 (CONT.)							
		$\lambda = 0.486$							
DATA SET 2									
$\lambda = 0.656$									
213.0	-12.95	213.0	-12.64						
238.0	-13.61	238.0	-13.33						
263.0	-14.26	263.0	-14.02						
288.0	-14.92	288.0	-14.71						
313.0	-15.57	313.0	-15.40						
338.0	-16.23	338.0	-16.09						
363.0	-16.88	363.0	-16.78						
388.0	-17.54	388.0	-17.47						
413.0	-18.19	413.0	-18.16						
438.0	-18.85	438.0	-18.85						
463.0	-19.50	463.0	-19.54						
488.0	-20.16	488.0	-20.23						
513.0	-20.81	513.0	-20.92						
538.0	-21.47	538.0	-21.61						
563.0	-22.12	563.0	-22.30						
DATA SET 5									
$\lambda = 0.632$									
DATA SET 3									
$\lambda = 0.589$									
213.0	-12.90	302.564	-16.580						
238.0	-13.56	306.462	-16.780						
263.0	-14.21	309.949	-16.840						
288.0	-14.87	314.667	-17.200						
313.0	-15.52	320.000	-17.280						
338.0	-16.18	325.538	-17.280						
363.0	-16.83	329.846	-17.400						
388.0	-17.49	333.538	-17.580						
413.0	-18.14	337.231	-17.780						
438.0	-18.80	339.692	-18.000						
463.0	-19.45	343.590	-18.080						
		347.282	-17.980						
		350.359	-18.020						

TABLE 35. COMPARISON OF DISPERSION EQUATIONS PROPOSED FOR BaF₂

Source	Wavelength and Temperature Ranges	Dispersion Equation λ in μm ; ν in cm^{-1}
Kaiser, W., Spitzer, W.G., Kaiser, R.H., and Howarth, L.E. 1962	10-80 μm	$n^2 - k^2 = \epsilon_{\infty} + \sum 4\pi \rho_i \nu_i^2 \frac{\nu_i^2 - \nu^2}{(\nu_i^2 - \nu^2)^2 + \gamma_i^2 \nu^2 \nu_i^2}$ $2nk = \sum_i 4\pi \rho_i \nu_i^2 \frac{\gamma_i \nu \nu_i}{(\nu_i^2 - \nu^2)^2 + \gamma_i^2 \nu^2 \nu_i^2} *$
Malitson, I.H. 1964	0.2652-10.346 μm 298 K	$n^2 = 1 + \frac{0.643356 \lambda^2}{\lambda^2 - (0.057789)^2} + \frac{0.506762 \lambda^2}{\lambda^2 - (0.10968)^2} + \frac{3.8261 \lambda^2}{\lambda^2 - (46.3864)^2}$
Selezneva, 1969	213-573 K	$\frac{dn}{dt} = a + 2b (T - 293.0)^\dagger$
Present work 1977	0.15-15.0 μm 293 K	$n^2 = 1.33973 + \frac{0.81070 \lambda^2}{\lambda^2 - (0.10065)^2} + \frac{0.19652 \lambda^2}{\lambda^2 - (29.87)^2} + \frac{4.52469 \lambda^2}{\lambda^2 - (53.82)^2}$

* i = 1, 2; $4\pi \rho_1 = 4.50$, $4\pi \rho_2 = 0.07$; $\nu_1 = 184 \text{ cm}^{-1}$, $\nu_2 = 278 \text{ cm}^{-1}$; $\gamma_1 = 0.020$, $\gamma_2 = 0.30$.

† For $\lambda = 0.656 \mu\text{m}$, $a = -15.05 \times 10^{-6}$, $b = -1.31 \times 10^{-6}$; for $\lambda = 0.589 \mu\text{m}$, $a = -15.00 \times 10^{-6}$, $b = -1.31 \times 10^{-6}$; for $\lambda = 0.486 \mu\text{m}$, $a = -14.85 \times 10^{-6}$, $b = -1.38 \times 10^{-6}$.

3.4. Magnesium Fluoride, MgF_2

Magnesium fluoride is an anisotropic ionic crystal having a rutile structure. It has a large forbidden gap and hence it is transparent in the UV and is used as an optical material in this spectral region. It is of particular interest in vacuum UV spectroscopy because of its use as a reflective coating for mirrors and gratings. It has been found that a MgF_2 layer of suitable thickness, evaporated onto aluminum, retards oxidation of the aluminum and greatly increases the reflectance in the vacuum UV. The application of MgF_2 to an aluminum-surfaced replica grating results in a much improved efficiency down to 0.11 micrometer.

The crystal can be grown in vacuum using the Stockbarger technique. Large specimens with weight over 2 kg and diameter of about 10 cm are available. MgF_2 is a uniaxial positive crystal and is transparent from 0.11 to 7.5 micrometers. When used as a reflector, it is highly polarizing for wavelengths less than 0.124 micrometer.

Although this material is transparent in the infrared up to 7.5 micrometers, measurements of refractive index were carried out only for the ultraviolet and visible regions. This fact can be realized from tables 37 and 38, in which we have compiled 38 data sets, including a few sets of thin film data for comparison. It is clear from the table that the majority of the measurements are either for vacuum ultraviolet beyond the transparent region or for thin films. For the transparent region, Steinmetz et al. [77] reported refractive indices of ordinary and extraordinary rays for four spectral lines from 0.178 to 0.2894 micrometer. Duncanson et al. [18] measured the refractive indices for the two rays at 18 wavelengths in the visible spectrum (0.4–0.7 micrometer). In our compilation, 0.7 micrometer is the longest wavelength at which both n_o and n_e have been measured. No measurement of n_o and n_e beyond the visible in the infrared region has been reported. However, refractive indices for the infrared region from 1.0 to 9.0 micrometers are available for IRTRAN 1, a hot pressed polycrystalline magnesium fluoride.

As mentioned above, the available data on the refractive indices of single crystals are very scanty. The crystal is transparent for a quite wide spectral region, about 7.5 micrometers in width, yet measurements have been carried out only over a range 0.5 micrometer in width, less than 7 percent of the total transparent region. Although Duncanson's values are accurate and reliable, the spectral range covered is narrow. Furthermore, the dispersion in the refractive indices is small, from 1.38359 to 1.37599 for the ordinary ray and from 1.39566 to 1.38771 for the extraordinary ray, not suitable for a wide range prediction. As a result, the Hartmann interpolation formulae (proposed by Duncanson et al. [18]) $n = 1.36957 + 0.0035821/(\lambda - 0.14925)$ for the ordinary ray and $n = 1.38100 + 0.0037415/(\lambda - 0.14947)$ for the extraordinary ray, are good only for the narrow spectral region from 0.4 to 0.7 micrometer.

In the present work, the available data are only a part of the input information needed for a Sellmeier dispersion equation. In order to get meaningful predictions for the whole transparent region, the key parameters for the dispersion equation are, for each ray, the dielectric constant, the effective UV resonant wavelength, the infrared resonant wavelength and if possible the strengths of each of the resonant wavelengths. It is fortunate

indeed that these key parameters, although not having been used for such purposes, are available in the literature (Barker [14] see tables 4, 5 and 6). Introduction of the key parameters into the Sellmeier equation yields fits to available data that are as close as the fits to the Hartmann formulae. The resulting equations for single crystal MgF_2 at 293 K in the transparent region, 0.14–7.5 micrometers, are:

$$n^2 = 1.27620 + \frac{0.60961 \lambda^2}{\lambda^2 - 0.08636^2} + \frac{0.0080 \lambda^2}{\lambda^2 - 18.0^2} + \frac{2.14973 \lambda^2}{\lambda^2 - 25.0^2} \quad (o\text{-ray}), \quad (24)$$

$$n^2 = 1.25385 + \frac{0.66405 \lambda^2}{\lambda^2 - 0.08504^2} + \frac{1.0899 \lambda^2}{\lambda^2 - 22.2^2} + \frac{0.1816 \lambda^2}{\lambda^2 - 24.4^2} + \frac{2.1227 \lambda^2}{\lambda^2 - 40.6^2} \quad (e\text{-ray}), \quad (25)$$

where λ is in units of micrometers. It should be noted that Barker's values have been modified so that the difference of refractive index between ordinary and extraordinary ray agree with the observed birefringence except in the region where anomalies of birefringence occur. Barker's values were so modified that the ratios of the parameters remained unchanged. For the available data of IRTRAN 1 we simply fit the data to a Sellmeier type quotation, to obtain

$$n^2 = 1.79079 + \frac{0.10822 \lambda^2}{\lambda^2 - 0.16733^2} + \frac{2.7814 \lambda^2}{\lambda^2 - 25.54^2} \quad (\text{IRTRAN 1}). \quad (26)$$

This equation is found to be as good as the Herzberger dispersion equation given in [20].

Equations (24) to (26) were used to generate the reference data given in the table of recommended values. Values of $dn/d\lambda$ were simply evaluated by taking the first derivative of these equations. Although the values of n are given to the fourth decimal place, this does not reflect the degree of accuracy and the extent of reliability. The values are so given simply for smoothness of tabulation. For the proper use of the tabulated values the reader should follow the criteria given below.

For ordinary and extraordinary rays:

Wavelength range micrometers	Estimated uncertainty, \pm
0.15–0.20	0.01
0.20–0.30	0.005
0.30–0.70	0.0001
0.70–1.00	0.003
1.00–5.00	0.005
5.00–10.0	0.01

For IRTRAN 1:

0.18–0.30	>0.05
0.30–1.00	>0.01
1.00–10.0	0.001

TABLE 36. RECOMMENDED VALUES ON THE REFRACTIVE INDEX AND ITS WAVELENGTH
DERIVATIVE FOR MAGNESIUM FLUORIDE AT 293K*

λ μm	Extraordinary				λ μm	Extraordinary				λ μm	IRTRAN 1		
	Ordinary Ray	Ray	IRTRAN 1	Ordinary Ray		Ray	IRTRAN 1	Ordinary Ray	Ray		n	$-dn/d\lambda$	
	n_o	$-dn_o/d\lambda$	n_e	$-dn_e/d\lambda$		n_c	$-dn_o/d\lambda$	n_e	$-dn_e/d\lambda$		n	$-dn/d\lambda$	
0.150	1.4792	2.0378	1.4941	2.0685	---	---	0.220	1.4130	0.4228	1.4263	0.4376	1.4308	1.1200
0.152	1.4752	1.9137	1.4900	1.9448	---	---	0.222	1.4122	0.4090	1.4254	0.4235	1.4286	1.0399
0.154	1.4715	1.8003	1.4863	1.8315	---	---	0.224	1.4114	0.3959	1.4246	0.4100	1.4266	0.9680
0.156	1.4680	1.6962	1.4827	1.7274	---	---	0.226	1.4106	0.3834	1.4238	0.3971	1.4248	0.9032
0.158	1.4647	1.6005	1.4794	1.6315	---	---	0.228	1.4098	0.3714	1.4230	0.3847	1.4230	0.8445
0.160	1.4616	1.5124	1.4762	1.5431	---	---	0.230	1.4091	0.3599	1.4222	0.3729	1.4214	0.7914
0.162	1.4587	1.4310	1.4732	1.4613	---	---	0.232	1.4084	0.3489	1.4215	0.3616	1.4199	0.7430
0.164	1.4559	1.3557	1.4703	1.3856	---	---	0.234	1.4077	0.3383	1.4208	0.3508	1.4184	0.6989
0.166	1.4532	1.2860	1.4676	1.3153	---	---	0.236	1.4071	0.3282	1.4201	0.3404	1.4171	0.6585
0.168	1.4507	1.2212	1.4651	1.2500	---	---	0.238	1.4064	0.3185	1.4194	0.3304	1.4158	0.6214
0.170	1.4483	1.1610	1.4626	1.1892	---	---	0.240	1.4058	0.3093	1.4188	0.3208	1.4146	0.5874
0.172	1.4461	1.1049	1.4603	1.1325	---	---	0.242	1.4052	0.3003	1.4181	0.3116	1.4134	0.5560
0.174	1.4439	1.0526	1.4581	1.0795	---	---	0.244	1.4046	0.2918	1.4175	0.3028	1.4123	0.5270
0.176	1.4419	1.0037	1.4560	1.0300	---	---	0.246	1.4040	0.2835	1.4169	0.2943	1.4113	0.5002
0.178	1.4399	0.9579	1.4540	0.9837	---	---	0.248	1.4034	0.2756	1.4163	0.2861	1.4103	0.4753
0.180	1.4380	0.9151	1.4521	0.9402	1.6085	17.5092	0.250	1.4029	0.2680	1.4158	0.2782	1.4094	0.4522
0.182	1.4362	0.8749	1.4502	0.8994	1.5780	13.3075	0.252	1.4024	0.2607	1.4152	0.2707	1.4085	0.4308
0.184	1.4345	0.8372	1.4485	0.8610	1.5544	10.4573	0.254	1.4019	0.2536	1.4147	0.2634	1.4077	0.4107
0.186	1.4329	0.8017	1.4468	0.8249	1.5356	8.4344	0.256	1.4014	0.2468	1.4142	0.2564	1.4069	0.3920
0.188	1.4313	0.7683	1.4451	0.7909	1.5203	6.9464	0.258	1.4009	0.2403	1.4137	0.2496	1.4061	0.3746
0.190	1.4298	0.7368	1.4436	0.7589	1.5076	5.8199	0.260	1.4004	0.2340	1.4132	0.2431	1.4054	0.3582
0.192	1.4284	0.7071	1.4421	0.7286	1.4958	4.9464	0.262	1.3999	0.2279	1.4127	0.2368	1.4047	0.3429
0.194	1.4270	0.6791	1.4407	0.7000	1.4877	4.2554	0.264	1.3995	0.2220	1.4122	0.2307	1.4040	0.3285
0.196	1.4256	0.6526	1.4393	0.6729	1.4797	3.6993	0.266	1.3990	0.2164	1.4118	0.2249	1.4034	0.3149
0.198	1.4244	0.6275	1.4380	0.6473	1.4728	3.2452	0.268	1.3986	0.2109	1.4113	0.2192	1.4028	0.3022
0.200	1.4231	0.6038	1.4367	0.6231	1.4667	2.8695	0.270	1.3982	0.2056	1.4109	0.2138	1.4022	0.2902
0.202	1.4220	0.5812	1.4355	0.6000	1.4613	2.5551	0.272	1.3978	0.2005	1.4105	0.2085	1.4016	0.2789
0.204	1.4208	0.5599	1.4343	0.5782	1.4554	2.2895	0.274	1.3974	0.1956	1.4101	0.2034	1.4010	0.2682
0.206	1.4197	0.5396	1.4332	0.5574	1.4521	2.0630	0.276	1.3970	0.1908	1.4097	0.1985	1.4005	0.2581
0.208	1.4187	0.5204	1.4321	0.5377	1.4482	1.8683	0.278	1.3966	0.1862	1.4093	0.1937	1.4000	0.2485
0.210	1.4176	0.5021	1.4310	0.5190	1.4446	1.6997	0.280	1.3963	0.1818	1.4089	0.1891	1.3995	0.2394
0.212	1.4166	0.4846	1.4300	0.5011	1.4414	1.5528	0.282	1.3959	0.1775	1.4085	0.1847	1.3991	0.2309
0.214	1.4157	0.4680	1.4290	0.4841	1.4384	1.4239	0.284	1.3956	0.1733	1.4081	0.1804	1.3986	0.2227
0.216	1.4148	0.4522	1.4281	0.4678	1.4357	1.3103	0.286	1.3952	0.1693	1.4078	0.1762	1.3982	0.2150
0.218	1.4139	0.4371	1.4272	0.4524	1.4331	1.2097	0.288	1.3949	0.1654	1.4074	0.1722	1.3977	0.2076

TABLE 36. RECOMMENDED VALUES ON THE REFRACTIVE INDEX AND ITS WAVELENGTH DERIVATIVE FOR MAGNESIUM FLUORIDE AT 293K (CONTINUED)*

λ μm	Extraordinary				Extraordinary			
	Ordinary Ray n_o	Ray $-dn_o/d\lambda$	IRTRAN 1 n	$-dn/d\lambda$	Ordinary Ray n_c	Ray $-dn_o/d\lambda$	IRTRAN 1 n	$-dn/d\lambda$
0.290	1.3948	0.1616	1.4071	0.1682	1.3973	0.2006	0.500	1.3797
0.292	1.3942	0.1580	1.4068	0.1644	1.3969	0.1940	0.510	1.3794
0.294	1.3939	0.1544	1.4064	0.1608	1.3966	0.1876	0.520	1.3792
0.296	1.3936	0.1510	1.4061	0.1572	1.3962	0.1816	0.530	1.3789
0.298	1.3933	0.1476	1.4058	0.1537	1.3958	0.1758	0.540	1.3787
0.300	1.3930	0.1444	1.4055	0.1504	1.3955	0.1703	0.550	1.3784
0.305	1.3923	0.1367	1.4048	0.1424	1.3947	0.1576	0.560	1.3782
0.310	1.3917	0.1296	1.4041	0.1350	1.3939	0.1462	0.570	1.3780
0.315	1.3910	0.1230	1.4034	0.1282	1.3932	0.1360	0.580	1.3778
0.320	1.3904	0.1168	1.4028	0.1218	1.3925	0.1267	0.590	1.3776
0.325	1.3899	0.1111	1.4022	0.1158	1.3919	0.1184	0.600	1.3775
0.330	1.3893	0.1057	1.4016	0.1102	1.3914	0.1108	0.620	1.3771
0.335	1.3888	0.1007	1.4011	0.1050	1.3908	0.1039	0.640	1.3768
0.340	1.3883	0.0960	1.4006	0.1001	1.3903	0.0976	0.660	1.3765
0.345	1.3878	0.0916	1.4001	0.0956	1.3898	0.0918	0.680	1.3763
0.350	1.3874	0.0875	1.3996	0.0913	1.3894	0.0865	0.700	1.3760
0.355	1.3870	0.0836	1.3992	0.0873	1.3890	0.0816	0.720	1.3758
0.360	1.3866	0.0800	1.3988	0.0835	1.3886	0.0772	0.740	1.3756
0.365	1.3862	0.0766	1.3983	0.0799	1.3882	0.0730	0.760	1.3754
0.370	1.3858	0.0733	1.3980	0.0766	1.3878	0.0692	0.780	1.3752
0.375	1.3854	0.0703	1.3976	0.0734	1.3875	0.0657	0.800	1.3750
0.380	1.3851	0.0674	1.3972	0.0704	1.3872	0.0624	0.820	1.3749
0.385	1.3848	0.0647	1.3969	0.0676	1.3869	0.0593	0.840	1.3747
0.390	1.3844	0.0621	1.3965	0.0649	1.3866	0.0565	0.860	1.3746
0.395	1.3841	0.0597	1.3962	0.0624	1.3863	0.0538	0.880	1.3744
0.400	1.3838	0.0574	1.3959	0.0600	1.3861	0.0514	0.900	1.3743
0.410	1.3833	0.0532	1.3953	0.0556	1.3856	0.0469	0.920	1.3741
0.420	1.3828	0.0494	1.3948	0.0516	1.3851	0.0430	0.940	1.3740
0.430	1.3823	0.0460	1.3943	0.0480	1.3847	0.0395	0.960	1.3739
0.440	1.3818	0.0428	1.3938	0.0448	1.3843	0.0364	0.980	1.3738
0.450	1.3814	0.0400	1.3934	0.0419	1.3840	0.0337	1.000	1.3736
0.460	1.3810	0.0374	1.3930	0.0392	1.3836	0.0313	1.050	1.3733
0.470	1.3807	0.0351	1.3926	0.0367	1.3833	0.0291	1.100	1.3731
0.480	1.3803	0.0330	1.3923	0.0345	1.3831	0.0271	1.150	1.3728
0.490	1.3800	0.0310	1.3919	0.0325	1.3828	0.0253	1.200	1.3726

TABLE 36. RECOMMENDED VALUES ON THE REFRACTIVE INDEX AND ITS WAVELENGTH

DERIVATIVE FOR MAGNESIUM FLUORIDE AT 293K (CONTINUED)*

λ μm	Extraordinary				λ μm	Extraordinary				λ μm	IRTRAN 1		
	Ordinary Ray	Ray	IRTRAN 1	n		Ordinary Ray	Ray	IRTRAN 1	n		n	$-dn/d\lambda$	
	n_o	$-dn_o/d\lambda$	n_e	$-dn_e/d\lambda$		n_o	$-dn_o/d\lambda$	n_e	$-dn_e/d\lambda$		n	$-dn/d\lambda$	
1.250	1.3723	0.0048	1.3838	0.0052	1.3763	0.0050	3.000	1.3618	0.0079	1.3724	0.0086	1.3639	0.0097
1.300	1.3721	0.0048	1.3835	0.0051	1.3760	0.0050	3.050	1.3614	0.0081	1.3720	0.0088	1.3634	0.0098
1.350	1.3718	0.0047	1.3833	0.0051	1.3758	0.0051	3.100	1.3610	0.0082	1.3716	0.0089	1.3629	0.0100
1.400	1.3716	0.0047	1.3830	0.0051	1.3755	0.0051	3.150	1.3606	0.0083	1.3711	0.0091	1.3624	0.0102
1.450	1.3714	0.0047	1.3828	0.0051	1.3753	0.0052	3.200	1.3602	0.0085	1.3706	0.0092	1.3619	0.0104
1.500	1.3711	0.0048	1.3825	0.0051	1.3750	0.0053	3.250	1.3598	0.0086	1.3702	0.0094	1.3614	0.0105
1.550	1.3709	0.0048	1.3822	0.0052	1.3747	0.0054	3.300	1.3593	0.0088	1.3697	0.0095	1.3609	0.0107
1.600	1.3706	0.0048	1.3820	0.0052	1.3745	0.0055	3.350	1.3589	0.0089	1.3692	0.0097	1.3603	0.0109
1.650	1.3704	0.0049	1.3817	0.0053	1.3742	0.0056	3.400	1.3584	0.0090	1.3687	0.0098	1.3598	0.0111
1.700	1.3701	0.0050	1.3814	0.0054	1.3739	0.0057	3.450	1.3580	0.0092	1.3682	0.0100	1.3592	0.0112
1.750	1.3699	0.0050	1.3812	0.0055	1.3736	0.0059	3.500	1.3575	0.0093	1.3677	0.0101	1.3586	0.0114
1.800	1.3696	0.0051	1.3809	0.0056	1.3733	0.0060	3.550	1.3570	0.0095	1.3672	0.0103	1.3581	0.0116
1.850	1.3694	0.0052	1.3806	0.0057	1.3730	0.0061	3.600	1.3566	0.0096	1.3667	0.0105	1.3575	0.0118
1.900	1.3691	0.0053	1.3803	0.0058	1.3727	0.0062	3.650	1.3561	0.0098	1.3662	0.0106	1.3569	0.0120
1.950	1.3688	0.0054	1.3800	0.0059	1.3724	0.0064	3.700	1.3556	0.0099	1.3656	0.0108	1.3563	0.0121
2.000	1.3686	0.0055	1.3797	0.0060	1.3720	0.0065	3.750	1.3551	0.0101	1.3651	0.0109	1.3557	0.0123
2.050	1.3683	0.0056	1.3794	0.0061	1.3717	0.0067	3.800	1.3546	0.0102	1.3645	0.0111	1.3550	0.0125
2.100	1.3680	0.0057	1.3791	0.0062	1.3714	0.0068	3.850	1.3541	0.0104	1.3640	0.0113	1.3544	0.0127
2.150	1.3677	0.0058	1.3788	0.0063	1.3710	0.0070	3.900	1.3535	0.0105	1.3634	0.0114	1.3538	0.0129
2.200	1.3674	0.0059	1.3785	0.0064	1.3707	0.0071	3.950	1.3530	0.0107	1.3628	0.0116	1.3531	0.0131
2.250	1.3671	0.0060	1.3782	0.0066	1.3703	0.0073	4.000	1.3525	0.0108	1.3622	0.0117	1.3525	0.0132
2.300	1.3668	0.0062	1.3778	0.0067	1.3699	0.0074	4.050	1.3519	0.0110	1.3616	0.0119	1.3518	0.0134
2.350	1.3665	0.0063	1.3775	0.0068	1.3696	0.0076	4.100	1.3514	0.0111	1.3610	0.0121	1.3511	0.0136
2.400	1.3662	0.0064	1.3771	0.0070	1.3692	0.0077	4.150	1.3508	0.0113	1.3604	0.0122	1.3504	0.0138
2.450	1.3658	0.0065	1.3768	0.0071	1.3688	0.0079	4.200	1.3502	0.0114	1.3598	0.0124	1.3497	0.0140
2.500	1.3655	0.0066	1.3764	0.0072	1.3684	0.0080	4.250	1.3497	0.0116	1.3592	0.0126	1.3490	0.0142
2.550	1.3652	0.0068	1.3761	0.0074	1.3680	0.0082	4.300	1.3491	0.0117	1.3585	0.0128	1.3483	0.0144
2.600	1.3648	0.0069	1.3757	0.0075	1.3676	0.0084	4.350	1.3485	0.0119	1.3579	0.0129	1.3476	0.0146
2.650	1.3645	0.0070	1.3753	0.0076	1.3671	0.0085	4.400	1.3479	0.0120	1.3573	0.0131	1.3468	0.0148
2.700	1.3641	0.0071	1.3749	0.0078	1.3667	0.0087	4.450	1.3473	0.0122	1.3566	0.0133	1.3461	0.0150
2.750	1.3638	0.0073	1.3745	0.0079	1.3663	0.0088	4.500	1.3466	0.0124	1.3559	0.0134	1.3453	0.0152
2.800	1.3634	0.0074	1.3741	0.0081	1.3658	0.0090	4.550	1.3460	0.0125	1.3552	0.0136	1.3446	0.0154
2.850	1.3630	0.0075	1.3737	0.0082	1.3654	0.0092	4.600	1.3454	0.0127	1.3545	0.0138	1.3438	0.0156
2.900	1.3626	0.0077	1.3733	0.0083	1.3649	0.0093	4.650	1.3448	0.0128	1.3539	0.0140	1.3430	0.0158
2.950	1.3622	0.0078	1.3729	0.0085	1.3644	0.0095	4.700	1.3441	0.0130	1.3532	0.0141	1.3422	0.0160

TABLE 36. RECOMMENDED VALUES ON THE REFRACTIVE INDEX AND ITS WAVELENGTH DERIVATIVE FOR MAGNESIUM FLUORIDE AT 293K (CONTINUED)*

λ μm	Extraordinary				λ μm	Extraordinary					
	Ordinary Ray	Ray	IRTRAN 1	n		Ordinary Ray	Ray	IRTRAN 1	n		
	n_o	$-dn_o/d\lambda$	n_e	$-dn_e/d\lambda$		n_o	$-dn_o/d\lambda$	n_e	$-dn_e/d\lambda$		$-dn/d\lambda$
4.750	1.3434	0.0132	1.3524	0.0143	1.3414	0.0162	7.300	1.2976	0.0233	1.3027	0.0253
4.800	1.3428	0.0133	1.3517	0.0145	1.3406	0.0164	7.400	1.2953	0.0238	1.3001	0.0258
4.850	1.3421	0.0135	1.3510	0.0147	1.3398	0.0166	7.500	1.2929	0.0243	1.2975	0.0264
4.900	1.3414	0.0137	1.3502	0.0149	1.3389	0.0168	7.600	1.2904	0.0248	1.2948	0.0269
4.950	1.3407	0.0138	1.3495	0.0151	1.3381	0.0170	7.700	1.2879	0.0253	1.2921	0.0275
5.000	1.3400	0.0140	1.3487	0.0152	1.3372	0.0172	7.800	1.2854	0.0258	1.2893	0.0281
5.100	1.3386	0.0144	1.3472	0.0156	1.3355	0.0176	7.900	1.2827	0.0263	1.2865	0.0286
5.200	1.3372	0.0147	1.3456	0.0160	1.3337	0.0181	8.000	1.2801	0.0269	1.2836	0.0292
5.300	1.3357	0.0151	1.3440	0.0164	1.3319	0.0185	8.100	1.2774	0.0274	1.2806	0.0298
5.400	1.3341	0.0154	1.3423	0.0168	1.3300	0.0189	8.200	1.2746	0.0280	1.2776	0.0305
5.500	1.3326	0.0158	1.3406	0.0171	1.3281	0.0194	8.300	1.2718	0.0286	1.2745	0.0311
5.600	1.3310	0.0161	1.3389	0.0175	1.3261	0.0198	8.400	1.2689	0.0292	1.2714	0.0317
5.700	1.3293	0.0165	1.3371	0.0179	1.3241	0.0203	8.500	1.2659	0.0298	1.2682	0.0324
5.800	1.3277	0.0169	1.3353	0.0184	1.3220	0.0208	8.600	1.2629	0.0304	1.2649	0.0331
5.900	1.3259	0.0173	1.3334	0.0188	1.3199	0.0212	8.700	1.2598	0.0310	1.2615	0.0338
6.000	1.3242	0.0177	1.3315	0.0192	1.3178	0.0217	8.800	1.2567	0.0316	1.2581	0.0345
6.100	1.3224	0.0181	1.3296	0.0196	1.3156	0.0222	8.900	1.2535	0.0323	1.2546	0.0352
6.200	1.3206	0.0185	1.3276	0.0201	1.3133	0.0227	9.000	1.2502	0.0330	1.2511	0.0359
6.300	1.3187	0.0189	1.3256	0.0205	1.3110	0.0232	9.100	1.2469	0.0336	1.2474	0.0367
6.400	1.3168	0.0193	1.3235	0.0209	1.3087	0.0237	9.200	1.2435	0.0343	1.2437	0.0375
6.500	1.3148	0.0197	1.3214	0.0214	1.3063	0.0242	9.300	1.2400	0.0351	1.2399	0.0382
6.600	1.3128	0.0201	1.3192	0.0219	1.3038	0.0247	9.400	1.2365	0.0358	1.2361	0.0391
6.700	1.3108	0.0205	1.3170	0.0223	1.3013	0.0253	9.500	1.2328	0.0365	1.2321	0.0399
6.800	1.3087	0.0210	1.3147	0.0228	1.2988	0.0258	9.600	1.2292	0.0373	1.2281	0.0407
6.900	1.3066	0.0214	1.3124	0.0233	1.2961	0.0264	9.700	1.2254	0.0381	1.2240	0.0416
7.000	1.3044	0.0219	1.3101	0.0238	1.2935	0.0269	9.800	1.2215	0.0389	1.2198	0.0425
7.100	1.3022	0.0223	1.3076	0.0243	1.2907	0.0275	9.900	1.2176	0.0397	1.2154	0.0434
7.200	1.3000	0.0228	1.3052	0.0248	1.2880	0.0281	10.000	1.2136	0.0406	1.2111	0.0444
											1.1813 0.0503

* IN THIS TABLE MORE DECIMAL PLACES ARE REPORTED THAN WARRANTED MERELY FOR THE PURPOSE OF TABULAR SMOOTHNESS AND INTERNAL COMPARISON. FOR UNCERTAINTIES OF TABULATED VALUES IN VARIOUS WAVELENGTH RANGES, SEE THE TEXT OF SUBSECTION 3.4. THE NUMBER OF DIGITS WITH AN OVERSTRIKE IS NOT RELATED TO THE ACCURACY OF THE VALUES.

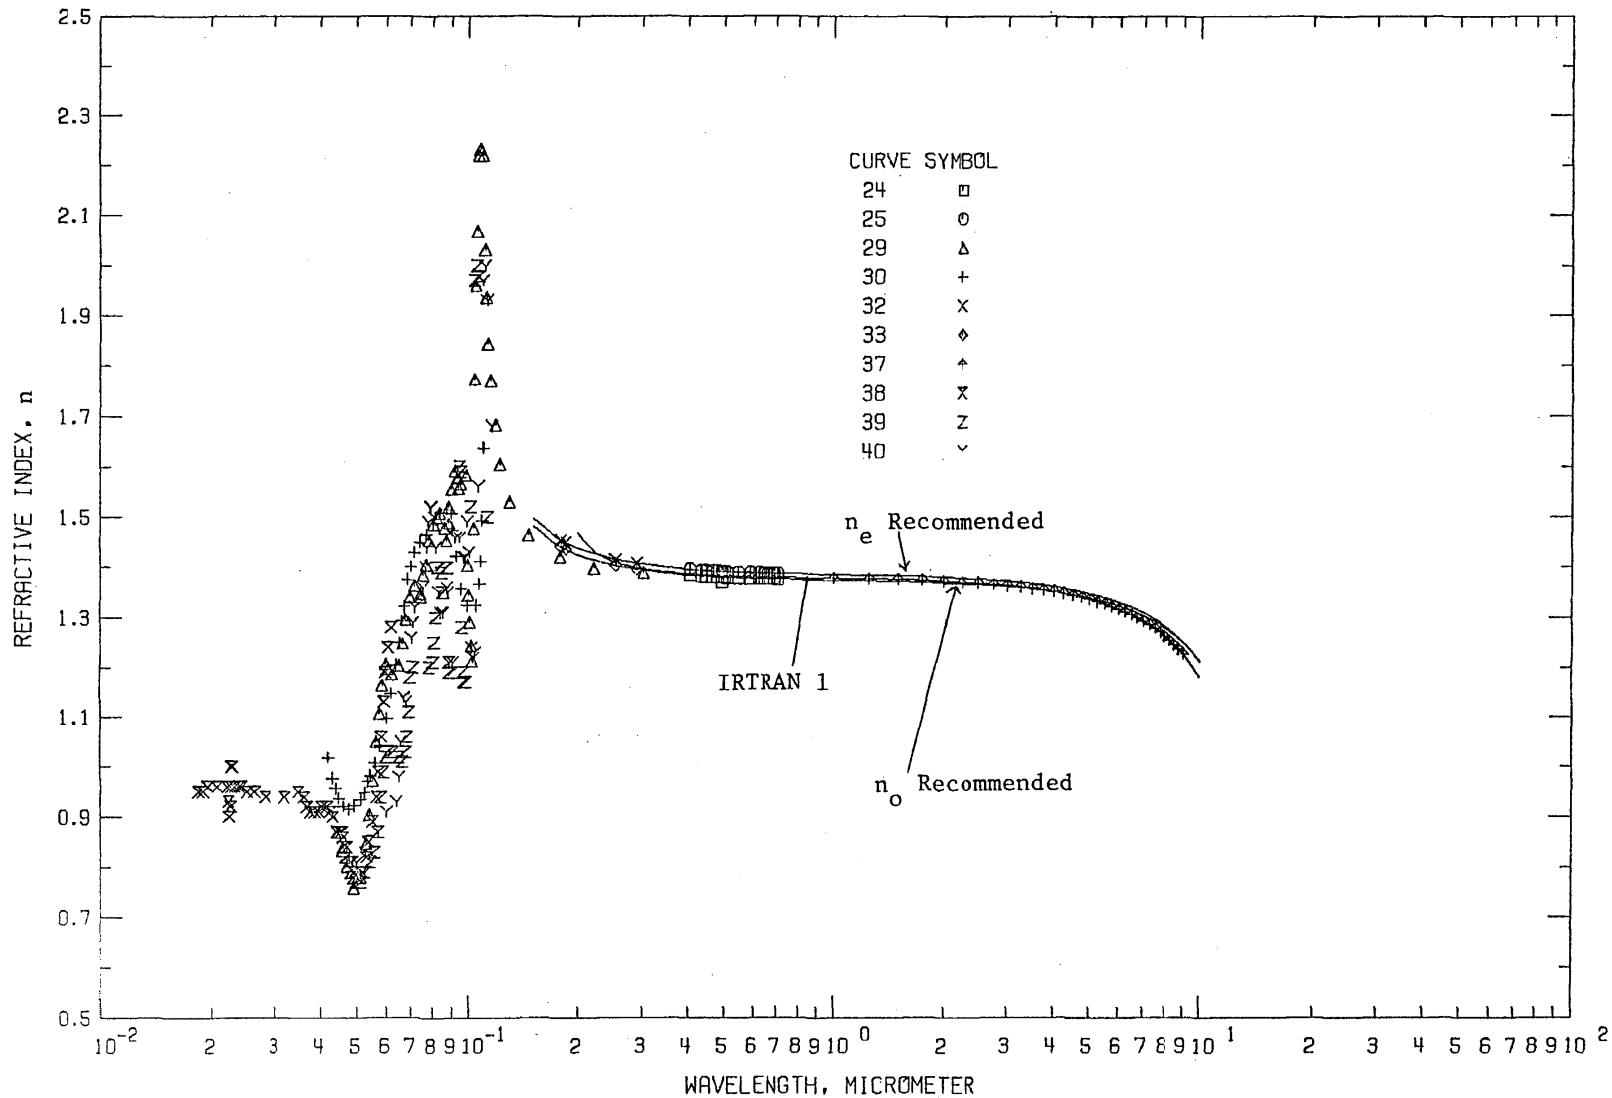


FIGURE 21. REFRACTIVE INDEX OF MAGNESIUM FLUORIDE (WAVELENGTH DEPENDENCE).

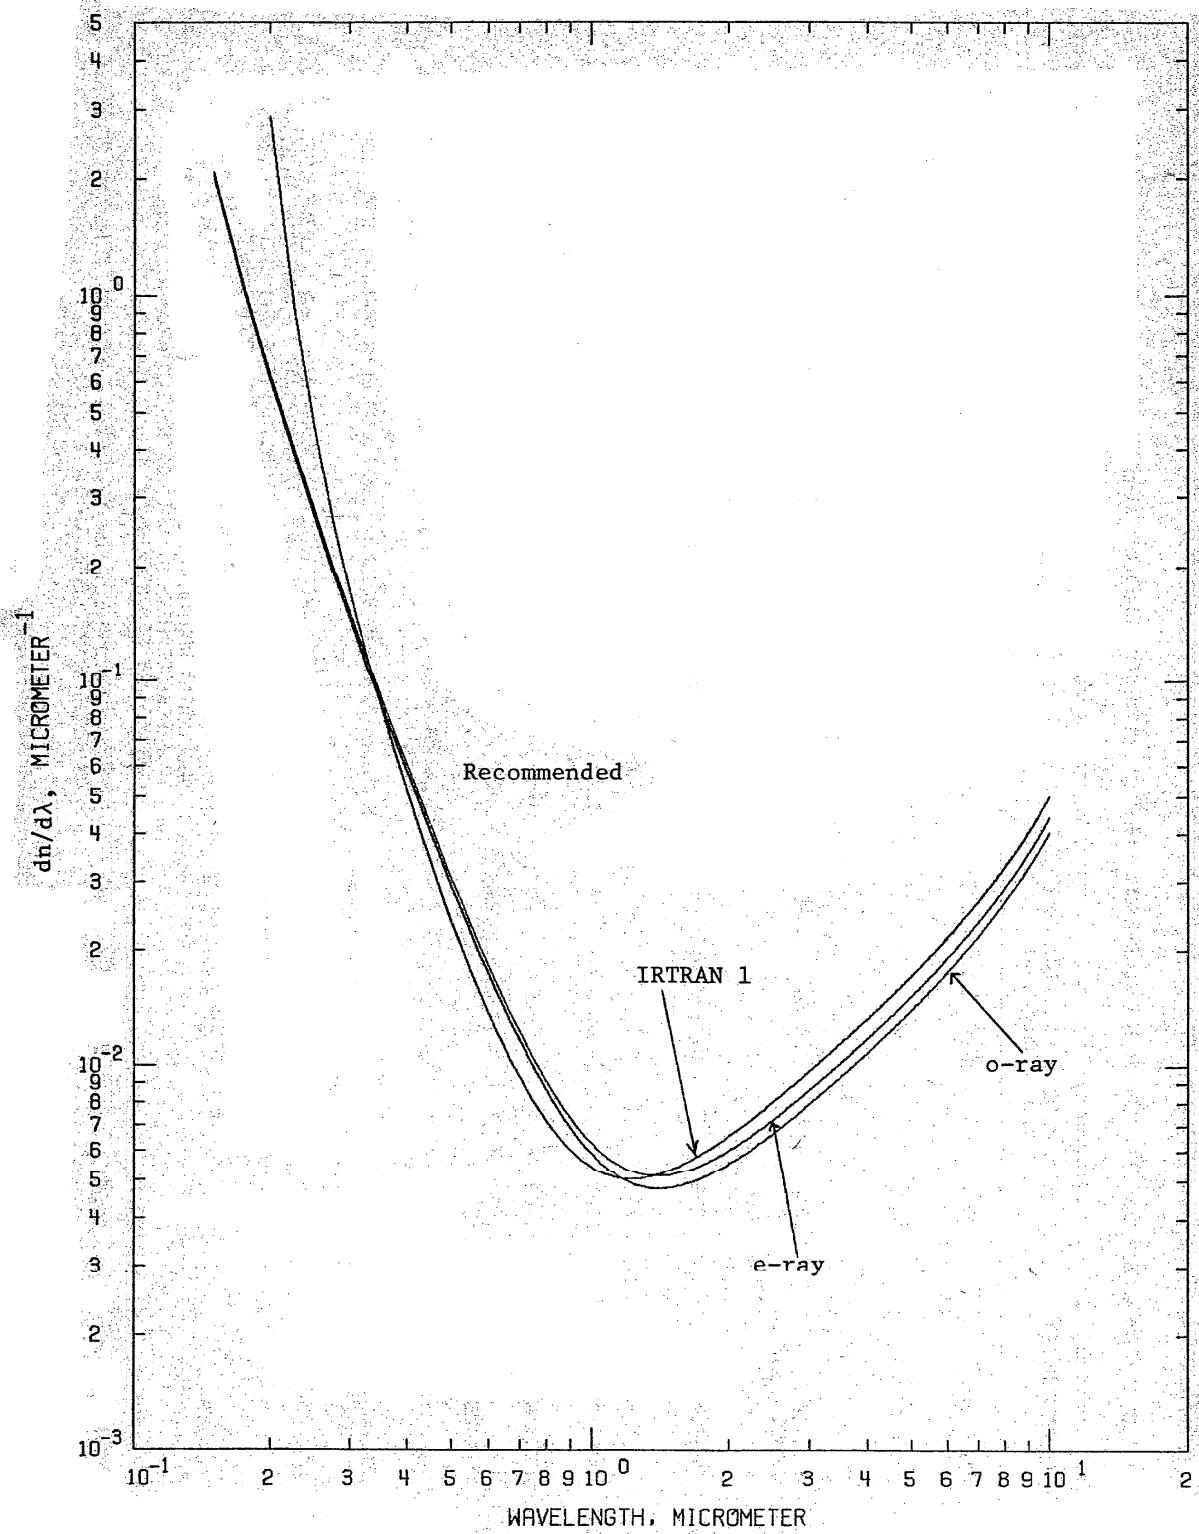


FIGURE 22. WAVELENGTH DERIVATIVE OF REFRACTIVE INDEX OF MAGNESIUM FLUORIDE.

TABLE 37. MEASUREMENT INFORMATION ON THE REFRACTIVE INDEX OF MAGNESIUM FLUORIDE (WAVELENGTH DEPENDENCE)

DATA SET NO.	REF. NO.	AUTHOR(S)	YEAR	METHOD USED	WAVELENGTH RANGE, μm	TEMP. K	SPECIFICATIONS AND REMARKS
1	69	ROOD, J.L.	1949	R	0.47-0.62	293	THIN FILM SPECIMEN OF VARIOUS THICKNESSES ON GLASS SUBSTRATE; REFRACTIVE INDEX DETERMINED BY NEAR NORMAL REFLECTION MEASUREMENT; IT WAS FOUND THAT THE INDEX OF REFRACTION OF FILMS WERE LOWER THAN THAT OF BULK MATERIAL AND CHANGING WITH AGE OF THE FILM; DATA EXTRACTED FROM A TABLE; UNCERTAINTY OF INDEX ONE UNIT OF THE THIRD DECIMAL PLACE; TEMPERATURE NOT GIVEN, 293K ASSUMED.
2	70	SCHULZ, L.G. SCHEIBNER, E.J.	1950	L	0.589	293	THIN FILM SPECIMEN OF VARIOUS THICKNESSES ON GLASS SUBSTRATE WITH SILVER OR GOLD LAYER; IT WAS FOUND THAT THE INDEX OF REFRACTION IN THE FILMS WAS THE SAME AS THAT OF THE BULK MATERIALS; TEMPERATURE NOT GIVEN, 293K ASSUMED.
3	71	MORITA, N.	1952	T	0.49-0.62	293	THIN FILM SPECIMEN; VACUUM DEPOSITED ON A GLASS SUBSTRATE; REFRACTIVE INDEX DETERMINED BY TRANSMISSION METHOD FOR 4 SPECTRAL LINES; DATA EXTRACTED FROM A TABLE; UNCERTAINTY OF INDEX AT THE THIRD DECIMAL PLACE.
4	71	MORITA, N.	1952	T	0.49-0.58	293	SIMILAR TO ABOVE BUT FOR THE SUBSTRATE TEMPERATURE AT 493K DURING DEPOSITION.
5	71	MORITA, N.	1952	T	0.58	293	SIMILAR TO ABOVE BUT FOR HIGHER SUBSTRATE TEMPERATURE.
6	72	HALL, J.E.JR. FERGUSON, W.F.C.	1954	I	0.42-0.76	293	VACUUM DEPOSITED; THIN FILM SPECIMEN OF 0.2-0.8 MICROMETER ON BLACK GLASS SUBSTRATE; AGED IN AIR FOR ONE HOUR AT 293K; REFRACTIVE INDEX DETERMINED BY INTERFERENCE METHOD; DATA EXTRACTED FROM A SMOOTH CURVE; TEMPERATURE NOT GIVEN, 293K ASSUMED.
7	72	HALL, J.E.JR. ET AL.	1954	I	0.42-0.76	293	SIMILAR TO ABOVE BUT FOR THE FILMS AGED FOR ONE WEEK.
8	73	JENNESS, J.R.JR.	1956	T	2.0	293	SINGLE CRYSTAL; VACUUM DEPOSITED; THIN FILM SPECIMEN OF 0.5 MICROMETER ON FUSED QUARTZ SUBSTRATE; REFRACTIVE INDEX DETERMINED BY TRANSMISSION METHOD FOR THE SPECTRAL LINE 2.0 MICROMETERS; TEMPERATURE NOT GIVEN, 293K ASSUMED.
9	74	MORITA, N.	1956	I	0.37-0.60	293	THIN FILM SPECIMEN OF 533 MICROMETER ON CROWN GLASS SUBSTRATE; VACUUM DEPOSITED; REFRACTIVE INDEX DETERMINED BY INTERFERENCE METHOD; DATA EXTRACTED FROM A FIGURE; UNCERTAINTY OF INDEX 0.01.
10	74	MORITA, N.	1956	I	0.37-0.60	293	SIMILAR TO ABOVE BUT FOR THIN FILM SPECIMEN OF 534 MICROMETER ON FUSED QUARTZ SUBSTRATE.

TABLE 37. MEASUREMENT INFORMATION ON THE REFRACTIVE INDEX OF MAGNESIUM FLUORIDE (WAVELENGTH DEPENDENCE) (CONTINUED)

DATA SET NO.	REF. NO.	AUTHOR(S)	YEAR	METHOD USED	WAVELENGTH RANGE, μm	TEMP. K	SPECIFICATIONS AND REMARKS
11	74	MORITA,N.	1956	I	0.39-0.56	293	SIMILAR TO ABOVE BUT FOR THIN FILM SPECIMEN OF 697 MICROMETER ON CROWN GLASS SUBSTRATE.
12	74	MORITA,N.	1956	I	0.39-0.54	293	SIMILAR TO ABOVE BUT FOR THIN FILM SPECIMEN OF 687 MICROMETER ON FUSED QUARTZ SUBSTRATE.
13	74	MORITA,N.	1956	I	0.37-0.55	293	SIMILAR TO ABOVE BUT FOR THIN FILM SPECIMEN OF 395 MICROMETER ON FUSED QUARTZ SUBSTRATE.
14	74	MORITA,N.	1956	I	0.397, 0.489	293	SIMILAR TO ABOVE BUT FOR THIN FILM SPECIMEN OF 350 MICROMETER ON CROWN GLASS SUBSTRATE.
15	74	MORITA,N.	1956	I	0.38-0.50	293	SIMILAR TO ABOVE BUT FOR THIN FILM SPECIMEN OF 596 MICROMETER ON CROWN GLASS SUBSTRATE; KEPT AT TEMPERATURE 513 K DURING DEPOSITION.
16	74	MORITA,N.	1956	I	0.39-0.59	293	SIMILAR TO ABOVE BUT FOR THIN FILM SPECIMEN OF 610 MICROMETER ON FUSED QUARTZ SUBSTRATE; KEPT AT 513 K DURING DEPOSITION.
17	74	MORITA,N.	1956	I	0.38-0.56	293	SIMILAR TO ABOVE BUT FOR THIN FILM SPECIMEN OF 829 MICROMETER ON CROWN GLASS SUBSTRATE; KEPT AT 673 K DURING DEPOSITION.
18	74	MORITA,N.	1956	I	0.34-0.53	293	SIMILAR TO ABOVE BUT FOR THIN FILM SPECIMEN OF 829 MICROMETER ON FUSED QUARTZ SUBSTRATE; KEPT AT 673 K DURING DEPOSITION.
19	74	MORITA,N.	1956	I	0.408, 0.508	293	SIMILAR TO ABOVE BUT FOR THIN FILM SPECIMEN OF 1090 MICROMETER ON CROWN GLASS SUBSTRATE; KEPT AT 623 K DURING DEPOSITION.
20	74	MORITA,N.	1956	I	0.42-0.58	293	SIMILAR TO ABOVE BUT FOR THIN FILM SPECIMEN OF 1095 MICROMETER ON FUSED QUARTZ SUBSTRATE; KEPT AT 623 K DURING DEPOSITION.
21	74	MORITA,N.	1956	I	0.39-0.58	293	SIMILAR TO ABOVE BUT FOR THIN FILM SPECIMEN OF 358 MICROMETER ON FUSED QUARTZ SUBSTRATE; KEPT AT 623 K DURING DEPOSITION.
22	74	MORITA,N.	1956	I	0.38-0.56	293	SIMILAR TO ABOVE BUT FOR THIN FILM SPECIMEN OF 470 MICROMETER ON CROWN GLASS SUBSTRATE; KEPT AT 593 K DURING DEPOSITION.
23	74	MORITA,N.	1956	I	0.34-0.51	293	SIMILAR TO ABOVE BUT FOR THIN FILM SPECIMEN OF 362 MICROMETER ON CROWN GLASS SUBSTRATE; KEPT AT 623 K DURING DEPOSITION.

TABLE 37. MEASUREMENT INFORMATION ON THE REFRACTIVE INDEX OF MAGNESIUM FLUORIDE (WAVELENGTH DEPENDENCE) (CONTINUED)

DATA SET NO.	REF. NO.	AUTHOR(S)	YEAR	METHOD USED	WAVELENGTH RANGE, μm	TEMP. K	SPECIFICATIONS AND REMARKS
24	18	DUNCANSON, A. STEVENSON, R.W.H.	1958	D	0.40-0.71	294	SYNTHETIC CRYSTAL; GROWN BY THE STOCKBARGER TECHNIQUE; PRISMATIC SPECIMEN; NEAR 60 DEGREE APEX ANGLE, 25MMX27MM VIEW SURFACE; REFRACTIVE INDEX DETERMINED BY DEVIATION METHOD FOR 18 ORDINARY SPECTRAL LINES; DATA EXTRACTED FROM A TABLE; A HARTMANN INTERPOLATION FORMULA BEST FIT THE RESULTS ALSO GIVEN.
25	18	DUNCANSON, A. ET AL.	1958	D	0.40-0.71	294	SIMILAR TO ABOVE BUT FOR EXTRAORDINARY RAY.
26	75	COLE, T.T. OPPENHEIMER, F.	1962	R	0.03-0.13	293	THIN FILM SPECIMEN OF UNSPECIFIED THICKNESS; VACUUM DEPOSITED; 10, 30, 50 AND 70 DEGREE INCIDENT REFLECTION SPECTRUM OBTAINED; REFRACTIVE INDEX DEDUCED FROM REFLECTION SPECTRUM WITH FRESNEL FORMULAE; DATA EXTRACTED FROM A TABLE; TEMPERATURE NOT GIVEN, 293K ASSUMED.
27	63	LUKIRSKII, A.P. SAVINOV, E.P. ERSHOV, O.A. SHEPELEV, YU.F.	1964	R	0.002-0.12	298	THIN FILM SPECIMEN OF MAGNESIUM FLUORIDE ON GOLD OR ALUMINIUM SUBSTRATE; REFRACTIVE INDEX DEDUCED FROM REFLECTION SPECTRUM WITH FRESNEL FORMULAE; DATA EXTRACTED FROM A TABLE.
28	49	FABRE, D. ROMAND, J. VODAR, B.	1964	R	0.08-0.17	293	THIN FILM SPECIMEN OF VARYING THICKNESS; VACUUM DEPOSITED; REFRACTIVE INDEX DETERMINED BY REFLECTANCE OF VARYING THICKNESS; DATA EXTRACTED FROM A FIGURE; TEMPERATURE NOT GIVEN, 293K ASSUMED.
29	76	WILLIAMS, M.W.	1967	R	0.04-0.30	293	SINGLE CRYSTAL; OBTAINED FROM OPTOVAC, INC.; PLATE SPECIMEN; 1MM THICK; HIGHLY POLISHED SURFACES; FOR WAVELENGTH REGION 0.1-0.3 MICROMETER NEAR NORMAL AND 75 DEGREE INCIDENT REFLECTION SPECTRUM OBTAINED; FOR REGION 0.04-0.13 MICROMETER 20, 70 AND 75 DEGREE INCIDENT REFLECTION SPECTRUM OBTAINED; REFRACTIVE INDEX DEDUCED FROM REFLECTION SPECTRUM WITH FRESNEL FORMULAE; DATA EXTRACTED FROM A SMOOTH CURVE; TEMPERATURE NOT GIVEN, 293K ASSUMED.
30	76	WILLIAMS, M.W.	1967	R	0.04-0.11	293	SINGLE CRYSTAL; VACUUM DEPOSITED; THIN FILM SPECIMEN OF UNKNOWN THICKNESS; 20 AND 70 DEGREE INCIDENT REFLECTION SPECTRUM OBTAINED; REFRACTIVE INDEX DEDUCED FROM REFLECTION SPECTRUM WITH FRESNEL FORMULAE; DATA EXTRACTED FROM A SMOOTH CURVE; TEMPERATURE NOT GIVEN, 293K ASSUMED.

M. M. L

TABLE 37. MEASUREMENT INFORMATION ON THE REFRACTIVE INDEX OF MAGNESIUM FLUORIDE (WAVELENGTH DEPENDENCE) (CONTINUED)

DATA SET NO.	REF. NO.	AUTHOR(S)	YEAR	METHOD USED	WAVELENGTH RANGE, μm	TEMP. K	SPECIFICATIONS AND REMARKS
31	51	HEITMANN, W. KOPPELMANN, G.	1967	L	0.6328	293	SINGLE CRYSTAL; HIGH PURITY; PRODUCTION OF SCHUCHARDT CO.; VACUUM DEPOSITED; THIN FILM SPECIMEN OF QUARTER WAVELENGTH ALTERNATE WITH ZNS AND ZNSE FILMS; REFRACTIVE INDEX DETERMINED BY MULTILAYER METHOD FOR 1 SPECTRAL LINES; DATA EXTRACTED FROM A TABLE; TEMPERATURE NOT GIVEN, 293K ASSUMED.
32	77	STEINMETZ, D.L. PHILLIPS, W.G. WIRICK, M. FORBES, F.F.	1967		0.17-0.29	293	SINGLE CRYSTAL; THE AUTHOR OBTAINED THE DATA THROUGH PRIVATE COMMUNICATION; DETAILS OF EXPERIMENT NOT GIVEN; REFRACTIVE INDEX OF EXTRAORDINARY RAYS FOR 4 SPECTRAL LINES WERE GIVEN; DATA EXTRACTED FROM A TABLE; TEMPERATURE NOT GIVEN, 293K ASSUMED.
33	77	STEINMETZ, D.L. ET AL.	1967		0.17-0.29	293	SIMILAR TO ABOVE BUT FOR ORDINARY RAYS.
34	78	NAGATA, K.	1968	A	0.45-0.65	293	THIN FILM SPECIMEN OF 0.05 TO 0.10 MICROMETER ON GLASS SUBSTRATE; VACUUM DEPOSITED; REFRACTIVE INDEX DETERMINED BY ABELES METHOD FOR 3 SPECTRAL LINES; DATA EXTRACTED FROM A TABLE; TEMPERATURE NOT GIVEN, 293K ASSUMED.
35	79	HASS, G. RAMSEY, J.B.	1969	I	0.16-0.56	293	THIN FILM SPECIMEN OF UNSPECIFIED THICKNESS BY VACUUM DEPOSITION ONTO QUARTZ PLATE BY A CO ₂ LASER; REFRACTIVE INDEX DETERMINED BY INTERFERENCE METHOD; DATA EXTRACTED FROM A SMOOTH CURVE; TEMPERATURE NOT GIVEN, 293K ASSUMED.
36	80	SHKLYAREVSKII, I.N. EL-SHAZLI, A.-A. GOVORUSHCHENKO, A.I.	1971	I	0.40-1.00	293	VACUUM DEPOSITED; THIN FILM SPECIMEN OF 0.133 TO 0.517 MICROMETER ON GLASS SUBSTRATE; 3MMX1.2MM AREA; REFRACTIVE INDEX DETERMINED BY INTERFERENCE METHOD; DATA EXTRACTED FROM A SMOOTH CURVE; TEMPERATURE NOT GIVEN, 293K ASSUMED.
37	20	EASTMAN KODAK CO.	1971	D	1.00-9.00	293	POLYCRYSTALLINE; KODAK INFRARED OPTICAL MATERIAL IRTRAN 1; DESCRIPTION OF SPECIMEN AND EXPERIMENT NOT GIVEN; TEMPERATURE NOT GIVEN, 293K ASSUMED; DATA EXTRACTED FROM A TABLE COMPUTED BY A GIVEN HERZBERGER DISPERSION EQUATION.
38	81	HANSON, W.F. ARAKAWA, E.T. WILLIAMS, M.W.	1972	R	0.015-0.06		SINGLE CRYSTAL; OBTAINED FROM ALPHA INORGANICS, INC.; POLISHED WITH 0.5 MICROMETER GRIT; 12 ANGLES FROM 20 TO 75 DEGREES INCIDENT REFLECTION SPECTRUM OBTAINED; REFRACTIVE INDEX DEDUCED FROM REFLECTION SPECTRUM WITH FRESNEL FORMULAE; DATA EXTRACTED FROM A FIGURE; TEMPERATURE NOT GIVEN, 293K ASSUMED.

TABLE 37. MEASUREMENT INFORMATION ON THE REFRACTIVE INDEX OF MAGNESIUM FLUORIDE (WAVELENGTH DEPENDENCE) (CONTINUED)

DATA SET NO.	REF. NO.	AUTHOR(S)	YEAR	METHOD USED	WAVELENGTH RANGE, μm	TEMP., K	SPECIFICATIONS AND REMARKS
39	82	THOMAS,J. STEPHAN,G. LEMONNIER,J.C. NISAR,M., ROBIN,S.	1973	R	0.04-0.12	293	SINGLE CRYSTAL; OBTAINED FROM THE HARSHAW CHEMICAL CO.; DISC SPECIMEN; WITH OPTICAL AXIS PARALLEL TO THE POLISHED FACES; REFLECTANCE MEASURED AT VARIOUS INCIDENT ANGLES FROM 25 TO 55 DEGREES; REFRACTIVE INDEX OF ORDINARY-RAY DEDUCED FROM REFLECTION SPECTRUM; DATA EXTRACTED FROM A FIGURE; TEMPERATURE NOT GIVEN, 293K ASSUMED.
40	82	THOMAS,J. ET AL.	1973	R	0.04-0.12	293	SIMILAR TO ABOVE BUT FOR EXTRAORDINARY-RAY.
41	83	YADAV,A.U.N. SHARMA,S.K. CHOPRA,K.L.	1974	L	0.20-0.70	293	THIN FILM SPECIMEN OF PURE MAGNESIUM FLUORIDE ON QUARTZ SUBSTRATE; VACUUM DEPOSITED; REFRACTIVE INDEX DETERMINED BY DEDUCTION OF THE REFLECTANCE AND TRANSMITTANCE OF THE FILM; DIGITIZED VALUES OF REFRACTIVE INDEX GIVEN; TEMPERATURE NOT GIVEN, 293K ASSUMED.

TABLE 38. EXPERIMENTAL REFRACTIVE INDEX OF MAGNESIUM FLUORIDE (WAVELENGTH DEPENDENCE)
[WAVELENGTH, λ , μm ; TEMPERATURE, T , K; REFRACTIVE INDEX, n]

λ	n	λ	n	λ	n	λ	n	λ	n	
DATA SET 1										
	$T = 293.0$		$T = 293.0$		$T = 293.0$		$T = 293.0$		$T = 293.0$	
0.47	1.339	0.58	1.360	0.379	1.428	0.397	1.416	0.408	1.406	
0.50	1.337			0.430	1.418	0.489	1.403	0.508	1.402	
0.52	1.343	DATA SET 6		0.501	1.409					
0.54	1.322	$T = 293.0$		0.601	1.408	DATA SET 15		DATA SET 20		
0.54	1.336					$T = 293.0$		$T = 293.0$		
0.54	1.337	0.426	1.375	DATA SET 10		0.383	1.445	0.421	1.377	
0.54	1.358	0.441	1.373	$T = 293.0$		0.430	1.431	0.500	1.434	
0.55	1.357	0.458	1.372			0.500	1.460	0.575	1.416	
0.55	1.363	0.476	1.371	0.373	1.408	DATA SET 16		DATA SET 21		
0.55	1.377	0.494	1.369	0.424	1.390	$T = 293.0$		$T = 293.0$		
0.56	1.346	0.513	1.369	0.499	1.400					
0.57	1.352	0.538	1.368	0.592	1.388	DATA SET 11		0.587562	1.37774	
0.57	1.362	0.562	1.367			0.395	1.424	0.398	1.430	
0.58	1.349	0.605	1.367	DATA SET 7		0.427	1.411	0.432	1.426	
0.60	1.346	0.674	1.366	$T = 293.0$		0.471	1.424	0.470	1.410	
		0.710	1.366			0.528	1.425	0.527	1.418	
DATA SET 2		$T = 293.0$	0.752	1.366	0.395	1.420	0.590	1.419	0.585	1.403
				0.431	1.401	DATA SET 17		DATA SET 22		
0.589	1.39	$T = 293.0$		0.493	1.419	$T = 293.0$		$T = 293.0$		
				0.560	1.407					
DATA SET 3										
	$T = 293.0$	0.425	1.399	DATA SET 12		0.386	1.409	0.381	1.387	
		0.442	1.397	$T = 293.0$		0.412	1.417	0.413	1.410	
		0.458	1.396			0.439	1.411	0.435	1.390	
0.49	1.391	0.482	1.395	0.391	1.428	0.474	1.413	0.473	1.406	
0.52	1.386	0.508	1.394	0.430	1.414	0.516	1.418	0.503	1.384	
0.56	1.387	0.537	1.393	0.491	1.426	0.563	1.419	0.560	1.406	
0.62	1.387	0.566	1.392	0.539	1.400					
		0.597	1.391							
DATA SET 4										
	$T = 293.0$	0.626	1.391	DATA SET 13		DATA SET 18		DATA SET 23		
		0.659	1.390	$T = 293.0$		$T = 293.0$		$T = 293.0$		
		0.701	1.390							
0.49	1.366	0.756	1.390	0.371	1.414	0.341	1.432	0.341	1.429	
0.56	1.387			0.440	1.412	0.377	1.410	0.409	1.415	
0.58	1.376	DATA SET 8		$T = 293.0$	0.551	1.392	0.439	1.409	0.510	1.411
						0.530	1.416			
		2.0	1.36							

TABLE 38. EXPERIMENTAL REFRACTIVE INDEX OF MAGNESIUM FLUORIDE (WAVELENGTH DEPENDENCE) (CONTINUED)

[WAVELENGTH, λ , μm ; TEMPERATURE, T , K; REFRACTIVE INDEX, n]

λ	n	λ	n	λ	n	λ	n	λ	n	λ	n
DATA SET 25(CONT.)											
0.706525	1.38771	0.1568	1.54	0.0939	1.557	0.0546	0.982	0.1780	1.43975	0.560	1.384
		0.1618	1.54	0.0953	1.565	0.0563	1.008	0.1850	1.43424	DATA SET 36	
DATA SET 26				0.0984	1.583	0.0579	1.043	0.2536	1.40208		
T = 293.0		DATA SET 29		0.0992	1.404	0.0601	1.097	0.2893	1.39485	T = 293.0	
				0.1000	1.344	0.0620	1.147			0.410	1.3999
0.0304	0.93			0.1008	1.290	0.0639	1.205			0.600	1.3993
0.0584	0.93	0.0447	0.870	0.1016	1.243	0.0652	1.249	DATA SET 34		0.800	1.3982
0.0920	1.03	0.0457	0.833	0.1024	1.212	0.0663	1.293	T = 293.0		1.020	1.3969
0.1048	1.20	0.0471	0.802	0.1033	1.477	0.0673	1.322				
0.1216	1.30	0.0492	0.759	0.1042	1.773	0.0685	1.375	0.450	1.390	DATA SET 37	
		0.0512	0.780	0.1050	1.960	0.0700	1.401	0.550	1.387		
DATA SET 27		0.0532	0.847	0.1059	2.068	0.0716	1.429	0.650	1.385	T = 293.0	
T = 298.0		0.0541	0.904	0.1068	2.221	0.0742	1.450			1.0000	1.3778
		0.0553	0.972	0.1078	2.233	0.0770	1.465	DATA SET 35		1.2500	1.3763
0.00236	0.99855	0.0566	1.051	0.1087	2.221	0.0800	1.485	T = 293.0		1.5000	1.3749
0.00314	0.99803	0.0576	1.106	0.1107	2.031	0.0837	1.509			1.7500	1.3735
0.0044	0.99734	0.0587	1.163	0.1117	1.935	0.0873	1.516	0.160	1.473	2.0000	1.3720
0.0067	0.99510	0.0599	1.206	0.1127	1.844	0.0898	1.507	0.164	1.467	2.2500	1.3702
0.0113	0.9800	0.0607	1.196	0.1148	1.770	0.0905	1.474	0.170	1.459	2.5000	1.3683
		0.0623	1.185	0.1180	1.682	0.0925	1.422	0.178	1.451	2.7500	1.3663
DATA SET 28		0.0649	1.204	0.1215	1.603	0.0953	1.357	0.186	1.444	3.0000	1.3640
T = 293.0		0.0663	1.248	0.1291	1.529	0.0992	1.324	0.194	1.438	3.2500	1.3614
		0.0677	1.295	0.1458	1.463	0.1050	1.324	0.204	1.433	3.5000	1.3587
0.0924	1.66	0.0696	1.341	0.1771	1.420	0.1068	1.366	0.216	1.427	3.7500	1.3558
0.0950	1.56	0.0716	1.363	0.2214	1.397	0.1078	1.411	0.230	1.422	4.0000	1.3526
0.0968	1.50	0.0742	1.347	0.3024	1.388	0.1087	1.492	0.242	1.418	4.2500	1.3492
0.0976	1.48	0.0746	1.341			0.1097	1.636	0.257	1.414	4.5000	1.3455
0.0991	1.51	0.0756	1.385	DATA SET 30				0.273	1.411	4.7500	1.3416
0.1034	1.77	0.0770	1.406	T = 293.0		DATA SET 31		0.293	1.407	5.0000	1.3374
0.1071	2.03	0.0784	1.453			T = 293.0		0.312	1.404	5.2500	1.3329
0.1081	2.08	0.0805	1.485	0.0421	1.018			0.331	1.400	5.5000	1.3282
0.1087	2.10	0.0821	1.499	0.0430	0.977	0.6328	1.33	0.350	1.398	5.7500	1.3232
0.1098	2.09	0.0837	1.508	0.0438	0.957			0.373	1.395	6.0000	1.3179
0.1112	2.05	0.0861	1.479	0.0447	0.937	DATA SET 32		0.399	1.393	6.2500	1.3122
0.1139	1.97	0.0873	1.454	0.0460	0.921	T = 293.0		0.422	1.391	6.5000	1.3063
0.1181	1.87	0.0885	1.488	0.0476	0.915			0.445	1.390	6.7500	1.3000
0.1226	1.79	0.0885	1.520	0.0492	0.922	0.1780	1.45365	0.473	1.389	7.0000	1.2934
0.1303	1.69	0.0898	1.554	0.0512	0.934	0.1850	1.44797	0.494	1.388	7.2500	1.2865
0.1386	1.62	0.0918	1.591	0.0525	0.949	0.2536	1.41483	0.517	1.387	7.5000	1.2792
0.1489	1.57	0.0932	1.577	0.0536	0.971	0.2893	1.4073	0.541	1.387		

TABLE 38. EXPERIMENTAL REFRACTIVE INDEX OF MAGNESIUM FLUORIDE (WAVELENGTH DEPENDENCE) (CONTINUED)
[WAVELENGTH, λ , μm ; TEMPERATURE, T , K; REFRACTIVE INDEX, n]

λ	n	λ	n	λ	n	λ	n	λ	n
DATA SET 37(CONT.)									
7.7500	1.2715	0.0460	0.86	0.0691	1.11	0.0641	0.93		
8.0000	1.2634	0.0471	0.84	0.0699	1.18	0.0650	0.98	0.20	1.43
8.2500	1.2549	0.0480	0.81	0.0709	1.20	0.0659	1.05	0.70	1.37
8.5000	1.2460	0.0492	0.79	0.0784	1.20	0.0670	1.14		
8.7500	1.2367	0.0500	0.78	0.0802	1.21	0.0680	1.13		
9.0000	1.2269	0.0508	0.78	0.0808	1.25	0.0702	1.26		
		0.0518	0.79	0.0817	1.30	0.0711	1.29		
DATA SET 38									
	$T = 293.0$	0.0532	0.82	0.0826	1.40	0.0720	1.32		
		0.0539	0.85	0.0837	1.40	0.0753	1.36		
		0.0553	0.89	0.0842	1.39	0.0767	1.40		
0.0185	0.95	0.0566	0.94	0.0848	1.35	0.0774	1.44		
0.0190	0.95	0.0574	0.99	0.0853	1.35	0.0781	1.49		
0.0195	0.96	0.0584	1.06	0.0867	1.40	0.0788	1.52		
0.0207	0.96	0.0593	1.13	0.0875	1.40	0.0794	1.52		
0.0221	0.96	0.0599	1.19	0.0887	1.21	0.0808	1.50		
0.0223	0.93	0.0607	1.24	0.0890	1.19	0.0819	1.44		
0.0224	0.90	0.0620	1.28	0.0904	1.19	0.0830	1.35		
0.0226	0.92			0.0933	1.58	0.0842	1.31		
0.0226	0.96	DATA SET 39		0.0942	1.60	0.0855	1.31		
0.0227	1.00	$T = 293.$		0.0950	1.59	0.0872	1.36		
0.0229	1.00			0.0961	1.28	0.0877	1.35		
0.0231	0.96	0.0459	0.84	0.0968	1.19	0.0887	1.21		
0.0237	0.96	0.0468	0.82	0.0975	1.17	0.0907	1.21		
0.0241	0.96	0.0482	0.79	0.0985	1.17	0.0923	1.46		
0.0250	0.95	0.0491	0.78	0.1014	1.52	0.0946	1.46		
0.0261	0.95	0.0499	0.77	0.1044	1.97	0.0970	1.42		
0.0281	0.94	0.0511	0.77	0.1054	2.00	0.0979	1.42		
0.0319	0.94	0.0527	0.79	0.1068	1.98	0.0991	1.49		
0.0348	0.95	0.0544	0.81	0.1125	1.50	0.1004	1.43		
0.0361	0.94	0.0558	0.83			0.1018	1.24		
0.0369	0.92	0.0571	0.87	DATA SET 40		0.1029	1.22		
0.0376	0.91	0.0581	0.94	$T = 293.$		0.1040	1.23		
0.0387	0.91	0.0591	0.99			0.1064	1.56		
0.0397	0.91	0.0599	1.02	0.0457	0.87	0.1093	1.7		
0.0403	0.92	0.0608	1.03	0.0470	0.84	0.1105	2.00		
0.0416	0.92	0.0627	1.03	0.0486	0.81	0.1126	1.93		
0.0424	0.91	0.0650	1.02	0.0500	0.81	0.1154	1.68		
0.0432	0.90	0.0663	1.01	0.0528	0.83				
0.0441	0.87	0.0677	1.03	0.0571	0.87				
0.0452	0.87	0.0683	1.06	0.0602	0.91				

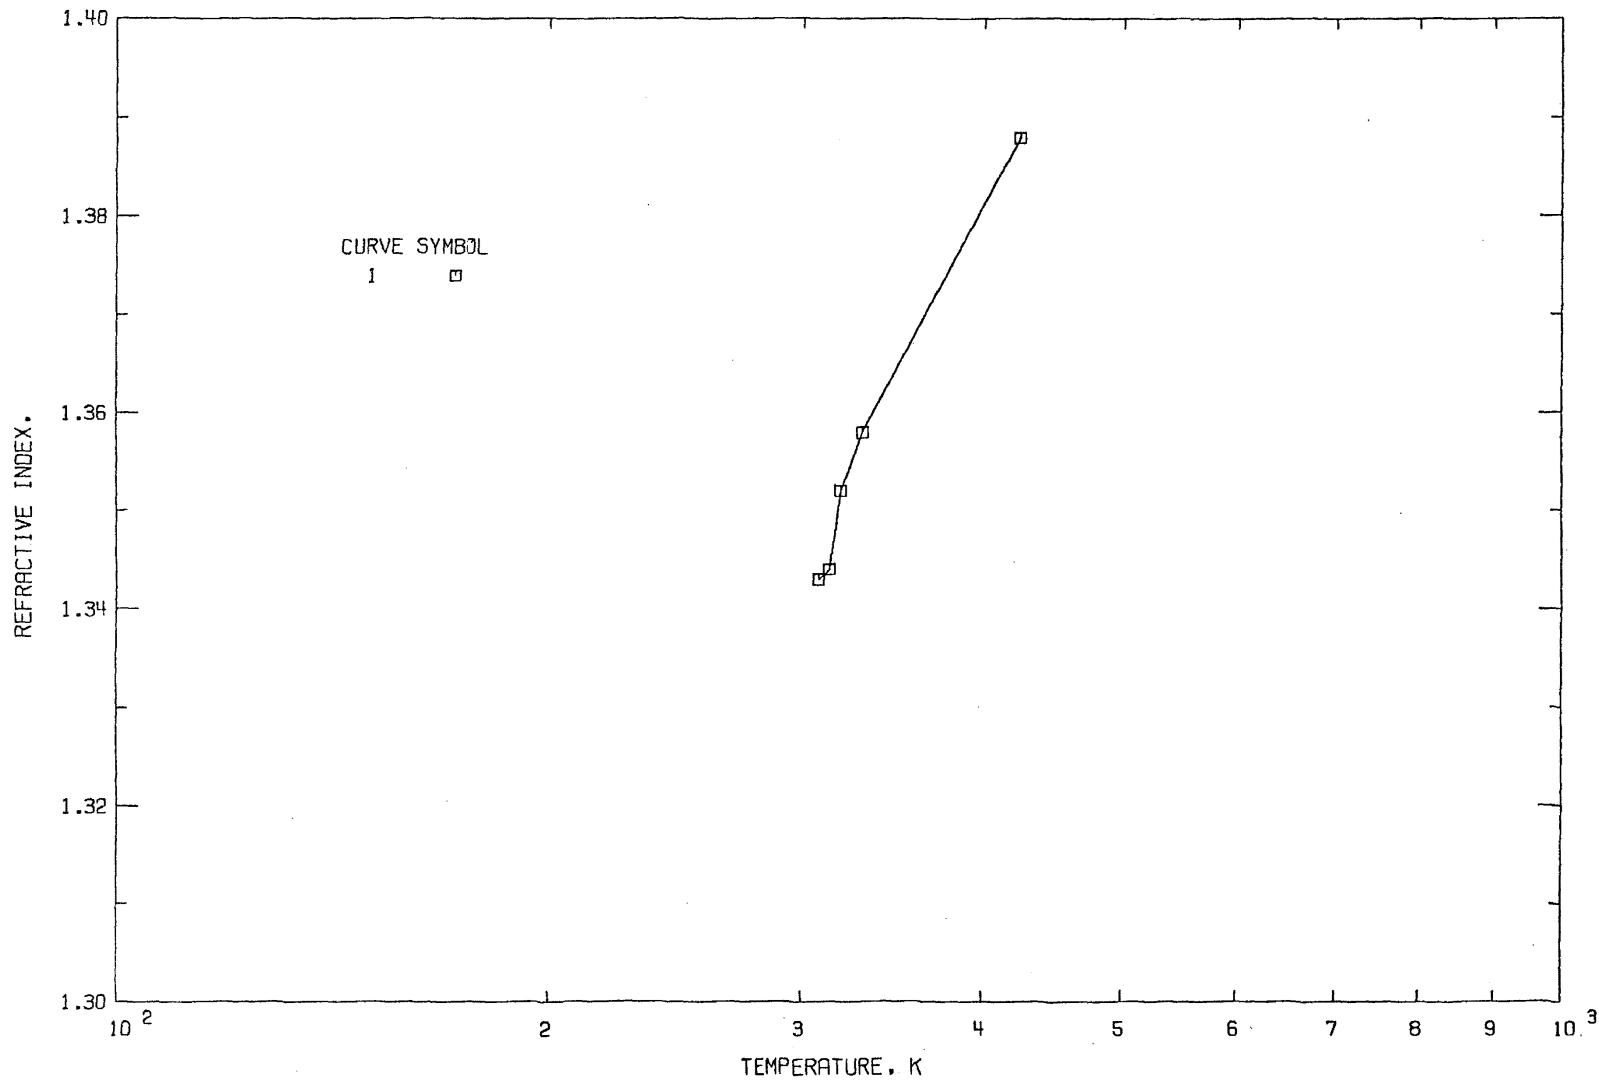


FIGURE 23. REFRACTIVE INDEX OF MAGNESIUM FLUORIDE (TEMPERATURE DEPENDENCE).

TABLE 39. MEASUREMENT INFORMATION ON THE REFRACTIVE INDEX OF MAGNESIUM FLUORIDE (TEMPERATURE DEPENDENCE)

DATA SET NO.	REF. NO.	AUTHOR(S)	YEAR	METHOD USED	WAVELENGTH RANGE, μm	TEMP. K	SPECIFICATIONS AND REMARKS
1	84	HACMAN, D.	1970	R	0.6328	303-573	THIN FILM SPECIMEN OF QUARTER WAVELENGTH ON GLASS SUBSTRATE AT TEMPERATURES BETWEEN 303 TO 573 K; REFRACTIVE INDEX DETERMINED BY USING THE BAUER FORMULA; DATA EXTRACTED FROM A FIGURE.

TABLE 40. EXPERIMENTAL REFRACTIVE INDEX OF MAGNESIUM FLUORIDE (TEMPERATURE DEPENDENCE)
[WAVELENGTH, λ , μm ; TEMPERATURE, T, K; REFRACTIVE INDEX, n]

T	n
DATA SET 1	
	$\lambda = 0.632$
307.8	1.343
313.1	1.344
318.6	1.352
329.9	1.358
423.4	1.388
483.0	1.413
488.7	1.410
493.7	1.404
510.9	1.403
532.6	1.415

H. H. LI

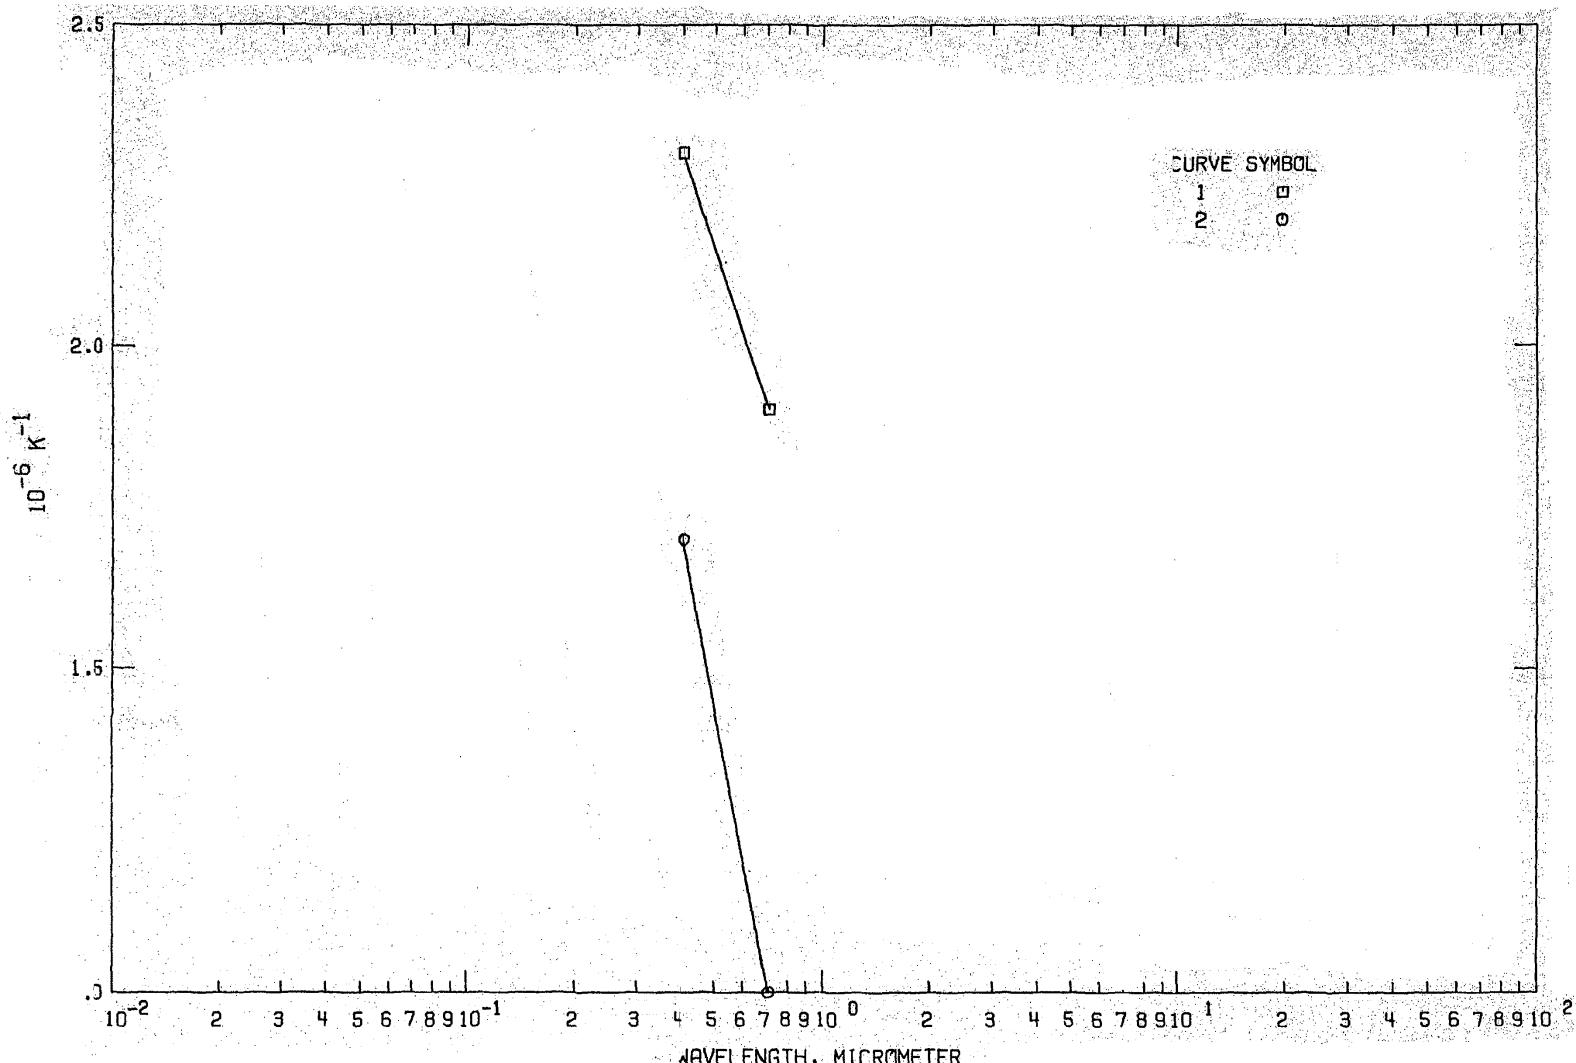


FIGURE 24. TEMPERATURE DERIVATIVE OF REFRACTIVE INDEX OF MAGNESIUM FLUORIDE (WAVELENGTH DEPENDENCE)

TABLE 41. MEASUREMENT INFORMATION ON THE TEMPERATURE DERIVATIVE OF REFRACTIVE INDEX OF MAGNESIUM FLUORIDE (WAVELENGTH DEPENDENCE)

DATA SET NO.	REF. NO.	AUTHOR(S)	YEAR	METHOD USED	WAVELENGTH RANGE, μm	TEMP. K	SPECIFICATIONS AND REMARKS
1	18	DUNCANSON, A. STEVENSON, R.W.H.	1958	D	0.40, 0.70	301	SYNTHETIC CRYSTAL; GROWN BY THE STOCKBARGER TECHNIQUE; PRISMATIC SPECIMEN; NEAR 60 DEGREE APEX ANGLE, 25MMX27MM VIEW SURFACE; REFRACTIVE INDEX DETERMINED BY DEVIATION METHOD: DN/DT DETERMINED FOR ORDINARY RAY OF 2 SPECTRAL LINES SPECTRAL LINES USING THE INDICES MEASURED AT 292 AND 310K; DATA EXTRACTED FROM A TABLE.
2	18	DUNCANSON, A. ET AL.	1958	D	0.40, 0.70	301	SIMILAR TO ABOVE BUT FOR EXTRAORDINARY RAY.

H. H. LI

TABLE 42. EXPERIMENTAL TEMPERATURE DERIVATIVE OF REFRACTIVE INDEX OF MAGNESIUM FLUORIDE (WAVELENGTH DEPENDENCE)
[WAVELENGTH, λ , μm ; TEMPERATURE, T , K; TEMPERATURE DERIVATIVE OF REFRACTIVE INDEX, dn/dT , 10^{-6} K^{-1}]

λ dn/dT

DATA SET 1
 $T = 301.0$

0.4047 2.3
0.7065 1.9

DATA SET 2
 $T = 301.0$

0.4047 1.7
0.7065 1.0

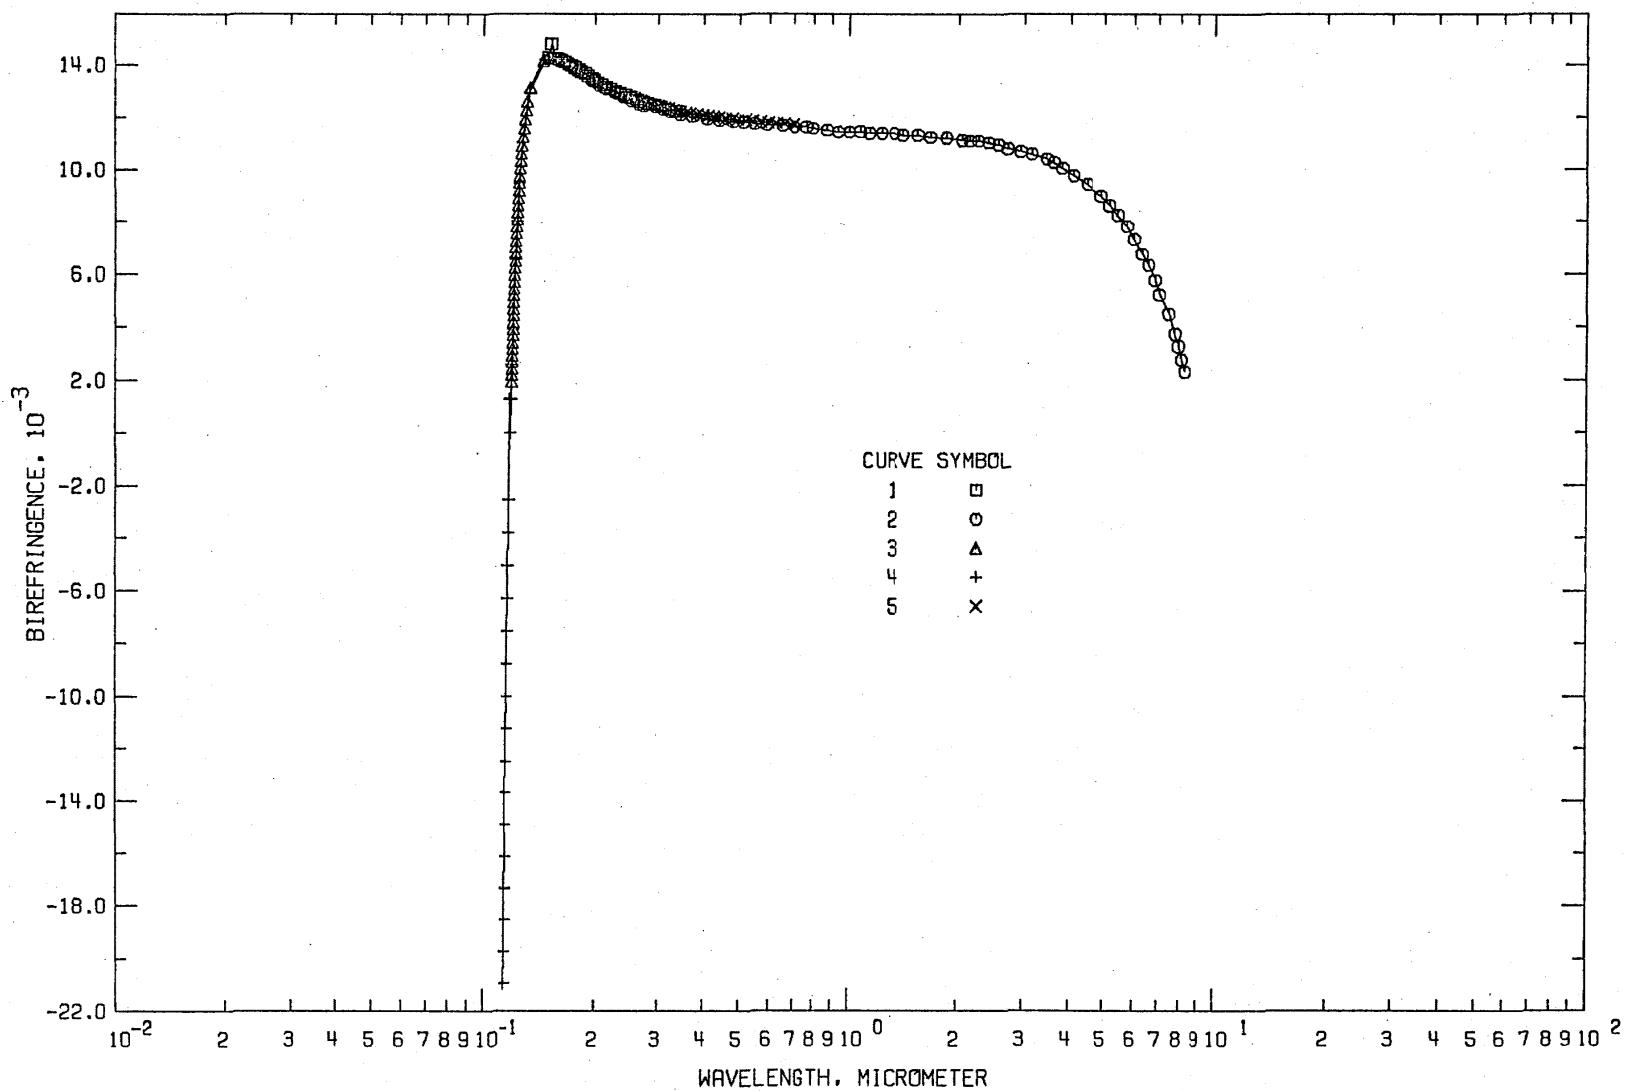


FIGURE 25. BIREFRINGENCE OF MAGNESIUM FLUORIDE (WAVELENGTH DEPENDENCE)

TABLE 43. MEASUREMENT INFORMATION ON THE BIREFRINGENCE OF MAGNESIUM FLUORIDE (WAVELENGTH DEPENDENCE)

DATA SET NO.	REF. NO.	AUTHOR(S)	YEAR	METHOD USED	WAVELENGTH RANGE, μm	TEMP. K	SPECIFICATIONS AND REMARKS
1	85	CHANDRASEKHAREN, U. DAMANY, H.	1968	I	0.15-0.34	293	SYNTHETIC CRYSTAL; PLATE SPECIMEN; 0.493MM THICK; BIREFRINGENCE DETERMINED BY INTERFERENCE METHOD FOR 30 SPECTRAL LINES; DATA EXTRACTED FROM A TABLE.
2	86	PALIK, E. J.	1968	C	0.20-8.50	293	SYNTHETIC CRYSTAL; OBTAINED FROM OPTOVAC INC.; PLATE SPECIMEN; 2.040CMX2.040CM AREA; 0.3252CM THICK; BIREFRINGENCE DETERMINED BY POLARIZATION METHOD; DATA EXTRACTED FROM A SMOOTH CURVE; TEMPERATURE NOT GIVEN, 293K ASSUMED.
3	87	CHANDRASEKHAREN, U. DAMANY, H.	1969	I	0.12-0.18	293	SYNTHETIC CRYSTAL; OBTAINED FROM OPTOVAC, INC.; PLATE SPECIMEN; 0.493MM THICK; CUT WITH OPTIC AXIS PARALLEL TO THE SURFACE AND POLISHED; REFRACTIVE INDEX DETERMINED BY INTERFERENCE PATTERN OF CHANNEL SPECTRA; DATA EXTRACTED FROM A TABLE; TEMPERATURE NOT GIVEN, 293K ASSUMED.
4	87	CHANDRASEKHAREN, U. ET AL.	1969	I	0.11-0.17	293	SIMILAR TO ABOVE BUT FOR A SPECIMEN OF 0.093MM THICK.
5	88	MODINE, F.A. MAJOR, R.W. SONDER, E.	1975	H	0.24-0.70	293	SINGLE CRYSTAL; PLATE SPECIMEN; 0.093CM THICK; BIREFRINGENCE DETERMINED BY A HIGH FREQUENCY MODULATION METHOD UTILIZING A PHOTOELASTIC POLARIZATION MODULATOR; DATA EXTRACTED FROM A FIGURE; TEMPERATURE NOT GIVEN, 293K ASSUMED.

TABLE 44. EXPERIMENTAL BIREFRINGENCE OF MAGNESIUM FLUORIDE (WAVELENGTH DEPENDENCE)
[WAVELENGTH, λ , μm ; TEMPERATURE, T, K; BIREFRINGENCE, Δn , 10^{-3}]

λ	Δn	λ	Δn	λ	Δn	λ	Δn	λ	Δn	λ	Δn
DATA SET 1											
<i>T = 293.0</i>											
0.15007	14.307	0.2535	12.66	4.0926	9.75	0.12338	7.007	0.11575	-14.903	0.3125	12.374
0.15305	14.821	0.2654	12.53	4.4567	9.41	0.12350	7.265	0.11595	-13.685	0.3194	12.333
0.15632	14.275	0.2735	12.46	4.8866	8.94	0.12384	7.536	0.11619	-12.467	0.3289	12.295
0.15952	14.237	0.2951	12.41	5.1525	8.59	0.12409	7.803	0.11644	-11.244	0.3389	12.265
0.16260	14.183	0.3090	12.30	5.4327	8.22	0.12436	8.072	0.11669	-10.016	0.3460	12.225
0.16598	14.140	0.3243	12.21	5.7544	7.81	0.12463	8.342	0.11693	-8.782	0.3571	12.195
0.16922	14.073	0.3451	12.10	6.0117	7.31	0.12493	8.616	0.11719	-7.544	0.3663	12.153
0.17265	14.008	0.3715	12.03	6.3387	6.75	0.12524	8.891	0.11752	-6.305	0.3831	12.116
0.17609	13.930	0.4083	11.94	6.5919	6.34	0.12558	9.170	0.11782	-5.057	0.3968	12.085
0.17967	13.849	0.4415	11.88	6.8709	5.76	0.12595	9.453	0.11821	-3.805	0.4098	12.051
0.18341	13.765	0.4808	11.85	7.0636	5.22	0.12634	9.738	0.11856	-2.544	0.4237	12.017
0.18753	13.694	0.5116	11.82	7.4822	4.49	0.12674	10.026	0.11901	1.277	0.4385	11.990
0.19157	13.600	0.5482	11.76	7.7627	3.73	0.12722	10.322	0.11949	0.0	0.4566	11.953
0.19599	13.516	0.5902	11.71	7.9617	3.26	0.12772	10.622	0.12001	1.288	0.4761	11.936
0.20065	13.431	0.6531	11.69	8.0912	2.76	0.12826	10.927	0.12058	2.588	0.4926	11.905
0.20576	13.356	0.7063	11.62	8.2795	2.31	0.12893	11.245	0.12135	3.907	0.5181	11.876
0.21102	13.269	0.7655	11.62			0.12971	11.577	0.12215	5.242	0.5405	11.851
0.21667	13.184	0.7961	11.57	DATA SET 3		0.13059	11.912	0.12318	6.609	0.5681	11.826
0.22292	13.113	0.8709	11.50	<i>T = 293.0</i>		0.13155	12.274	0.12447	8.013	0.5952	11.801
0.22933	13.025	0.9332	11.44			0.13228	12.611	0.12613	9.474	0.6250	11.774
0.23619	12.935	1.0000	11.44	0.12028	1.952	0.13505	13.149	0.12861	11.039	0.6578	11.757
0.24354	12.865	1.0715	11.45	0.12037	2.197	0.14532	14.149	0.13423	12.962	0.7042	11.736
0.25221	12.790	1.1376	11.40	0.12050	2.442	0.14946	14.249	0.14720	14.215		
0.26088	12.700	1.2274	11.40	0.12059	2.691	0.15295	14.271	0.15480	14.146		
0.27030	12.611	1.3335	11.40	0.12073	2.939	0.15619	14.257				
0.28124	12.551	1.4158	11.32	0.12087	3.187	0.15940	14.226	DATA SET 5			
0.29352	12.503	1.5524	11.32	0.12100	3.436	0.16260	14.182	<i>T = 293.0</i>			
0.30632	12.427	1.6788	11.24	0.12120	3.688	0.16578	14.123				
0.31985	12.327	1.8535	11.21	0.12132	3.937	0.16906	14.060	0.2457	12.860		
0.33531	12.242	2.0464	11.14	0.12144	4.188	0.17243	13.990	0.2493	12.821		
		2.1478	11.11	0.12160	4.440	0.17590	13.915	0.2538	12.779		
		2.2646	11.11	0.12172	4.691			0.2583	12.735		
DATA SET 2											
<i>T = 293.0</i>											
0.1972	13.40	2.4099	11.04	0.12187	4.944	DATA SET 4		0.2638	12.689		
		2.5644	10.97	0.12202	5.200	<i>T = 293.0</i>		0.2688	12.648		
		2.7227	10.81	0.12221	5.454			0.2732	12.608		
		3.2944	10.70	0.12238	5.709	0.11486	-20.951	0.2785	12.569		
		3.1550	10.60	0.12256	5.966	0.11502	-19.746	0.2857	12.528		
		3.4594	10.41	0.12277	6.226	0.11521	-18.542	0.2906	12.488		
		3.6141	10.27	0.12295	6.484	0.11536	-17.329	0.2994	12.447		
		3.8195	10.02	0.12315	6.744	0.11558	-16.122	0.3048	12.407		

TABLE 45. COMPARISON OF DISPERSION EQUATIONS PROPOSED FOR MgF_2

Source	Wavelength and Temperature Ranges	Dispersion Equation λ in μm ; ν in cm^{-1}
Duncanson, A. and Stevenson, R. W. H. 1958	0.40-0.70 μm 294 K	$n = 1.36957 + \frac{35.821}{\lambda - 1492.5}$ for ordinary ray, $n = 1.38100 + \frac{37.415}{\lambda - 1494.7}$ for extraordinary ray.
Eastman Kodak Co. 1971	1.0-9.0 μm 293 K	$n = 1.3776955 + \frac{1.3515529 \times 10^{-3}}{\lambda^2 - 0.028} + \frac{2.1254394 \times 10^{-4}}{(\lambda^2 - 0.028)^2} - 1.5041172 \times 10^{-3} \lambda^2 - 4.4109708 \times 10^{-6} \lambda^4$ for IRTRAN 1.
Present work 1977	0.15-10.0 μm 293 K	$n^2 = 1.27620 + \frac{0.60967 \lambda^2}{\lambda^2 - (0.08636)^2} + \frac{0.00800 \lambda^2}{\lambda^2 - (18.0)^2} + \frac{2.14973 \lambda^2}{\lambda^2 - (25.0)^2}$ for ordinary ray, $n^2 = 1.25385 + \frac{0.66405 \lambda^2}{\lambda^2 - (0.08504)^2} + \frac{1.08987 \lambda^2}{\lambda^2 - (22.2)^2} + \frac{0.18159 \lambda^2}{\lambda^2 - (24.4)^2} + \frac{2.12272 \lambda^2}{\lambda^2 - (40.6)^2}$ for extraordinary ray, $n^2 = 1.79079 + \frac{0.10822 \lambda^2}{\lambda^2 - (0.16733)^2} + \frac{2.78138 \lambda^2}{\lambda^2 - (25.54)^2}$ for IRTRAN 1.

3.5. Calcium Chloride, CaCl_2

Available data on the refractive index of calcium chloride are given in tables 46 and 47, and are plotted in figure 26, where data for hydrated calcium chloride and molten salt are also pre-

sented for comparison. As the refractive index was measured only for the single spectral line (0.589 micrometer) and the material is not suitable for optical applications, data analysis and data prediction were not attempted.

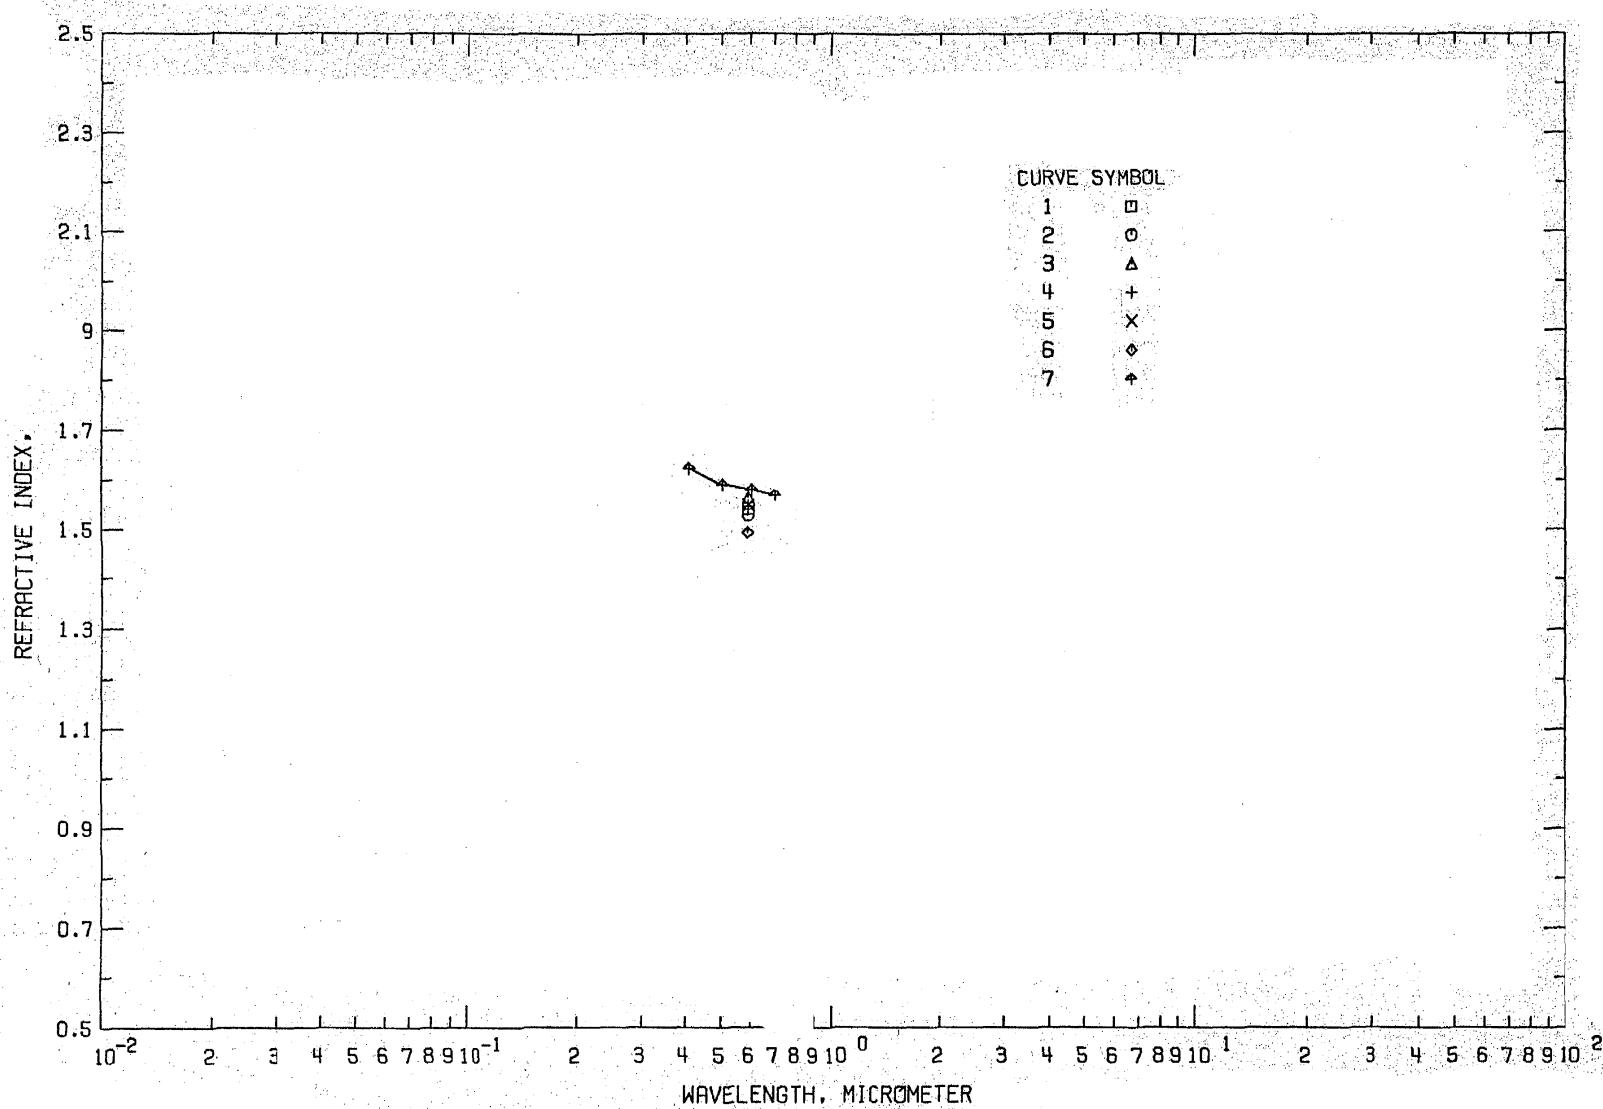


FIGURE 26. REFRACTIVE INDEX OF CALCIUM CHLORIDE (WAVELENGTH DEPENDENCE).

TABLE 46. MEASUREMENT INFORMATION ON THE REFRACTIVE INDEX OF CALCIUM CHLORIDE (WAVELENGTH DEPENDENCE)

DATA SET NO.	REF. NO.	AUTHOR(S)	YEAR	METHOD USED	WAVELENGTH RANGE, μm	TEMP. K	SPECIFICATIONS AND REMARKS
1	62	WULFF, P. HEIGL, A.	1931	M	0.589	298	WATER FREE FRAGMENTS OF SINGLE CRYSTAL; REFRACTIVE INDEX DETERMINED BY IMMERSION METHOD FOR THE MEAN OF SODIUM D LINES; MAXIMUM VALUE OF REFRACTIVE INDEX WAS DETERMINED FOR THIS BIREFRINGENT MATERIAL; DATA EXTRACTED FROM A TABLE; UNCERTAINTY OF INDEX 0.002.
2	62	WULFF, P. ET AL.	1931	M	0.589	298	SIMILAR TO ABOVE BUT FOR MINIMUM REFRACTIVE INDEX; UNCERTAINTY OF INDEX 0.002.
3	89	WULFF, P. SCHALLER, D.	1934	P	0.589	298	CRYSTAL OF TETRA-HYDRATED CALCIUM CHLORIDE WITH UNKNOWN STRUCTURE; REFRACTIVE INDEX DETERMINED BY A PULFRICH REFRACTOMETER METHOD FOR THE MEAN OF SODIUM D LINES; MAXIMUM VALUE OF INDEX OBTAINED; DATA EXTRACTED FROM A TABLE; UNCERTAINTY OF INDEX AT THE THIRD DECIMAL PLACE.
4	89	WULFF, P. ET AL.	1934	P	0.589	298	SIMILAR TO ABOVE BUT FOR MINIMUM VALUE OF INDEX; UNCERTAINTY OF INDEX AT THE THIRD DECIMAL PLACE.
5	89	WULFF, P. ET AL.	1934	P	0.589	298	CRYSTAL OF HEKA-HYDRATED CALCIUM CHLORIDE WITH HEXAGONAL STRUCTURE; REFRACTIVE INDEX DETERMINED BY A PULFRICH REFRACTOMETER METHOD FOR THE MEAN OF SODIUM D LINES; INDEX OF ORDINARY RAY OBTAINED; DATA EXTRACTED FROM A TABLE; UNCERTAINTY OF INDEX 0.001.
6	89	WULFF, P. ET AL.	1934	P	0.589	298	SIMILAR TO ABOVE BUT FOR EXTRAORDINARY RAY; UNCERTAINTY OF INDEX 0.001.
7	90	MARCOUX, J.	1971	F	0.4-0.7	1045	MOLTEN SALT; VYCOR TUBE FILLED WITH THE MELT FORMED A CYLINDRICAL LENS; REFRACTIVE INDEX DETERMINED BY FOCAL LENGTH DETERMINATION METHOD FOR 4 SPECTRAL LINES; DATA EXTRACTED FROM A TABLE; UNCERTAINTY OF INDEX 0.005.

H. H. LI

TABLE 47. EXPERIMENTAL REFRACTIVE INDEX OF CALCIUM CHLORIDE (WAVELENGTH DEPENDENCE)
[WAVELENGTH, λ - um; TEMPERATURE, T, K; REFRACTIVE INDEX, n]

λ	n
DATA SET 1	
T = 298.0	
0.589	1.542
DATA SET 2	
T = 298.0	
0.589	1.531
DATA SET 3	
T = 298.0	
0.589	1.566
DATA SET 4	
T = 298.0	
0.589	1.548
DATA SET 5	
T = 298.0	
0.589	1.5504
DATA SET 6	
T = 298.0	
0.589	1.4949
DATA SET 7	
T = 1045.	
0.4047	1.623
0.5000	1.590
0.6000	1.580
0.6943	1.570

3.6. Strontium Chloride, SrCl_2

The structure of SrCl_2 is of the CaF_2 type. The space group is O_h^5 . There has been considerable interest in SrCl_2 , CaF_2 , BaF_2 , and SrF_2 . One of the reasons for this interest is that these crystals are nearly ideal host lattices for paramagnetic ions. Many electronic excitation and magnetic resonance experiments have been performed on rare earth ions and other ions in these materials. For some of these investigations, the host lattice was SrCl_2 . It is of some importance to study the optical properties of pure strontium chloride.

SrCl_2 single crystals are highly hygroscopic. The hydrated form $\text{SrCl}_2 \cdot \text{H}_2\text{O}$ readily comes into being when SrCl_2 crystals are exposed to air. Special precautions are necessary when growing the crystals, and preparing and storing the samples. The crystals can be grown in an inert gas atmosphere by the Czochralsky method. Grinding and polishing the sample surfaces can be accomplished with an abrasive dispersed in a water-free organic liquid. For storage the material should be immersed in a waterfree organic liquid, such as paraffin oil.

Direct measurement on the refractive index of SrCl_2 was re-

ported by Wulff and Heigl [62] for only a single spectral line at 0.589 micrometer, as given in tables 48 and 49, and figure 27, where the refractive index of hydrated strontium chloride is also listed for the purpose of comparison. This single value is probably the only directly measured value available. Another investigation on the refractive index was carried out by Droste and Geick [91], in which the refractive index was deduced from the reflection spectrum by Lorentz theory. As the available data is very scanty and the material is not suitable for optical application, no attempt was made at data analysis and data prediction. We present only the available raw data as shown in tables 48 and 49, and the following related properties:

$$\epsilon_0 = 7.55,$$

$$\epsilon_\infty = 2.86,$$

$$\nu_{TO} = 138 \text{ cm}^{-1},$$

$$\text{and} \quad \nu_{LO} = 223 \text{ cm}^{-1}.$$

The above values were taken from [91].

REFRACTIVE INDEX OF ALKALINE EARTH HALIDES

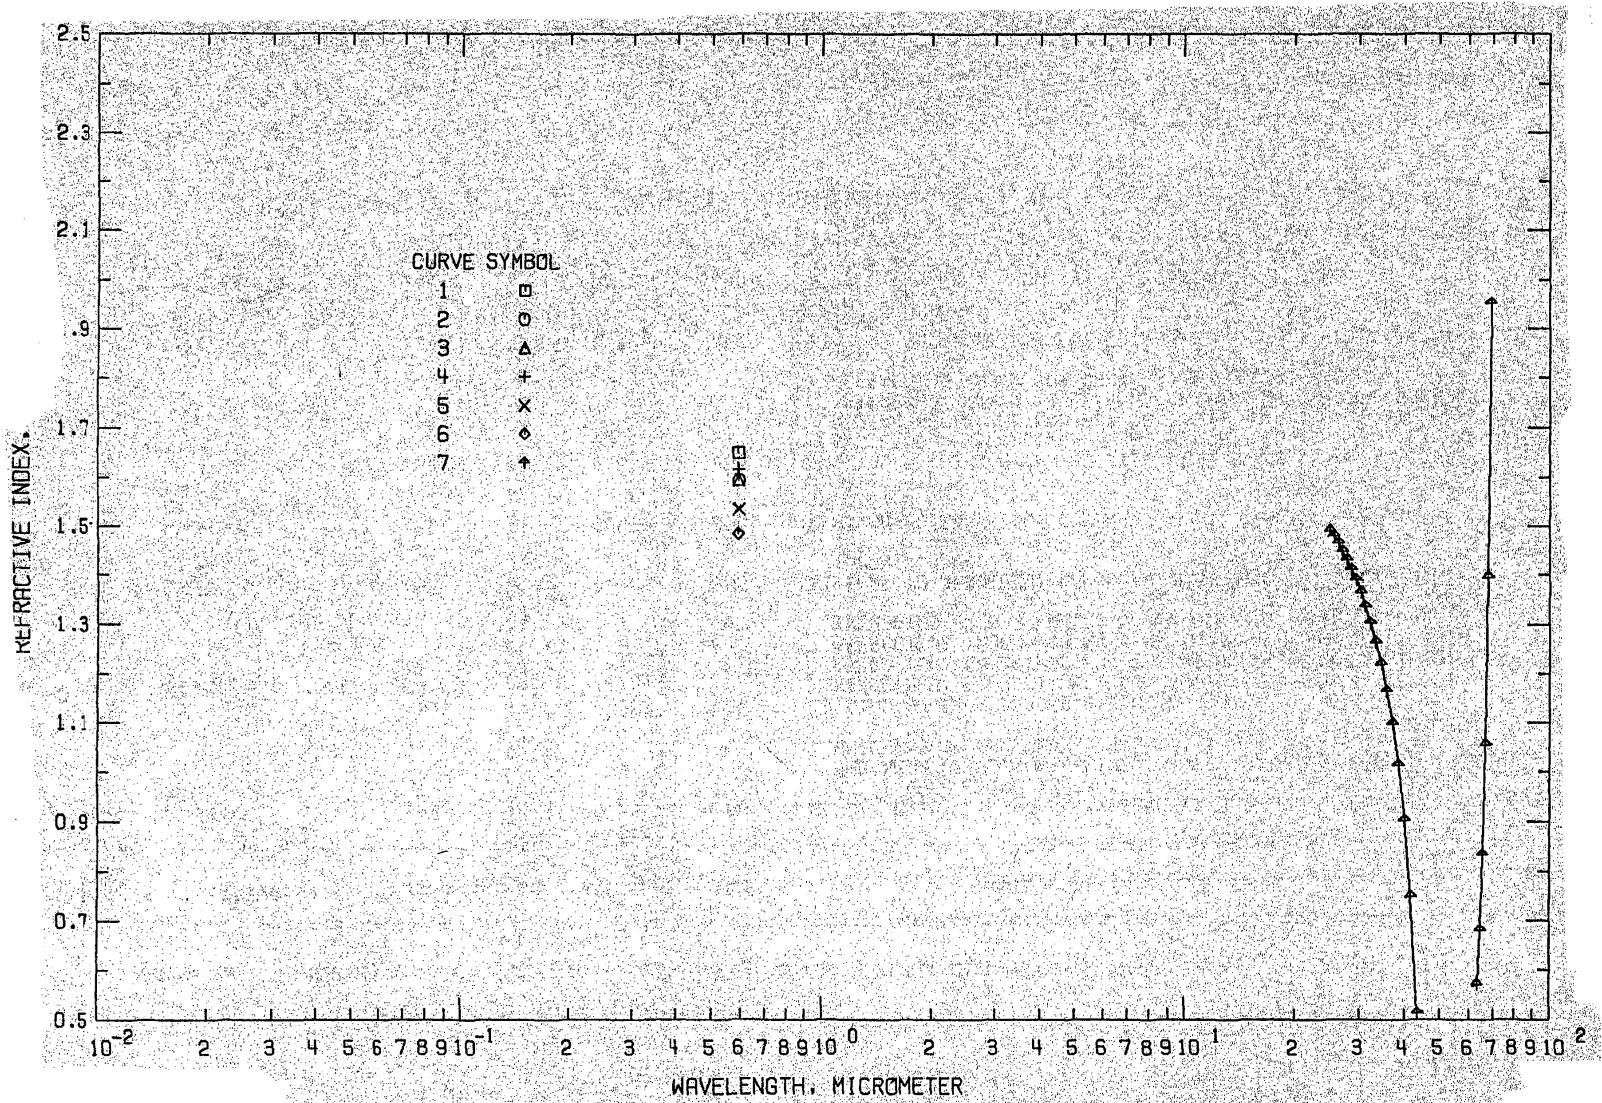


FIGURE 27. REFRACTIVE INDEX OF STRONIUM CHLORIDE (WAVELENGTH DEPENDENCE).

TABLE 48. MEASUREMENT INFORMATION ON THE REFRACTIVE INDEX OF STRONTIUM CHLORIDE (WAVELENGTH DEPENDENCE)

DATA SET NO.	REF. NO.	AUTHOR(S)	YEAR	METHOD USED	WAVELENGTH RANGE, μm	TEMP., K	SPECIFICATIONS AND REMARKS
1	62	WULFF, P. HEIGL, A.	1931	M	0.589	298	SINGLE CRYSTAL; 1-2 MM FRAGMENTS; OBTAINED FROM COOLING THE MELT; REFRACTIVE INDEX DETERMINED BY IMMERSION METHOD FOR THE MEAN OF SODIUM D LINES; DATA EXTRACTED FROM A TABLE; UNCERTAINTY OF INDEX 0.00003.
2	62	WULFF, P. ET AL.	1931	P	0.589	298	CRYSTAL OF DI-HYDRATED STRONTIUM CHLORIDE OF MONOCLINIC STRUCTURE; REFRACTIVE INDEX DETERMINED BY A PULFRICH REFRACTOMETER METHOD FOR THE MEAN OF SODIUM D LINES; REFRACTIVE INDEX FOR RAYS ALONG A-AXIS OBTAINED; DATA EXTRACTED FROM A TABLE; UNCERTAINTY OF INDEX 0.0002.
3	62	WULFF, P. ET AL.	1931	P	0.589	298	SIMILAR TO ABOVE BUT FOR RAYS ALONG B-AXIS; UNCERTAINTY OF INDEX 0.0004.
4	62	WULFF, P. ET AL.	1931	P	0.589	298	SIMILAR TO ABOVE BUT FOR RAYS ALONG C-AXIS; UNCERTAINTY OF INDEX 0.0001.
5	62	WULFF, P. ET AL.	1931	P	0.589	298	CRYSTAL OF HEXA-HYDRATED STRONTIUM CHLORIDE OF TRIGONAL STRUCTURE; REFRACTIVE INDEX DETERMINED BY A PULFRICH REFRACTOMETER METHOD FOR THE MEAN OF SODIUM D LINES; DATA EXTRACTED FROM A TABLE; UNCERTAINTY OF INDEX 0.00003; REFRACTIVE INDEX FOR ORDINARY RAY OBTAINED.
6	62	WULFF, P. ET AL.	1931	P	0.589	298	SIMILAR TO ABOVE BUT FOR EXTRAORDINARY RAY; UNCERTAINTY OF INDEX 0.0003.
7	91	DROSTE, R. GEICK, R.	1974	R	25-250	300	SINGLE CRYSTAL; GROWN BY A CZOCHRALSKY METHOD; ANNEALED AT 923K FOR 24 HOURS; REFRACTIVE INDEX DEDUCED FROM REFLECTION SPECTRUM WITH LORENTZ THEORY; DATA EXTRACTED BY EVALUATING A GIVEN EQUATION.

TABLE 49. EXPERIMENTAL REFRACTIVE INDEX OF STRONTIUM CHLORIDE (WAVELENGTH DEPENDENCE)
 [WAVELENGTH, λ , μm ; TEMPERATURE, T ; REFRACTIVE INDEX, n]

λ	n	λ	n	λ	n
DATA SET 1					
$T = 298.0$					
0.589	1.64986	32.26	1.305	83.33	4.598
		33.33	1.266	85.11	4.389
		34.48	1.221	86.96	4.213
DATA SET 2					
$T = 298.0$					
		35.71	1.166	88.89	4.063
		37.04	1.099	90.91	3.933
		38.46	1.014	93.02	3.820
0.589	1.5942	40.00	0.903	95.24	3.721
		41.67	0.749	97.56	3.633
DATA SET 3					
$T = 298.0$					
		43.48	0.514	100.00	3.555
		45.45	0.240	111.11	3.313
		47.62	0.175	125.00	3.147
0.589	1.5948	50.00	0.171	142.86	3.027
		52.63	0.188	166.67	2.939
DATA SET 4					
$T = 298.0$					
		53.33	0.196	200.00	2.873
		54.05	0.205	250.00	2.825
		54.79	0.215		
0.589	1.6172	55.56	0.228		
		56.34	0.243		
DATA SET 5					
$T = 298.0$					
		57.14	0.261		
		57.97	0.283		
		58.82	0.309		
0.589	1.53560	59.70	0.341		
		60.61	0.379		
DATA SET 6					
$T = 298.0$					
		61.54	0.428		
		62.50	0.490		
		63.49	0.572		
0.589	1.48565	64.52	0.681		
		65.57	0.833		
DATA SET 7					
$T = 300.0$					
		66.67	1.055		
		67.80	1.396		
		68.97	1.952		
25.00	1.492	70.18	2.900		
25.64	1.480	71.43	4.431		
26.31	1.466	72.73	6.094		
27.03	1.450	74.07	6.719		
27.78	1.433	75.47	6.455		
28.57	1.413	76.92	5.976		
29.41	1.392	78.43	5.528		
30.30	1.367	80.00	5.155		
31.25	1.338	81.63	4.849		

3.7. Barium Chloride, BaCl₂

Available data on the refractive index of barium chloride are given in tables 50 and 51, and are plotted in figure 28, where data for hydrated barium chloride are also presented for com-

parison. As the refractive index was measured only for the single spectral line 0.589 micrometer, and the material is not suitable for optical application, data analysis and data prediction were not attempted.

REFRACTIVE INDEX OF ALKALINE EARTH HALIDES

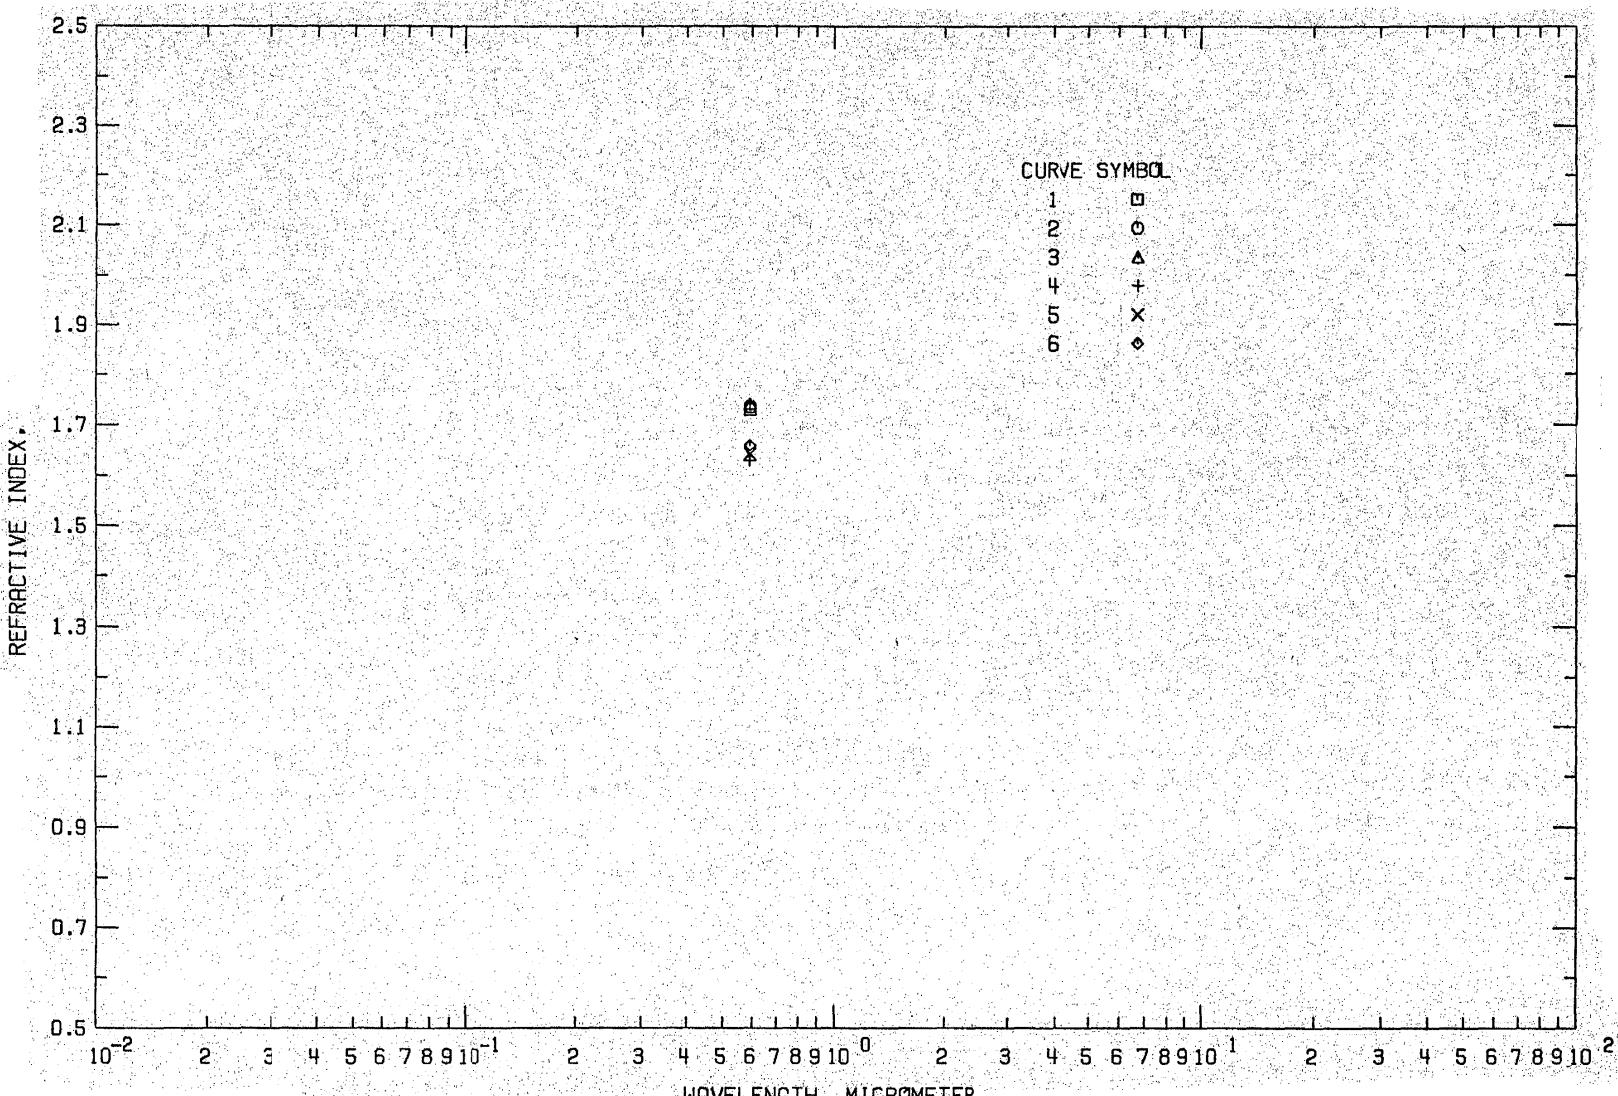


FIGURE 28. REFRACTIVE INDEX OF BARIUM CHLORIDE (WAVELENGTH DEPENDENCE).

TABLE 50. MEASUREMENT INFORMATION ON THE REFRACTIVE INDEX OF BARIUM CHLORIDE (WAVELENGTH DEPENDENCE)

DATA SET NO.	REF. NO.	AUTHOR(S)	YEAR	METHOD USED	WAVELENGTH RANGE, μm	TEMP. K	SPECIFICATIONS AND REMARKS
1	62	WULFF, P. HEIGL, A.	1931	P	0.589	298	BIAXIAL CRYSTAL; PRODUCED BY SLOWLY COOLING OF THE MELT; REFRACTIVE INDEX DETERMINED BY A PULFRICH REFRACTOMETER FOR THE MEAN OF SODIUM D LINES ALONG A-AXIS; DATA EXTRACTED FROM A TABLE; UNCERTAINTY OF INDEX 0.00015.
2	62	WULFF, P. ET AL.	1931	P	0.589	298	SIMILAR TO ABOVE BUT FOR RAYS ALONG B-AXIS; UNCERTAINTY OF INDEX 0.00015.
3	62	WULFF, P. ET AL.	1931	P	0.589	298	SIMILAR TO ABOVE BUT FOR RAYS ALONG C-AXIS; UNCERTAINTY OF INDEX 0.00015.
4	62	WULFF, P. ET AL.	1931	P	0.589	298	CRYSTAL OF DI-HYDRATED BARIUM CHLORIDE OF MONOCLINIC STRUCTURE; REFRACTIVE INDEX DETERMINED BY A PULFRICH REFRACTOMETER FOR THE MEAN OF SODIUM D LINES ALONG A-AXIS; DATA EXTRACTED FROM A TABLE; UNCERTAINTY OF INDEX 0.00006.
5	62	WULFF, P. ET AL.	1931	P	0.589	298	SIMILAR TO ABOVE BUT FOR RAYS ALONG B-AXIS; UNCERTAINTY OF INDEX 0.00010.
6	62	WULFF, P. ET AL.	1931	P	0.589	298	SIMILAR TO ABOVE BUT FOR RAYS ALONG C-AXIS; UNCERTAINTY OF INDEX 0.00010.

H. H. LI

REFRACTIVE INDEX OF ALKALINE EARTH HALIDES

TABLE 51. EXPERIMENTAL REFRACTIVE INDEX OF BARIUM CHLORIDE (WAVELLENGTH DEPENDENCE)
[WAVELENGTH, λ , AND TEMPERATURE, T , K; REFRACTIVE INDEX, n]

λ	n
DATA SET 1 $T = 288.0$	
0.589	1.73024
DATA SET 2 $T = 298.0$	
0.589	1.73611
DATA SET 3 $T = 298.0$	
0.589	1.74196
DATA SET 4 $T = 298.0$	
0.589	1.62905
DATA SET 5 $T = 298.0$	
0.589	1.64191
DATA SET 6 $T = 298.0$	
0.589	1.65829

4. Conclusions and Recommendations

Experimental data on the refractive index of alkaline earth halides and its temperature derivative are exhaustively surveyed and reviewed. In addition, values of physical properties which are related to the dispersion phenomena are selected from the open literature.

Of the twenty alkaline earth halides, only the four fluorides (MgF_2 , CaF_2 , SrF_2 , and BaF_2) are suitable for optical applications; others are either physically inadequate or chemically too unstable for utilization. As a consequence, available data on the refractive index and its temperature derivative largely concern the four fluorides.

The purpose of the present work was to survey and compile the available data and to generate recommended values of the refractive index and its temperature derivative for alkaline earth halides. We have generated recommended values for the four fluorides (as shown in figures 29, 30, and 31). The state of knowledge on the refractive index of this group of materials is also presented.

The technology related to high-power infrared lasers is progressing rapidly and, consequently, there is an increasing need to determine the effects that exposures to high-power light beams have on materials. Among other things, refractive indices at elevated temperatures are needed. Unfortunately, an exhaustive survey of the open literature, as in the present work, shows that refractive indices as a function of wavelength are only available near room temperature. Measurements on the refractive index at higher temperatures are limited to a few wavelengths. In a few cases, the temperature derivative of the refractive index has also been measured in the vicinity of room temperature. Even though it is clear that high temperature data are lacking, recent measurements reported in the open literature were still carried out at near room temperature. Consequently, our basic knowledge of the refractive index at high temperatures is still scanty. For the purpose of providing data useful to modern science and technology, as well as for the future development of optical devices, a well planned and systematic program of measurement of the refractive index of selected materials over a wide range of temperatures and wavelengths is highly recommended.

REFRACTIVE INDEX OF ALKALINE EARTH HALIDES

285

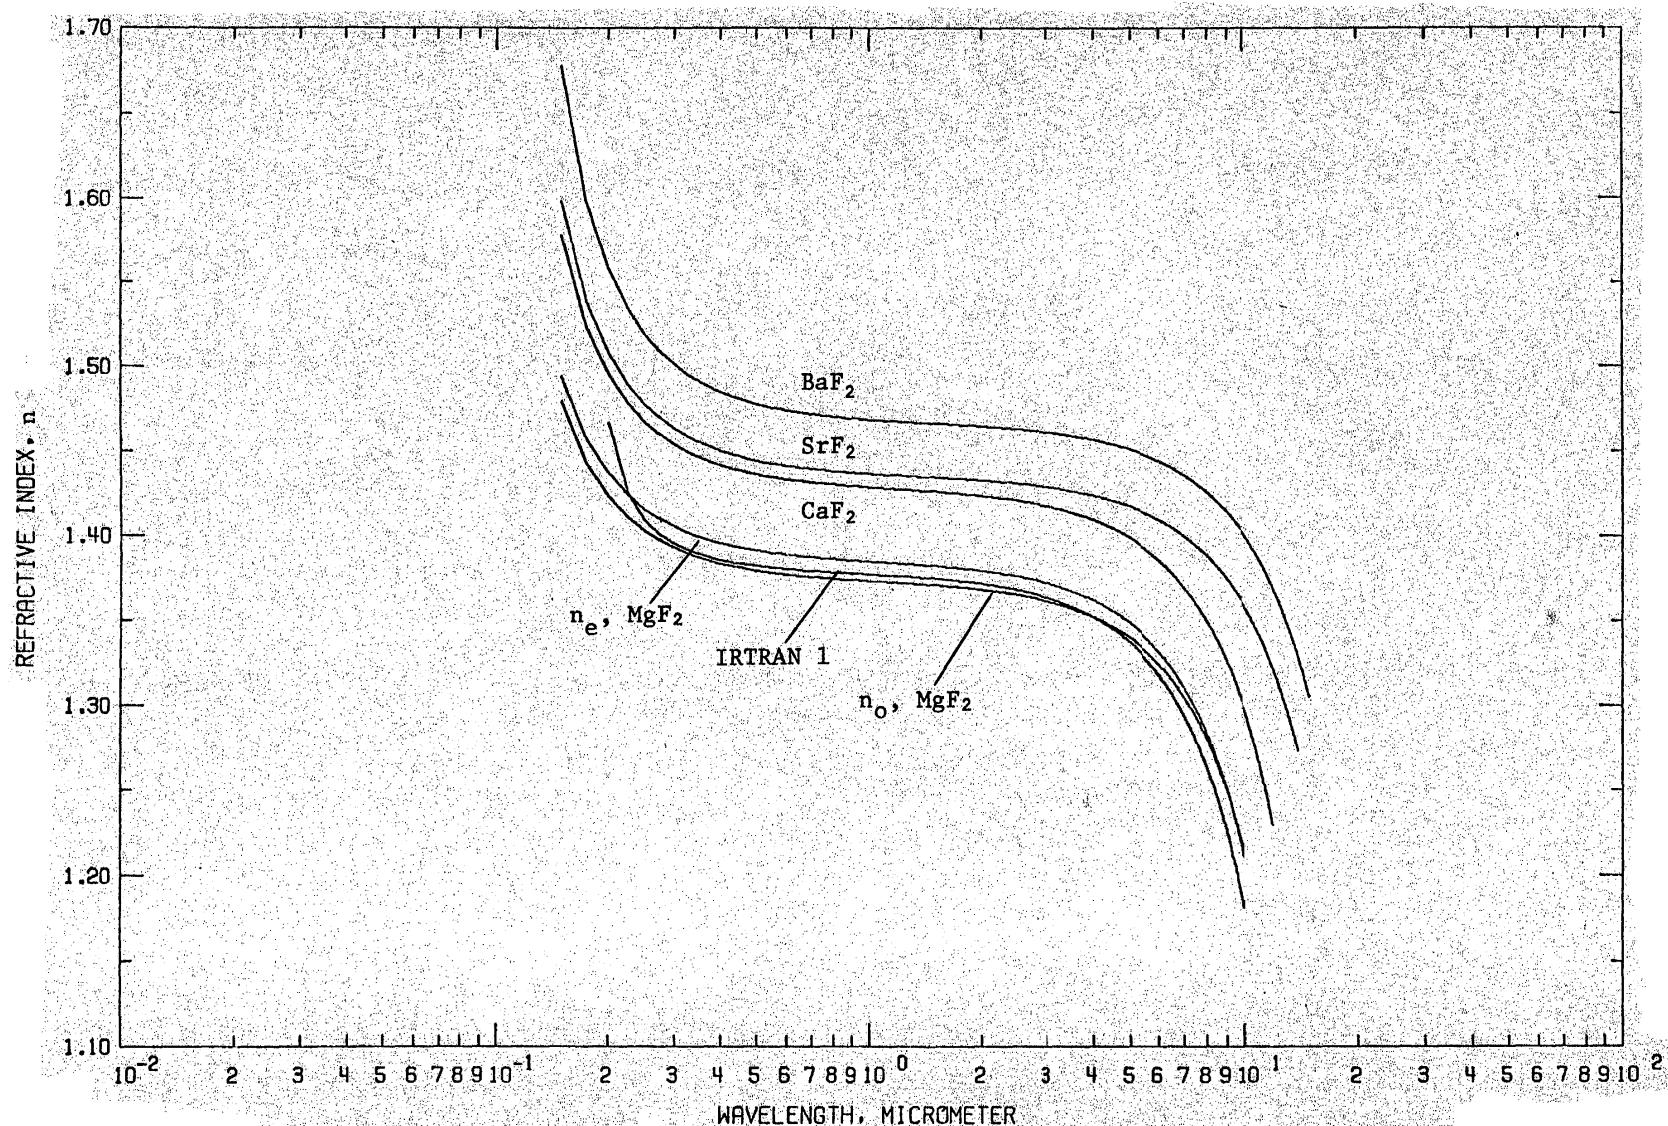


FIGURE 29. REFRACTIVE INDEX OF ALKALINE EARTH HALIDES (WAVELENGTH DEPENDENCE).

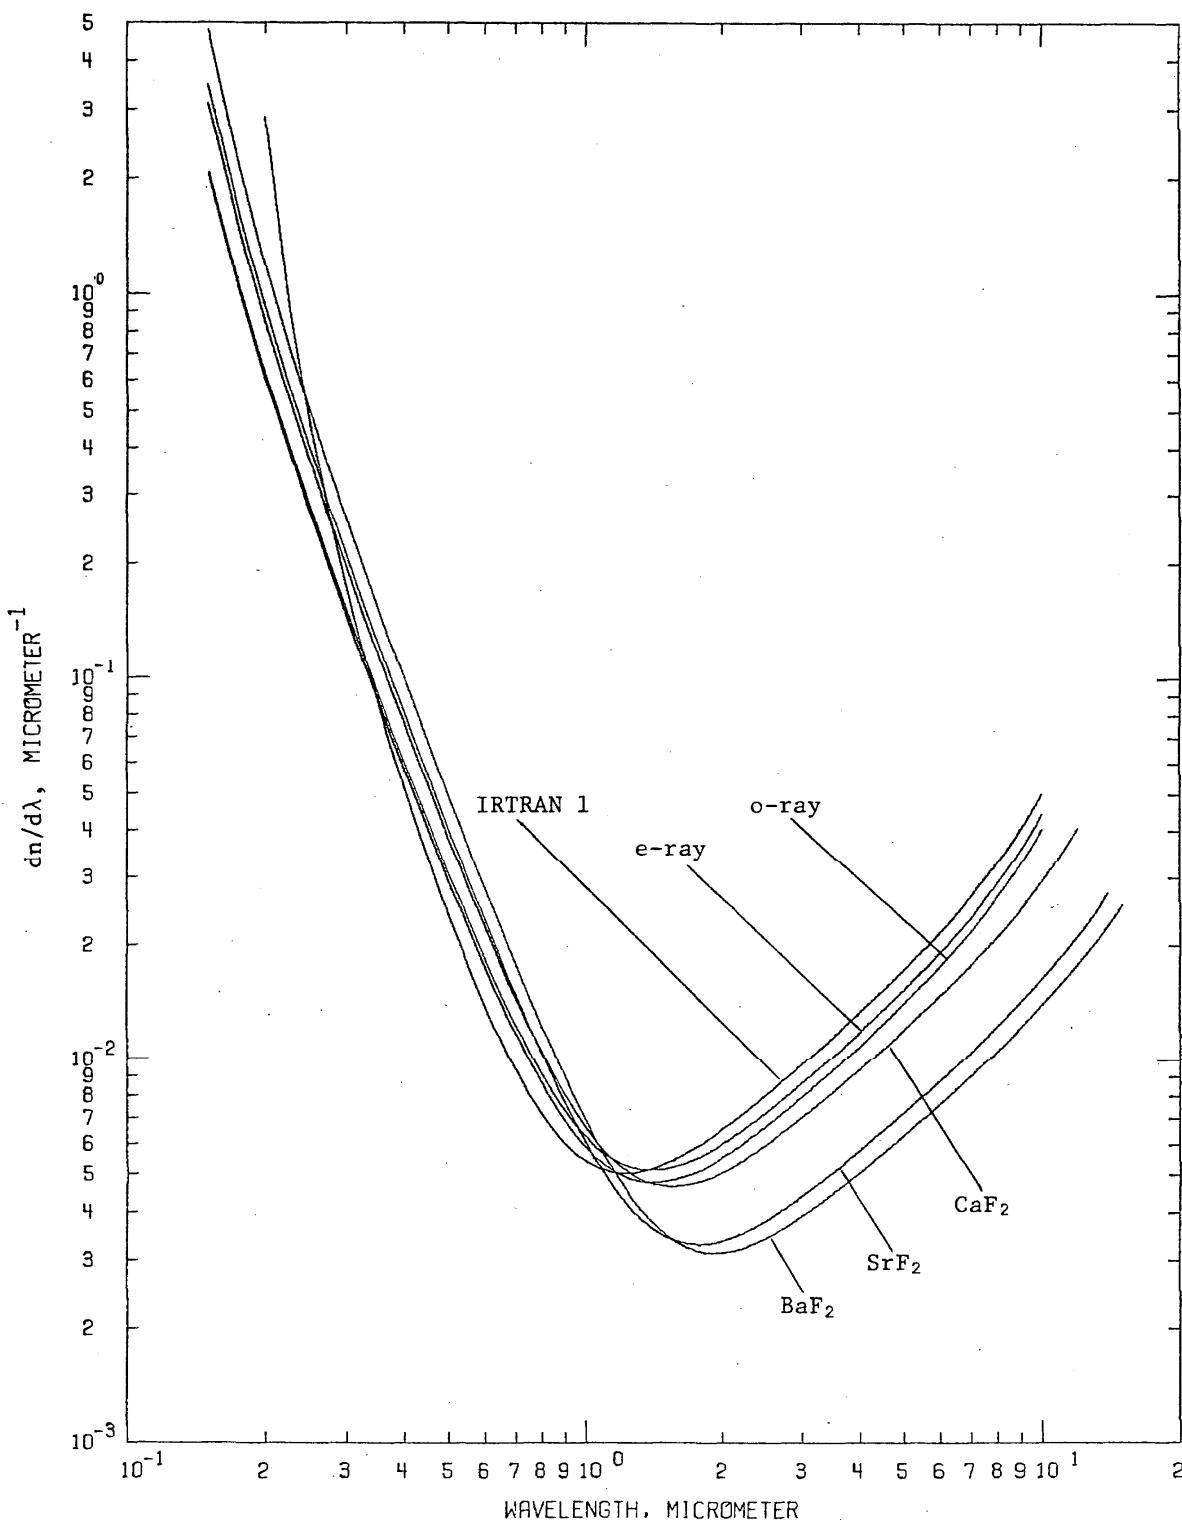


FIGURE 30. WAVELENGTH DERIVATIVE OF REFRACTIVE INDEX OF ALKALINE EARTH HALIDES .

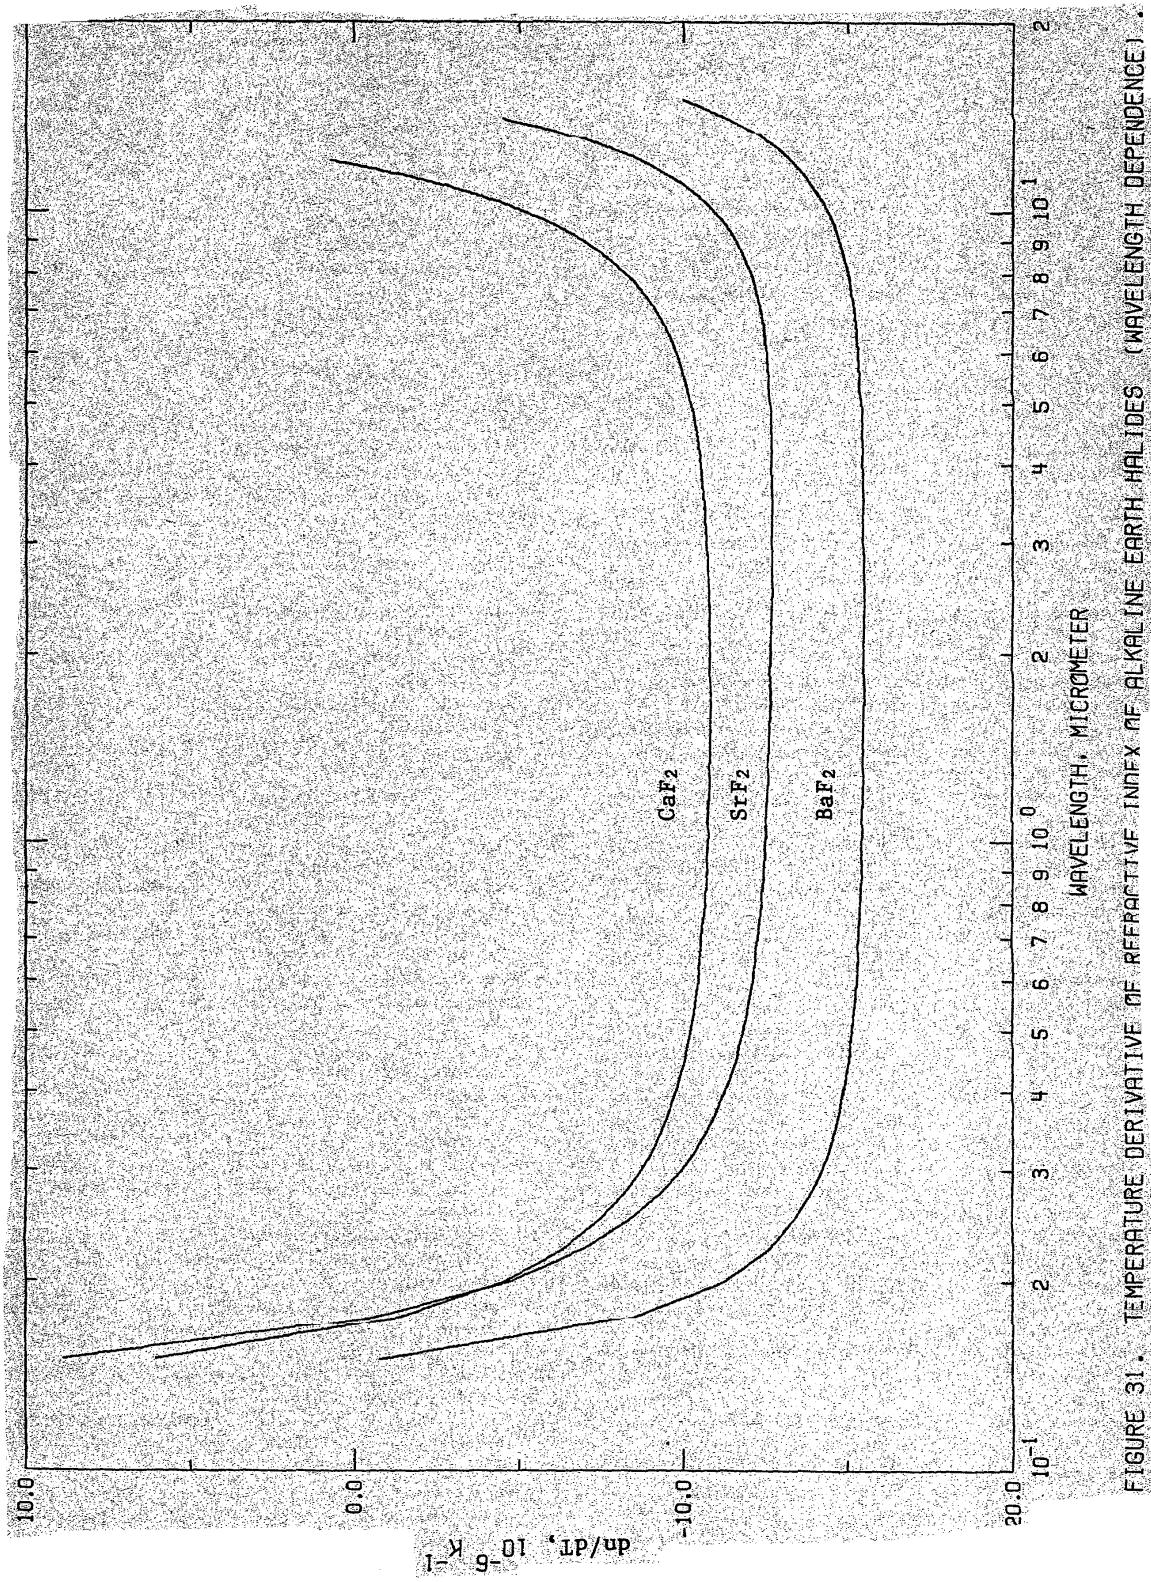


FIGURE 31. TEMPERATURE DERIVATIVE OF REFRACTIVE INDEX OF ALKALINE EARTH HALIDES (WAVELENGTH DEPENDENCE).

5. Acknowledgement

The work is supported by the Office of Standard Reference Data (OSRD) of the National Bureau of Standards (NBS), U.S. Department of Commerce.

The author is grateful to Dr. S. A. Rossmassler of OSRD for his helpful suggestions and encouragement during the course of the present work. The author is especially indebted to Dr. H. M. James of CINDAS staff for his generous pre-review of this work and his many suggestions which have enhanced the report. Furthermore, the assistance provided by the CINDAS Scientific Documentation Division is gratefully acknowledged.

6. References

- [1] Wyckoff, R. W. G., "Crystal Structures", 2nd edition, Interscience Publishers, 1, 239, 1965.
- [2] Zachariasen, W. H., Quoted by Kittel, C. in "Introduction to Solid State Physics", 3rd edition, J. Wiley, 105, 1967.
- [3] Laser Focus, **12**, (5), 1976.
- [4] Garton, G., and Walker, P. J., "Growth from the Melt of Single Crystals of Some Chlorides With the Cadmium Chloride Structure" *J. Crystal Growth* **33**, 331-4, 1976.
- [5] Monberg, E., and Ebisuzaki, Y., "Growth of a Large Single Crystal of Orthorhombic BaBr₂", *J. Crystal Growth*, **21**, 307-9, 1974.
- [6] National Materials Advisory Board, "High-Power Infrared-Laser Windows," National Academy of Sciences-National Academy of Engineering, Washington, D.C., Publication NMAB-292, 168 pp., 1972.
- [7] Smakula, A., "Physical Properties of Optical Crystals with Special Reference to Infrared," Office of Technical Services, U.S. Dept. of Commerce Document No. 111,052, 286 pp., 1952.
- [8] Ballard, S. S., McCarthy, K. A., and Wolfe, W. L., "Optical Materials for Infrared Instrumentation," Michigan Univ., Willow Run Lab., Rept. No. 2389-11-5, 115 pp., 1959. [AD217 367]
- [9] Coblenz, W. W., "Transmission and Refraction Data on Standard Lens and Prism Material with Special Reference to Infrared Spectroradiometry," *J. Opt. Soc. Amer.*, **4**, 432-47, 1920.
- [10] Landolt-Bornstein, Physikalisch-Chemische Tabellen, 5th Edition, Vol. 2, 911-22, 1923; Vol. 3, 1467-72, 1935; 6th Edition, Vol. 2, No. 8, 2-405-2-432, 1962.
- [11] Gray, D. E., (Editor), American Institute of Physics Handbook, 3rd Edition, McGraw-Hill Book Co., New York, 2342 pp., 1972.
- [12] Weast, R. C., (Editor), Handbook of Chemistry and Physics, The Chemical Rubber Co., Ohio, 1969.
- [13] Fowles, G. R., Introduction to Modern Optics, Holt, Rinehart and Winston, Inc., New York, 304 pp., 1968.
- [14] Barker, A. S. Jr., "Transverse and Longitudinal Optic Mode Study in MgF₂ and ZnF₂", *Phys. Rev.*, **136**, (A5), A1290-5, 1964.
- [15] Lowndes, R. P., "Anharmonicity in the Alkaline Earth Fluorides", *J. Phys. C, Solid State Phys.*, **4** (18), 3083-94, 1971.
- [16] Bosomworth, D. R., "Far-infrared Optical Properties of CaF₂, SrF₂, BaF₂, and CdF₂", *Phys. Rev.*, **157**(3), 709-15, 1967.
- [17] Kaiser, W., Spitzer, W. G., Kaiser, R. H., and Howarth, L. E., "Infrared Properties of Calcium Fluoride, Strontium Fluoride and Barium Fluoride", *Phys. Rev.*, **127**(6), 1950-54, 1962.
- [18] Duncanson, A., and Stevenson, R. W. H., "Some Properties of Magnesium Fluoride Crystallized From the Melt", *Roy. Soc. of London, Proc.*, **72**, 1001-6, 1958.
- [19] Andeen, C., Fontanella, J., and Schuele, D., "Low-Frequency Dielectric Constant of The Alkaline Earth Fluorides by the Method of Substitution," *J. Appl. Phys.*, **42**(6), 2216-9, 1971.
- [20] Eastman Kodak Co., "Kodak Infrared Optical Materials", Eastman Kodak Publication U-72, 1971.
- [21] Rao, K. V. and Smakula, A., "Dielectric Properties of Alkaline Earth Fluoride Single Crystals", *J. Appl. Phys.*, **37**, 319, 1966.
- [22] Jones, B. W., "The Dielectric Constant of Ionic Solids and Its Change with Hydrostatic Pressure", *Phil. Mag.*, **16**, 1085, 1967.
- [23] Denham, P., Field, G. R., Morse, P. L. R., and Wilkinson, G. R., "Optic and Dielectric Prop. of Lattice Dynamics of Some Fluorite Structured Ionic Crystals", *Wheat Stone Phys., Lab., King's College, London, Proc. Roy. Soc., London*, **A317**, 55-77, 1970.
- [24] Rubloff, G. W., "Far Ultraviolet Reflectance Spectra and the Electron Structure of Ionic Crystals", *Phys. Rev.*, **B5**(2), 662-84, 1972.
- [25] Nisar, M., and Robin, S., "Far Ultraviolet Electronic Spectra of SrF₂ and BaF₂", *Pak. J. Sci. Ind. Res.*, **17**(2-3), 49-54, 1974.
- [26] Ramachandran, G. N., "Thermo-optic Behavior of Solids, III. Fluorspar", *Proc. Ind. Acad. Sci.*, **A25**, 286-95, 1947.
- [27] Tsay, Y. F., Bendow, B., and Mitra, S. S., "Theory of the Temperature Derivative of the Refractive Index in Transparent Crystals", *Phys. Rev.*, **B8**(6), 2688-96, 1973.
- [28] Stefan, J. M., "The Influence of Heat on the Light Refraction of Solids," *Sitzungsber. Akad. Wiss. Wien*, **2**, 63, 223-45, 1871.
- [29] Sarasin, E., "Refractive Indices of Calcium Fluoride in the Extreme Ultraviolet Wavelength Region", *Archives d. Sciences, Phys. and Nature*, **10**, 303-4, 1883.
- [30] Pulfrich, C., "Influence of the Temperature on the Refraction of Glasses," *Ann. Phys. Chem.*, **45**(4), 609-65, 1892.
- [31] Rubens, H., and Snow, B. W., "Refraction of Long Wavelength Radiation in Rocksalt, Sylvite, and Fluorite," *Wied. Ann.*, **46**, 529-41, 1892.
- [32] Rubens, H., "The Dispersion of Infrared Radiation," *Wied. Ann.*, **45**, 238-61, 1892.
- [33] Carvallo, E., "Spectre Calorifique de la Fluorine", *Compt. Rend.*, **116**, 1189-91, 1893.
- [34] Simon, H. T., "The Dispersion of Ultraviolet Rays", *Wied. Ann.*, **53**, 542-58, 1894.
- [35] Rubens, H., "The Dispersion of Infrared Radiation in Fluorite," *Wied. Ann.*, **51**, 381-95, 1894.
- [36] Rubens, H., "Proof of the Ketteler-Helmholtz Dispersion Formula," *Wied. Ann.*, **53**, 267-86, 1894.
- [37] Paschen, F., "The Dispersion of Fluorite in Infrared", *Wied. Ann.*, **53**, 301-33, 1894.
- [38] Paschen, F., "The Wavelength Scale of the Infrared Spectrum of Fluorite", *Wied. Ann.*, **56**, 762-7, 1895.
- [39] Langley, S. P., "The Dispersion of Rock Salt and Fluorite," *Ann. Astrophys. Obs. Smithsonian Inst.*, **1**, 219-37, 1900.
- [40] Paschen, F., "A New Measurement of the Dispersion of Fluorite in Infrared", *Ann. Phys.*, **4**, 299-303, 1901.
- [41] Martens, F. F., "The Dispersion of Ultraviolet Radiation," *Ann. Phys.*, **6**, 603-40, 1901.
- [42] Martens, F. F., "The Dispersion of Fluorite, Sylvite, Rocksalt, Quartz, and Calcite, as Well as the Dispersion of a Diamond," *Ann. Phys.*, **8**, 459-65, 1902.
- [43] Pfund, A. H., "The Brewsterian Angle and Refractive Indices," *J. Opt. Soc. Amer.*, **31**(11), 679-82, 1974.
- [44] Ramadier-Delbes, "Interferometry by Thin Films in the Infrared. Determination of the Refractive Index of Calcium Fluoride From 7 to 15 Microns (in Fr.)", *J. Phys. Radium*, **11**(11), 622-6, 1950.
- [45] Heisen, A., "Determination of the Refractive Indices of Several Fluoride Vapour-Deposited Films and Carbon Films", *Optik*, **18**(2), 59-68, 1961.
- [46] Heilmann, C., "The Extinction Coefficient and Refractive Index of Calcium Fluoride in the Infrared Region (in Ger.)", *Z. fuer Phys.*, **176**(3), 253-60, 1963.
- [47] Houston, T. W., Johnson, L. F., Kisliuk, P., and Walsh, D. J., "Temperature Dependence of the Refractive Index of Optical Maser Crystals", *J. Opt. Soc. Amer.*, **53**, 1286-91, 1963.
- [48] Malitson, I. H., "A Redetermination of Some Optical Properties of Calcium Fluoride", *Appl. Optics*, **2**(11), 1103-1107, 1963.
- [49] Fabre, D., Romand, J., and Vodas, B., "Optical Constant of Alkali Fluorides and Alkaline Earth Fluorides (in Fr.)", *J. Phys.*, **25**(1-2), 55-9, 1964.
- [50] Berman, L. V., and Zhukov, A. G., "Optical Properties of Calcium Fluoride in the Wavelength Range 170-600 Microns", *Opt. and Spectrosc.*, **19**(5), 433-5, 1965.
- [51] Heitmann, W., and Koppelman, G., "Refractive Index Determination of High Reflectivity Dielectric Multiple Layers", *Z. fuer Angewandte Phys.*, **23**(4), 221-6, 1967.

- [52] Field, G. R., and Wilkinson, G. R., "A Calculation of the Refractive Index of Calcium Fluoride Using Experimentally Determined Oscillator Parameters", *Spectrochim. Acta, Part A*, **29**(4), 59–64, 1973.
- [53] Ganin, V. A., Kurin, M. G., Sidorin, V. K., Sidovin, K. K., Starostin, N. V., Startsev, G. P., and Shepilov, M. P., "Optical Constants and Energy-Band Structure of Fluorite-Type Crystals", *Sov. Phys., Solid State*, **16**(12), 2313–8, 1975.
- [54] Barbaron, M., "Refractive Index of Solids at Low Temperatures (in Fr.)", *Ann. Phys.*, **6**, 899–959, 1951.
- [55] Reed, J. O., "The Influence of the Temperature on the Refraction and Dispersion of Some Crystals and Glasses," *Ann. Phys. Chem.*, **65**, 707–44, 1898.
- [56] Micheli, F. J., "The Influence of the Temperature on the Ultraviolet Radiation Dispersion in Fluorite, Rocksalt, Quartz, and Calcite," *Ann. Phys.*, **4**, 7, 772–89, 1902.
- [57] Liebreich, E., "The Change of the Refractive Index With the Temperature in the Infrared Region for Rocksalt, Sylvite, and Fluorite," *Verh. Deut. Phys. Ges.*, **13**(1), 1–18, 1911.
- [58] Liebreich, E., "The Optical Temperature Coefficient for Rocksalt, Sylvite, and Fluorite in the Region of lower Temperatures," *Verh. Deut. Phys. Ges.*, **13**(18–19), 700–12, 1911.
- [59] Lipson, H. G., Tsay, Y. F., Bendow, B., and Ligor, P. A., "Temperature Dependence of the Refractive Index of Alkaline Earth Fluorides," *Appl. Opt.*, **15**(10), 2352–4, 1976.
- [60] Harris, R. J., Johnston, G. T., Kepple, G. A., Krok, P. C., and Mukai, H., "Infrared Thermo-Optic Coefficient Measurement of Polycrystalline ZnSe, ZnS, CdTe, CaF₂ and BaF₂, Single-Crystal KCl, and Tl-20 Glass," *Appl. Opt.*, 1977.
- [61] Selezneva, A. M., "Thermoptical Properties of LiF, BaF₂ and Corundum Crystals," *Soviet J. of Optical Technol.*, **36**(6), 754–6, 1969.
- [62] Thilo, F., "X-ray Investigation and Entropy Relationships of Alkaline Earth Fluorides," *Z. Kristallogr.*, **65**, 720–2, 1927.
- [63] Wulff, P., and Heigl, A., "Refractometric Measurements on Crystals," *Z. Kristallogr.*, **77**, 84–121, 1931.
- [64] Lukirskii, A. P., Savinov, E. P., Ershov, O. A., and Shepelev, Yu. F., "Reflection Coefficients of Radiation in the Wavelength Range from 23.6 to 113 Å for a Number of Elements and Substances and the Determination of Refractive Index and Absorption Coefficients," *Opt. Spectros.* (USSR), **16**(2), 168–728, 1964.
- [65] Gisin, M. A., "Optical Constants of Thin Strontium Fluoride Films," *Opt. and Spectrosc.*, **27**(2), 194–5, 1969.
- [66] Dickinson, S. K., "Infrared Laser Window Materials Property Data for ZnSe, KCl, NaCl, CaF₂, SrF₂, and BaF₂," AFCRL-TR-75-0318, 175, 1975.
- [67] Wulff, P., "An Interferometric Method to Determine the Refraction in Crystals," *Z. Elektrochem.*, **34**, 611–6, 1928.
- [68] Malitson, I. H., "Refractive Properties of Barium Fluoride," *J. Opt. Soc. Amer.*, **54**(5), 628–32, 1964.
- [69] Rood, J. L., "Some Properties of Thin Evaporated Films on Glass," *J. Opt. Soc. Amer.*, **39**, 854–9, 1979.
- [70] Schulz, L. G., and Scheibner, E. J., "An Experimental Study of the Change in Phase Accompanying Reflection of Light from Thin Evaporated Films," *J. Opt. Soc. Amer.*, **40**(11), 761–5, 1950.
- [71] Morita, N., "Evaporated Magnesium Fluoride Films," *Scientific Research Inst. J.*, **46**(1280), 127–9, 1952.
- [72] Hall, J. F., Jr., and Ferguson, W. F. C., "Dispersion of Zinc Sulfide and Magnesium Fluoride Films in the Visible Spectrum," *J. Opt. Soc. Amer.*, **45**(2), 74–75, 1955.
- [73] Jennes, J. R., Jr., "Reflection-reducing Coatings of Magnesium Fluoride and Lithium Fluoride in the Near Infrared," *J. Opt. Soc. Amer.*, **46**(3), 157–9, 1956.
- [74] Morita, N., "Optical Properties of Magnesium Fluoride Films," *Phys. Soc. of Japan, J.*, **11**(9), 975–80, 1956.
- [75] Cole, T. T., and Oppenheimer, F., "Polarization by Reflection and some Optical Constants in the Extreme Ultraviolet," *Appl. Opt.*, **16**, 709–10, 1962.
- [76] Williams, M. W., MacRae, R. A., and Arakawa, E. T., "Optical Properties of Magnesium Fluoride in the Vacuum Ultraviolet," *J. Appl. Phys.*, **38**(4), 1701–5, 1967.
- [77] Steinmetz, D. L., Phillips, W. G., Wirick, M., and Forbes, F. F., "A Polarizer for the Vacuum Ultraviolet," *Appl. Opt.*, **6**(6), 1001–4, 1967.
- [78] Nagata, K., "Inhomogeneity in Refractive Index of Evaporated Magnesium Fluoride Film," *Japan J. of Appl. Phys.*, **7**(10), 1181–5 1968.
- [79] Hass, G., and Ramsey, J. B., "Vacuum Deposition of Dielectric and Semiconductor Films by a CO₂ Laser," *Appl. Opt.*, **8**(6), 1115–8, 1969.
- [80] Shklyarevskii, I. N., El-Shazli, A. F. A., and Govorushchenko, A. I., "Dispersion of the Refractive Index in Magnesium Fluoride, Lithium fluoride, and Cryolite Films," *Opt. Spektrosk.*, **32**(4), 769–71, 1971.
- [81] Hanson, W. F., Arakawa, E. T., and Williams, M. W., "Optical Properties of MgO and MgF₂ in the Extreme Ultraviolet Region," *J. Appl. Phys.*, **43**(4), 1661–5, 1972.
- [82] Thomas, J., Stephan, G., Lemouvier, J. C., Nisar, M., and Robin, S., "Optical Anisotropy of MgF₂ in UV Absorption Region," *Phys. Stat. Sol.*, **56**(1), 163–70, 1973.
- [83] Yadava, V. N., Sharma, S. K., and Chopra, K. L., "Optical Dispersion of Homogeneously Mixed ZnS-MgF₂ Film," *Thin Solid Films*, **22**(1), 57–66, 1974.
- [84] Hacman, D., "Optical and Partial Pressure Analysis During Deposition of MgF₂ Films in Ultra High Vacuum," *Optica Acta*, **17**(9), 659–66, 1970.
- [85] Chandrasekharan, V., and Damany, H., "Birefringence of Sapphire, Magnesium Fluoride and Quartz in the Vacuum Ultraviolet, and Retardation Plates," *Appl. Opt.*, **7**(5), 939–41, 1968.
- [86] Palik, E. D., "A Magnesium Fluoride Soleil Compensator for the Near Infrared," *Appl. Optics*, **7**(5), 978–9, 1968.
- [87] Chandrasekharan, V., and Damany, H., "Anomalous Dispersion of Birefringence of Sapphire Crystals and Magnesium Fluoride in the Vacuum Ultraviolet," *Appl. Opt.*, **8**(3), 671–5, 1969.
- [88] Modine, F. A., Major, R. W., and Sander, E., "High Frequency Polarization Modulation Method for Measuring Birefringence," *Appl. Opt.*, **14**(3), 757–60, 1975.
- [89] Wulff, P., and Schaller, D., "Refractometric Measurements on Crystals and Comparison of Isomorphic Salts With Noble Gas Resembling and Non-Resembling Cations. 8. Communication About Refraction and Dispersion of Crystals," *Z. Kristallogr.*, **87**, 43–71, 1934.
- [90] Marcoux, J., "Measurement of the Index of Refraction of Some Molten Ionic Salts," *Rev. Sci. Instrum.*, **42**(5), 600–2, 1971.
- [91] Drosté, R., and Geick, R., "Investigation of the Infrared-Active Lattice Vibration in SrCl₂," *Phys. Status Solidi*, **B62**(2), 511–7, 1974.
- [92] Tsay, Y. F., Lipson, H. G., and Ligor, P. A., "The temperature variation of the thermo-optic coefficient of CaF₂," *J. Appl. Phys.*, **48**(5), 1953–5, 1977.
- [93] Dodge, M. J., "Refractive Index and Temperature Coefficient of Refractive Index of Hot-Forged Calcium Fluoride", NBS Special Publication 462, Laser Induced Damage in Optical Materials, 64–8, 1976.
- [94] Smakula, A., *Einkristalle—Wachstum, Herstellung und Anwendung*, Springer-Verlag, Berlin, 1962.
- [95] Kohlausch, F., "Praktischen Physik," B. G. Teubner, Leipzig, Vol. II, 528, 1943.