

Thermodynamic Properties of Selected Binary Aluminum Alloy Systems

Cite as: Journal of Physical and Chemical Reference Data **16**, 109 (1987); <https://doi.org/10.1063/1.555788>
Submitted: 21 August 1985 . Published Online: 15 October 2009

P. D. Desai



[View Online](#)



[Export Citation](#)


ARTICLES YOU MAY BE INTERESTED IN

Flash Method of Determining Thermal Diffusivity, Heat Capacity, and Thermal Conductivity
Journal of Applied Physics **32**, 1679 (1961); <https://doi.org/10.1063/1.1728417>

Reference Data for the Density and Viscosity of Liquid Aluminum and Liquid Iron
Journal of Physical and Chemical Reference Data **35**, 285 (2006); <https://doi.org/10.1063/1.2149380>

Thermodynamic Properties of Iron and Silicon

Journal of Physical and Chemical Reference Data **15**, 967 (1986); <https://doi.org/10.1063/1.555761>



Thermodynamic Properties of Selected Binary Aluminum Alloy Systems

P. D. Desai

Center for Information and Numerical Data Analysis and Synthesis, Purdue University, West Lafayette, Indiana 47906

Received August 21, 1985; revised manuscript received May 20, 1986

This work reviews the data and information available through March 1985 on the various thermodynamic properties of five binary aluminum alloy systems: Al-Fe, Al-Mn, Al-Ni, Al-Si, and Al-Ti. The thermodynamic properties covered in this work are heat capacity, Gibbs energy, enthalpy, and entropy of formation. Existing data have been evaluated and analyzed. The values for heat capacity and room-temperature enthalpy of formation for a large number of alloys have been generated. For each of the binary alloy systems, the recommended values for integral Gibbs energy, enthalpy, and entropy of formation as well as the partial quantities, activity, and activity coefficients for each component covering the entire composition range have been reported. These values are reported for both solid and liquid alloys.

Key words: activity; activity coefficient; aluminum-iron; aluminum-manganese; aluminum-nickel; aluminum-silicon; aluminum-titanium; enthalpy; entropy; Gibbs energy; heat capacity; phase diagram.

Contents

1. Introduction	110	8. Thermodynamic Properties of Al-Ti Binary Alloy System	121
2. General Background	110	8.1. Phase Diagram and Structures	121
3. Evaluation of Data	111	8.2. Solid Alloys	121
4. Thermodynamic Properties of Al-Fe Binary Alloy System	111	8.3. Liquid Alloys	122
4.1. Phase Diagram and Structures	111	8.4. References	124
4.2. Solid Alloys	112	9. Acknowledgments	124
4.3. Liquid Alloys	113		
4.4. References	114		
5. Thermodynamic Properties of Al-Mn Binary Alloy System	115		
5.1. Phase Diagram and Structures	115		
5.2. Solid Alloys	115		
5.3. Liquid Alloys	116		
5.4. References	116		
6. Thermodynamic Properties of Al-Ni Binary Alloy System	116		
6.1. Phase Diagram and Structures	116	1. Low-temperature data for solid Al-Fe alloys ..	112
6.2. Solid Alloys	117	2. Electronic specific heat coefficient of Al-Fe al-	112
6.3. Liquid Alloys	119	loys	
6.4. References	119	3a. High-temperature heat capacity of solid Al-Fe	113
7. Thermodynamic Properties of Al-Si Binary Alloy System	120	alloys	
7.1. Phase Diagram and Structures	120	3b. High-temperature heat capacity of solid Al-Fe	113
7.2. Liquid Alloys	120	alloys	
7.3. References	121	4. Enthalpies of formation for solid Al-Fe alloys	113
		at 298.15 K	
		5. Recommended integral quantities for solid Al-	113
		Fe alloys at 1173 K	
		6. Recommended partial molar quantities for sol-	113
		id Al-Fe alloys at 1173 K	
		7. Recommended integral quantities for liquid	114
		Al-Fe alloys at 1873 K	
		8. Recommended partial molar quantities for liq-	114
		uid Al-Fe alloys at 1873 K	
		9. Low-temperature heat capacity of solid Al-Mn	115
		alloys	
		10. Integral quantities for liquid Al-Mn alloys at	
		980 K	115

©1987 by the U.S. Secretary of Commerce on behalf of the United States. This copyright is assigned to the American Institute of Physics and the American Chemical Society.
Reprints available from ACS; see Reprints List at back of issue.

11. Recommended integral quantities for liquid Al-Mn alloys at 1600 K	116	24. High-temperature heat capacity of solid Al-Ti alloys	121
12. Recommended partial molar quantities for liquid Al-Mn alloys at 1600 K	116	25. Enthalpies of formation for solid Al-Ti alloys at 298.15 K	122
13. Low-temperature heat capacity of solid Al-Ni alloys	117	26. High-temperature data for solid Al-Ti alloy as a function of temperature, $x_{\text{Ti}} = 0.25$	122
14. High-temperature data for the ordered Al-Ni β' -phase, $x_{\text{Ni}} = 0.50$	117	27. Recommended integral quantities for solid Al-Ti alloys at 973 K	122
15. High-temperature data for Al-Ni α' phase, $x_{\text{Ni}} = 0.766$	117	28. Recommended partial molar quantities for solid Al-Ti alloys at 973 K	123
16. Enthalpies of formation for solid Al-Ni alloys at 298.15 K	118	29. Recommended integral quantities for solid Al-Ti alloys at 1780 K	123
17. Recommended integral quantities for solid Al-Ni alloys at 1273 K	118	30. Recommended partial molar quantities for solid Al-Ti alloys at 1780 K	123
18. Recommended partial molar quantities for solid Al-Ni alloys at 1273 K	119	31. Enthalpies of formation for liquid Al-Ti alloys at 2000 K	124
19. Recommended integral quantities for liquid Al-Ni alloys at 1873 K	119		
20. Recommended partial molar quantities for liquid Al-Ni alloys at 1873 K	120		
21. Recommended integral quantities for liquid Al-Si alloys at 1700 K	120		
22. Recommended partial molar quantities for liquid Al-Si alloys at 1700 K	120		
23. Low-temperature heat capacity of solid Al-Ti alloys	121		

List of Figures

1. Aluminum-iron phase diagram	111
2. Aluminum-manganese phase diagram	115
3. Aluminum-nickel phase diagram	116
4. Aluminum-silicon phase diagram	120
5. Aluminum-titanium phase diagram	121

1. Introduction

The principal objective of this work was to critically evaluate and analyze data on the thermodynamic properties of five binary alloy systems: Al-Fe, Al-Mn, Al-Ni, Al-Si, and Al-Ti.

The general background information for these properties is reported in Sec. 2. Discussion of the thermodynamic properties and the details of data analysis are reported in Secs. 3-8. For the Al-Fe alloy system, heat capacity values are reported for $x_{\text{Fe}} = 0.15-0.95$ and cover the temperature range from 1.4 to 1400 K. The room-temperature integral enthalpies of formation, ΔH , are reported for $x_{\text{Fe}} = 0.1-0.75$. The integral Gibbs energies of formation, the partial Gibbs energies of formation, and the activities and activity coefficients for solid alloys are reported for $x_{\text{Fe}} = 0.243-0.90$ at 1173 K. For liquid alloys at 1873 K, the integral and partial Gibbs energies, enthalpies, entropies, activities, and activity coefficients for Al and for Fe are reported for $x_{\text{Fe}} = 0.0-1.0$.

For the Al-Mn alloy system, C_p° values from below 1 to 4.5 K are reported for $x_{\text{Mn}} = 0.00045-0.167$. The integral Gibbs energy, enthalpy, and entropy of formation for solid alloys at 980 K are reported. For liquid alloys at 1600 K, the integral and partial Gibbs energy, enthalpy, entropy, activity, and activity coefficients for Al and for Mn are reported for $x_{\text{Mn}} = 0.0-1.0$.

For all Al-Ni alloy system, low-temperature C_p° values are reported for $x_{\text{Ni}} = 0.25-0.90$. High-temperature C_p° values are reported for $x_{\text{Ni}} = 0.5$ from 400 to 1500 K. The

room-temperature ΔH are reported for $x_{\text{Ni}} = 0.25-0.90$. The recommended integral Gibbs energy of formation for solid alloys as well as other quantities are reported at 1273 K. For liquid alloys at 1873 K, integral ΔG , ΔH , and ΔS , as well as partial quantities and the activity and activity coefficients for $x_{\text{Ni}} = 0.0-1.0$ have been reported.

For the Al-Si alloy system, the integral and partial Gibbs energies, enthalpy, and entropy of formation for liquid alloys and the activity and activity coefficients are reported at 1700 K for the entire range of composition.

For the Al-Ti alloy system, C_p° values are reported for several alloys and cover the temperature range from 1.4 to 1700 K. The room-temperature enthalpy of formation, ΔH , is reported for $x_{\text{Ti}} = 0.25-0.89$. Integral and partial Gibbs energies of formation along with activities and activity coefficients for solid alloys are reported at 973 and 1780 K for $x_{\text{Ti}} = 0.5-1.0$. For liquid alloys at 2000 K, integral and partial enthalpies of formation covering the entire range of composition are also reported.

Units used are J mol^{-1} for the thermodynamic functions; the composition is expressed in mole fraction x .

2. General Background

To understand the nature of the metallic chemical bond in an alloy, knowledge of the electronic contribution to C_p° is essential. A few such measurements, mainly those near liquid helium temperature, have been reported. The Kopp-Neumann additivity law usually supplies a reasonably good approximation a few hundred degrees above room tempera-

ture, except in the region near the curie temperature or at order-disorder transition in the alloy.

The relative partial molar Gibbs energy ΔG_A of one of the components is frequently measured by the emf, vapor pressure, chemical equilibria, or distribution coefficients method. If ΔG_A is known over a range of compositions which includes one composition where ΔG_B of the other component is independently known, then ΔG_B and the integral molar free energy ΔG can be calculated over the entire composition range by the use of Gibbs-Duhem integration. If ΔG_A is known over a temperature range, relative partial molar entropy can be calculated: $\Delta S_A = -(\partial G_A / \partial T)_x$ at constant $x = x_A$, the atom fraction of A in the alloy. Thus partial and integral molar entropies and enthalpies can also be calculated. It is worth noting that errors in ΔG_A measurements are multiplied when temperature coefficients are taken. Seemingly reliable ΔG_A values may, therefore, produce erroneous ΔS_A values. It is common practice to derive entropy values by combining the Gibbs energies with calorimetric enthalpies of formation (ΔH values), which are measured from direct reaction of the metallic components in the calorimeter. Liquid metal solution calorimetry has had great success, but the accuracy of acid solution calorimetry has been disappointing. Combustion calorimetry presents formidable difficulties and, therefore, has not been often tried successfully.

3. Evaluation of Data

Knowledge of the functional form of the temperature dependence of a measured property is essential for the comparison of the same property values measured at different temperatures. Enthalpies and entropies can be assumed independent of temperature over moderate temperature range. Gibbs free energy values reported by different sources at different temperatures are difficult to compare in the absence of reliable entropy values.

All experimental results of the same property at various temperatures are plotted as a function of temperature after the properties have been reduced, wherever possible, to a single evaluating temperature. The best results are obtained if the data are expressed in the form of a function which varies comparatively slowly with composition. The α function has proven satisfactory for partial molar free energies:

$$\alpha_A = \Delta G_A^{\text{ex}} / (1 - x_A)^2.$$

If ΔG_A (or α_A) is known over a range of concentration and ΔG_B (or ΔG_B^{ex}) is known independently at one concentration x_0 , then ΔG_B can be calculated over the entire range of concentration by the following equation derived from the Gibbs-Duhem relation:

$$\begin{aligned} \Delta G_{B,x}^{\text{ex}} &= \Delta G_{B,x_0}^{\text{ex}} + x_0(1 - x_0)\alpha_{A,x_0} \\ &\quad - x(1 - x)\alpha_{A,x} + \int_{x_0}^x \alpha_A \, dx. \end{aligned}$$

For $\Delta G_B^{\text{ex}} = 0$ at $x_0 = 0$,

$$\Delta G_{B,x}^{\text{ex}} = -(1 - x)\alpha_{A,x} + \int_0^x \alpha_A \, dx.$$

The β function has similar advantages:

$$\beta_A = \Delta S_A^{\text{ex}} / (1 - x_A)^2.$$

The Gibbs-Duhem integration can be carried out by substituting β_A for α_A in the above equation to obtain ΔS_B . From ΔG and ΔS of the two components, it is easy to calculate partial enthalpies and other integral quantities.

For analyzing measured enthalpies by calorimetry, the Q function is useful:

$$Q = \Delta H / x(1 - x).$$

Partial quantities can be derived from the Q function:

$$\Delta H_A = x_B^2 \left(Q - x_A \frac{dQ}{dx_B} \right),$$

$$\Delta H_B = x_A^2 \left(Q - x_B \frac{dQ}{dx_A} \right).$$

Entropies calculated from these enthalpies and Gibbs energies from equilibrium measurements are normally more accurate than those derived solely from the temperature coefficients.

4. Thermodynamic Properties of Al-Fe Binary Alloy System

4.1. Phase Diagram and Structures

The phase diagram shown in Fig. 1 was taken from Kubaschewski¹ without further evaluation. The main characteristics are a wide (α -Fe) solid solution and five stable phases with homogeneity ranges. The ordered β'' (AlFe) region is now divided into two additional fields, namely, high-

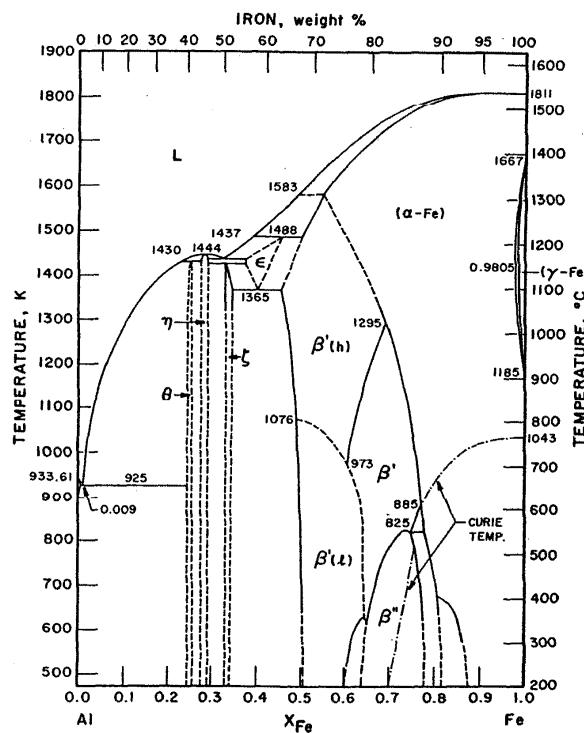


FIG. 1. Aluminum-iron phase diagram.

temperature $\beta'(\text{h})$ and low-temperature $\beta'(\ell)$. Transformation between these three phases is reversible. The aluminum-rich region below 1000 K is extremely complicated and many features reported so far are not completely resolved. Pearson^{2,3} lists the following phases:

θ , " $\theta\text{-Al}_3\text{Fe}$," with a very complex end-centered monoclinic structure.

η , " $\eta\text{-Al}_5\text{Fe}_2$," with an end-centered orthorhombic structure.

β' , "AlFe," with an ordered bcc (B2) structure isotropic with CsCl.

β'' , "AlFe₃," with an ordered bcc (DO₃) structure isotropic with BiF₃ (confirmed by Lesoille and Gielen⁴).

"Al₆Fe," with an orthorhombic structure isotropic with Al₆Mn. This is a metastable phase (not shown on the phase diagram).

Hansen⁵ reported structures for the following phases:

ζ , " $\zeta\text{-Al}_2\text{Fe}$," with a complex rhombohedral structure.

ϵ , with a complex bcc structure (nearly hexagonal with parameters very similar to those of $\zeta\text{-Al}_2\text{Fe}$ according to Taylor and Jones⁶).

du Chatenier and Goedemoed⁷ found from C_p° measurements that a very small amount of Fe ($x_{\text{Fe}} = 0.001$) raised the superconducting transition temperature of Al from 1.16 to 1.5 K.

4.2. Solid Alloys

The C_p° values of Table 1 were taken from the data of Cheng *et al.*⁸ The data for $x_{\text{Fe}} = 0.50$ showed a marked "upturn anomaly," which was explained as being due to the formation of magnetic clustering and was confirmed by Pakchanin *et al.*⁹⁻¹¹ A series of investigations by Pakchanin *et al.*⁹⁻¹¹ for $x_{\text{Fe}} = 0.5\text{--}0.88$ and Okamoto and Beck¹³ for $x_{\text{Fe}} = 0.75$ indicated a decrease in the electronic specific heat γ , and the Debye temperature θ , with an increase in the degree of short or long range ordering and some uncertainty in the derived γ value. These γ values are in generally fair agreement with those of Cheng *et al.*⁸ except for the lower value of $x_{\text{Fe}} = 0.50$ alloy. Electronic specific heat coefficient values from these and other investigations are also reported in Table 2.

Table 1. Low-temperature data for solid Al-Fe alloys

x_{Fe}	Phase	T, K				$\gamma \times 10^3$	θ_D, K
		1.4	2	3	4		
		$C_p^{\circ} \times 10^2, \text{J mol}^{-1}\text{K}^{-1}$					
0.512	$\alpha_2(\ell)$	3.18	3.95	5.27	6.61	12.76**	440
0.5914	$\alpha_2(\ell)$	1.88	2.75	4.32	6.15	13.18	242
0.6392	β''	1.81	2.65	4.15	5.82	12.89	262
0.6977	β''	1.93	2.78	4.24	5.81	13.68	334
0.7547	β''	1.41	2.03	3.07	4.13	10.08	500
0.7547	β''	1.10	1.58	2.42	3.32	7.79	395
0.7547	($\alpha\text{-Fe}$)	1.38	1.99	3.06	4.20	9.79	353
0.7672		0.829	1.20	1.84	2.54	5.86	401
0.8391		0.726	1.06	1.69	2.42	5.06	314
0.8989		0.759	1.09	1.65	2.24	5.40	540
0.9232		0.758	1.09	1.68	2.32	5.36	414
0.9488		0.736	1.07	1.65	2.30	5.19	382
1.000*	($\alpha\text{-Fe}$)	0.697	1.00	1.53	2.10	4.94	465

* From recommended values for Fe.¹⁴

** Anomalous behavior at lowest temperatures.

Table 2. Electronic specific heat coefficients of Al-Fe alloys

Source	x_{Fe}	Phase	γ $\text{mJ mol}^{-1}\text{K}^{-2}$
Desai ¹⁴	1.00	($\alpha\text{-Fe}$)	4.94
Shinozaki ¹²	0.99	($\alpha\text{-Fe}$)	4.88
	0.98	($\alpha\text{-Fe}$)	4.95
Cheng <i>et al.</i> ⁸	0.95	($\alpha\text{-Fe}$)	5.15
	0.92	($\alpha\text{-Fe}$)	5.36
	0.90	($\alpha\text{-Fe}$)	5.40
Pakchanin <i>et al.</i> ⁹	0.88	($\alpha\text{-Fe}$)	4.98
	0.84	($\alpha\text{-Fe}$)	5.08
Cheng <i>et al.</i> ⁸	0.84	($\alpha\text{-Fe}$)	5.06
	0.77	($\alpha\text{-Fe}$)	5.86
	0.75	($\alpha\text{-Fe}$)	9.79
Pakchanin <i>et al.</i> ¹¹	0.75	β''	8.74
Cheng <i>et al.</i> ⁸	0.75	β''	7.79
Pakchanin <i>et al.</i> ¹¹	0.75	β'	9.63
Cheng <i>et al.</i> ⁸	0.75	β'	10.08
	0.70	β''	13.68
Pakchanin <i>et al.</i> ¹¹	0.65	β''	12.80
Cheng <i>et al.</i> ⁸	0.64	β''	12.89
	0.59	$\beta'(\ell)$	13.18
	0.512	$\beta'(\ell)$	12.76
Okamoto and Beck ¹³	0.51	$\beta'(\text{h})$	10.71
	0.51	$\beta'(\ell)$	11.55

Minayev and Iveronova¹⁵ graphically reported C_p° data for alloys in the complex region of the phase diagram ($x_{\text{Fe}} = 0.734\text{--}1.00$) where fully unresolved order-disorder transformations are occurring. These transformations produce λ -type anomalies, often with some first-order latent heats. Kinetic factors will displace these to higher temperatures and probably alter their shape. The C_p° values reported in Table 3a are taken from these measurements. It is worth noting that superimposed ferromagnetic anomalies may depend on the degree of order present at the time of measurement in some compositions. Hence, C_p° values from Table 3a may not represent equilibrium values for $x_{\text{Fe}} = 0.734$ and 0.808. Minayev and Iveronova¹⁵ and Iveronova *et al.*¹⁶ found a dip in the C_p° curve between 450 and 550 K for quenched alloys in the range $x_{\text{Fe}} = 0.84\text{--}0.74$. Similar behavior was observed by Troschkina and Kutcherenko¹⁷ for FeAl(β') alloy. The C_p° values from Table 3b were taken from the data of Orehotsky and Schroder.¹⁸ The data of Eguchi *et al.*¹⁹ for $x_{\text{Fe}} = 0.75$ yielded higher C_p° values.

ΔH values in Table 4 were taken from the direct reaction calorimetry of Kubaschewski and Dench.²⁰ ΔH values of Oelsen and Middell²¹ were more exothermic than the tabulated values by about 400–2400 J mol⁻¹, and those of Ferro²² for $x_{\text{Fe}} = 0.50$ were slightly less exothermic. Acid solution calorimetry of Dilts²³ for $x_{\text{Fe}} = 0.75$ yielded values less exothermic by about 2000 J mol⁻¹. These investigators did not make any attempt to establish the final state of the alloys they studied. Gorelkin *et al.*²⁴ measured the ΔH for a number of aluminum alloys using an isothermal calorimetric technique. Their ΔH value for $x_{\text{Fe}} = 0.75$ is -30.96 ± 8.4 kJ mol⁻¹, for $x_{\text{Fe}} = 0.5$ is 40.79 ± 6.3 kJ mol⁻¹, and for $x_{\text{Fe}} = 0.33$ is -18.83 ± 6.3 kJ mol⁻¹.

The recommended ΔG_{Al} values of Table 6 agree ($+3200$ J mol⁻¹) with the emf measurements of Radcliff *et al.*²⁵ and the vapor pressure measurements of Gross *et al.*,²⁶


Table 3a. High-temperature heat capacity of solid Al-Fe alloys

T, K	x_{Fe}					
	0.734	0.808	0.837	0.851	0.887	1.000
	$C_p^0, \text{ J mol}^{-1} \text{ K}^{-1}$					
350	27.68	28.54	27.79	28.32	27.95	27.54
400	27.68	28.92	27.87	28.33	28.07	27.77
500	27.74	29.73	28.36	28.79	28.57	28.47
600	29.54	30.74	29.69	30.34	29.92	30.00
640	30.89	32.13	30.90	31.26	30.90	31.04
650	31.13	32.79	32.14	31.50	31.19	31.35
700	32.40	37.14	34.73	32.89	32.92	32.98
729	33.40	40.31	35.43	33.88	34.04	34.03
750	34.28	39.40	35.84	34.70	34.88	34.81
775	35.58	39.11	36.30	35.74	36.02	35.77
800	37.73	40.05	36.75	36.90	37.19	36.95
838	43.83	41.79	37.39	38.73	39.48	39.24
880	36.82	43.90	38.42	40.88	42.54	42.29
900	37.21	44.96	30.35	41.94	44.14	43.82
920	37.73	46.01	45.10	43.06	45.76	45.39
935	38.20	45.62	53.56	44.00	47.03	46.67
950	38.74	45.24	49.08	45.14	48.39	48.04
992	40.67	44.68	44.12	58.77	54.30	52.97
1000	41.08	44.69	44.00	50.75	56.37	54.41
1021	42.28	45.01	44.11	47.60	69.04	59.95
1050	44.10	46.12	45.13	46.22	56.18	76.45
1053	44.31	46.28	45.30	55.82	79.12	
1060	44.80	46.62	45.78	55.13	64.90	
1080	46.24		47.48	53.79	56.41	
1100	47.79		49.64	52.77	56.71	
1110	48.62		50.81	52.31	56.88	
1130	50.30		53.35	52.88	57.28	

Table 3b. High-temperature heat capacity of solid Al-Fe alloys

T, K	x_{Fe}			T, K	x_{Fe}		
	0.90	0.79	0.75		0.90	0.79	0.75
	$C_p^0, \text{ J mol}^{-1} \text{ K}^{-1}$						
550	30.12	29.67		950	48.67	38.18	
600	31.50	31.34		975	51.43	38.96	
650	32.93	33.62		1000	56.52	37.37	
700	34.50	36.80		1017	61.35		
725	35.35	38.80		1025	50.73		
750	36.25	36.25	41.31	1050	46.05		
775	37.24	37.24	44.83	1075	43.13		
795	38.09	38.09	50.48	1100	41.73		
800	38.31	38.31	43.50	1150	40.36		
825	39.54	39.54	37.72	1200	39.50		
850	40.92	41.08	36.78	1250	38.91		
875	42.42	43.47	37.70	1300	38.47		
890	43.45	45.62	37.08	1350	38.14		
900	44.18	41.60	35.98	1400	37.89		
925	46.22	38.96					

except that the latter's value near $x_{\text{Fe}} = 0.94$ is considerably less exothermic (16 kJ mol^{-1}). Isopiestic measurements of Eldridge and Komarek²⁷ are within $\pm 8000 \text{ J mol}^{-1}$ of the recommended values. Vapor pressure measurements of Gulbransen and Andrews²⁸ at $x_{\text{Fe}} = 0.894$ yielded much lower values of a_{Fe} than those recommended. Other quantities of

Table 4. Enthalpies of formation for solid Al-Fe alloys at 298.15 K^a

x_{Fe}	Phase	ΔH		Phase	ΔH
		kJ mol^{-1}	kJ mol^{-1}		
0.25	θ	-27.91		0.50	β'
0.333		$[-18.83 \pm 6.3]$			$[-40.79 \pm 6.3]$
0.335		-26.15		0.60	β'
					-19.98
				0.70	β' or β''
					-15.73
				0.75	β''
					$[30.96 \pm 8.4]$
				0.80	(α -Fe) ^b
					-11.00
				0.90	(α -Fe) ^b
					-5.77

^avalues in brackets are from Gorelkin et al.²⁴
^bspinodal state uncertain.

Table 5. Recommended integral quantities for solid Al-Fe alloys at 1173 K^a

$$(1-x)\text{Al}(s) + x_{\text{Fe}}(\text{a}) = \text{Al}_{1-x}\text{Fe}_x(s)$$

x_{Fe}	Phase	ΔG	ΔG^{ex}
		J mol^{-1}	J mol^{-1}
0.243 ^b	θ	0.716	0.946
0.257 ^b	θ	0.228	0.306
0.274 ^b	η	0.228	0.314
0.290 ^b	η	0.128	-20083
0.330 ^b	ζ	0.128	-14435
0.342 ^b	ζ	0.073	-25522
0.48 ^b	$\beta'(\text{h})$	0.073	-25522
0.50		0.061	-27263
		0.122	-20503
0.60	$\beta'(\text{h})$	0.022	-37094
0.70	β'	0.006	-49420
0.80		0.001	-64240
0.90		0.000	-82923
1.00	(α -Fe)	0.000	-60466
		0.000	-72200
		0.000	1.000
		0.000	0

^aNote standard states.

^bPhase boundaries.

Tables 5 and 6 were calculated from the recommended ones using the Gibbs-Duhem relation.

4.3. Liquid Alloys

The recommended ΔG_{Al} values of Table 8 are in general based ($\pm 1500 \text{ J mol}^{-1}$) on the values calculated from the distribution of Al between $\text{Ag}(\ell)$ and $\text{Fe}(\ell)$ by Chipman and Floridis²⁹ and on the emf data of Batalin et al.³⁰ Woolley and Elliott³¹ calculated ΔG_{Al} values from the data of Chipman and Floridis,²⁹ which are about 2700 J mol^{-1} less exothermic. The values of Vachet et al.³² from their data of distribution between $\text{Ag}(\ell)$ and $\text{Fe}(\ell)$ are 500 J mol^{-1} less exothermic for $x_{\text{Fe}} > 0.8$ and up to 2400 J mol^{-1} more exothermic than the recommended values for $x_{\text{Fe}} < 0.8$ with the largest deviation occurring at $x_{\text{Fe}} = 0.5$. The following lower temperature measurements were corrected to 1873 K using the recommended ΔS_{Al} values which compare with the recommended ΔG_{Al} values as follows. The emf studies of

Table 6. Recommended partial molar quantities for solid Al-Fe alloys at 1173 K^a

x_{Fe}	Phase	Al component		Fe component
		$\text{Al}(s) = \text{Al}(\text{alloy})(s)$	$\text{Al}_{1-x}\text{Fe}_x(s)$	
		γ_{Al}	ΔG_{Al}	ΔG_{Fe}
			J mol^{-1}	J mol^{-1}
0.243 ^b	θ	0.716	0.946	-3255
0.257 ^b	θ	0.228	0.306	-11538
0.274 ^b	η	0.228	0.314	-14435
0.290 ^b	η	0.128	0.180	-20083
0.330 ^b	ζ	0.128	0.190	-11312
0.342 ^b	ζ	0.073	0.111	-25522
0.48 ^b	$\beta'(\text{h})$	0.073	0.140	-25522
0.50		0.061	0.122	-27263
		(± 0.006)	(± 0.012)	(± 0.005)
			(± 0.050)	(± 0.050)
0.60	$\beta'(\text{h})$	0.022	0.056	-37094
0.70	β'	0.006	0.021	-49420
0.80		0.001	0.007	-64240
0.90		0.000	0.002	-82923
1.00	(α -Fe)	0.000	0.000	-60466
		0.000	0.000	1.000
		0.000	0.000	0

^aNote standard states.

^bPhase boundaries.

Table 7. Recommended integral quantities for liquid Al-Fe alloys at 1873 K
 $(1-x)Al(x) + xFe(x) = Al(1-x)Fe_x(x)$

x_{Fe}	ΔG	ΔH	ΔG^{ex}	ΔS	ΔS^{ex}
	J mol ⁻¹	J mol ⁻¹	J mol ⁻¹ K ⁻¹	J mol ⁻¹ K ⁻¹	J mol ⁻¹ K ⁻¹
0.1	-10012	-8383	-4949	0.870	-1.833
0.2	-16293	-14291	-8500	1.069	-3.092
0.3	-20319	-17997	-10806	1.240	-3.839
0.4	-22483	-19740	-12002	1.465	-4.131
0.5	-22990	-19742	-12196	1.734	-4.029
(±1.00)	(±1.700)	(±2.5)	(±2.100)	(±2.5)	
0.6	-21964	-18175	-11484	2.023	-3.573
0.7	-19390	-15265	-9877	2.202	-2.876
0.8	-15210	-11655	-7418	2.160	-2.001
0.9	-9183	-6029	-4121	1.684	-1.018

Table 8. Recommended partial molar quantities for liquid Al-Fe alloys at 1873 K
 $Al(x) = Al \text{ (in alloy)}(x)$

x_{Al}	γ_{Al}	γ_{Fe}	ΔG_{Al}	$\Delta G_{Al}^{\text{ex}}$	ΔH_{Al}	ΔS_{Al}	$\Delta S_{Al}^{\text{ex}}$
			J mol ⁻¹	J mol ⁻¹	J mol ⁻¹	J mol ⁻¹ K ⁻¹	J mol ⁻¹ K ⁻¹
1.0	1.000	1.000	0	0	0	0.000	0.000
0.9	0.859	0.954	-2367	-727	-1292	0.574	-0.302
0.8	0.673	0.841	-6167	-2692	-4754	0.755	-1.101
0.7	0.488	0.697	-11170	-5616	-9946	0.654	-2.312
0.6	0.331	0.551	-17235	-9280	-16381	0.456	-3.791
0.5	0.209	0.418	-24394	-13600	-23805	0.315	-5.449
(±0.027)	(±0.053)	(±2.100)	(±2.100)	(±3500)	(±2.5)	(±2.5)	(±2.5)
0.4	0.122	0.304	-32791	-18522	-31813	0.522	-7.096
0.3	0.064	0.212	-42882	-24132	-39999	1.539	-8.471
0.2	0.028	0.141	-55534	-30470	-48320	3.851	-9.530
0.1	0.009	0.090	-73369	-37511	-56473	9.020	-10.124
0.0	0.000	0.055	=	-45290	-64300	=	-10.149

Ichise *et al.*³³ (1673 K) are up to 1900 J mol⁻¹ less exothermic, except their values are 800 J mol⁻¹ more exothermic for $x_{Fe} = 0.9$, while those of Mitani and Nagai³⁴ (1473 K) are up to 3800 J mol⁻¹ less exothermic. Vapor pressure studies of Coskum and Elliott³⁵ (1588 K) are up to 500–4500 J mol⁻¹ more exothermic, while those of Gross *et al.*²⁶ (1573 K) are about 2100 J mol⁻¹ less exothermic. Mass spectrometric vapor pressure measurements of Belton and Fruehan³⁸ yielded ΔG_{Al} values 400–6000 J mol⁻¹ less exothermic than the recommended values for $x_{Fe} < 0.8$, the largest deviation occurring at high Fe contents. The emf studies of Fruehan³⁹ for $x_{Fe} = 0.97$ –0.9996 and those of Sudavstova and Batalin⁴⁰ for $x_{Fe} = 0.90$ –0.98 yielded considerably more exothermic ΔG_{Al} values.

The recommended ΔH values of Table 7 are primarily based on the direct reaction calorimetry of Woolley and Elliott³¹ (90–980 J mol⁻¹ more exothermic) and the high-temperature isothermal calorimetric values of Petrushevskii *et al.*⁴¹ (150 J mol⁻¹ less exothermic for $x_{Fe} > 0.8$ and up to 1300 J mol⁻¹ more exothermic for $x_{Fe} < 0.8$). Jounel *et al.*³⁶ and Mathieu *et al.*³⁷ reported a value of -128.4 kJ mol⁻¹ at 971 K for ΔH_{Fe} at $x_{Fe} = 0.0$, while Dannohil and Lukas⁴² reported a value of -121.8 kJ mol⁻¹ at 1023 K. These values compare with the recommended value of -97.4 kJ mol⁻¹ at 1873 K and 95.19 kJ mol⁻¹ reported by Petrushevskii *et al.*⁴¹ Other quantities from Tables 7 and 8 are calculated from the recommended ΔG_{Al} and ΔH values using the Gibbs–Duhem relation.

4.4. References

- ¹O. Kubaschewski, *Iron-Binary Phase Diagram* (Springer, Berlin, 1982).
- ²W. B. Pearson, *A Handbook of Lattice Spacings and Structures of Metals and Alloys* (Pergamon, London, 1958), Vol. 1.
- ³W. B. Pearson, *A Handbook of Lattice Spacings and Structures of Metals and Alloys* (Pergamon, London, 1967), Vol. 2.
- ⁴M. R. Lesoile and P. M. Gielen, "The Mechanism of Phase Transformations in Crystalline Solids," in Proceedings of the International Symposium Institute of Metals, Manchester, England, 1969, pp. 223–224.
- ⁵M. Hansen, *Constitution of Binary Alloys*, 2nd ed. (McGraw-Hill, New York, 1958).
- ⁶A. Taylor and R. M. Jones, *J. Phys. Chem. Solids* **6**, 21 (1958).
- ⁷F. D. du Chatenier and S. H. Goedemoed, *Phys. Lett.* **7**, 108 (1963).
- ⁸C. H. Cheng, K. P. Gupta, C. T. Wei, and P. A. Beck, *J. Phys. Chem. Solids* **25**, 759 (1964).
- ⁹L. M. Pakchanin, P. V. Petrenko, Yu. L. Pilipchuk, and S. P. Repetskii, *Metallofizika* **5**, 105 (1983).
- ¹⁰L. M. Pakchanin, P. V. Petrenko, Yu. L. Pilipchuk, and S. P. Repetskii, *Metallofizika* **5**, 112 (1983).
- ¹¹L. M. Pakchanin, P. V. Petrenko, Yu. L. Pilipchuk, and S. P. Repetskii, *Ukr. Fiz. Zh.* **28**, 1422 (1983).
- ¹²S. S. Shinozaki, *Trans. Jpn. Inst. Met.* **9**, 82 (1968).
- ¹³H. Okamoto and P. A. Beck, *Monatsh. Chem.* **103**, 907 (1972).
- ¹⁴P. D. Desai, "Thermodynamic Properties of Iron," CINDAS Report No. 78, 1984.
- ¹⁵A. I. Minayev and V. I. Iveronova, *Phys. Met. Metallogr.* **22**, 64 (1966).
- ¹⁶V. I. Iveronova, A. I. Minayev, and V. M. Silonov, *Phys. Met. Metallogr.* **33**, 72 (1972).
- ¹⁷V. A. Troschkina and L. A. Kurcherenko, *J. Phys. Chem. Solids* **33**, 1511 (1972).
- ¹⁸J. Orehotsky and K. Schroder, *Phys. Status Solidi* **19**, 93 (1973).
- ¹⁹T. Eguchi, H. Matsuda, K. Oki, S. Kiyoto, and K. Yasutake, *Trans. Jpn. Inst. Met.* **8**, 176 (1967).
- ²⁰O. Kubaschewski and W. A. Dench, *Acta Metall.* **3**, 339 (1955).
- ²¹W. Oelsen and W. Middell, *Mitt. Kaiser Wilhelm Inst. Eisenforsch.* **Duesseldorf** **19**, 1 (1937).
- ²²R. Ferro, *Atti. Accad. Naz. Lincei Cl. Sci. Fis. Mat. Nat. Rend.* **36**, 653 (1963).
- ²³W. Biltz, *Z. Metallkd.* **29**, 73 (1937).
- ²⁴O. S. Gorelkin, A. S. Dubrovin, O. D. Kolesnikova, Yu. Ya. Demidov, and N. A. Chrikov, *Proizvod. Ferrosplavov* **1**, 123 (1972).
- ²⁵S. V. Radcliff, B. L. Averbach, and M. Cohen, *Acta Metall.* **9**, 169 (1961).
- ²⁶P. Gross, D. L. Levi, E. W. Dewing, and G. L. Wilson, "The Activities of Al in Binary Al-Fe Alloys," in *Proc. Symp. Phys. Chem. Process Metallurgy Pittsburgh* (AIME, New York, 1959), Part I, pp. 403–412.
- ²⁷J. Eldridge and K. L. Komarek, *Trans. Metall. Soc. AIME* **230**, 226 (1964).
- ²⁸E. A. Gulbransen and K. F. Andrews, *Trans. Metall. Soc. AIME* **221**, 1247 (1961).
- ²⁹J. Chipman and T. P. Floridis, *Acta Metall.* **3**, 456 (1955).
- ³⁰G. I. Batalin, E. A. Beloborodova, V. A. Stukalo, and L. V. Goncharuk, *Russ. J. Phys. Chem.* **45**, 1139 (1971).
- ³¹F. Woolley and J. F. Elliott, *Trans. Metall. Soc. AIME* **245**, 1872 (1967).
- ³²F. Vachet, P. Desre, and E. Bonnier, *C. R. Acad. Hebd. Seances Acad. Sci.* **260**, 453 (1965).
- ³³E. Ichise, T. Yamauchi, and T. Mori, *Tetsu To Hagane* **63**, 417 (1977).
- ³⁴H. Mitani and H. Nagai, *J. Jpn. Inst. Met.* **32**, 752 (1968).
- ³⁵A. Coskum and J. F. Elliott, *Trans. Metall. Soc. AIME* **242**, 253 (1968).
- ³⁶B. Jounel, J. C. Mathieu, and P. Desre, *C. R. Acad. Hebd. Seances Acad. Sci.* **266C**, 773 (1968).
- ³⁷J. C. Mathieu, B. Jounel, P. Desre, and E. Bonnier, *Thermodynamics Nuclear Material Symposium Vienna*, 1967, 767 (1968).
- ³⁸G. R. Belton and R. J. Fruehan, *Trans. Metall. Soc. AIME* **245**, 113 (1969).
- ³⁹R. J. Fruehan, *Metall. Trans.* **1**, 3403 (1970).

⁴⁰V. S. Sudavstova and G. I. Batalin, Zh. Ukr. Chem. 46, 268 (1980).

⁴¹M. S. Petrushevskii, Yu. O. Esin, P. V. Gel'd, and V. M. Sandkov, Russ. Metall. 6, 149 (1952).

⁴²H. D. Dannohl and H. L. Lukas, Z. Metallkd. 65, 642 (1974).

5. Thermodynamic Properties of Al-Mn Binary Alloy System

5.1. Phase Diagram and Structures

The phase diagram shown in Fig. 2 was taken from Godecke and Koster.¹ It differs from the previously reported phase diagram in the following respects: the high-temperature modification of $\text{Al}_{11}\text{Mn}_{4H}$ has an extended range of homogeneity and the room-temperature modification $\text{Al}_{11}\text{Mn}_{4K}$ is a single phase, while $\gamma_2(\text{AlMn})$ -phase has two high-temperature modifications, γ and γ_1 . Metastable $\text{Al}_{10}\text{Mn}_3$ appears at moderate cooling rates. Rao *et al.*² identified several other intermediate metastable phases by annealing the rapidly quenched Al-rich commercial Al-Mn alloys. Refinement of the phase diagram and the identification of new metastable phases have been reported, e.g., Shechtman *et al.*,³ Varich *et al.*,⁴ Gorichok and Vengrenovich,⁵ Teplova *et al.*,⁶ Vintainkin *et al.*,⁷ and by Sakamoto *et al.*⁸ Godecke and Koster¹ and Pearson⁹ report the following intermediate phases:

ϵ , "Al₆Mn," with the orthorhombic (D_{2h}) prototype structure.

ζ , "Al₄Mn," with a hexagonal structure.

H , "Al₁₁Mn_{4H}," with an orthorhombic structure.

λ , "Al₁₁Mn_{4R}," with a triclinic structure.

γ , " η -Al-Mn," with a hexagonal structure.

γ_2 , with a bc rhombohedral structure.

ϵ , with a hexagonal structure.

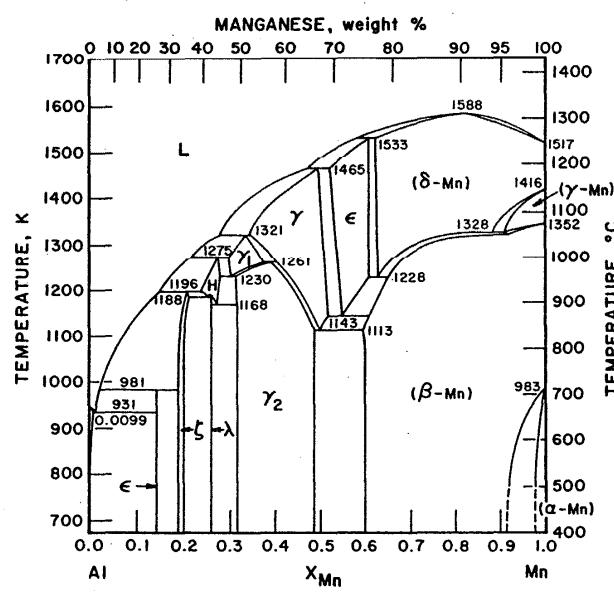


FIG. 2. Aluminum-manganese phase diagram.

Table 9. Low-temperature heat capacity of solid Al-Mn alloys

T, K	x_{Mn}			
	0.00045	0.001	0.004	0.167
0.4	0.00054 ^a			
0.5	0.00103 ^a			
0.84	0.00270 ^a			
1.0	0.00139			
1.4	0.00215	0.00206	0.00207	0.00197
2.0		0.00306	0.00304	0.00286
3.0		0.00500	0.00484	0.00449
4.0		0.00744	0.00699	0.00635
4.5				0.00739
$\gamma \times 10^3$		1.42	1.45	1.38
$J \text{ mol}^{-1} \text{ K}^{-2}$				

^aSuperconductor.

5.2. Solid Alloys

C_p° values of Table 9 were taken from the data of Martin.¹⁰ He found that the electronic specific heat term γ is the same for aluminum and the single alloy ($x_{\text{Mn}} = 0.00045$), which he measured in the normal state, and that the superconducting transition temperature T_c dropped to 0.84 K from 1.160 K for pure aluminum. However, C_p° measurements of Aoki and Ohtsuka¹¹ for $x_{\text{Mn}} = 0.001$ and 0.004 indicated an increase in γ with composition. C_p° values for $x_{\text{Mn}} = 0.167$ were taken from the data of Dunlop *et al.*¹²

The ΔG values in Table 10 were based on the emf studies of Samokhval and Vecher,¹³ who reported only integral quantities. ΔH values were based on the temperature coefficients of Samokhval and Vecher,¹³ which were referred to Al(s) assuming $\Delta_{\text{fus}}S^\circ = 11.337 \text{ J mol}^{-1} \text{ K}^{-1}$ for Al invariant with T . Reaction calorimetry of Kubaschewski and Heymer¹⁴ yielded values in fair agreement with those report-

Table 10. Integral quantities for liquid Al-Mn alloys at 980 K^a

x_{Mn}	Phase	ΔG J mol^{-1}	ΔH J mol^{-1}	ΔS $\text{J mol}^{-1} \text{ K}^{-1}$
0.142	ϵ		-15750	
0.190	ζ		-20050	
0.20	ζ		-20900	
0.267	λ		-22050	
0.32	γ_2		-22920	
0.40		-21070	-24080	-3.071
0.45		-20640	-24410	-3.847
		(±3000)	(±3000)	(±3.00)
0.485	γ_2		-24500	
0.60	(β -Mn)		-24000	
0.68		-18410	-22710	-4.388
0.75		-16030	-19550	-4.000
0.80		-13830	-17250	-3.490
0.85		-11170	-13810	-2.694
0.90	(β -Mn)		-9680	

^aNote standard states.

Table 11. Recommended integral quantities for liquid Al-Mn alloys at 1600 K
 $(1-x)Al(x) + xMn(x) = Al_{(1-x)}Mn_x(x)$

x_{Mn}	ΔG	ΔH	ΔG^{ex}	ΔS	ΔS^{ex}
	$J \text{ mol}^{-1}$	$J \text{ mol}^{-1}$	$J \text{ mol}^{-1} \text{ K}^{-1}$		$J \text{ mol}^{-1} \text{ K}^{-1}$
0.1	-7322	-6392	-2997	0.581	-2.122
0.2	-11986	-11901	-5329	0.553	-4.108
0.3	-15162	-15414	-7066	-0.156	-3.236
0.4	-17216	-16908	-8263	0.192	-5.403
0.5	-18521	-16848	-9300	1.046	-4.718
(±0.000)	(±4000)	(±3000)	(±2.50)	(±2.50)	(±2.50)
0.6	-19232	-15470	-10279	2.350	-3.244
0.7	-18979	-13171	-10853	3.630	-1.449
0.8	-16988	-10432	-10342	4.344	0.184
0.9	-12217	-5687	-7893	4.081	1.379

ed by Samokhval and Vecher¹³ except at $x_{Mn} = 0.50$, where they were about 3000 J mol⁻¹ less exothermic. Most of their measurements were in questionable one-phase regions. Although Kubaschewski and Heymer¹⁴ claimed that they checked the completeness of alloy formation, they failed to give the structure and phases to which their alloys belong.

5.3. Liquid Alloys

The recommended ΔH values in Table 11 were based on the calorimetric measurements of Esin *et al.*,¹⁵ who measured ΔH_{Al} from $x_{Mn} = 0.4\text{--}1.0$ and ΔH_{Mn} from $x_{Mn} = 0.0\text{--}0.4$. They did not report experimental data; instead, smooth values of partial and integral enthalpies covering the entire composition range were reported. A consistency check of their partial quantities using the Gibbs-Duhem relation failed to produce reasonably close ΔH_{Mn} from ΔH_{Al} values. Therefore, ΔH_{Al} and ΔH_{Mn} values in Table 12 were recalculated from their ΔH values. ΔH_{Al} values reported by Esin *et al.*¹⁵ are up to 3300 J mol⁻¹ (at $x_{Mn} = 0.5$) less exothermic and ΔH_{Mn} are up to 4450 J mol⁻¹ (at $x_{Mn} = 0.3$) more exothermic than the recommended values.

The recommended ΔG_{Mn} values in Table 12 are based on the tabulated $\Delta G_{Al}^{\text{ex}}$ values of Batalin *et al.*¹⁶ derived from their measured emf data and the calculated $\Delta G_{Al}^{\text{ex}}$ and $\Delta S_{Al}^{\text{ex}}$ values. It is worth noting that the emf data, which they reported graphically, failed to reproduce their tabulated partial quantities, especially for low Mn concentrations. Other quantities in Tables 11 and 12 were calculated from the recommended ΔG_{Mn} values, using the Gibbs-Duhem relation, the partial and the integral enthalpy values.

5.4. References

- T. Godecke and W. Koster, Z. Metallkd. **62**, 727 (1971).
- M. H. Rao, G. Sridhar, and C. Suryanarayana, Z. Metallkd. **74**, 585 (1983).
- D. Shechtman, R. J. Schaefer, F. S. Biancaniello, Metall. Trans. A **15**, 1987 (1984).
- N. I. Varich, B. N. Litvin, and P. Rozdaibeda, Izv. Akad. Nauk SSSR Met. **4**, 145 (1977).
- B. O. Gorichok and R. D. Vengrenovich, Izv. Vyssh. Uchebn. Zaved. Tsvetn. Metall. **4**, 106 (1977).
- G. N. Teplova, N. F. Lashko, and G. I. Morozova, Zavod. Lab. **41**, 918 (1975).
- E. Z. Vintainkin, V. A. Udoenko, N. N. Luarasabishvili, and D. F. Litvin, Dokl. Akad. Nauk. SSSR **210**, 1327 (1973).
- Y. Sakamoto, N. Kato, S. Kojima, and M. Tsukahara, Matsushita Electric Industrial Co. Ltd., Japan Kokai, 7658, 993 (cl. GO1N33/20) Appl. 74/134,064, 1974.
- W. B. Pearson, *A Handbook of Lattice Spacings and Structures of Metals and Alloys* (Pergamon, New York, 1967), Vol. 2.
- D. L. Martin, Proc. Phys. Soc. London **78**, 1489 (1961).

Table 12. Recommended partial molar quantities for liquid Al-Mn alloys at 1600 K

x_{Al}	$Al(x) = Al_{(in \text{ alloy})}(x)$					
	ΔG_{Al}	$\Delta G_{Al}^{\text{ex}}$	ΔH_{Al}	ΔS_{Al}	$\Delta S_{Al}^{\text{ex}}$	$J \text{ mol}^{-1}$
1.0	1.000	1.000	0	0	0.000	0.000
0.9	0.878	0.974	-1734	-333	-202	0.958
0.8	0.725	0.906	-4286	-1318	-2691	0.997
0.7	0.570	0.814	-7488	-2744	-8244	-0.473
0.6	0.445	0.741	-10775	-3980	-14200	-2.141
0.5	0.365	0.731	-13396	-4175	-20707	-4.569
(±0.110)	(±0.053)	(±1000)	(±1000)	(±4000)	(±2.50)	(±2.50)
0.4	0.274	0.685	-17222	-5033	-26968	-6.091
0.3	0.142	0.474	-25941	-9925	-31413	-3.420
0.2	0.042	0.212	-42047	-20636	-39840	-1.379
0.1	0.004	0.040	-73340	-42709	-50738	14.126
0.0	0.000	0.000	→	-121272	-63800	→

x_{Mn}	$Mn(x) = Mn_{(in \text{ alloy})}(x)$					
	ΔG_{Mn}	$\Delta G_{Mn}^{\text{ex}}$	ΔH_{Mn}	ΔS_{Mn}	$\Delta S_{Mn}^{\text{ex}}$	$J \text{ mol}^{-1}$
0.0	0.000	0.082	→	-33300	-64600	→
0.1	0.013	0.132	-57604	-26973	-62103	-2.812
0.2	0.040	0.201	-42786	-21376	-48739	-3.721
0.3	0.083	0.278	-33068	-17052	-32144	0.578
0.4	0.133	0.332	-26877	-14688	-20970	3.692
0.5	0.169	0.398	-23646	-14425	-12988	6.661
(±0.044)	(±0.088)	(±4000)	(±4000)	(±4000)	(±2.50)	(±2.50)
0.6	0.213	0.355	-20571	-13776	-7806	7.978
0.7	0.300	0.429	-15995	-11250	-5353	6.651
0.8	0.446	0.558	-10736	-7168	-2600	5.085
0.9	0.665	0.739	-5425	-4024	-681	2.965
1.0	1.000	1.000	0	0	0	0.000

¹¹R. Aoki and T. Ohtsuka, J. Phys. Soc. Jpn. **26**, 651 (1969).

¹²J. B. Dunlop, G. Gruner, and A. D. Caplin, J. Phys. F **4**, 2203 (1974).

¹³V. S. Samokhval and A. A. Vecher, Izv. Akad. Nauk SSSR Met. **2**, 75 (1971).

¹⁴O. Kubaschewski and G. Heymer, Trans. Faraday Soc. **56**, 473 (1960).

¹⁵Yu. O. Esin, N. T. Bobrov, M. S. Petrushevskii, and P. V. Gel'd, Russ. J. Phys. Chem. **47**, 1103 (1973).

¹⁶G. I. Batalin, E. A. Beloborodova, V. A. Stukalo, and A. A. Chekhovskoi, Ukr. Khim. Zh. Russ. Ed. **38**, 825 (1972).

6. Thermodynamic Properties of Al-Ni Binary Alloy System

6.1. Phase Diagram and Structures

The phase diagram shown in Fig. 3 was taken from the preliminary investigation of Singleton *et al.*¹ In general, this

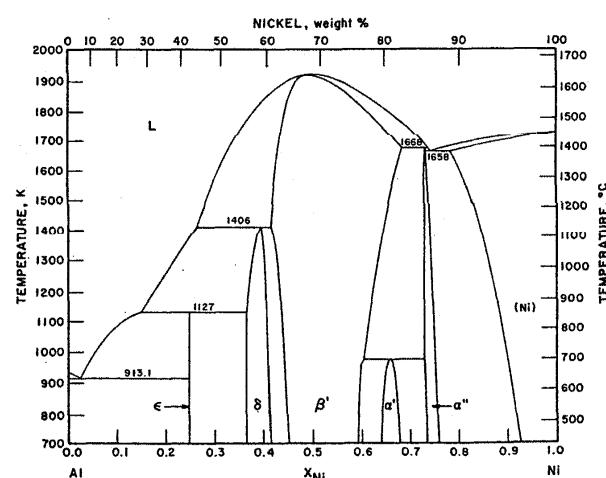


FIG. 3. Aluminum-nickel phase diagram.

Table 13. Low-temperature heat capacity of solid Al-Ni alloys

T, K	x_{Ni}									
	0.25	0.46	0.49	0.51	0.53	0.56	0.75	0.90	1.00	C_p° , $\text{J mol}^{-1}\text{K}^{-1}$
1.5		0.0018	0.0020							
2	0.0027	0.0025	0.0027	0.0031	0.0034	0.0039	0.0177	0.0150	0.0142	
3	0.0043	0.0038	0.0043	0.0048	0.0054	0.0062	0.0266	0.0228	0.0217	
4	0.0064	0.0054	0.0062	0.0069	0.0078	0.0090	0.0355	0.0315	0.0295	
5						0.0129	0.0447			0.0381
6							0.0543			0.0477
7							0.0645			0.0583
8							0.0756			0.0698
9							0.0877			0.0826
10							0.101			0.0963
11							0.116			
12							0.133			
13							0.153			
14							0.178			
	γ	1.24	1.19	1.31	1.37	1.50	1.52	6.50	6.82	7.055
	$\text{mJ mol}^{-1}\text{K}^{-2}$									

phase diagram is similar to the one assessed by Hultgren *et al.*,² although a new phase, Al_3Ni_5 (α'), has been added. Singleton *et al.*¹ lists the following intermediate phases:

ϵ , "Al₃Ni" has an orthorhombic (DO₁₁) isotypic with CFe_3 .

δ , "Al₃Ni₂" has an ordered trigonal (D5₁₃) prototype structure.

β' , "AlNi" has an ordered bcc (B₂) structure isotypic with CsCl. At high temperatures it probably transforms to a disordered phase (see Sec. 6.2).

α' , "Al₃Ni₅" has an orthorhombic structure isotypic with Ga₂Pt₅.

α'' , "AlNi₃" has an ordered fcc (L1₂) structure isotypic with AuCu₃.

6.2. Solid Alloys

The C_p° values of Table 13 were taken from the data of

Table 14. High-temperature data for the ordered Al-Ni β' -phase, $x_{\text{Ni}} = 0.50$

T K	C_p°		T K	C_p°	
	$\text{J mol}^{-1}\text{K}^{-1}$	$\text{J mol}^{-1}\text{K}^{-1}$		$\text{J mol}^{-1}\text{K}^{-1}$	$\text{J mol}^{-1}\text{K}^{-1}$
60	5.52		298.15	23.98	
80	8.97		300	23.01	
100	12.09		400	24.25	
120	14.47		500	24.84	
140	16.37		600	25.19	
160	17.93		700	25.51	
180	19.17		800	26.19	
200	20.16		900	27.42	
220	20.94		950	28.25	
250	21.89				


Gupta *et al.*³ ($x_{\text{Ni}} = 0.90$), of de Dood and de Chatel⁴ ($x_{\text{Ni}} = 0.75$), and of Dunlop *et al.*⁵ ($x_{\text{Ni}} = 0.25$), respectively. C_p° values for other compositions were taken from Galli *et al.*,⁶ who observed upturns in C_p°/T versus T^2 plots at the lower temperatures for alloys x_{Ni} compositions > 0.50 which were confirmed by two other investigators. This behavior was partially attributed to the formation of magnetic clusters. de Dood and de Chatel⁴ also measured C_p° of several alloys in the range of existence of the AlNi₃ phase, α'' ($x_{\text{Ni}} = 0.73-0.76$), and concluded that the most nearly ferromagnetic sample ($x_{\text{Ni}} = 0.748$) had the highest heat capacity ($\gamma = 7.77 \text{ mJ mol}^{-1}\text{K}^{-2}$).

C_p° values of Table 14 for $x_{\text{Ni}} = 0.50$ were taken from the data of Sandakova *et al.*⁷ and of Kucherenko and Troshkina.⁸ Sandakova *et al.*⁷ have reported

Table 15. High-temperature data for Al-Ni α' phase, $x_{\text{Ni}} = 0.766$

T K	C_p°	
	$\text{J mol}^{-1}\text{K}^{-1}$	$\text{J mol}^{-1}\text{K}^{-1}$
400	24.40	
500	25.62	
600	26.55	
700	27.26	
800	27.96	
900	28.95	
1000	30.33	
1100	32.40	
1200	34.20	
1300	35.47	
1400	36.41	
1500	36.12	

Table 16. Enthalpies of formation for solid Al-Ni alloys at 298.15 K




x_{Ni}	Phase	ΔH $\text{J mol}^{-1}\text{K}^{-1}$
0.25	ϵ	-37850
0.368 ^a	δ	-55500
0.40		-59050
0.415 ^a	δ	-60500
0.451 ^a	β'	-66650
0.500		-71650 (+2000)
0.592 ^a	β'	-57100
0.640 ^a	α'	-54000
0.680 ^a	α'	-48050
0.734 ^a	α''	-41000
0.759 ^a	α''	-37550
0.930 ^a	(Ni)	-10950

^aApproximate phase boundaries.

$H^\circ(298.15 \text{ K}) - H^\circ(0 \text{ K}) = 4320 \text{ J mol}^{-1}$ and $S^\circ(298.15 \text{ K}) = 27.0 \text{ J mol}^{-1} \text{ K}^{-1}$ for this alloy. C_p° measurements of Kucherenko and Troshkina,⁸ Troshkina and Khomyakov,⁹ and of Kucherenko *et al.*¹⁰ on quenched and annealed samples indicated an order-disorder transformation in the β' -phase region. Moreover, Kucherenko *et al.*¹⁰ reported that the disordering temperatures for nickel-rich alloys (β' -

Table 17. Recommended integral quantities for solid Al-Ni alloys at 1273 K^a



x_{Ni}	Phase	ΔG J mol^{-1}	ΔG^{ex}
0.375 ^b	δ	-47164	-40162
0.403 ^b	δ	-49353	-42217
0.429 ^b	β'	-50791	-43562
0.45		-51938	-44654
0.50		-53931	-46595 (+8000) (+8000)
0.55		-51810	-44527
0.60		-47869	-40746
0.631 ^b	β'	-44842	-37878
0.728 ^b	α	-35392	-29200
0.742 ^b	α	-33934	-27891
0.864 ^b		-20477	-16268
0.90	(Ni)	-16095	-12655
0.95		-8890	-6788

^aNote standard states.

^bPhase boundaries.

phase region) were higher than those for $x_{\text{Ni}} = 0.50$. Additionally, Pop and Ilonca¹¹ have reported C_p° data for $x_{\text{Ni}} = 0.766$. The C_p° values of Table 15 were taken from the measurements of Kovaleav *et al.*¹²

ΔH values of Table 16 were essentially based on the calorimetric measurements of Oelsen and Middel¹³ except in the β' -phase region, where more weight was given to the data of Henig and Lukas¹⁴ and of Dannoehl and Lukas.¹⁵ The data of Kubaschewski,¹⁶ especially in the β' -phase region, are as much as 13 kJ mol^{-1} less exothermic than the tabulated values. The data of Eskov *et al.*¹⁷ and of Sandakova *et al.*⁷ for $x_{\text{Ni}} = 0.50$ are less exothermic by as much as 12 kJ mol^{-1} and 10 kJ mol^{-1} , respectively. The value reported by Bokshstein *et al.*¹⁸ at $x_{\text{Ni}} = 0.748$ from their temperature coefficients of vapor pressure measurements is in fair agreement with the tabulated value.

ΔG_{Al} values of Table 18 were based on the isopiestic measurements of Steiner and Komarek,¹⁹ emf studies of Malkin and Pokidyshev,²⁰ of Schaefer and Gokcen,²¹ and of Schaefer.²² Other quantities in Tables 17 and 18 were calculated from ΔG_{Al} values using the Gibbs-Duhem relation. Hanneman and Seybolt²³ carried out the Gibbs-Duhem integration of the data of Steiner and Komarek¹⁹ without having access to the data of Malkin and Pokidyshev.²⁰ Their

Table 18. Recommended partial molar quantities for solid Al-Ni alloys at 1273 K^a

Al component $\text{Al}(s) = \text{Al}(\text{in alloy})(s)$

x_{Al}	Phase	γ_{Al}	ΔG_{Al} J mol^{-1}	$\Delta G_{\text{Al}}^{\text{ex}}$
0.625 ^b	δ	0.446	-8544	-3569
0.597 ^b	δ	0.0775	-27062	-21602
0.571 ^b	β'	0.0775	-27062	-21131
0.55		0.0704	-28090	-21762
0.50		0.0125 (+0.007)	-46400 (+0.013) (+8000)	-39064 (+8000)
0.45		0.000197	-90300	-81849
0.40		0.000068	-101600	-91902
0.369 ^b	β'	0.000043	-106322	-95780
0.272 ^b	α	0.000043	-106322	-92552
0.258 ^b	α	0.000018	-115780	-101441
0.136 ^b		0.000018	-115780	-94664
0.10	(Ni)	0.0000031	-134106	-109735
0.05		0.00000031	-158733	-127026
0.00		0.000	-∞	-144930

Ni component $\text{Ni}(s) = \text{Ni}(\text{in alloy})(s)$

x_{Ni}	Phase	γ_{Ni}	ΔG_{Ni} J mol^{-1}	$\Delta G_{\text{Ni}}^{\text{ex}}$
0.375 ^b	δ	0.000027	-111530	-101149
0.403 ^b	δ	0.000416	-82374	-72755
0.429 ^b	β'	0.000416	-82374	-73417
0.45		0.000471	-81085	-72634
0.50		0.00301 (+0.002)	-61462 (+0.003) (+8000)	-54126 (+8000)
0.55		0.147	-20319	-13991
0.60		0.320	-12049	-6642
0.631 ^b	β'	0.432	-8890	-4017
0.728 ^b	α	0.432	-8890	-5530
0.742 ^b	α	0.596	-5476	-2317
0.864 ^b		0.596	-5476	-3928
0.90	(Ni)	0.754	-2983	-1868
0.95		0.910	-1003	-460
1.00		1.000	0	0

^aNote standard states.

^bPhase boundaries.

Table 19. Recommended integral quantities for liquid Al-Ni alloys at 1873 K
 $(1-x)Al(\ell) + xNi(\ell) = Al_{(1-x)}Ni_x(\ell)$

x_{Ni}	ΔG	ΔH	ΔG_{ex}^{ex}	ΔS	ΔS_{ex}^{ex}
	J mol ⁻¹	J mol ⁻¹	J mol ⁻¹	J mol ⁻¹ K ⁻¹	J mol ⁻¹ K ⁻¹
0.1	-14737	-13637	-9675	0.587	-2.116
0.2	-25964	-26850	-18172	-0.473	-4.633
0.3	-34734	-38379	-25222	-1.946	-7.025
0.4	-40773	-46796	-30292	-3.216	-8.812
0.5	-42858	-50003	-32054	-3.815	-9.583
	(±8000)	(±15000)	(±8000)	(±4.270)	(±4.270)
0.6	-40336	-46960	-29855	-3.537	-9.133
0.7	-34745	-39589	-25232	-2.586	-7.665
0.8	-26362	-28874	-18569	-1.341	-5.502
0.9	-15122	-15460	-10060	-0.180	-2.883

ΔG_{Ni} values in most cases are as much as 2800 J mol⁻¹ less exothermic than the ΔG_{Ni} values of Table 18.

6.3. Liquid Alloys

Vachet *et al.*²⁸ measured the distribution of Al between Ag(ℓ) and Ni(ℓ). They gave their results at 1873 K for $x_{Ni} = 0.60\text{--}0.96$ in terms of ΔG_{Al} only, which were calculated using Wilder and Elliott's²⁹ data for Ag-Al. Schaefer and Gokcen²¹ and Schaefer²² reported ΔG_{Al} values from the emf studies. Their measurements covered the temperature range of 950–1200 K for $x_{Ni} = 0.005\text{--}0.205$. Therefore, the recommended ΔH_{Al} values of Table 20 were combined with ΔG_{Al} values and ΔS_{Al}^{ex} values were calculated for each of these measurements. The recommended ΔS_{Al}^{ex} values of Table 20, with the exception of the values for $x_{Ni} = 0.2\text{--}0.6$ which were interpolated, were based on these calculated values. The ΔS_{Ni}^{ex} values were calculated from the recommended ΔS_{Al}^{ex} values using the Gibbs-Duhem relation. Other quantities of Tables 19 and 20 were calculated from the recommended ΔH and ΔS^{ex} values using the standard procedure. Mass spectrometric Knudsen-cell measurements of Johnston and Palmer³⁰ yielded ΔG_{Al} values, which are up to 10 kJ mol⁻¹ less exothermic than the recommended values.

Sandakov *et al.*²⁴ measured ΔH_{Al} for $x_{Ni} = 0.40\text{--}1.00$ and ΔH_{Ni} for $x_{Ni} = 0.0\text{--}0.55$. The partial molar enthalpies of other components were calculated by means of the Gibbs-Duhem equation. In order to obtain a consistent set of ΔH_{Al} and ΔH_{Ni} values, the Gibbs-Duhem calculations of ΔH_{Al} values were carried out to obtain ΔH_{Ni} values using the equation reported by Woolley and Elliott.²⁵ The ΔH_{Al} and ΔH_{Ni} values thus obtained are reported in Table 20, and ΔH values calculated from these partial values are reported in Table 19. ΔH values reported by Sandakov *et al.*²⁴ and by Bobrov *et al.*²⁶ are up to 400 J mol⁻¹ more exothermic for $x_{Ni} > 0.6$ and up to 1600 J mol⁻¹ less exothermic below $x_{Ni} = 0.6$. ΔH_{Al} and ΔH_{Ni} values at infinite dilution reported in Table 20 are in fairly good agreement with those reported by Sandakov *et al.*,²⁴ Bobrov *et al.*,²⁶ and by Gorokhov *et al.*²⁷

6.4. References

- M. F. Singleton, J. Murray, and P. Nash, Illinois Institute of Technology, Chicago, IL (private communications).
- R. Hultgren, P. D. Dcsai, D. T. Hawkins, M. Gleisner, K. K. Kelly, and D. D. Wagman, *Selected Values of the Thermodynamic Properties of Binary Alloys* (American Society for Metals, Metals Park, OH, 1973).
- K. P. Gupta, C. H. Cheng, and P. A. Beck, Phys. Rev. A **133**, 203 (1964).
- W. de Dood and P. F. de Chatel, J. Phys. F **3**, 1039 (1973).
- J. B. Dunlop, G. Gruner, and A. D. Caplin, J. Phys. F **4**, 2203 (1974).
- G. Galli, Ph.D. thesis (University of Pittsburgh, 1959).
- M. I. Sandakova, V. M. Sandakov, G. I. Kalishevich, and P. V. Gel'd, Russ. J. Phys. Chem. **45**, 901 (1971).
- L. A. Kucherenko and V. A. Troshkina, Russ. Metall. **1**, 115 (1971).
- V. A. Troshkina and K. G. Khomyakov, Russ. J. Inorg. Chem. **6**, 1233 (1961).
- L. A. Kucherenko, N. M. Aristova, V. A. Troshkina, and V. I. Fadeyeva, Russ. Metall. **6**, 97 (1978).
- I. Pop and G. Ilonca, Phys. Status Solidi A **14**, 283 (1972).
- A. I. Kovalev, M. B. Bronfin, Yu. V. Loshchinin, and V. A. Vetrogradskii, High Temp. High Pressures **8**, 581 (1976).
- W. Oelsen and W. Middel, Mitt. Kaiser Wilhelm Inst. Eisenforsch. Düsseldorf **19**, 1 (1937).
- E. T. Henig and H. L. Lukas, J. Calorim. Anal. Therm. **13**, 7 (1975).
- H. D. Danneohl and H. L. Lukas, Z. Metallkd. **65**, 642 (1974).
- O. Kubaschewski, Trans. Faraday Soc. **54**, 814 (1958).
- V. M. Eskov, V. V. Samokhval, and A. A. Vecher, Russ. Metall. (Engl. Transl.) **2**, 118 (1974).
- S. Z. Bokshein, M. B. Bronfin, I. A. Drugova, and S. T. Kishkin, Khim. Metal. Splavov **188** (1973).
- A. Steiner and K. L. Komarek, Trans. Metall. Soc. AIME **230**, 786 (1964).
- V. I. Malkin and V. V. Pokidyshev, Izv. Akad. Nauk SSSR Met. **2**, 166 (1966).
- S. C. Schaefer and N. A. Gokcen, High Temp. Sci. **11**, 31 (1979).
- S. C. Schaefer, "Thermodynamic Properties of the Aluminum-Nickel System," U.S. Bur. Mines Rep. Invest. No. 7993, 1975.
- R. E. Hanneman and A. U. Seybolt, Trans. Metall. Soc. AIME **245**, 434 (1969).
- Yu. O. Sandakov, O. Esin, and P. V. Gel'd, Russ. J. Phys. Chem. **45**, 1020 (1970).
- F. Woolley and J. F. Elliott, Trans. Metall. Soc. AIME **239**, 1872 (1967).
- N. B. Bobrov, Yu. O. Esin, and M. S. Petrushevskii, Tr. Ural. Politekh. Inst. **231**, 75 (1974).
- L. N. Gorokhov, A. M. Emelyanov, Yu. S. Khodeev, E. S. Levin, M. S. Petrushevskii, and P. V. Gel'd, High Temp. **14**, 355 (1976).
- F. Vachet, P. Desré, and E. Bonnier, C. R. Acad. Sci. **260**, 453 (1965).
- T. C. Wilder and J. F. Elliott, J. Electrochem. Soc. **107**, 628 (1960).
- G. R. Johnston and L. D. Palmer, High Temp. High Pressures **12**, 261 (1980).

Table 20. Recommended partial molar quantities for liquid Al-Ni alloys at 1873 K
 $Al(\ell) = Al_{(in \text{ alloy})}(\ell)$

Al component			$Al(\ell) = Al_{(in \text{ alloy})}(\ell)$				
x_{Al}	γ_{Al}	γ_{Al}	ΔG_{Al}	ΔG_{Al}^{ex}	ΔH_{Al}	ΔS_{Al}	ΔS_{Al}^{ex}
			J mol ⁻¹	J mol ⁻¹	J mol ⁻¹	J mol ⁻¹ K ⁻¹	J mol ⁻¹ K ⁻¹
1.0	1.000	1.000	0	0	0	0.000	0.000
0.9	0.868	0.964	-2204	-563	-18	1.167	0.291
0.8	0.680	0.851	-5996	-2521	-1684	2.302	0.447
0.7	0.458	0.654	-12172	-6618	-7605	2.439	0.527
0.6	0.222	0.371	-23413	-15458	-21936	0.788	-3.459
0.5	0.0561	0.112	-44858	-34064	-50500	-3.012	-8.775
	(±0.022)	(±0.044)	(±8000)	(±8000)	(±1500)	(±4.5)	(±4.5)
0.4	0.0152	0.0381	-65168	-50899	-79488	-7.646	-15.264
0.3	0.0046	0.0154	-83728	-64979	-103782	-10.707	-20.717
0.2	0.0012	0.0060	-104641	-79578	-126208	-11.515	-24.896
0.1	0.0002	0.0024	-130072	-94214	-146448	-8.744	-27.888
0.0	0.000	0.0010	-∞	-100840	-162300	∞	-29.610

Ni component $Ni(\ell) = Ni_{(in \text{ alloy})}(\ell)$

Ni component			$Ni(\ell) = Ni_{(in \text{ alloy})}(\ell)$				
x_{Ni}	γ_{Ni}	γ_{Ni}	ΔG_{Ni}	ΔG_{Ni}^{ex}	ΔH_{Ni}	ΔS_{Ni}	ΔS_{Ni}^{ex}
			J mol ⁻¹	J mol ⁻¹	J mol ⁻¹	J mol ⁻¹ K ⁻¹	J mol ⁻¹ K ⁻¹
0.0	0.000	0.0013	-∞	-103971	-136400	∞	-17.314
0.1	0.0003	0.0028	-127536	-91679	-136208	-4.630	-23.774
0.2	0.0011	0.0056	-105838	-80775	-127512	-11.571	-24.953
0.3	0.0037	0.0122	-87379	-68630	-110186	-12.177	-22.187
0.4	0.0137	0.0342	-66813	-52544	-84087	-9.223	-16.841
0.5	0.0726	0.145	-40838	-30644	-49506	-4.628	-10.391
	(±0.029)	(±0.058)	(±8000)	(±8000)	(±1500)	(±4.5)	(±4.5)
0.6	0.217	0.362	-23781	-15826	-25275	-0.798	-5.045
0.7	0.413	0.591	-13752	-8198	-12077	0.894	-2.071
0.8	0.647	0.808	-6792	-3317	-14540	1.202	-0.653
0.9	0.860	0.955	-2350	-709	-906	0.771	-0.105
1.0	1.000	1.000	0	0	0	0.000	0.000

7. Thermodynamic Properties of Al-Si Binary Alloy System

7.1. Phase Diagram and Structures

The simple eutectic phase diagram with two solid solutions, (Al) phase with fcc and diamond cubic (Si) phase shown in Fig. 4 and similar to the one reported by Hultgren *et al.*,² was taken from Murray and McAlister.¹

7.2. Liquid Alloys

The recommended ΔH values of Table 21 agree within $\pm 225 \text{ J mol}^{-1}$ with the reaction calorimetry of Bros *et al.*³ Enthalpies reported by Korber *et al.*⁴ are about 900 J mol^{-1} more exothermic than the recommended values. The reaction calorimetric values of Batalin *et al.*⁵ agree within $\pm 600 \text{ J mol}^{-1}$ except for $x_{\text{Si}} = 0.25-0.7$, where their values are as much as 3000 J mol^{-1} more exothermic than the recommended values. Recent measurements of Gizenko *et al.*⁶ yielded up to 500 J mol^{-1} more exothermic values. They also reported ΔH_{Al} and ΔH_{Si} values which appeared to be inconsistent with one another. Therefore, less weight was given to these measurements. The recommended ΔH values of Murray and McAlister¹ are up to 90 J mol^{-1} more exothermic below $x_{\text{Si}} = 0.2$ and about $30-50 \text{ J mol}^{-1}$ less exothermic above. The direct reaction calorimetry of Mathieu *et al.*⁷ at 962 K for $x_{\text{Si}} = 0.000-0.0095$, yielded a value of about $-10500 \text{ J mol}^{-1}$ for ΔH_{Si} at $x_{\text{Fe}} = 0.0$, which compares with the recommended values of $-11200 \text{ J mol}^{-1}$. ΔH_{Al} and ΔH_{Si} from Table 22 were calculated from the recommended ΔH value using the Gibbs-Duhem relation.

Although there have been several measurements from which Gibbs energy values can be derived, they were at different temperatures, making it difficult to compare them on the same basis. Therefore, the recommended ΔH_{Al} values from Table 22 were combined with ΔG_{Al} values from each of these measurements, and ΔS_{Al} values were calculated. The recommended ΔS_{Al} values of Table 22 were based on the results of Berthon *et al.*⁸ and Chatillon *et al.*⁹ The values of Schaefer and Gokcen¹⁰ are up to 0.35 e.u. higher than the

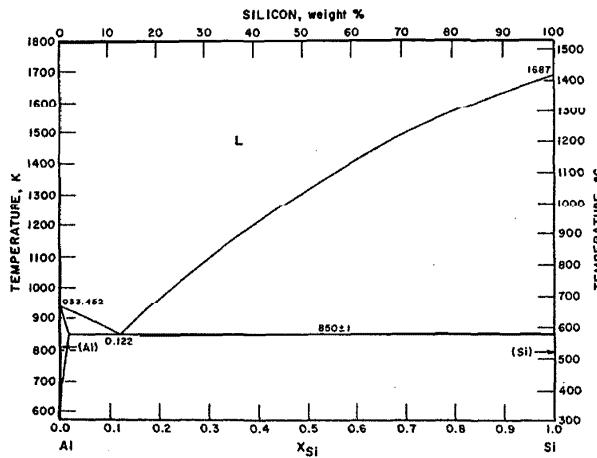


FIG. 4. Aluminum-silicon phase diagram.

Table 21. Recommended integral quantities for liquid Al-Si alloys at 1700 K

$$(1-x) \text{Al}(l) + x\text{Si}(l) = \text{Al}_{(1-x)}\text{Si}_x(l)$$

x_{Si}	ΔG	ΔH	ΔG^{ex}	ΔS	ΔS^{ex}
	J mol^{-1}	J mol^{-1}	J mol^{-1}	$\text{J mol}^{-1}\text{K}^{-1}$	$\text{J mol}^{-1}\text{K}^{-1}$
0.1	-5568	-1154	-973	2.596	-0.106
0.2	-8691	-2080	-1618	3.889	-0.272
0.3	-10616	-2657	-1982	4.682	-0.397
0.4	-11615	-2883	-2102	5.136	-0.459
0.5	-11807	-2809	-2010	5.293	-0.470
(± 700)	(± 500)	(± 700)	(± 700)	(± 706)	(± 706)
0.6	-11255	-2484	-1743	5.159	-0.436
0.7	-9977	-1360	-1344	4.716	-0.362
0.8	-7966	-1326	-893	3.906	-0.255
0.9	-4981	-664	-387	2.539	-0.163

recommended values. ΔG_{Al} values thus obtained from the recommended ΔH_{Al} and ΔS_{Al} values compared with the measured data when corrected to 1700 K using the recommended ΔS_{Al} values as follows:

Source	Deviation, J mol^{-1}
Berthon <i>et al.</i> ⁸	± 100
Chatillon <i>et al.</i> ⁹	± 900
Schaefer and Gokcen ¹⁰	-500
Mitani and Nagai ¹¹	-700 ($x_{\text{Si}} < 0.5$) 4000 ($x_{\text{Si}} > 0.5$)
Loseva <i>et al.</i> ¹²	up to -6000

The data of Batalin *et al.*¹³ are as much as 9900 J mol^{-1} more exothermic than the recommended values. Other quantities from Tables 21 and 22 are calculated from the recommended ΔH_{Al} and ΔS_{Al} values using the Gibbs-Duhem relation.

Table 22. Recommended partial molar quantities for liquid Al-Si alloys at 1700 K

Al Component			$\text{Al}(l) = \text{Al}(\text{in alloy})(l)$			
x_{Al}	γ_{Al}	ΔG_{Al}	$\Delta G_{\text{Al}}^{\text{ex}}$	ΔH_{Al}	ΔS_{Al}	$\Delta S_{\text{Al}}^{\text{ex}}$
		J mol^{-1}		J mol^{-1}	$\text{J mol}^{-1}\text{K}^{-1}$	
1.0	1.000	1.000	0	0	0.000	0.000
0.9	0.889	0.988	-1661	-172	-0.929	0.053
0.8	0.766	0.958	-3767	-613	-1.892	0.037
0.7	0.640	0.914	-6313	-1272	-4.478	2.844
0.6	0.518	0.864	-9291	-2071	-2.613	3.928
0.5	0.406	0.812	-12737	-2940	-3.844	5.231
(± 0.019)	(± 0.039)	(± 700)	(± 700)	(± 500)	(± 706)	(± 706)
0.4	0.306	0.765	-16743	-3792	-5.090	6.855
0.3	0.219	0.730	-21458	-4441	-6.146	9.007
0.2	0.146	0.730	-27196	-4448	-6.572	12.131
0.1	0.075	0.749	-36628	-4082	-6.640	17.640
0.0	0.000	0.773	--	-3642	-6.642	-1.765

Si Component			$\text{Si}(l) = \text{Si}(\text{in alloy})(l)$			
x_{Si}	γ_{Si}	ΔG_{Si}	$\Delta G_{\text{Si}}^{\text{ex}}$	ΔH_{Si}	ΔS_{Si}	$\Delta S_{\text{Si}}^{\text{ex}}$
		J mol^{-1}		J mol^{-1}	$\text{J mol}^{-1}\text{K}^{-1}$	
0.0	0.000	0.460	--	-10980	-11200	-0.130
0.1	0.056	0.560	-40729	-8183	-10801	17.605
0.2	0.134	0.671	-28388	-5640	-8202	11.874
0.3	0.232	0.773	-20656	-3639	-5409	8.969
0.4	0.344	0.859	-15100	-2149	-3288	6.948
0.5	0.463	0.927	-10876	-1079	-1773	5.355
(± 0.022)	(± 0.044)	(± 700)	(± 700)	(± 500)	(± 706)	(± 706)
0.6	0.584	0.974	-7597	-377	-746	4.030
0.7	0.699	0.999	-5057	-16	-166	2.877
0.8	0.800	1.000	-3158	-4	-14	1.849
0.9	0.902	1.002	-1465	24	0	0.862
1.0	1.000	1.000	0	0	0	0.000

7.3. References

- ¹J. L. Murray and A. J. McAlister, Bull. Alloy Phase Diagr. **5**, 74 (1984).
- ²R. Hultgren, P. D. Desai, D. T. Hawkins, M. Gleiser, and K. K. Kelley, *Selected Values of the Thermodynamic Properties of Binary Alloys* (American Society for Metals, Metals Park, OH, 1973).
- ³J. P. Bros, H. Eslami, and P. Gaune, Ber. Bunsenges. Phys. Chem. **85**, 333 (1981).
- ⁴F. Korber, W. Oelsen, and H. Lichlenberg, Mitt. Kaiser Wilhelm Inst. Eisenforsch. Duesseldorf **19**, 156 (1937).
- ⁵G. I. Batalin, E. A. Beloborodova, A. N. Shlapak, I. V. Nikolaenko, and V. P. Kurach, Russ. J. Phys. Chem. **55**, 888 (1981).
- ⁶N. V. Gizenko, B. I. Emelin, S. N. Kileso, M. I. Gasik, and A. N. Zv'yaylo, Russ. Metall. **1**, 29 (1983).
- ⁷J. C. Mathieu, B. Jourel, P. Desré, and E. Bonnier, in *Proceedings of the Thermodynamic Nuclear Material Symposium, Vienna, 1967* (Int. Atomic Agency, Vienna, 1968), pp. 767-776.
- ⁸O. Berthon, G. Petot-Ervas, C. Petot, and P. Desré, C. R. Acad. Sci. Paris **268**, C1939 (1969).
- ⁹C. Chatillon, M. Allibert, and A. Pattoret, High Temp. High Pressures **7**, 1983 (1975).
- ¹⁰S. C. Schaefer and N. A. Gokcen, High Temp. Sci. **11**, 31 (1979).
- ¹¹H. Mitani and H. Nagai, Jpn. Inst. Met. **31**, 1296 (1967).
- ¹²A. F. Loseva, A. I. Almuklemedov, V. N. Tyumentsev, and M. A. Luzhova, Russ. J. Phys. Chem. **51**, 290 (1977).
- ¹³G. I. Batalin, E. A. Beloborodova, and V. A. Stukalo, Russ. Metall. **2**, 44 (1971).

8. Thermodynamic Properties of Al-Ti Binary Alloy System

8.1. Phase Diagram and Structures

The phase diagram shown in Fig. 5 was taken from the preliminary investigation of Murray.¹ Loiseau and Lasalmonie³ have recently reported the existence of an additional three phases around equiatomic composition: Ti₄₆Al₅₄ and Ti₄₂Al₅₈ corresponding to an ordered superstructure of an fcc type different from AuCu. The transformation between them can be achieved by introducing periodic antiphase boundaries. The third phase, "Ti₂Al," is of complex structure. Murray¹ and Pearson² list the following intermediate phases:

γ , "Al₃Ti," has the tetragonal (DO₂₂) prototype.

δ , has the tetragonal (DO₂₃) structure isotropic with Al₃Zr.

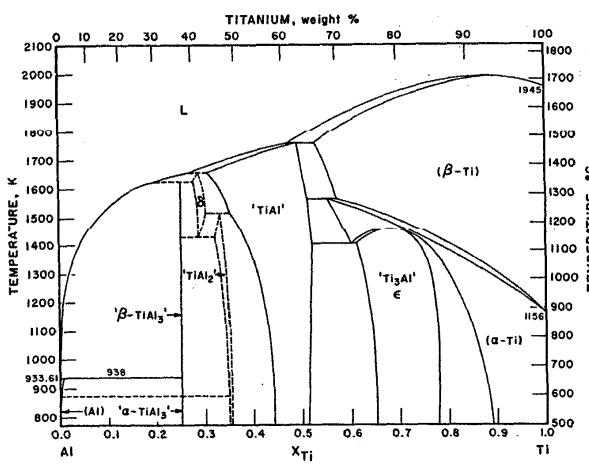


FIG. 5. Aluminum-titanium phase diagram.

Table 23. Low-temperature heat capacity of solid Al-Ti alloys

T, K	x_{Ti}					
	0.0 'Al'	0.25 ' γ '	0.75 ' ϵ '	0.914 '(a-Ti)'	0.95 '(a-Ti)'	1.00 'Ti'
1.4			0.0027		0.0050	0.006473
2	0.0029		0.0039		0.0073	0.00687
3	0.00472		0.0060		0.0113	0.01068
4	0.00699		0.0082	0.0164	0.0159	0.0149
5	0.00986	0.005		0.0212		0.0198
10	0.0359	0.021		0.0604		0.0623
15	0.0982	0.048		0.145		0.147
20	0.223	0.095		0.322		0.338
25	0.456	0.189		0.613		0.661
30	0.837	0.356		1.100		1.172
40	2.064	0.992		2.503		2.665
50	3.827	2.029		4.352		4.690
60	5.800	3.420		6.399		6.918
80	9.690	6.642		10.340		11.030
100	12.996	9.832		13.650		14.388
120	15.637	12.615		16.228		16.862
140	17.615	14.874		18.164		18.788
160	19.190	16.694		19.731		20.255
180	20.439	18.148		20.838		21.423
200	21.435	19.320		21.436		22.338
220	22.203	20.240		22.174		23.088
240	22.828	21.004		22.728		23.734
260	23.358	21.652		23.235		24.286
280	23.832	22.207		23.696		24.762
298.15	24.225	22.620				25.142
	$x_{\text{Ti}}^{-1} \text{K}^{-2}$	0.00135		0.00192	0.00374	0.00354
	$C_p^o (298.15 \text{ K})$	28.35	23.10			30.67

"TiAl₂" has the tetragonal structure isotropic with HfGa₂.

"TiAl" has the tetragonal structure isotropic with AuCu.

ϵ , "Ti₃Al," has an ordered hexagonal (DO₁₉) structure isotropic with Ni₃Sn.


8.2. Solid Alloys

The C_p^o values of Table 23 for $x_{\text{Ti}} = 0.25$ were taken from the data of Stuve and Ferrante,⁴ for $x_{\text{Ti}} = 0.75$, and $x_{\text{Ti}} = 0.95$ from the data of Ho *et al.*,⁵ and for $x_{\text{Ti}} = 0.914$ from those of Ilycv *et al.*⁶ The C_p^o values for Al and Ti were taken from the recommended CINDAS values.^{7,8} The C_p^o values of Table 24 were taken from the plane temperature waves

Table 24. High-temperature heat capacity of solid Al-Ti alloys


T, K	x_{Ti}			
	0.787	0.92	0.936	0.97
298.15	21.85			
300	21.90			
400	23.68			
500	25.09			
600	26.29			
700	27.74			
800	29.55	35.02	32.63	30.13
900	31.69	36.89	33.99	31.78
1000	34.02	38.49	35.85	33.76
1100	40.84	38.55	35.95	
1180		42.65	39.60	36.80
1200		42.91	39.55	36.65
1240		43.10	38.35	34.75
1300		39.81	33.65	30.80
1320		37.26	33.40	30.35
1400		35.92	33.37	30.83
1500		36.79	34.40	32.26
1600		37.87	35.85	33.82
1700		39.11	37.57	35.45

Table 25. Enthalpies of formation for solid Al-Ti alloys at 298.15 K



x_{Ti}	Phase	ΔH° J mol ⁻¹
0.25	γ	-36800 ± 2100
0.349	TiAl ₂	-40100 ± 2100
0.355	TiAl ₂	-40200 ± 2100
0.444	TiAl	-39200 ± 2100
0.513	TiAl	-38000 ± 2100
0.653	ϵ	-31000 ± 2100
0.778	ϵ	-23000 ± 2100
0.892	(α -Ti)	-12000 ± 2100

Table 26. High-temperature data for solid Al-Ti alloys as a function of temperature, $x_{Ti} = 0.25^a$



T	C _p J mol ⁻¹ K ⁻¹	ΔC_p^b J mol ⁻¹ K ⁻¹	H _T J mol ⁻¹	ΔH_T^0 J mol ⁻¹ K ⁻¹	ΔG_T^0 J mol ⁻¹ K ⁻¹	S _T J mol ⁻¹ K ⁻¹	ΔS_T^0 J mol ⁻¹ K ⁻¹	$-(\frac{\partial H}{\partial T})_{298.15}^0$ T
298.15	22.62	-1.960	0	-36800	-35061	0.000	-5.834	23.096
300	22.67	-1.946	42	-36804	-35050	0.140	-5.846	23.096
400	24.17	-1.786	2393	-36985	-34435	6.890	-6.374	24.006
500	25.07	-2.128	4858	-37178	-33773	12.38	-6.811	25.763
600	25.70	-2.730	7398	-37419	-33076	17.02	-7.239	27.782
700	26.19	-3.522	9993	-37730	-32321	21.01	-7.727	29.832
800	26.63	-4.574	12635	-38131	-31525	24.54	-8.257	31.840
900	27.06	-6.070	15319	-38659	-30677	27.71	-8.869	33.775
1000	27.52	-4.510	18047	-39179	-29745	30.57	-9.434	35.627
1100	28.04	-4.442	20825	-39623	-28779	33.22	-9.858	37.384
1200	28.67	-2.372	23659	-40961	-27741	35.69	-11.017	39.068
1300	29.43	-1.825	26564	-41169	-26619	38.01	-11.192	40.679

^aNote standard states.

^bValues for T ≥ 1000 K are referred to Al(s).

with the modulated electronic heating technique of Zaretskii and Peletskii.⁹

The recommended ΔH values of Table 25 were based on the direct reaction calorimetry of Kubaschewski and Dench¹⁰ and of Kubaschewski and Heymer.¹¹ The recommended C_p° values of Table 26 were based on the copper-block drop calorimetry of Stuve and Ferrante.⁴ Other thermodynamic functions were calculated by integrating the C_p° values and by combining the entropy and enthalpy data with the standard enthalpy of formation at 298.15 from Table 25.

Table 27. Recommended integral quantities for solid Al-Ti alloys at 973 K^a
 $(1-x)Al(s) + xTi(s) = Al_{1-x}Ti_x(s)$

x_{Ti}	Phase	ΔG	ΔG^{ex}
		J mol ⁻¹	J mol ⁻¹
0.500	θ	-31513 (±2000)	-25906 (±2000)
0.513 ^b	θ	-31197	-25592
0.649 ^b	ϵ	-25918	-20675
0.700	ϵ	-23312	-18371
0.779 ^b	ϵ	-18056	-13784
0.870 ^b	(α -Ti)	-11521	-8395
0.900	(α -Ti)	-9255	-6626

^aNote standard states.
^bPhase boundaries.

The necessary thermodynamic functions needed for these calculations were taken from Desai.^{7,8}

The recommended ΔG_{Al} values of Table 28 were based on the emf studies of Samokhval and Vecher¹² and Samokhval *et al.*¹³ $\Delta G_{Al(s)}$ values obtained from their reported emf values were transformed to $\Delta G_{Al(\epsilon)}$ by applying the required standard state correction: $(T_m - 973) \times \Delta_{\text{fus}}S^{\circ} = -446 \text{ J mol}^{-1}$. ΔG_{Ti} and other quantities of Table 28 were calculated from the recommended ΔG_{Al} values using the Gibbs-Duhem relation. The recommended ΔG and ΔG^{ex} values of Table 27 were calculated from partial quantities of Table 28.

The recommended ΔG_{Al} values of Table 30 were taken from the mass spectrometric vapor pressure coupled with a triple Knudsen cell measurement of Hoch and Usell.¹⁴ Their a_{Al} values had a considerable scatter. The recommended $\Delta G_{Al(\epsilon)}$ values obtained from their $a_{Al(\epsilon)}$ were converted to $\Delta G_{Al(s)}$ by applying the required standard state correction: $(T_m - 1780) \times \Delta_{\text{fus}}S^{\circ} = -9550 \text{ J mol}^{-1}$. ΔG_{Ti} and other values of Table 29 and 30 were calculated using the method discussed above.

8.3. Liquid Alloys

The recommended ΔH_{Al} values of Table 31 were based on the high-temperature vacuum calorimetric measurements of Esin *et al.*^{15,16} The recommended ΔH_{Ti} values of Table 31 were calculated from ΔH_{Al} values and the Gibbs-Duhem relation. ΔH_{Al} and ΔH_{Ti} values were combined to yield ΔH values of Table 31.

Table 28. Recommended partial molar quantities for solid Al-Ti alloys at 973 K^a

x_{Ti}	Phase	Al(s) = Al(in alloy)(s)				Ti(s) = Ti(in alloy)(s)			
		α_{Al}	γ_{Al}	ΔG_{Al}	ΔG_{Al}^{ex}	α_{Ti}	γ_{Ti}	ΔG_{Ti}	ΔG_{Ti}^{ex}
				J mol ⁻¹				J mol ⁻¹	
0.500		0.01203 (±0.003)	0.0241 (±0.005)	-35760 (±2000)	-30153 (±2000)	0.0344 (±0.021)	0.0687 (±0.053)	-27266 (±2000)	-21659 (±2000)
0.513 ^b	θ	0.00180	0.0037	-51110	-45289	0.219	0.427	-12293	-6893
0.649 ^b	ε	0.00180	0.0051	-51110	-42640	0.219	0.337	-12293	-8796
0.700		0.00032	0.0011	-65050	-55310	0.511	0.730	-5425	-2540
0.779 ^b	ε	0.00011	0.00050	-74000	-61788	0.763	0.980	-2185	-165
0.870 ^b	(α-Ti)	0.00011	0.00082	-74000	-57495	0.763	0.877	-2185	-1058
0.900		0.00005	0.0005	-80350	-61722	0.846	0.940	-1356	-504
1.000	(α-Ti)	0.000	0.00017	-∞	-70300	1.000	1.000	0	0

^aNote standard states.^bPhase boundaries.Table 29. Recommended integral quantities for solid Al-Ti alloys at 1780 K^a

$$(1-x)Al(s) + xTi(s) = Al_{1-x}Ti_x(s)$$


x_{Ti}	ΔG	ΔG^{ex}
	J mol ⁻¹	
0.493 ^b	-25187 (±2000)	-14930 (±2000)
0.548 ^b	-24552	-14362
0.6	-23726	-13765
0.7	-20860	-11819
0.8	-16262	-8857
0.9	-9719	-4908

^aNote standard states.^bPhase boundary.Table 30. Recommended partial molar quantities for solid Al-Ti alloys at 1780 K^a

x_{Ti}	Al(s) = Al(in alloy)(s)				Ti(s) = Ti(in alloy)(s)			
	α_{Al}	γ_{Al}	ΔG_{Al}	ΔG_{Al}^{ex}	α_{Ti}	γ_{Ti}	ΔG_{Ti}	ΔG_{Ti}^{ex}
			J mol ⁻¹				J mol ⁻¹	
0.493 ^b	0.124 (±0.015)	0.245 (±0.031)	-30881 (±2000)	-20814 (±2000)	0.271 (±0.024)	0.549 (±0.048)	-19332 (±2000)	-8865 (±2000)
0.548 ^b	0.124	0.275	-30881	-19114	0.271	0.494	-19332	-10430
0.6	0.089	0.221	-35881	-22320	0.348	0.580	-15622	-8062
0.7	0.042	0.141	-46851	-29032	0.519	0.741	-9721	-4442
0.8	0.017	0.085	-60363	-36544	0.702	0.877	-5237	-1935
0.9	0.005	0.048	-78878	-44801	0.871	0.968	-2034	-475
1.0	0.000	0.026	∞	-53775	1.000	1.000	0	0

^aNote standard states.^bPhase boundary.

Table 31. Enthalpies of formation for liquid Al-Ti alloys at 2000 K



x_{Ti}	ΔH	ΔH_{Al}	ΔH_{Ti}
	J mol ⁻¹		
0.0		0	-114136
0.1	-11158	-557	-106566
0.2	-11949	-6155	-75126
0.3	-25274	-13941	-51717
0.4	-27669	-23104	-34516
0.5	-27710	-32725	-22695
(+2000)	(+2000)	(+2000)	
0.6	-25752	-43060	-14214
0.7	-21908	-51773	-6795
0.8	-16275	-67827	-3387
0.9	-8978	-82280	-833
1.0		-98000	0

8.4. References

- ¹J. L. Murray, Natl. Bur. Stand. (private communications, 1984).
- ²W. B. Pearson, *A Handbook of Lattice Spacings and Structures of Metals and Alloys* (Pergamon, New York, 1967), Vol. 2.
- ³A. Loiseau and A. Lasalmonie, Acta Crystallogr. B **39**, 580 (1983).
- ⁴J. M. Stuve and M. J. Ferrante, U. S. Bur. Mines Rep. Invest. No. 7834, 1955.
- ⁵J. C. Ho, P. C. Gehlen, and E. W. Collings, Solid State Commun. **7**, 511 (1969).
- ⁶L. B. Iliyev, V. I. Ovcharenko, and V. A. Pervakov, Phys. Met. Metallogr. USSR **46**, 34 (1978).
- ⁷P. D. Desai, "Thermodynamic Properties of Aluminum," CINDAS Report No. 76, Purdue University, 1984.

⁸P. D. Desai, "Thermodynamic Properties of Titanium," CINDAS Report No. 77, Purdue University, 1984.

⁹Ye. B. Zaretskii and B. Ye. Petelskii, High Temp. **18**, 751 (1980).

¹⁰O. Kubaschewski and W. A. Dench, Acta Metall. **3**, 339 (1955).

¹¹O. Kubaschewski and G. Heymer, Trans. Faraday Soc. **56**, 473 (1960).

¹²V. V. Samokhval and A. A. Vecher, Dokl. Akad. Nauk Beloruss SSR **14**, 119 (1970).

¹³V. V. Samokhval, P. A. Poleshchuk, and A. A. Vecher, Russ. J. Phys. Chem. **145**, 1174 (1971).

¹⁴M. Hoch and R. J. Usell, Jr., Metall. Trans. **2**, 2627 (1971).

¹⁵Yu. Esin, N. P. Bobrov, M. S. Petrushevskii, and P. V. Gel'd, High Temp. **13**, 70 (1973).

¹⁶Yu. Esin, N. P. Bobrov, M. S. Petrushevskii, and P. V. Gel'd, Russ. Metall. **5**, 86 (1974).

9. Acknowledgments

This work was supported by the National Science Foundation through the Joint Program on Critical Compilation of Physical and Chemical Data coordinated through the Office of Standard Reference Data (OSRD) of the National Bureau of Standards. The author wishes to express appreciation to Dr. John R. Rumble, Jr., of the NBS/OSRD for his guidance, to Professors Leo Brewer and Ralph Hultgren of the University of California at Berkeley, California, for providing their entire holdings of the thermodynamic properties database to CINDAS, and Professor D. R. Gaskell of the School of Materials Engineering, Purdue University, for valuable suggestions. The assistance of Mrs. G. M. Halstead for preparing computer programs for various thermodynamic calculations and Mrs. D. M. Lenartz for typing is also acknowledged.